

Alma Mater Studiorum Università di Bologna
Archivio istituzionale della ricerca

Evaluation of 3D printed mouthpieces for musical instruments

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

Published Version:

Bacciaglia A., Ceruti A., Liverani A. (2020). Evaluation of 3D printed mouthpieces for musical instruments. RAPID PROTOTYPING JOURNAL, 26(3), 577-584 [10.1108/RPJ-07-2019-0187].

Availability:

This version is available at: <https://hdl.handle.net/11585/717047> since: 2024-05-29

Published:

DOI: <http://doi.org/10.1108/RPJ-07-2019-0187>

Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).
When citing, please refer to the published version.

(Article begins on next page)

This is the final peer-reviewed accepted manuscript of:

Bacciaglia, A., Ceruti, A. and Liverani, A. (2020), "Evaluation of 3D printed mouthpieces for musical instruments", Rapid Prototyping Journal, Vol. 26 No. 3, pp. 577-584..

The final published version is available online at: **<https://doi.org/10.1108/RPJ-07-2019-0187>**

Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

When citing, please refer to the published version.

Evaluation of 3D printed mouthpieces for musical instruments

1) Antonio Bacciaglia,

PhD Student, Department of Industrial Engineering (DIN), University of Bologna, Bologna, Italy

Email: antonio.bacciaglia2@unibo.it

2) Alessandro Ceruti,

Assistant Professor, Department of Industrial Engineering (DIN), University of Bologna, Bologna, Italy

Email: alessandro.ceruti@unibo.it

3) Alfredo Liverani,

Full Professor, Department of Industrial Engineering (DIN), University of Bologna, Bologna, Italy

Email: alfredo.liverani@unibo.it

Abstract

Purpose – The evaluation of advantages and criticalities related to the application of additive manufacturing to the production of parts for musical instruments will be discussed. A comparison between traditional manufacturing and additive manufacturing based on different aspects is carried out.

Design/methodology/approach – A set of mouthpieces produced through different additive manufacturing techniques has been designed, manufactured, and evaluated using an end-user satisfaction-oriented approach. A musician has been tasked to play the same classical music piece with different mouthpieces and the sound has been recorded in a recording studio. The mouthpiece and sound characteristics have been evaluated in a structured methodology.

Findings – The quality of the sound and comfort of 3D printed mouthpieces can be similar to the traditional ones provided that an accurate design and proper materials and technologies are adopted. When personalization and economic issues are considered, additive manufacturing is superior to mouthpieces produced by traditional techniques.

Research limitations/implications – In this research a mouthpiece for trombone has been investigated. A wider analysis where several musical instruments and related parts are considered can provide more data.

Practical implications – The production of mouthpieces with Additive Manufacturing techniques is suggested due to the advantages which can be tackled in terms of customization, manufacturing cost and time reduction.

Originality/value – This research is carried out using a multidisciplinary approach where several data have been considered to evaluate the end user satisfaction of 3D printed mouthpieces.

Keywords Additive manufacturing, Musical instruments, Fused deposition modelling, Stereolithography, Dental materials.

Introduction

Additive Manufacturing (AM) can be defined as the set of technologies allowing the manufacturing of a component from a CAD model in short time. Different materials and technologies can be adopted to build products through AM techniques (Gibson et al., 2010). Each manufacturing technology presents peculiarities, advantages and limitations, as discussed in (Pham and Gault, 1998), but the description of each single technology is behind the scope of this work. Just to provide the reader with an example, the Fused Deposition Modelling (FDM) is one of the most popular technique due to its low costs and wide range of available materials (Agarwala et al., 1996), (Pandey et al., 2003). FDM is based on the melting of a wire in ABS or PLA plastics in a nozzle along paths generated from the slicing of a CAD 3D model. It holds the largest market share and many research results are available in literature, making it a well-known manufacturing process. However, it is important to underline some FDM limitations such as low layer resolution, rough surface, component anisotropy, low strength, stairs effect and so on. A completely different approach is used in other AM techniques, such as Selective Laser Sintering (SLS) (Beaman and Deckard, 1986) and Stereolithography (SLA) (Cooper, 2001): a high energy source, namely a laser or UV light, is used to solidify the primary material (metal or plastic powders for SLS; a liquid resin for SLA) in order to obtain the final shape with high accuracy, resolution and low roughness (Di Angelo et al., 2017). A disadvantage of the SLA technique is the time degradation: the material changes its properties and shape in time. However, this drawback can be mitigated through post-processing curing with heat and UV rays. On the other hand, SLS produces durable parts melting metal powders with good mechanical properties, but with a higher cost, both for raw material and machine. Nowadays, AM techniques are used to produce small series components, aesthetical prototypes, customized products for evaluation, and parts in wax to allow casting. Focusing the attention on the development of musical instruments, AM can be useful in two main applications: reconstruction and replication of ancient musical instruments for conservation reasons, and design of musical instruments with specific features not achievable through traditional manufacturing. About the first application, ancient musical instrument components (i.e. wooden mouthpieces) are very rare, sensitive and susceptible to damages; moreover, fires, earthquakes, flooding or robbery can lead to the loss of rare musical instruments. Technological instruments such as x-ray tomography scans can be used to reconstruct the three-dimensional shape. When the 3D model is obtained, AM technologies can be used to manufacture the parts. Broadly speaking, the quality of the AM musical instruments is affected by the layer thickness and machine accuracy used to manufacture it. (Celentano et al., 2016) shows that the surface roughness (with ABS plastic) which can be obtained through FDM can lead to air leakages and imperfections at the surface level, making the part not suitable for the musician

due to the low comfort. On the other hand, SLS and SLA allow better surface finishing creating smoother and more comfortable parts without problems of air leakage. Sources available in literature (e.g. Zoran, 2011) suggest also the use of Polyjet technology for the musical instrument manufacturing: the multi-materials capability assuring good accuracy and surface smoothness are strength point. The multi-material printing capability has been used to manufacture a flute with soft and rigid regions, particularly interesting in the valve areas, used to change air pressure inside the channels. In this way, different pitches are obtained, so that the human perception of a sound wave at a specific frequency is guaranteed. However, as it happens for SLA, Polyjet suffers from the material decomposition in time, making it useful for prototype manufacturing. It is worth nothing that AM materials and building processes affect the obtainable sound because of different properties such as density, accuracy, heat resistance, strength, roughness and porosity. The ancient instrument reconstruction is described in (Savan and Simian, 2014), where an ancient cornett is CT-scanned and a subsequent manufacturing using nylon with SLS technology is described. The research of new shapes useful to obtain extreme acoustic capabilities is described in (Kantaros and Diegel, 2018) where a discussion of the AM techniques which can be used is presented. Following (Zoran, 2008), musical instruments must be stiff and strong to avoid deformation that can affect the sound and the acoustic requirements.

Regarding wind instruments, additional constrains must be considered: the air flowing inside the instrument creates moisture that can change the characteristics of the sound; in addition, the material used to produce the mouthpiece, or in general the components close or in contact with the mouth, must be biocompatible. Nevertheless, AM has a great potential to support wind musical instruments, because complex shapes can produce unexplored and unconventional sounds, showing customization potentials as well (Dabin et al., 2016). Moreover, complex shapes, that can be manufactured by additively processes and not by removal or moulding techniques, don't show limitations in geometry and manufacturing constrains (Aita-Holmes et al., 2015). This design freedom perfectly fits the high customization needed in the musical instrument design process, that can become faster, easier to produce, cheaper, and more end-user appealing, well-described by the musician-tailored design concept (Lorenzoni and Doubrovskj and Verlinden, 2013).

The aim of the study is the evaluation of the AM technology as a potential way to produce musical instruments parts: its novelty and originality lie in the development of a methodology useful to evaluate purposes. The limits of current literature are that available papers describe how it is possible to produce parts obtained through AM, but the description of procedures to follow to score alternatives, based on the end user satisfaction, are not described.

This work is organized as follows: after this section, the mouthpiece for trombone product is analysed keeping into consideration the requirements by the end-user. In the next section, the design of mouthpiece parts is described, together with some notes on possible materials and technology which can be used. Finally, another section describes the tests carried out to evaluate the end user satisfaction of different kinds of mouthpieces; the conclusion ends the paper.

End user-oriented approach

Modern engineering aims to customer satisfaction: methodologies such as Quality Function Deployment (QFD), Taguchi, robust design (Frizziero et al., 2019) are fundamental to drive the design towards products which are perceived with high value by the end user (Ulman, 2017). This approach has been followed in this study, following these phases: interview with end users, main requirements detection, and ranking of requirements importance. In the following, several design alternatives have been proposed and evaluated through a MADM (Multi Attribute Decision Making analysis) approach, used to score the solutions based on the end users' feedbacks. At first, a set of interviews has been carried out involving a professional practitioner of trombone and two different professors of music: the needs suggested by users have been regrouped where similar concepts were expressed. A matrix has been used to compute the relative importance of each requirement. All the requirements are written in rows and columns, and a value is filled in the intersection cells (see Table 1): 1 if the requirement in rows has the same importance of the requirement in column, 2 if the requirement in rows is more important than that in columns, 0 otherwise. At the end of each single line the sum of numbers is computed, and the overall sum of these sums is recorded at the bottom of the table. The relative importance of each requirement can be computed by dividing the sum value of the line by the overall sum.

Table 1 - Requirements relative importance.


	Quality of sound	Customization and personal symbol	No gluing lips when cold	Mouth and lips comfort	Buying Cost	Mouthpiece easiness of storing	Loudness of sound	Sum of line values	Relative Importance
Quality of sound	1	2	2	1	2	2	2	12	24.5
Customization and personal symbol	0	1	0	0	1	2	0	4	8.2
No gluing lips when cold	0	2	1	1	1	2	1	8	16.3
Mouth and lips comfort	1	2	1	1	2	2	1	10	20.4
Buying Cost	0	1	1	0	1	2	0	5	10.2

Mouthpiece easiness of storing	0	0	0	0	0	1	0	1	2.0
Loudness of sound	0	2	1	1	2	2	1	9	18.4
Sum of numbers in the Sum of line values rows								49	

Mouthpiece design

This section mainly focuses on the mouthpiece geometry description, alternative designs and manufacturing technology. From literature (Svoboda and Roth, 2017), there are 2 different techniques to play a trombone: the downstream (the more common) and the upstream. The difference consists of the dominant (wider vibrations) lip and in the direction of the exiting air flow from the mouth (respectively towards down in the downstream and up for the upstream). This air flow impacts the inner part of the mouthpiece, flows through the mouthpiece throat section and goes into the instrument itself. The produced sound strongly depends on the mouthpiece geometry: there are different geometry parameters that affect the sound such as cup, rim, throat and backbore dimensions (see Figure 1a).

Figure 1 – (a) Mouthpiece geometry and design parameters; (b) commercial mouthpiece dimensions [mm]

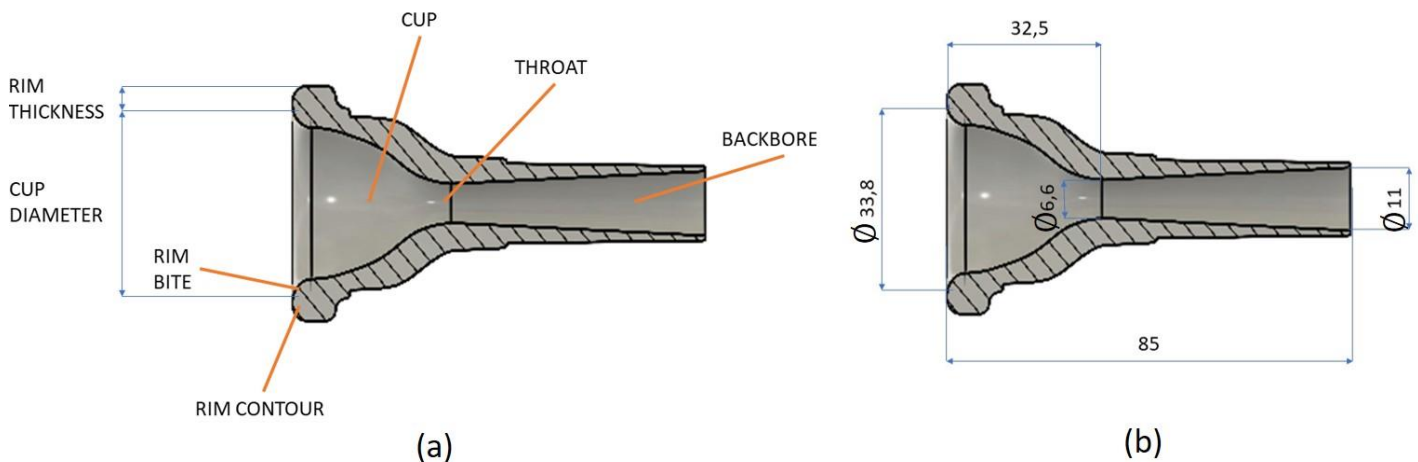


The shape of a commercial metallic (brass) mouthpiece, whose original dimensions are reported in Figure 1b, has been replicated in AM using SLA and FDM techniques to evaluate the effect of the change in material. A set of different mouthpiece geometries has been 3D modelled and manufactured to investigate the influence of the geometry changes on the sound.

Alternative mouthpiece geometries

The first mouthpiece, referred in the following of the text as #1, has the same shape of the commercial metallic mouthpiece (#7) used by the musician involved in tests. In order to satisfy player needs in terms of external personalization and improved component comfort, the first mouthpiece alternative version, called #2, is personalized with moustache in the exterior part and with a lower value for the inner rim radius to make the mouthpiece more comfortable for the player with respect to the original one (1,72mm with respect 3,75mm of #7) (see Figure 2). The #3 mouthpiece is designed for light music purposes, with a smaller cup volume due to a reduction of diameter (29,4 vs 33,8mm) and depth (25,1 vs 32,5mm). In the exterior, a minimal design is adopted with a writing personalization. Figure 2 shows a design alternative (#4) with the same internal shape as the previous model but with a more traditional external shape. Afterwards, two completely different alternatives from a geometry perspective are designed: the first one (#5) is based on a non-axisymmetric shape, with almost sharp edges of the rim and an elliptical cup, with axis length of 23,9 and 30,1mm. The second one (#6) follows the original shape, but a small bulge is added to increase the player comfort, and to reduce the lip swelling in case of long period of playing. The metallic mouthpiece usually played by the musician involved in the test has been labelled with #7; finally, the specimen #8 is identical to #4, apart the reduction of the dimensions of the mouthpiece support structure which is removed after the printing.

Figure 2 - Manufactured mouthpieces geometries.

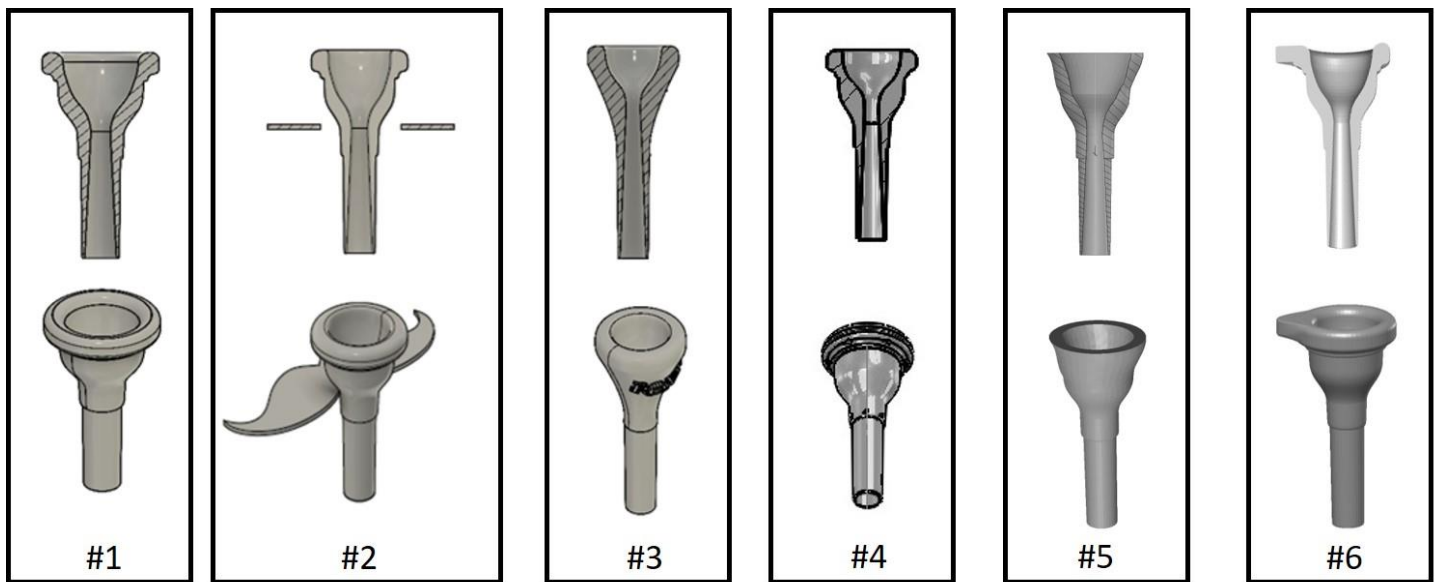

Additive Manufacturing Technology and Material

In order to produce the above mouthpiece models, SLA technique is chosen in specimens #2, #3, #4, #5, #6, and #8 due to the external high-quality finishing, the overall accuracy level that is possible to achieve and its quite affordable prices. The smooth surface characteristic is extremely important not only for exterior design, but also for the player comfort and for sound creation: the Formlabs Form 2 machine has been used. One of the problems related to the SLA technology is

that the material support is made of the same final object material and can't be removed by washing procedures, but only by hand. For this reason, the placement of the material support must be carefully chosen, in order to have the best geometry where the painstakingly operation of supports removing and following polishing is reduced as much as possible. Specimens #4 and #8 differ only for the design of supports: in #4 a support density of 1,30 and a support-part contact dimension of 0,4mm is chosen in the pre-processing software, while in #8 the settings are respectively 1,00 and 0,9mm. These setting modifications do not affect the sound performances but contribute only at the external surface finishing. One of the models (#1) is manufactured using an FDM Crealty 3D CR 10s5 machine in order to compare the geometry and sound characteristics and to check the impact of the FDM criticalities listed in literature (Figure 3): the metal used in high quality commercial mouthpieces (#7) is brass.

Figure 3 - Original (brass) and manufactured mouthpieces in AM: the orange ones in SLA while the white ones by FDM technology



The mouthpiece internal channel needs to be smooth in order to produce a good sound, so that no material support must be placed inside. For this reason, the only possible object orientation is to place the backbore axis perpendicular to the building platform and the cup on the opposite side with respect to the building platform (Figure 4). This is the only constraint noticed by the authors while manufacturing the alternative mouthpiece geometries.

Figure 4 - Mouthpiece growing direction to avoid material support in the interior channels



The Form 2 SLA machine can use different types of photoreactive resins, each one assuring good exterior smooth surface. In this project, a biocompatible resin (Dental SG) that is usually used for dental prosthesis or for objects in direct contact with human tissues has been selected: in this way, the possibility of contact between toxic materials and player mouth is avoided. In order to overcome the material degradation in time, a post-processing method, based on UV ray curing, is used to strengthen the mouthpieces and to avoid possible deformations during the experimental tests. It is worth noting that after the post-processing the mouthpieces change their colour from yellow (see Figure 4) to orange (see Figure 3).


Test and feedback

All the configurations previously presented have been tested by a single musician and evaluated, respect to the requirements selected after the interviews with end users. A description of the way in which the most significant features have been scored follows.

Quality sound, loudness and comfort


The comfort and quality sound have been assessed by asking to a musician to play the same music piece with 8 mouthpieces. The musician is asked to score the mouthpieces from 1 (low comfort) to 10 (high comfort). The recordings have been acquired using a professional Rode NTK microphone, and a Motu 8pre USB amplifier system, with a 44100Kh frequency, and saved in WAV format (see Figure 5). About sound quality, two Professors of music and the musician himself have been asked to listen to the high-quality registrations of the piece played with the 8 mouthpieces. All the experimenters are unaware that number 4 and 8 are identical: this is done to check repeatability of judgement.

Figure 5 - Recording studio.

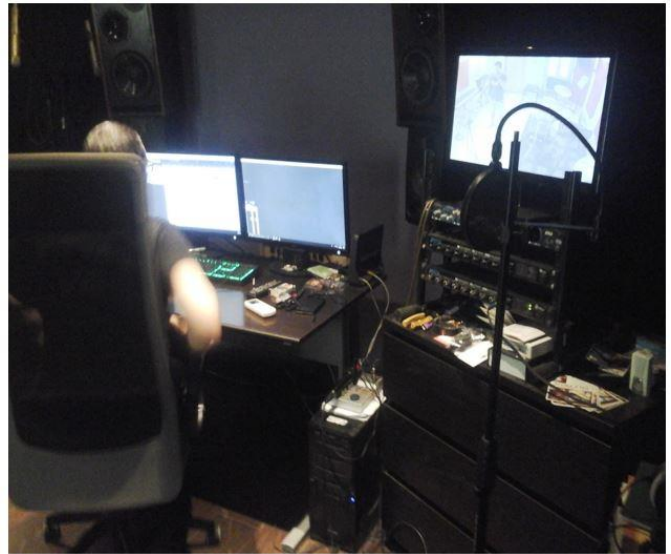


The following Figure 6 shows the results of three scorings (musician and two Professors), and the mean and standard deviation. A good agreement can be noticed between experts scoring.

Figure 6 - Sound quality assessment by experts.

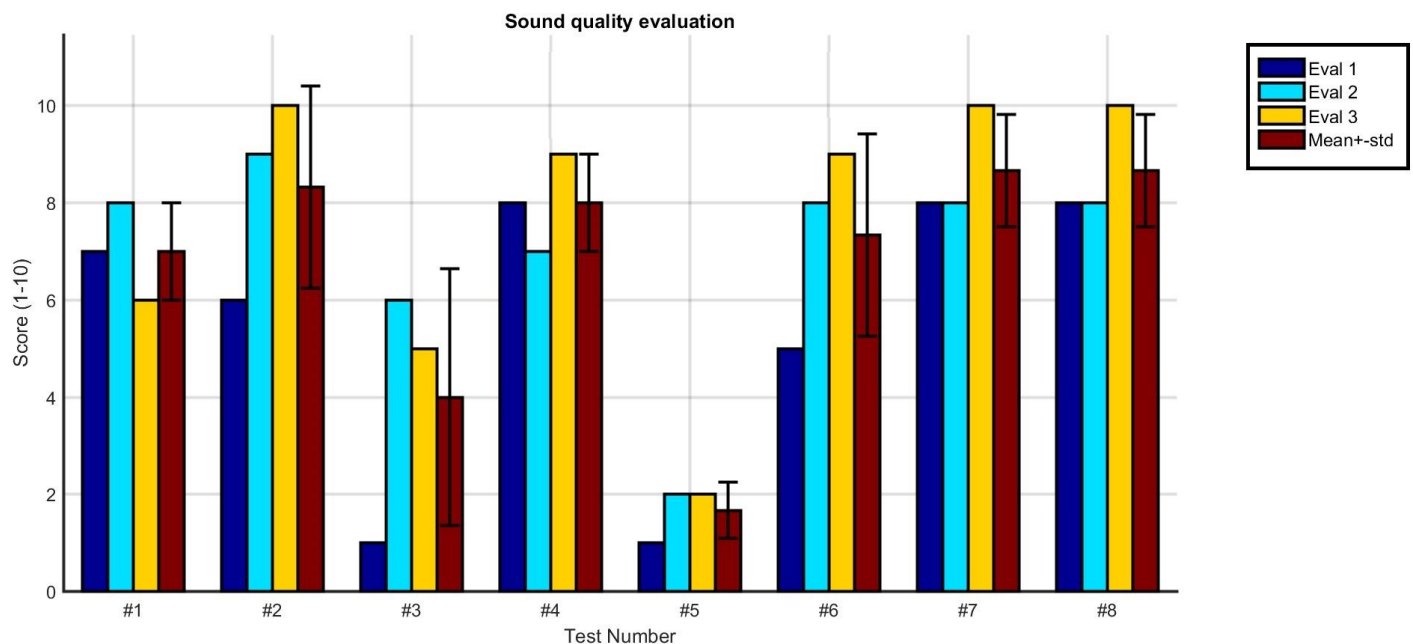


About comfort, the musician keeps into consideration features like lips adhesion, roundness of the mouthpiece, air leaks from sides, surface roughness. The scores given in the 8 tests are summarised in Figure 7.

Figure 7 - Mouthpiece comfort assessment by musician.

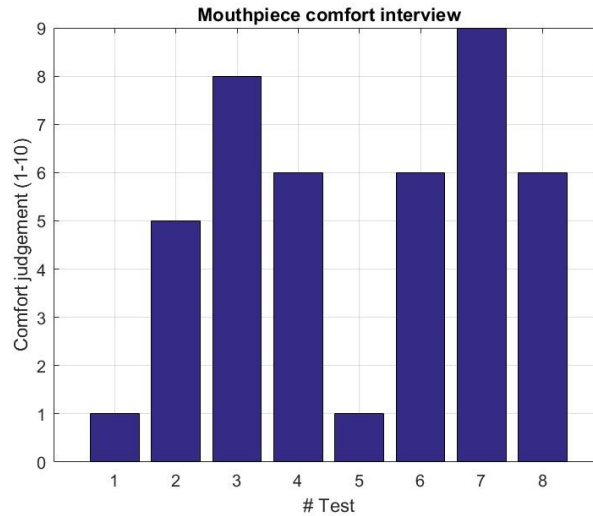

The sound loudness is a key parameter in the evaluation of wind musical instruments: The mean intensity value of the sounds in tests can be a good reference for non-expert people in the music field: the higher the sound intensity, the better the sound perception. A sound analysis in time domain and a comparison of the mean intensity value has been carried out: the mean absolute value of the sound intensity (where all the sound pauses are deleted) is included in Figure 8.

Figure 8 - Mouthpiece sound analysis assessment in terms of mean absolute intensity value.

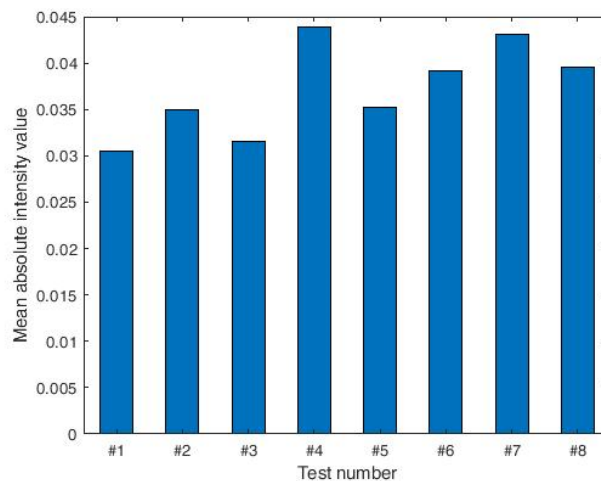

As the reader can notice, quite reduced differences can be noticed among all the mean intensity values. The mouthpieces #4, #6 and #8 show performances like the metallic one (#7). The lowest sound quality is achieved by the FDM mouthpiece due to air leaks. Scores are given assuming 1 for null intensity value, and 10 for the highest intensity.

Economical assessment

A comparison between mouthpieces has been carried out keeping into account economic issues, with all the prices referring to June 2019. The commercial cost (200€) has been considered for the brass mouthpiece. When dealing with mouthpieces produced by AM techniques direct material cost, machine depreciation, VAT, 50% reseller/producer gain

have been considered to assess costs (see Table 2). The Form 2 machine costs roughly 4000€, while the FDM machine costs less than 1000€. For all the machines a pay-back time of 3000h (average 4 months of continuous printing) has been considered. About the cost of raw materials, a litre cartridge of dental resin costs 250€, while a coil of PLA wire (1 Kg) can be purchased for 25€.

Table 2 - Costs assessment.

Mouthpiece #	Resin / wire quantity	Time to print	Direct/indirect costs	Reseller/producer Gain added	Total price [€] (incl. VAT 22%)	Score
1	13g	1h 35min	0.85	1.28	2	10
2	50,81ml	6h 45min	21.70	32.55	40	8
3	32,49ml	6h 5min	16.23	24.35	30	9
4	38ml	5h 45min	17.17	25.75	31	9
5	27,50ml	5h 45min	14.54	21.81	27	9
6	34,09ml	6h 5min	16.63	24.95	30	9
7	/	/	/	/	200	1
8	38ml	5h 45min	17.17	25.75	31	9

Other assessments


The metal mouthpiece can lead to the gluing of lips when playing trombone outside in cold winter days, and a score 3 is given because it must be stored in a pocket to keep it warm. On the other hand, both FDM and SLA score 10 because both PLA and resins are insensitive to low temperatures. About customization, FDM and SLA outclass metal traditional mouthpieces because it is possible to add writings or distinctive features (like a pair of printed moustache asked by a musician). A higher score is given to SLA because it is possible modelling thin surfaces without the risk of collapsing. Only one mouthpiece has been manufactured through FDM because the roughness is a main factor at play which reduces the appealing of this technology. It is worth nothing that FDM technology suffers from high roughness values due to two main factors, namely filament profile and staircase effect, which are visible even to a naked eye (Di Angelo, Di Stefano and Marzola, 2017). Some experimental measurements were performed using the *Alpa Face Test25* roughness tester (Figure 9) in the region near the contact area with the mouth. The results in terms of R_a are collected in Table 3. As it can be seen, the FDM technology is affected by a surface roughness that is an order of magnitude higher with respect to SLA

technology, and the overall comfort can be compromised. About mouthpiece easiness of storing, the overall dimensions of the mouthpiece have been considered.

Table 3 – Roughness measurements.

	Mean value (μm)	Standard deviation
SLA	3,29	0,70
FDM	24,99	1,96

Figure 9 – Roughness measurements for mouthpiece produce using SLA and FDM technology.

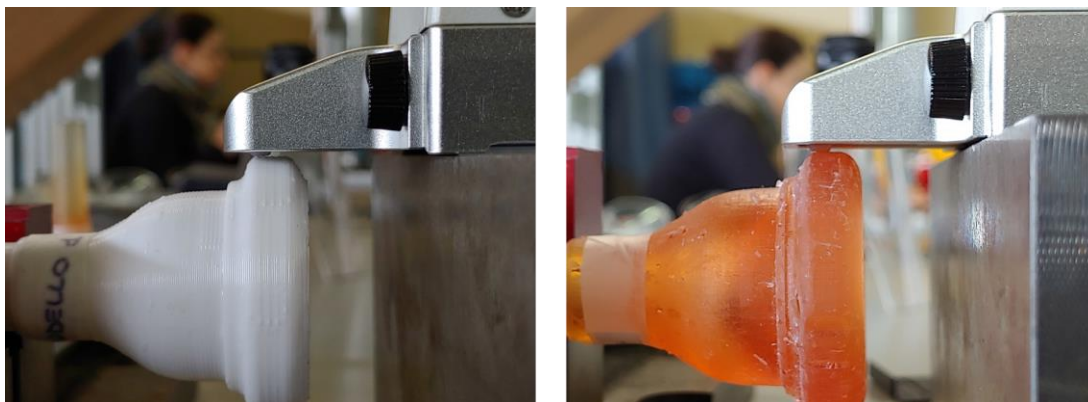

MADM analysis

A multi attribute decision making (MADM) analysis has been carried out in order to understand the mouthpiece better fitting the end-user needs: The Technique for Order Preference by Similarity to Ideal Solution (TOPSIS) (Ishizaka and Nemery, 2013) approach has been followed (Ceruti et al., 2018). At first, a table listing all the requirements, their relative importance, and the scores for each single solution is filled: the last column lists the sum of the square of the values in the same line (Table 4).

Table 4 - TOPSIS matrix.

Requirement	Relative importance	#1	#2	#3	#4	#5	#6	#7	#8	Sum of squares in line
Quality of sound	24.49	7	8.2	4	8	1.7	7.3	8.7	8.7	403.8
Customization and personal symbol	6.12	4	10	4	4	4	4	1	4	197

No gluing lips when cold	18.37	10	10	10	10	10	10	3	10	709
Mouth and lips comfort	20.41	1	5	8	6	1	6	9	6	280
Buying Cost	10.20	10	8	9	9	9	9	1	9	570
Mouthpiece easiness of storing	2.04	10	5	10	10	9	8	10	10	670
Loudness of sound	18.37	6.8	8	7	10	8	9.1	9.8	9.1	584.9

In the following, the matrix is normalized by dividing the scores times the sum of squares of the line and multiplying by the relative importance of the requirement (see Table 5). The best and worst value in each line is recorded. The Euclidean distance of each solution from the best (D_{best}) and worst (D_{worst}) solution is found. Finally, the relative distance of each single configuration from the worst solution can be computed by (Ishizaka and Nemery, 2013):

$$S = \frac{D_{worst}}{D_{worst} + D_{wbest}}$$

The higher the distance between solution and the worst one, the better it is. From this analysis it appears that the most end-user satisfying solution is the mouthpiece #8, which is even superior to mouthpiece #7 in metal.

Table 5 - TOPSIS Normalized matrix.

Weighted matrix	#1	#2	#3	#4	#5	#6	#7	#8	Best	worst
Quality of sound	0.4245	0.4973	0.2426	0.4852	0.1031	0.4427	0.5276	0.5276	0.5276	0.1031
Customization and personal symbol	0.1243	0.3108	0.1243	0.1243	0.1243	0.1243	0.0311	0.1243	0.3108	0.0311
No gluing lips when cold	0.2591	0.2591	0.2591	0.2591	0.2591	0.2591	0.0777	0.2591	0.2591	0.0777
Mouth and	0.0729	0.3644	0.5831	0.4373	0.0729	0.4373	0.6560	0.4373	0.6560	0.0729

lips comfort										
Buying Cost	0.1790	0.1432	0.1611	0.1611	0.1611	0.1611	0.0179	0.1611	0.1790	0.0179
Mouthpiece easiness of storing	0.0305	0.0152	0.0305	0.0305	0.0274	0.0244	0.0305	0.0305	0.0305	0.0152
Loudness of sound	0.2135	0.2512	0.2198	0.3140	0.2512	0.2858	0.3077	0.2858	0.3140	0.2135
D_best	0.629	0.302	0.361	0.291	0.748	0.302	0.370	0.289		
D_worst	0.414	0.607	0.585	0.593	0.252	0.562	0.728	0.617		
(S) Relative distance from worst	0.397	0.668	0.618	0.671	0.252	0.651	0.663	0.681		

The application of the methodology based on QFD and TOPSIS was fundamental to consider in a proper way pros and cons of all the design alternatives proposed. The application of such a design process where different products are evaluated in a multi-disciplinary keeps into consideration several requirements (each one with a relative weight and importance) provides more reliable results than a subjective evaluation carried out by musicians.

Conclusion

The scope of this paper is the evaluation of AM technologies in the production of parts of musical instruments. A QFD approach has been applied to detect what the end user wants; a set of alternatives has been designed and produced with FDM and SLA AM techniques. Finally, the compliance of the design alternatives to the single end-user requirements has been scored, and a TOPSIS approach has been applied to solve this multi attribute decision problem. The methodology has been applied to a mouthpiece for trombone. When a comparison between traditional metallic mouthpieces and the ones produced with FDM and SLA techniques, analyses show that the best design solution is obtained with a SLA printed mouthpiece. AM provides high customization capability and good economic impact for low production series. With an accurate design and material selection similar sound to commercial mouthpieces can be obtained using SLA technology. The porous structure typical of FDM components don't assure good sound quality in the tests carried out.

The conclusion that can be drawn from this study is that Additive Manufacturing can be applied to increase end-user satisfaction of musical instruments parts. Further studies involving different musical instruments and parts should be

carried out to investigate other design scenarios. An industrial production of 3D printed mouthpieces is suggested to Companies.

Acknowledgments

The Authors thank the following students of Mechanical and Aerospace Engineering at the School of Engineering and Architecture of the University of xxx for their support to the research: xxxx, xxxx, xxxx, xxxx, xxxx and xxxx. A special thank to Mr. xxxx, who played the musical pieces and to Professors of Music involved in the evaluation of sound quality.

References

- Agarwala M. K. and Jamalabad V. R. and Langrana N. A. and Safari A. and Whalen P. J. and Danforth S. C., (1996) "Structural quality of parts processed by fused deposition", *Rapid Prototyping Journal*, Vol. 2, No. 4, pp. 4 - 19
- Aita-Holmes C. and Liacouras P. and Wilson W. O. and Grant G. T., (2015), "Digital capture, design, and manufacturing of an extraoral device for a clarinet player with Bell's palsy", *The Journal of Prosthetic Dentistry*, Vol. 114, No. 2, pp. 297-300.
- Beaman J. J. and Deckard C. R., (1986), "Selective laser sintering with assisted powder handling".
- Celentano F. and May N. and Simoneau E. and DiPasquale R. and Shahbazi Z. and Shahbazmohamadi S., (2016), "3D printing for manufacturing antique and modern musical instrument parts" in *ASME 2016 International Mechanical Engineering Congress and Exposition*, Phoenix, Arizona, USA.
- Ceruti A. and Fiorini T. and Boggi S. and Mischi L. (2018) "Engineering optimization based on dynamic technique for order preference by similarity to ideal solution fitness: Application to unmanned aerial vehicle wing airfoil geometry definition", *Journal of Multi-Criteria Decision Analysis* 25(3-4), pp. 88-100
- Cooper K., (2001), "Rapid Prototyping Technology", CRC Press.
- Dabin M. and Narushima T. and Beirne S. T. and Ritz C. H. and Grady K., (2016), "3D modelling and printing of microtonal flutes", *Proceedings of the 16th International Conference on New Interfaces for Musical Expression (NIME 2016)*. Brisbane, Australia: Queensland Conservatorium Griffith University, pp. 286-290.
- Di Angelo L. and Di Stefano P. and Marzola A. (2017) "Surface quality prediction in FDM additive manufacturing", *The International Journal of Advanced Manufacturing Technology*, December 2017, Volume 93, Issue 9–12, pp 3655–3662
- Frizziero L. and Donnici G. and Liverani A. and Dhaimini K. (2019) "Design for additive manufacturing and advanced development methods applied to an innovative multifunctional fan", *International Journal of Manufacturing, Materials, and Mechanical Engineering* 9(2), pp. 1-32.
- Gibson I. and Rosen D. and Stucker B., (2010), "Additive manufacturing technologies", Springer, New York.
- Ishizaka A. and Nemery P. (2013) "Multi-Criteria Decision Analysis: Methods and Software", John Wiley & Sons, Ltd, ISBN:9781119974079
- Kantaros A. and Diegel O., (2018), "3D printing technology in musical instrument research: reviewing the potential", *Rapid Prototyping Journal*, vol. 24, n. 9, pp. 1511 - 1523.
- Lorenzoni V. and Doubrovskij Z. and Verlinden J., (2013), "Embracing the digital in instrument making: towards a musician-tailored mouthpiece by 3D printing", *Proceedings of the Stockholm Music Acoustics Conference 2013, SMAC 2013*, Stockholm, Sweden, pp. 419-424.

Pandey P. M. and Reddy N. V. and Dhande S. G., (2003), "Slicing procedures in layered manufacturing: a review" Rapid Prototyping Journal, Vol. 9, No. 5, pp. 274-288

Pham D. and Gault R. (1998) "A comparison of rapid prototyping technologies", International Journal of Machine Tools and Manufacture, Vol. 38, pp. 1257 - 1287

Savan J. and Simian R., (2014), "CAD modelling and 3D printing for musical instrument research: The Renaissance cornett as a case study", Early Music, vol. 42, n. 4, pp. 537 - 544.

Svoboda M. and Roth M., (2017) "The Techniques of Trombone Playing", Baerenreiter Verlag.

Ulman D. G., (2017) "The Mechanical Design Process" 6th Edition, McGraw Hill Higher Education

Zoran A. and Maes P., (2008), "Considering Virtual and Physical Aspects in Acoustic Guitar Design", in Proceedings of the 2008 Conference on New Interfaces for Musical Expression (NIME08), Genova, Italy.

Zoran A., (2011), "The 3D printed flute: digital fabrication and design of musical instruments", Journal of New Music Research, vol. 40, n. 4, pp. 379-387.