

Alma Mater Studiorum Università di Bologna  
Archivio istituzionale della ricerca

Methane Oxidation to Methanol in Water

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

*Published Version:*

Freakley S.J., Dimitratos N., Willock D.J., Taylor S.H., Kiely C.J., Hutchings G.J. (2021). Methane Oxidation to Methanol in Water. ACCOUNTS OF CHEMICAL RESEARCH, 54(11), 2614-2623 [10.1021/acs.accounts.1c00129].

*Availability:*

This version is available at: <https://hdl.handle.net/11585/834163> since: 2021-10-02

*Published:*

DOI: <http://doi.org/10.1021/acs.accounts.1c00129>

*Terms of use:*

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).  
When citing, please refer to the published version.

(Article begins on next page)

This is the final peer-reviewed accepted manuscript of:

**Simon J. Freakley, Nikolaos Dimitratos, David J. Willock, Stuart H. Taylor, Christopher J. Kiely and Graham J. Hutchings “Methane oxidation to Methanol in water” in Accounts of Chemical Research, 54 (2021), 2614-2623**

The final published version is available online at:  
<https://dx.doi.org/10.1021/acs.accounts.1c00129>

#### Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

***When citing, please refer to the published version.***

# **Methane Oxidation to Methanol in Water**

**Simon J. Freakley,<sup>1</sup> Nikolaos Dimitratos,<sup>2</sup> David J. Willock,<sup>3</sup> Stuart H. Taylor,<sup>3</sup> Christopher J. Kiely<sup>4</sup> and Graham J. Hutchings<sup>3\*</sup>**

<sup>1</sup> Department of Chemistry, University of Bath, Claverton Down, Bath, BA2 7AY, UK; orcid.org/0000-0002-6395-6646

<sup>2</sup> Dipartimento di Chimica Industriale “Toso Montanari”, Università degli Studi di Bologna, Viale Risorgimento 4, 40136, Bologna, Italy; orcid.org/0000-0002-6620-4335

<sup>3</sup> Max Planck Centre on the Fundamentals of Heterogeneous Catalysis, FUNCAT, Cardiff Catalysis Institute and School of Chemistry, Main Building, Park Place, Cardiff, CF10 3AT, UK; orcid.org/0000-0001-8885-1560; Email: [hutch@cf.ac.uk](mailto:hutch@cf.ac.uk).

<sup>4</sup> Department of Materials Science and Engineering, Lehigh University, 5 East Packer Avenue, Bethlehem, PA 18015, USA; orcid.org/0000-0001-5412-0970

## CONSPECTUS


Methane represents one of the most abundant carbon sources for fuel or chemical production. However, remote geographical locations and high transportation costs result in a substantial proportion being flared at source. The selective oxidation of methane to methanol remains a grand challenge for catalytic chemistry, due to the large energy barrier for initial C-H activation and prevention of over oxidation to CO<sub>2</sub>. Indirect methods such as steam reforming produce CO and H<sub>2</sub> chemical building blocks, however, they consume large amounts of energy over multi-stage processes. This makes the development of low temperature selective oxidation of methane to methanol highly desirable and explains why it has remained an active area of research over the last 50 years.

The thermodynamically favourable oxidation of methane to methanol would ideally use only molecular oxygen. Nature effects this transformation with the enzyme *methane monooxygenase (MMO)* in aqueous solution and ambient temperature with the addition of two equivalents of reducing cofactor. *MMO* active sites are Fe and Cu oxo-clusters and the incorporation of these metals into zeolitic frameworks can result in biomimetic activity. Most approaches to methane oxidation using metal doped zeolites use high temperature with oxygen or N<sub>2</sub>O, however demonstrations of catalytic cycles without catalyst regeneration cycles are limited. Over the last 10 years we have developed Fe-Cu-ZSM-5 materials for the selective oxidation of methane to methanol in aqueous conditions at 50 °C using H<sub>2</sub>O<sub>2</sub> as an oxidant (effectively O<sub>2</sub> + 2 reducing equivalents) which compete with *MMO* in terms of activity. To date these materials are among the most active and selective catalysts for methane oxidation at this mild condition but industrially H<sub>2</sub>O<sub>2</sub> is an expensive oxidant to use in the production of methanol.

This observation of activity under mild conditions led to new approaches to utilise O<sub>2</sub> as the oxidant. Supported precious metal nanoparticles have been shown to be active for a range of C-H activation reactions using O<sub>2</sub> and H<sub>2</sub>O<sub>2</sub>, but the rapid decomposition of H<sub>2</sub>O<sub>2</sub> over metal surfaces limits efficiency. We identified that this decomposition could be minimised by removing the support material and carrying out the reaction with colloidal AuPd nanoparticles. The efficiency of methanol production with H<sub>2</sub>O<sub>2</sub> consumption was increased four orders of magnitude and crucially it was demonstrated for the first time that molecular O<sub>2</sub> could be incorporated into the methanol produced with 91% selectivity. The understanding gained from

these two approaches provides valuable insight into possible new routes to selective methane oxidation which will be presented here in the context of our own research in this area.

## GRAPHICAL ABSTRACT

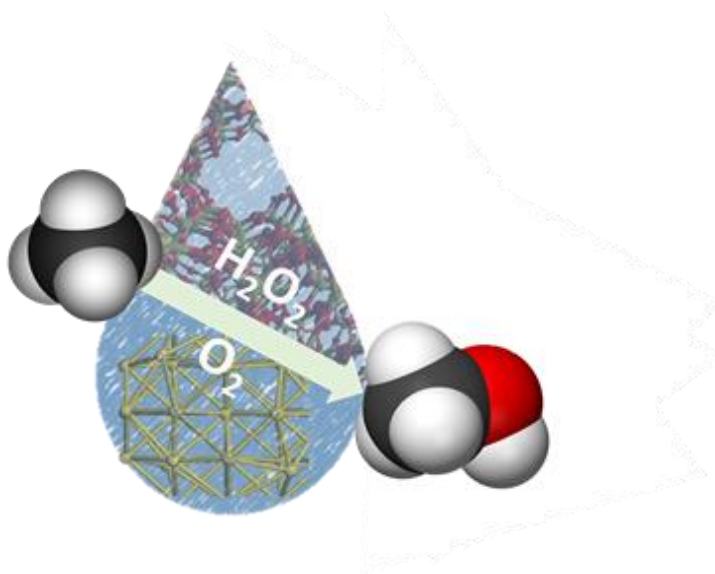

## KEY REFERENCES

- Hammond, C.; Forde, M. M.; Ab Rahim, M. H.; Thetford, A.; He, Q.; Jenkins, R. L.; Dimitratos, N.; Lopez-Sanchez, J. A.; Dummer, N. F.; Murphy, D. M.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Stangland, E. E.; Kang, J.; Hagen, H.; Kiely, C. J.; Hutchings, G. J. **Direct Catalytic Conversion of Methane to Methanol in an Aqueous Medium by Using Copper-Promoted Fe-ZSM-5.** *Angew. Chemie. Int. Ed.* **2012**, 51 (21), 5129–5133. [doi.org/10.1002/anie.201108706](https://doi.org/10.1002/anie.201108706) *Demonstrates that methane can be selectively oxidised at relatively mild conditions with similar total turnover numbers to the enzymatic reaction using metal doped acidic zeolites.*<sup>1</sup>
- Hammond, C.; Dimitratos, N.; Jenkins, R. L.; Lopez-Sanchez, J. A.; Kondrat, S. A.; Ab Rahim, M. H.; Forde, M. M.; Thetford, A.; Taylor, S. H.; Hagen, H.; Stangland, E. E.; Kang, J. H.; Moulijn, J. M.; Willock D. J.; Hutchings G. J. **Elucidation and Evolution of the Active Component within Cu/Fe/ZSM-5 for Catalytic Methane Oxidation: From Synthesis to Catalysis** *ACS Catal.* **2013**, 3, 689-699. [doi.org/10.1021/cs3007999](https://doi.org/10.1021/cs3007999) *A di-nuclear Fe-oxo site is described as a potential active site within the zeolite which interacts with H<sub>2</sub>O<sub>2</sub> and methane and has similar structural features to the active site in the enzyme methane monooxygenase.*<sup>2</sup>
- Ab Rahim, M. H.; Forde, M. M.; Jenkins, R. L.; Hammond, C.; He, Q.; Dimitratos, N.; Lopez-Sanchez, J. A.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Murphy, D. M.; Kiely,

C. J.; Hutchings, G. J. **Oxidation of Methane to Methanol with Hydrogen Peroxide Using Supported Gold-Palladium Alloy Nanoparticles.** *Angew. Chemie. Int. Ed.* **2013**, 125 (4), 1318–1322. [doi.org/10.1002/ange.201207717](https://doi.org/10.1002/ange.201207717) Catalysts that are active for  $H_2O_2$  synthesis can initiate a radical chain reaction to produce methanol using preformed  $H_2O_2$  and in situ formed  $H_2O_2$  from the reaction of  $H_2$  and  $O_2$ .<sup>3</sup>

- Agarwal, N.; Freakley, S. J.; McVicker, R. U.; Althahban, S. M.; Dimitratos, N.; He, Q.; Morgan, D. J.; Jenkins, R. L.; Willock, D. J.; Taylor, S. H.; Kiely, C. J.; Hutchings, G. J. **Aqueous Au-Pd Colloids Catalyze Selective  $CH_4$  Oxidation to  $CH_3OH$  with  $O_2$  under Mild Conditions.** *Science*, **2017**, 358 (6360), 223–227. [doi.org/10.1126/science.aan6515](https://doi.org/10.1126/science.aan6515) In the presence of  $H_2O_2$  and  $O_2$  colloidal AuPd nanoparticles can produce methanol with oxygen incorporation from molecular oxygen through a radical pathway at ambient temperature.<sup>4</sup>

## 1. DIRECT METHANE CONVERSION – WHY IS IT IMPORTANT AND TOPICAL?

One of the greatest challenges in chemistry for academics and industrialists is the activation and selective oxidation of a C-H bond. The challenge is especially true for the selective oxidation of methane to methanol under mild reaction conditions, a reaction that has fascinated scientists for over a century. Our approach has focussed on the use of CuFe-ZSM-5<sup>1,2</sup> or AuPd colloidal nanoparticles<sup>3,4</sup> with H<sub>2</sub>O<sub>2</sub> as the terminal oxidant. In this way we have opened a new catalytic approach that can pave the way to find a catalysed process for the selective oxidation of methane to methanol using O<sub>2</sub> as the terminal oxidant.

Methane is an abundant feedstock and is the major constituent of natural gas.<sup>5-7</sup> It can be extracted from shale gas and other sources, including emission from natural sources, such as natural wetlands, agriculture, and the generation of methane in landfills during waste decomposition. Although the life-time of methane in the atmosphere is much shorter than that of carbon dioxide, the emerging problem is that methane is more effective greenhouse gas than carbon dioxide being ca. 28-36 times more detrimental.<sup>8</sup> Moreover, the observed continuous rise in temperature of the planet can also contribute significantly to the rise of methane emission globally further exacerbating the climate problem. Therefore, the necessity to transform methane to a useful and more environmentally friendly chemical, as opposed to just flaring to form carbon dioxide is essential. At this moment, the majority of methane produced is combusted either for heating purposes or in the production of electricity. Unfortunately, especially in the case of oil fields, when methane is recovered it is directly flared, producing large amounts of carbon dioxide as a consequence. Indeed 4% of global natural gas production is flared annually as it is not considered economic for recovery and use. This represents a huge resource of  $145 \times 10^9 \text{ m}^3/\text{annum}$  natural gas, but as it is flared it results in  $2.75 \times 10^8$  tons of CO<sub>2</sub> be emitted to the environment.<sup>9</sup> Therefore, there exists a critical need to find an economic way to transform methane to useful and high value-added chemicals at the scale required for these geographic locations.

The chemical activation of methane is very challenging because its relative inertness ( $\Delta H_{\text{C-H}} = 438.8 \text{ kJ mol}^{-1}$ ) and low reactivity, which means that the current industrial utilization of methane tends to be based on indirect, energy intensive routes. For example, the conversion of methane to methanol, one of the most important products in moving towards a methanol economy,

requires first the production of syngas (CO/H<sub>2</sub>) using either steam reforming of methane or partial oxidation which require to be operated at a large scale to be economic. Syngas can subsequently be transformed to methanol using a copper catalyst. However, syngas can also be catalytically transformed to a range of important hydrocarbon products. Hence the direct conversion of methane to methanol has become a highly desirable prospect since it represents one of the most promising routes to direct utilisation of remote sources of natural gas. Early work on methane oxidation used high temperatures with oxide catalysts and this typically led to hydrocarbons rather than oxygenates as products<sup>10</sup> unless the reaction conditions were closely controlled.<sup>11</sup> Over many decades, the gas-phase oxidation of methane to methanol has been intensively investigated using a wide range of catalysts and different experimental conditions. It has been concluded that it is a major challenge to achieve a high selectivity to methanol while simultaneously maintaining high methane conversion since the methanol produced is more reactive than methane and overoxidation can predominate at high conversions and this facilitates the consecutive oxidation of methanol to other products such as formaldehyde, formic acid and carbon oxides. Considering all these observations, it is evident that an alternative approach for the selective oxidation of methane to methanol has to be discovered which avoids the use of high temperatures. This goal requires the development of novel catalysts that can oxidise methane selectively at lower reaction temperatures, *i.e.*,  $\leq 200$  °C and possibly considering the use of alternative oxidants. In this way, it may become possible to minimise the overoxidation of methanol and therefore improve the yield of methanol and other useful oxygenated products such as formaldehyde and formic acid.


## 2. BACKGROUND ON ALTERNATIVE APPROACHES

A range of low temperature approaches to this problem have to date been investigated with the majority of them having disadvantages that include incomplete catalytic cycles, low turnover frequency or space-time-yield or they pose unwanted environmental issues due to the choice of solvent, catalyst and oxidant involved. For example, several homogeneous catalysts have been proposed for methane oxidation using strong acidic conditions. Periana and co-workers reported the synthesis and utilisation of a bipyrimidyl -Pt complex in oleum for the conversion of methane to methyl bisulfate in the presence of concentrated sulphuric acid and using SO<sub>3</sub> as the desired oxidant.<sup>12</sup> The yield to methyl bisulfate achieved was above 70% with 81%



selectivity and to obtain the final desired methanol product, the methyl bisulfate is then reacted with water. The high selectivity achieved in this approach is due to the absence of free methanol during the oxidation step because the bisulfate acts as a protective group and therefore avoids the overoxidation issues observed when directly forming the methoxy species at higher temperatures which can be easily overoxidized. In a similar matter, Schüth and co-workers have proposed a heterogeneous bifunctional catalyst, based on the use of a platinum-modified covalent triazine framework (CTF-Pt) which gave results similar to that of the reaction proposed by Periana and showed high stability after recycling without a significant loss of activity or selectivity.<sup>13</sup> Although the results obtained from both these approaches were promising, from an industrial standpoint they are severely limited by the associated issues of toxicity, waste disposal, corrosion, difficulties with the recyclability of the acidic media, and the high capital cost for the construction of large scale plants.

Recently an alternative low temperature approach (at around 200 °C) has been proposed based on a stepwise conversion of methane to methanol as illustrated in Figure 1.

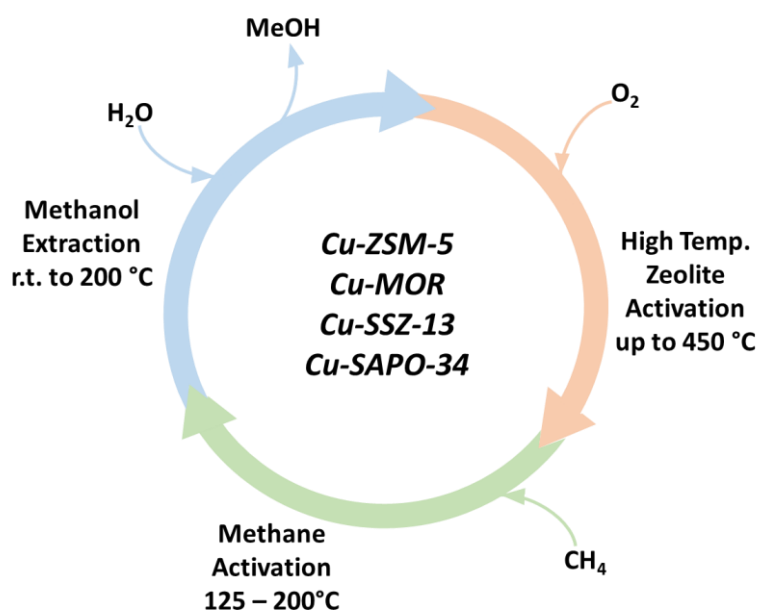

**Figure 1.** Illustration of the three-step conversion of methane to methanol including (i) typical activation of the material, (ii) oxidation of methane to form surface bound methanol precursors, and (iii) extraction of methanol, for example with water redrawn from ref 14.


In this new approach, the first step is the activation of catalyst material at high temperature, (~ 450 °C) using either O<sub>2</sub> or N<sub>2</sub>O as the preferred oxidant. In the second step, the oxidant is removed from the reactor and methane is introduced and passed over the activated catalyst material at temperatures between 125 and 200 °C. In the final step, the surface methoxy formed at the active sites is extracted with water to form methanol. The active catalyst materials used in this stepwise approach were either Fe-ZSM-5 activated by N<sub>2</sub>O or Cu-ZSM-5 activated by molecular oxygen. The proposed active sites in the case of the N<sub>2</sub>O activated Fe-ZSM-5 catalysts were the bridging oxygen( $\mu_2$ ) of the Fe-oxo species which facilitates hydrogen atom abstraction from methane.<sup>14,15</sup> In a similar way, the activation of Cu-ZSM-5 by molecular oxygen enabled the formation of bis( $\mu$ -oxo) di-copper clusters and these sites have been proposed to activate and convert methane to methanol. This stepwise approach has been extended to a range of additional zeolite frameworks which have shown an even higher methanol yield than those of the initial studies. Cu-mordenite catalysts when operated in a two stage non-closed catalytic cycle can form CH<sub>3</sub>OH.<sup>16-18</sup> An oxidised Cu species is reacted with CH<sub>4</sub> to form a surface methoxyl which is subsequently extracted at a lower temperature with water. van Bokhoven and co-workers demonstrated<sup>19</sup> that Cu-mordenite can oxidise CH<sub>4</sub> with a continuous flow of H<sub>2</sub>O to produce methanol; however, this reaction is stoichiometric rather than catalytic as the turnover is 0.21 mol CH<sub>3</sub>OH/mol Cu. Despite the promising results yielded by this approach, Bokhoven and co-workers have reported<sup>14</sup> that significant improvements are still needed for the industrial utilisation of this stepwise process, particularly in the areas of (i) reactor design, (ii) development of materials that allow faster cycling, (iii) utilisation of lower amounts of water/acetonitrile during the extraction process to reach a higher concentration of methanol in the extraction solution, and (iv) improving the efficiency and economic viability of the stepwise process.

### **3. SELECTIVE METHANE OXIDATION USING AuPd ALLOYS WITH H<sub>2</sub>O<sub>2</sub>**

An alternative low temperature approach as proposed by our group was the utilisation of H<sub>2</sub>O<sub>2</sub> as the alternative oxidant under mild reaction conditions (50-70 °C) using water as the preferred solvent with all the initial experiments being conducted in batch autoclave reactors. It is known that methane monooxygenase can operate and activate methane selectively at similar temperatures (around 50 °C) with high selectivity to methanol and using water as the desired

solvent using a di-iron cluster as the active site. In the methane monooxygenase the hydroperoxide oxidant is delivered by a cofactor that reduces molecular oxygen. Removal of the cofactor and using  $\text{H}_2\text{O}_2$  only gives a very slow oxidation. We considered that there was considerable scope to design catalysts that can activate and convert methane to methanol under mild reaction conditions while avoiding overoxidation to  $\text{CO}_2$ . Sorokin and co-workers have also reported the activation of methane using  $\text{H}_2\text{O}_2$  under mild conditions using a  $\mu$ -nitrido iron phthalocyanine complex grafted onto a silica support as a possible bio-inspired heterogeneous catalyst.<sup>20,21</sup> However, this catalyst was unstable with significant leaching of iron occurring during the reaction and methanol was also formed by oxidation of the phthalocyanine complex.<sup>22</sup>

Our team was one of the winners of the 2007 Dow Methane Challenge<sup>23</sup> and the approach we initially adopted was based on catalysis by gold. We had previously shown that the combination of gold and palladium to form supported bimetallic nanoparticle catalysts were effective catalysts for the direct synthesis of  $\text{H}_2\text{O}_2$ <sup>24</sup> and the selective oxidation of benzyl alcohol to benzaldehyde.<sup>25</sup> We considered that alcohol oxidation and direct  $\text{H}_2\text{O}_2$  synthesis can be linked through the formation of a hydroperoxy species in solution and that these hydroperoxy species could be useful oxidants as is the case for methane monooxygenase. Based on this observation, our initial work on low temperature selective methane oxidation investigated the performance of Au-Pd nanoparticles supported on  $\text{TiO}_2$  in an aqueous solvent using  $\text{H}_2\text{O}_2$  at  $50^\circ\text{C}$ .<sup>26</sup> Catalysts were prepared by impregnation and the most active contained a 5 wt.% metal loading (1:1 Au:Pd). The catalyst was highly selective towards methyl-hydroperoxide and methanol (>90%), although the productivity was relatively low ( $0.28 \text{ mol}_{(\text{products})}\text{kg}_{(\text{cat})}^{-1}\text{h}^{-1}$ ). Changing the support material from  $\text{TiO}_2$  to  $\text{CeO}_2$ ,  $\text{SiO}_2$ ,  $\text{Al}_2\text{O}_3$  or carbon did not result in an improved performance. The primary reaction product was methyl-hydroperoxide which was subsequently converted to methanol. Once generated methanol was further oxidised to formic acid, which was a major route to the formation of carbon dioxide. In addition, carbon oxides could be formed by direct conversion of methyl-hydroperoxide and methanol, allowing us to propose the reaction scheme presented in Figure 2.

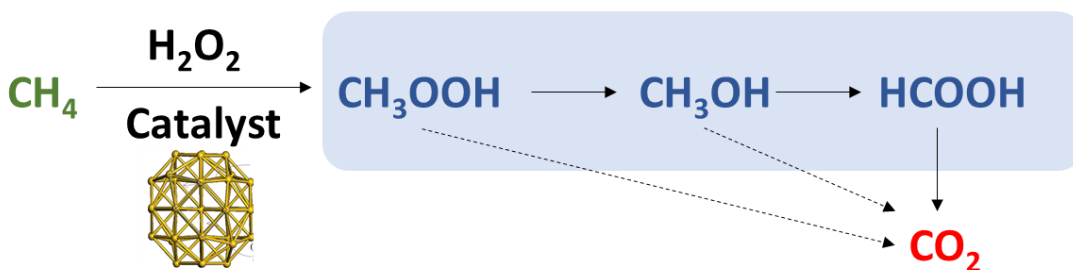


**Figure 2.** Methane oxidation using  $\text{H}_2\text{O}_2$  over Au-Pd/ $\text{TiO}_2$  supported catalysts.

Since gold-palladium bimetallic nanoparticle catalysts are effective for the direct synthesis of  $\text{H}_2\text{O}_2$  from  $\text{H}_2/\text{O}_2$ ,<sup>27-29</sup> and because they are also selective for methane oxidation with  $\text{H}_2\text{O}_2$ , we postulated that it should be conceptually possible to generate hydroperoxy radicals *in-situ* from hydrogen and oxygen and subsequently use them to selectively oxidise methane. Hence, the Au-Pd/ $\text{TiO}_2$  catalyst prepared by an impregnation route was investigated using a mixture of methane, hydrogen and oxygen, diluted with nitrogen to ensure our experiments were conducted outside of the flammable limits.<sup>26</sup> The *in-situ* hydroperoxy approach demonstrated a clear advantage as methanol selectivity was increased to 68% from 49% when using preformed  $\text{H}_2\text{O}_2$ , whilst the productivity remained constant. When the reaction was carried out with molecular oxygen (i.e. without co-fed hydrogen, and without  $\text{H}_2\text{O}_2$ ), there was no selectivity towards oxygenated products. In these initial studies the decomposition of  $\text{H}_2\text{O}_2$  or the non-selective utilisation of hydrogen in the *in situ* peroxy experiments remained the major problem.

In more recent work, we have investigated varying the preparation procedure for the Au-Pd/ $\text{TiO}_2$  catalyst, to attempt to improve the productivity of methane oxidation using  $\text{H}_2\text{O}_2$ . Gold-palladium bimetallic nanoparticles were deposited onto  $\text{TiO}_2$  using a stabiliser-free colloidal preparation immobilisation route.<sup>30</sup> In particular, thermal treatment of the  $\text{TiO}_2$  support prior to deposition of the metal nanoparticles, and thermal treatment of the supported catalyst, were used as strategies to control the mean metal particle size and the ratio of rutile/anatase and the metal particle size respectively. High temperature thermal treatments were found to be the most beneficial, with  $\text{TiO}_2$  calcination at  $800^\circ\text{C}$  for 3 h prior to metal deposition, followed by the same treatment after metal deposition producing the best catalyst. A productivity of  $0.677 \text{ mol}_{(\text{products})}\text{kg}_{(\text{cat})}^{-1}\text{h}^{-1}$  was achieved, whilst the  $\text{H}_2\text{O}_2$  consumption remained high.

Although our bimetallic gold-palladium supported catalysts showed promising activity for methane selective oxidation, they still exhibited relatively low rates of product formation. In an

attempt to improve on the methane oxidation activity of bimetallic Au-Pd catalysts, trimetallic Au-Pd-Cu catalysts supported on  $\text{TiO}_2$  were investigated for low temperature selective oxidation of methane with  $\text{H}_2\text{O}_2$  at  $50^\circ\text{C}$ . Encouragingly, the rate of methane oxidation using the Au-Pd-Cu/ $\text{TiO}_2$  catalysts was increased by a factor of 5, when compared to Au-Pd/ $\text{TiO}_2$ . Furthermore, the selectivity to oxygenated products remained very high ( $>95\%$ ), demonstrating that considerable scope still exists for design of multi-component metal nanoparticles for selective methane oxidation at low temperatures. However, as the catalyst productivity increases using such nanoparticle-alloy catalysts, there is also a general increase of the amount of  $\text{H}_2\text{O}_2$  consumed with an associated decrease in the efficiency of  $\text{H}_2\text{O}_2$  utilisation.

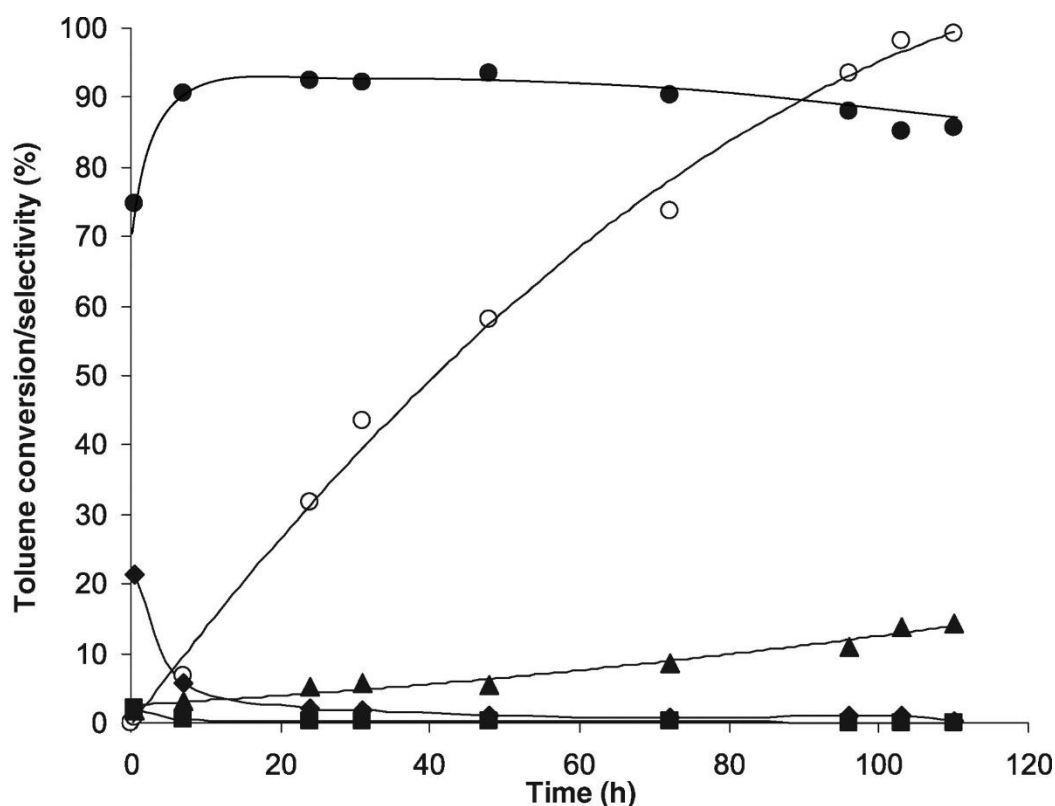


**Figure 3.** Toluene conversion using 1 wt% AuPd/C,  $160^\circ\text{C}$ ;  $\text{P}_{\text{O}_2}$  0.1 MPa; toluene (20 ml); catalyst (0.8 g,) ○ conversion, ■ benzyl alcohol selectivity, ◆ benzaldehyde selectivity, ▲ benzoic acid selectivity, ● benzyl benzoate. Reproduced with permission from ref 31. Copyright 2011 AAAS.

As part of our studies on C-H bond activation with AuPd alloys we decided to investigate the oxidation of the methyl group in toluene as a more reactive model for such oxidation reactions.

For this we used molecular oxygen as the terminal oxidant.<sup>31</sup> By elevating the temperature we found that toluene could be oxidised in a solvent-free reaction to form benzyl benzoate in very high yields (Figure 3). The high selectivity to benzyl benzoate rather than forming benzoic acid is considered to be due the reaction of two of the initial products namely benzyl alcohol and benzaldehyde to form a hemiacetyl that is subsequently oxidised to the ester. We reasoned that if similar chemistry could be carried out with methane in place of toluene this could form the basis of a new reaction. Unfortunately, this has not been found to be possible to date but this is still an area of active research.

#### **4. METHANE OXIDATION USING ZSM-5 CATALYSTS WITH H<sub>2</sub>O<sub>2</sub>**

As metal-support interactions can be a key factor in heterogeneous catalysis, we decided the nature of the support required more careful investigation. Our work based around bimetallic gold-palladium nanoparticles for methane selective oxidation largely focused on using TiO<sub>2</sub> as a support, and we developed an understanding that the metal support interface was largely responsible for the excessive decomposition of H<sub>2</sub>O<sub>2</sub>, resulting in the low efficiency of its use to effectively oxidise methane. Consequently, our strategy of catalyst design started to focus on identification of more effective catalyst support and in particular an acidic support could be beneficial in stabilising H<sub>2</sub>O<sub>2</sub> as acid is often utilised as a stabiliser during H<sub>2</sub>O<sub>2</sub> synthesis. At the same time, by drawing on the analogy with methane monooxygenase, we also postulated that confinement of the reactants would be a beneficial factor in bringing together important small molecular reacting species with the active sites in the catalyst. This led us to investigate microporous zeolites as supports for selective methane oxidation catalysts.

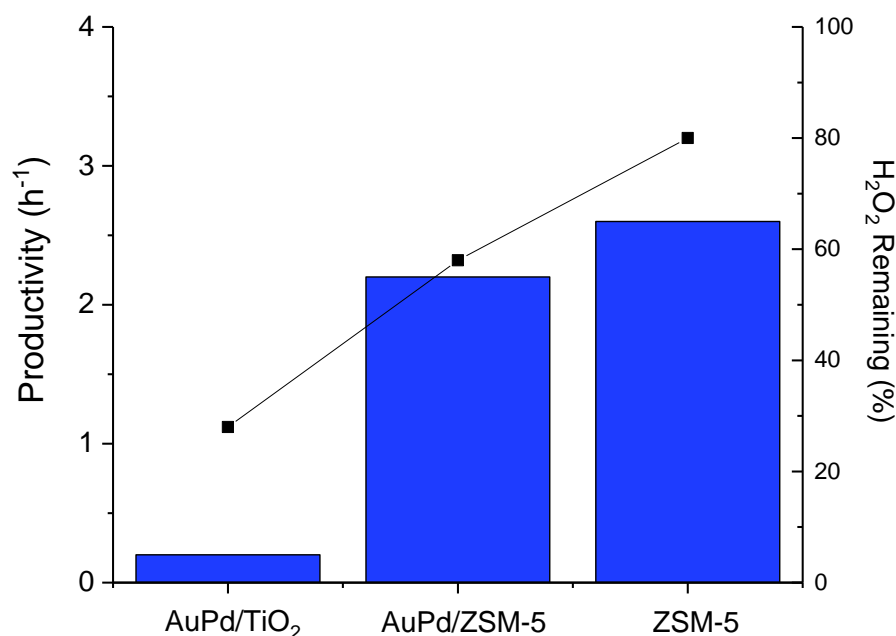


**Figure 4.** Methane oxidation with AuPd and ZSM-5 catalysts showing that ZSM-5 by itself is a superior catalyst. *Reaction conditions:* Catalyst (27mg, calcined 400°C, 3 h);  $P_{(\text{CH}_4)}$ :30.5 bar;  $[\text{H}_2\text{O}_2]$ :0.5M; 50°C; 30 min; 1500 rpm.

Although we initially investigated ZSM-5 as a support for the Au-Pd nanoparticles, to our surprise it quickly became evident that ZSM-5 was more active *without* being decorated with Au-Pd nanoparticles (Figure 4). Indeed, H-ZSM-5 ( $\text{SiO}_2/\text{Al}_2\text{O}_3 = 30$ ) calcined at 550°C was identified as the most active Si:Al ratio from a range of ZSM-5 materials we investigated. Under standard reaction conditions (Figure 4), ZSM-5 gave a conversion of 0.3% with 95% selectivity towards oxygenated products of methyl-hydroperoxide, methanol and formic acid.<sup>32</sup> The reason for the enhanced activity was due to some extent to the decrease in decomposition of  $\text{H}_2\text{O}_2$ .

To further elucidate the identity of the catalytically active species, elemental analysis was employed, showing that the ZSM-5 contained a small, but nevertheless significant amount, of iron in the zeolite framework. When additional iron was added in the form of extra-framework species, there was a further increase in the methane conversion to 0.7% and the high selectivity towards methanol maintained, with only low quantities of carbon oxides formed. Spectroscopic investigations using EXAFS revealed that iron was present as a di-iron complex containing


antiferromagnetically coupled high-spin octahedral  $\text{Fe}^{3+}$  centres. Combining data from characterisation experiments with DFT molecular modelling studies we proposed a closed catalytic cycle for methane selective oxidation as shown in Figure 5.

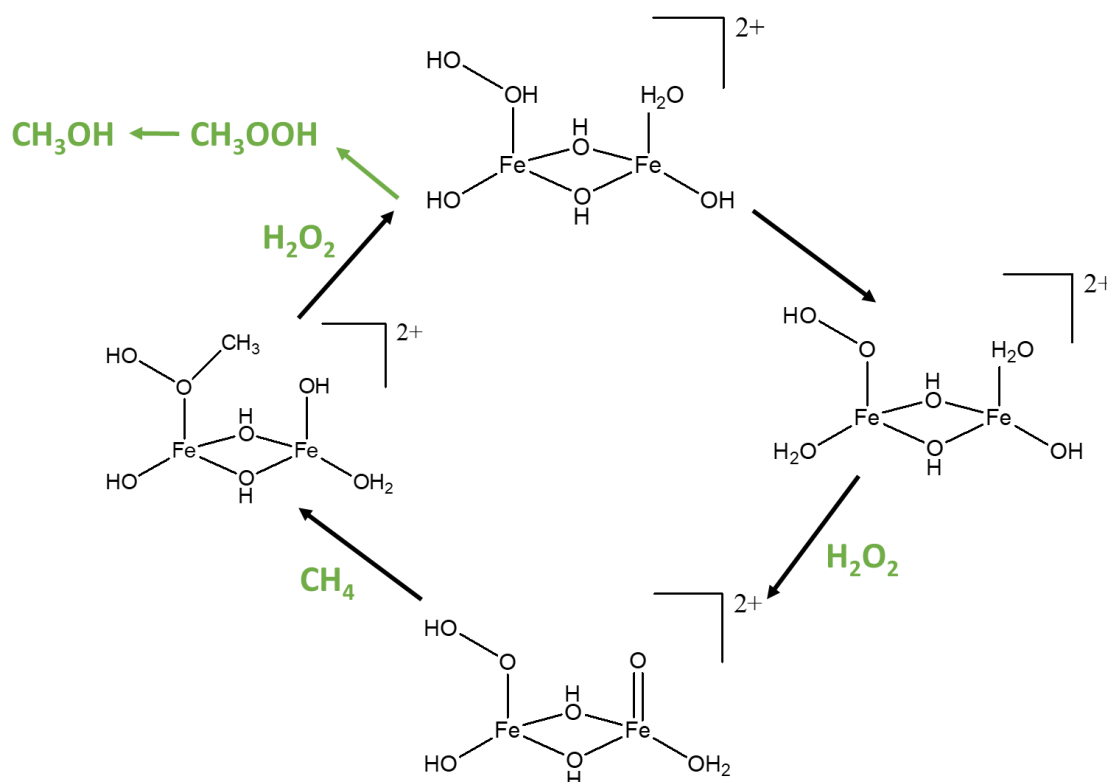

**Figure 5** Proposed cycle for the catalytic selective oxidation of methane by a binuclear iron species in ZSM-5.

In common with our previous observations on methane oxidation with  $\text{H}_2\text{O}_2$  using Au-Pd/ $\text{TiO}_2$  catalysts, methyl-hydroperoxide was also the primary reaction product over the Fe-ZSM-5 catalyst. Subsequently, the methyl-hydroperoxide formed can then undergo selective conversion to methanol, or a non-selective conversion to formic acid. Formic acid is also produced by consecutive oxidation of methanol, and once formed formic acid is the precursor to form undesirable carbon oxides. The catalytic cycle requires two equivalents of  $\text{H}_2\text{O}_2$  to produce a single equivalent of methanol, providing an upper limit on the efficiency of  $\text{H}_2\text{O}_2$  use.




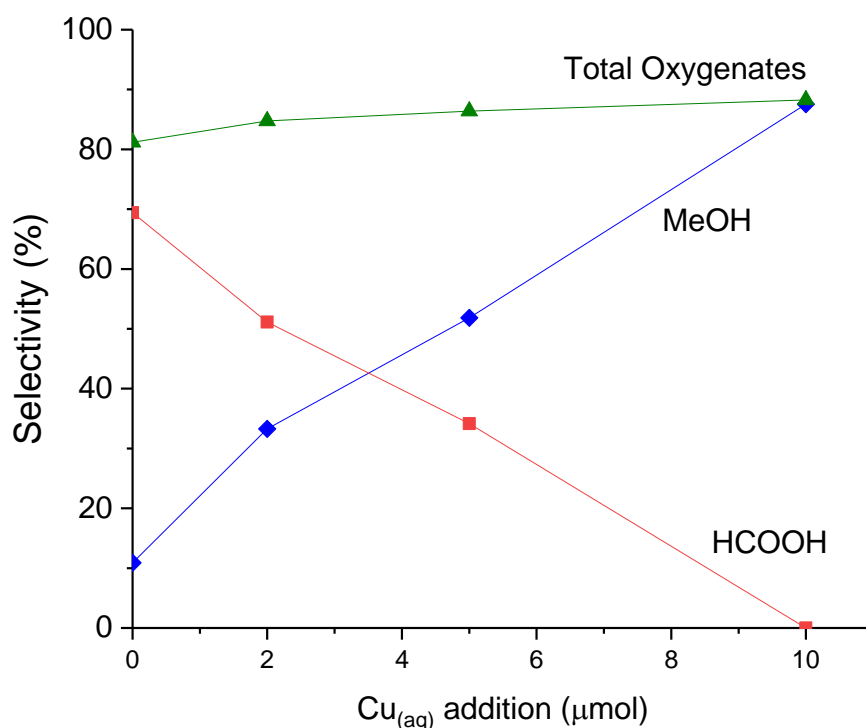


**Figure 6.** Effect of adding  $\text{Cu}^{2+}$  to a reaction catalysed by Fe-ZSM-5. *Reaction conditions:*  $\text{P}(\text{CH}_4)$ :30.5 bar;  $[\text{H}_2\text{O}_2]$ :0.5M; 50°C; 30 min; 1500 rpm.

Increasing the iron concentration further increased the catalyst activity, however, it had a deleterious effect on methanol selectivity.<sup>32</sup> For a 2.5 wt.% Fe-ZSM-5 (30) catalyst a typical product distribution was 1% methyl-hydroperoxide, 10% methanol, 72% formic acid and 17% carbon oxides, hence impeding over-oxidation of methanol was an important factor to increase its yield. A key discovery was the importance of adding copper to the Fe-ZSM-5 catalyst. Incorporating copper, either as an extra-framework species or as homogeneous  $\text{Cu}^{2+}$  ions in solution (Figure 6), markedly increased the selectivity to methanol whilst maintaining methane conversion.<sup>32</sup> We found that the acidity of ZSM-5 was leading to a higher level of  $\text{H}_2\text{O}_2$  decomposition and that by using the non-acidic silicalite-1 framework improved results could be achieved. Adding Cu in an additional solid to the heterogeneously catalysed reaction had a marked effect (Figure 7). With a Fe-silicalite catalyst without Cu added it is possible to achieve a 10% methane conversion with a total oxygenate selectivity of 96% but this was mainly formic acid and only 8% methanol was observed. Addition of Cu-silicate, and inactive material in this reaction. Enables 93% selectivity to methanol to be achieved at 9.5% conversion. The addition

of  $\text{Cu}^{2+}$  clearly hindered the oxidation of methanol to formic acid. EPR studies demonstrated that the  $\text{Cu}^{2+}$  species were acting as scavengers for hydroxyl radicals, which were responsible for the over-oxidation of methanol to formic acid.<sup>23</sup> The proposed reaction scheme operating with iron and copper added to the ZSM-5 framework is shown in Figure 8. We demonstrated that these bimetallic catalysts could be used in a continuous flow reactor without deactivation but with 93% methanol selectivity at 0.5% conversion.<sup>33</sup> The mechanism using this catalyst does not involve the formation of surface bound methoxyl species which has proved problematic to desorb as methanol in other approaches.

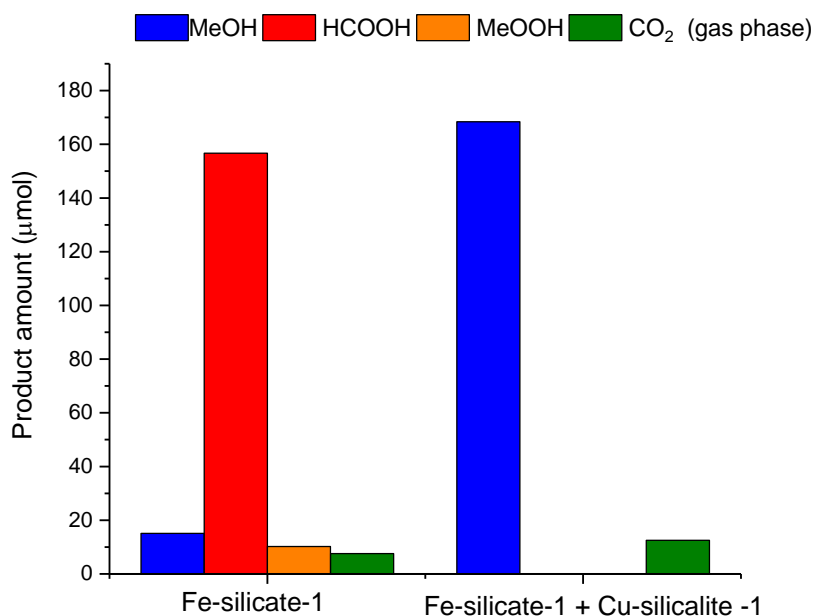

**Figure 7.** Addition of Cu-silicalite-1 to Fe-silicalite-1 switches the reaction selectivity from formic acid to methanol. Reaction conditions:  $\text{P}(\text{CH}_4)$  3 bar;  $[\text{H}_2\text{O}_2]$  1.0M; 70°C, 30 min; 1500 rpm.

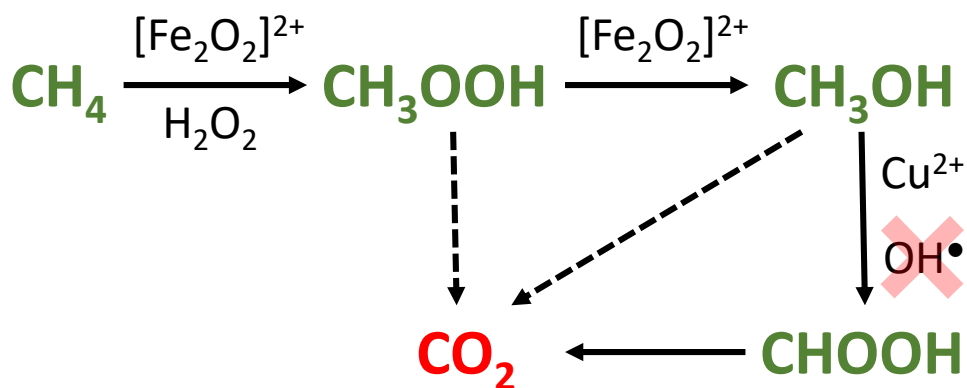

**Figure 8.** Proposed reaction scheme for copper-iron-ZSM-5 catalyst.

## 5. A RETURN TO AuPd CATALYSTS


In the earlier part of this account, we demonstrated that we could achieve closed catalytic cycles for low temperature selective oxidation of methane using either supported Au-Pd catalysts, Cu/Fe/ZSM-5 or Cu-silicalite-1 + Fe-silicalite-1 catalysts. These oxidations were carried out using  $\text{H}_2\text{O}_2$  as oxidant. Unfortunately, the use of  $\text{H}_2\text{O}_2$  is economically unfavourable, as its cost can be greater than methanol. Hence, the goal is to selectively oxidise methane to methanol using molecular oxygen. As noted earlier we could successfully oxidise the methyl group of toluene using Au-Pd/ $\text{TiO}_2$  and AuPd/C catalysts using molecular oxygen in a solvent-free reaction.<sup>31</sup> A direct analogy can be drawn between the selective oxidation of the primary C-H bond in toluene and the primary C-H bond in methane, and our study demonstrated the fundamental fact that selective oxidation of a primary C-H bond could be achieved under relatively mild conditions using molecular oxygen. However before switching all of our attention to using molecular oxygen, we needed to understand why the efficiency of  $\text{H}_2\text{O}_2$  usage was often very poor, especially when using  $\text{TiO}_2$  supported Au-Pd catalysts, as they have been so effective in direct  $\text{H}_2\text{O}_2$  synthesis.

Against this background, we investigated  $\text{H}_2\text{O}_2$  decomposition and methane selective oxidation using  $\text{H}_2\text{O}_2$  over a range of sol immobilised gold-palladium nanoparticle catalysts on a range of different supports. To differentiate the relative contributions to  $\text{H}_2\text{O}_2$  decomposition by the support and the colloidal nanoparticles, decomposition over the support only and unsupported colloidal nanoparticles were studied in addition to the regular sol-immobilised catalysts. Interestingly,  $\text{H}_2\text{O}_2$  decomposition was very low over the unsupported AuPd colloid


as well as a range of, and it was only when the colloid was immobilised on the support surface that the peroxide decomposition rate was enhanced significantly (Figure 9). This led us to intensively investigate the polyvinylpyrrolidone (PVP) stabilised Au-Pd colloidal suspension for methane oxidation by  $\text{H}_2\text{O}_2$ , and it was found to be extremely active and selective towards methanol and oxygenates at  $50^\circ\text{C}$ .<sup>34</sup> The choice of using PVP was crucial as the PVP does not decompose during the oxidation reaction to produce methyl-hydroperoxide, methanol or formic acid. In contrast, use of polyvinyl alcohol as the colloid stabiliser does give rise to methanol in a blank reaction. Comparing the colloidal suspension with the same colloidal nanoparticles supported on  $\text{TiO}_2$ , the unsupported colloidal catalyst was an order of magnitude more active and produced methyl-hydroperoxide and methanol with over 90% selectivity. The unsupported colloidal catalyst was also very stable, displaying no evidence of metal leaching or nanoparticle agglomeration, and the methane oxidation performance was consistently repeatable when fresh aliquots of  $\text{H}_2\text{O}_2$  were added (Figure 10). Although there was some sintering of the AuPd nanoparticles on use (Figure 11) the catalyst retained activity. The initial experiments were conducted with methane and  $\text{H}_2\text{O}_2$  alone but we realised the  $\text{H}_2\text{O}_2$  was also decomposing during reaction giving rise to some  $\text{O}_2$  and so we decided to add  $\text{O}_2$  to the reaction and we observed that the amount of oxygenated products increased (Figure 10). Use of  $^{18}\text{O}_2$  showed that the oxygen in the methanol product originated from molecular oxygen (Figure 10) and this represented the first example of low temperature selective oxidation of methane to methanol where molecular oxygen is incorporated. We showed that by decreasing the amount of  $\text{H}_2\text{O}_2$  added we could produce more mol oxygenates as products when compared to the mol of  $\text{H}_2\text{O}_2$  added. We referred to this as the gain factor (Figure 10) which with appropriate reaction conditions we could reach ca. 1.6.

We investigated the mechanism for this reaction with the Au-Pd nanoparticles using EPR spectroscopy and we identified using spin trapping experiments that  $\text{H}_2\text{O}_2$  forms hydroxyl radicals in solution by interaction with the nanoparticle. We concluded that the interaction of  $\text{H}_2\text{O}_2$  with the AuPd colloidal nanoparticle leads to a hydroxyl radical flux that reacts with  $\text{CH}_4$  in solution as this will be in excess. This will lead to the generation of methyl radicals which can react with  $\text{O}_2$  to form methyl-hydroperoxide as the primary product which then reacts further to form methanol with the oxygen in the C-OH bond originating from  $\text{O}_2$ . We observed that at least 70% of oxygen in the methanol product originated from molecular oxygen as some  $\text{O}_2$  is


produced from  $\text{H}_2\text{O}_2$  decomposition in a parallel pathway. Based on our experimental observations and identification of radical species in the reaction media we were able to propose a reaction scheme to rationalise our observations (Figure 12). In this reaction the  $\text{H}_2\text{O}_2$  acts as an initiator to produce very reactive hydroxyl radicals that activate methane. Once all of the  $\text{H}_2\text{O}_2$  is consumed the reaction ceases, but addition of further  $\text{H}_2\text{O}_2$  starts the reaction again (Figure 10). Although it was possible to dramatically increase the efficiency of  $\text{H}_2\text{O}_2$  use, it was still an essential ingredient, as removing it completely and carrying out the reaction with molecular oxygen alone resulted in no methane oxidation. Hence, we propose that the  $\text{H}_2\text{O}_2$  plays a crucial role in the formation of hydroxyl radicals for molecular methane activation and that the unsupported bimetallic colloidal nanoparticle is efficient at producing these radicals.

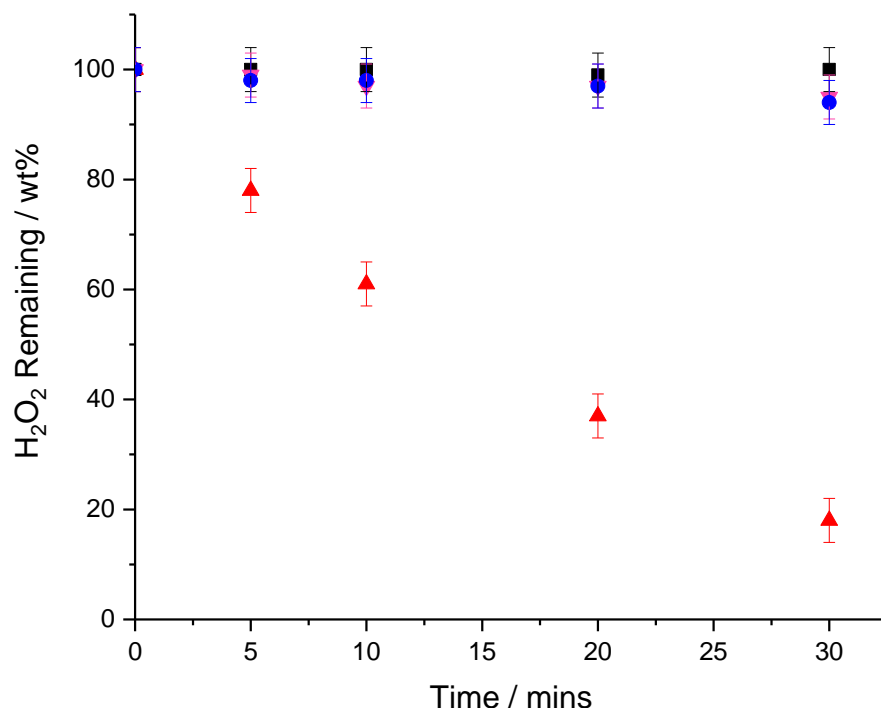


**Figure 9.** Decomposition of 4 wt%  $\text{H}_2\text{O}_2$  in  $\text{H}_2\text{O}$  (10 mL) with stirring at ambient temperature and pressure. Key: ■ water; ▼ AuPd colloid (0.66  $\mu\text{mol}$  metal); ●  $\text{TiO}_2$  (9mg); ▲ AuPd/ $\text{TiO}_2$  (0.66  $\mu\text{mol}$  metal, 9mg).

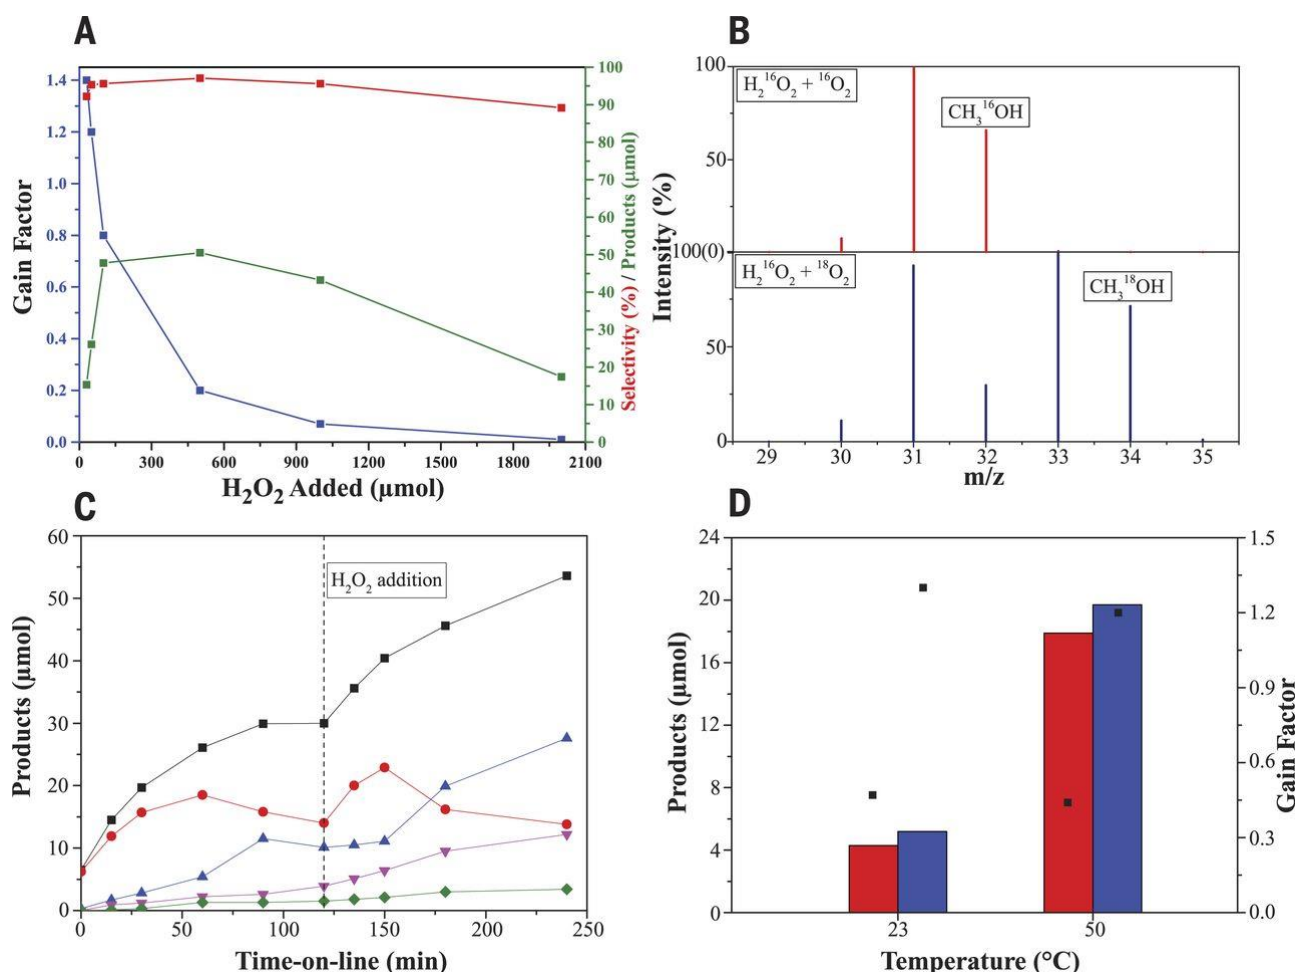

**Figure 10.** Methane oxidation using unsupported AuPd colloids. (A) Gain factor (blue line), selectivity (red line) and total amount of products (green line) as a function of the different amounts of H<sub>2</sub>O<sub>2</sub> used. (B) GC-MS spectra of CH<sub>3</sub>OH formed (m/z = 32 and 34 for CH<sub>3</sub><sup>16</sup>OH and CH<sub>3</sub><sup>18</sup>OH respectively) during methane oxidation via H<sub>2</sub><sup>16</sup>O<sub>2</sub> + <sup>16</sup>O<sub>2</sub> (*upper spectrum*) or H<sub>2</sub><sup>16</sup>O<sub>2</sub> + <sup>18</sup>O<sub>2</sub> (*lower spectrum*). (C) Time-on-line and AuPd colloid re-use study for the methane oxidation reaction employing 50 μmol H<sub>2</sub>O<sub>2</sub> and 5 bar O<sub>2</sub> showing no induction period. Total products (black line), and individual products (CH<sub>3</sub>OOH (red line), CH<sub>3</sub>OH (blue line), HCOOH (pink line) and CO<sub>2</sub> (green line)), subsequent second addition of H<sub>2</sub>O<sub>2</sub> is made at 20 min (D) Oxidation of CH<sub>4</sub> performed at 23° and 50°C with 50 μmol H<sub>2</sub>O<sub>2</sub>. The blue and red bars represent reactions performed with and without 5 bar O<sub>2</sub>, respectively. The black squares (■) indicate their respective gain factors. Reproduced with permission from ref 34. Copyright 2017 AAAS.

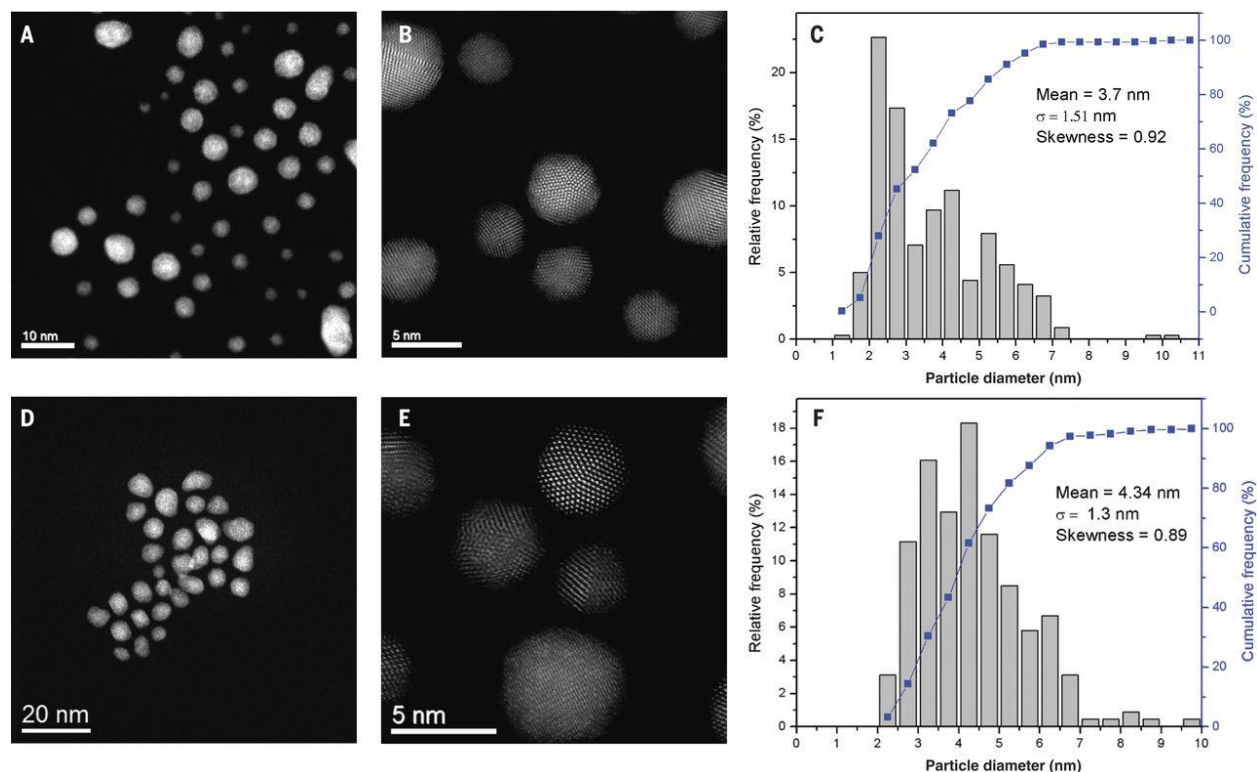

**Figure 11.** Representative HAADF images and particle size distributions for the unsupported AuPd-PVP sol in the fresh (A to C) and after a CH<sub>4</sub> oxidation reaction (D to F). Reproduced with permission from ref 34. Copyright 2017 AAAS.

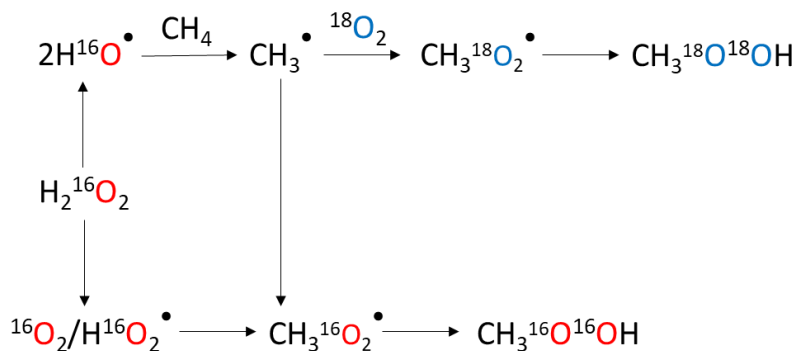

**Figure 12.** Proposed reaction scheme for methane oxidation using colloids in the presence of H<sub>2</sub>O<sub>2</sub> and O<sub>2</sub>.

## 6. CONCLUSIONS AND PERSPECTIVES

Using AuPd colloids and Cu promoted Fe-zeolites as catalysts we have shown that using  $\text{H}_2\text{O}_2$  as an oxidant in water as the preferred solvent it is possible to oxidise methane to methanol in a closed catalytic cycle. At the time of these studies this advance was a step change but as methanol formation required excess  $\text{H}_2\text{O}_2$  the advance was not of commercial interest. However, it is important that oxygen is used as the oxidant rather than  $\text{H}_2\text{O}_2$ . In our investigations we also showed that reacting methane with  $\text{H}_2$  and  $\text{O}_2$  to form  $\text{H}_2\text{O}_2$  in situ also was effective. In this case the  $\text{H}_2$  is being used as a co-reductant and this is very similar to a recent study by Stephanopoulos and co-workers<sup>35</sup> where methane was oxidized with  $\text{O}_2$  with CO as the co-reductant. A related study by Ma and co-workers also shows the importance of CO as a co-reductant for ethane oxidation. In the future we need to identify catalysts and reaction conditions where methane can be oxidized with  $\text{O}_2$  without the requirement for a co-reductant. Recent studies by Roman-Leshkov<sup>37,38</sup> have shown that Cu-mordenite can be used for a continuous flow gas phase oxidation of methane using  $\text{O}_2$  and water. The turn-over numbers are only just catalytic, but it shows that a continuous catalytic cycle can be achieved; however, this requires immense improvement. Very recently it has been found that water is the source of the oxygen in the methanol and  $\text{O}_2$  is required to close the catalytic cycle by oxidizing Cu.<sup>39</sup>

Considering using  $\text{H}_2\text{O}_2$  as an initiator for generating  $\cdot\text{CH}_3$  we consider that other routes to generate  $\cdot\text{CH}_3$  could be used. Rather than using  $\text{H}_2\text{O}_2$ , it would be highly desirable to devise a method of coupling the AuPd colloidal catalyst with a photochemical<sup>40</sup> or electrochemical fuel cell<sup>41</sup> to generate  $\cdot\text{OH}$  for H abstraction to facilitate  $\cdot\text{CH}_3$  radical formation. If a flux of  $\cdot\text{CH}_3$  radicals can be established at 150-200 °C and quenched with  $\text{O}_2$  this could provide the basis for a viable new route to methanol. Hence, the overarching remaining research is to identify catalysts that can activate methane with  $\text{O}_2$  in a continuous flow reactor enabling this flux of  $\cdot\text{CH}_3$  radicals to be continuously produced enabling a concentrated product stream of methanol to be produced; the approach we describe presents a starting point for this quest.



## AUTHOR INFORMATION

### Corresponding Author

**Graham J. Hutchings** – Max Planck Centre on the Fundamentals of Heterogeneous Catalysis, FUNCAT, Cardiff Catalysis Institute and School of Chemistry, Main Building, Park Place, Cardiff, CF10 3AT, UK; [orcid.org/0000-0001-8885-1560](https://orcid.org/0000-0001-8885-1560); Email: [hutch@cf.ac.uk](mailto:hutch@cf.ac.uk)

### Authors

**Simon J. Freakley** - Department of Chemistry, University of Bath, Claverton Down, Bath, BA2 7AY, UK; [orcid.org/0000-0002-6395-6646](https://orcid.org/0000-0002-6395-6646)

**Nikolaos Dimitratos** - Dipartimento di Chimica Industriale “Toso Montanari”, Università degli Studi di Bologna, Viale Risorgimento 4, 40136, Bologna, Italy; [orcid.org/0000-0002-6620-4335](https://orcid.org/0000-0002-6620-4335)

**David J. Willock** - Max Planck Centre on the Fundamentals of Heterogeneous Catalysis, FUNCAT, Cardiff Catalysis Institute and School of Chemistry, Main Building, Park Place, Cardiff, CF10 3AT, UK; [orcid.org/0000-0002-8893-1090](https://orcid.org/0000-0002-8893-1090)

**Stuart H. Taylor** - Max Planck Centre on the Fundamentals of Heterogeneous Catalysis, FUNCAT, Cardiff Catalysis Institute and School of Chemistry, Main Building, Park Place, Cardiff, CF10 3AT, UK; [orcid.org/0000-0002-1933-4874](https://orcid.org/0000-0002-1933-4874)

**Christopher J. Kiely** - Department of Materials Science and Engineering, Lehigh University, 5 East Packer Avenue, Bethlehem, PA 18015, USA; [orcid.org/0000-0001-5412-0970](https://orcid.org/0000-0001-5412-0970)

### Biographies

**Simon Freakley** obtained his PhD from Cardiff University and since 2020 is a Lecturer at the University of Bath. His interests concern the synthesis and characterisation of heterogeneous catalysis.

**Nikolaos Dimitratos** obtained his PhD from Liverpool University, and is Associate Professor at the University of Bologna. He specialises in the development of nanoparticulate materials.

**David J. Willock** obtained his PhD from University of London and is a Reader in Computational Chemistry at Cardiff University and studies the mechanisms of catalysed reactions.

**Stuart Taylor** is a Professor at Cardiff University working on heterogeneous catalysis, with a focus on oxidation reactions.

**Christopher Kiely** is a Professor of Materials Science at Lehigh University, USA. He uses advanced analytical electron microscopy techniques to study catalyst materials.

**Graham Hutchings, FRS** is Regius Professor of Chemistry at Cardiff University with broad interests in heterogeneous catalysis.

## **Notes**

The authors declare no competing financial interest.

## **ACKNOWLEDGEMENTS**

We thank the Dow Chemical Company for funding through the Dow Methane Challenge that supported a major part of the work we discuss. We also thank Exxon Mobil for funding for funding part of the work discussed.

## REFERENCES

- (1) Hammond, C.; Forde, M. M.; Ab Rahim, M. H.; Thetford, A.; He. Q.; Jenkins, R. L.; Dimitratos, N.; Lopez-Sanchez, J. A.; Dummer, N. F.; Murphy, D. M.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Stangland, E. E.; Kang, J.; Hagen, H.; Kiely, C. J.; Hutchings, G. J. Direct catalytic conversion of methane to methanol in an aqueous medium by using copper-promoted Fe-ZSM-5. *Angew. Chemie. Int. Ed.* **2012**, 51, 5129–5133.
- (2) Hammond, C.; Dimitratos, N.; Jenkins, R. L.; Lopez-Sanchez, J. A.; Kondrat, S. A.; ab Rahim, M. H.; Forde, M. M.; Thetford, A.; Taylor, S.H.; Hagen, H.; Stangland, E. E.; Kang, J. H.; Moulijn, J. M.; Willock D. J.; Hutchings G. J. Elucidation and Evolution of the Active Component within Cu/Fe/ZSM-5 for Catalytic Methane Oxidation: From Synthesis to Catalysis. *ACS Catal.* **2013**, 3, 689-699.
- (3) Ab Rahim, M. H.; Forde, M. M.; Jenkins, R. L.; Hammond, C.; He. Q.; Dimitratos, N.; Lopez-Sanchez, J. A.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Murphy, D. M.; Kiely, C. J.; Hutchings, G. J. Oxidation of methane to methanol with hydrogen peroxide using supported gold-palladium alloy nanoparticles. *Angew. Chemie. Int. Ed.* **2013**, 12, 1318–1322.
- (4) Agarwal, N.; Freakley, S. J.; McVicker, R. U.; Althahban, S. M.; Dimitratos, N.; He. Q.; Morgan, D. J.; Jenkins, R. L.; Willock, D. J.; Taylor, S. H.; Kiely, C. J.; Hutchings, G. J. Aqueous Au-Pd colloids catalyze selective CH<sub>4</sub> oxidation to CH<sub>3</sub>OH with O<sub>2</sub> under mild conditions. *Science* **2017**, 358, 223–227.
- (5) Bridger, G. W.; Spencer, M. S. In *Catalyst Handbook*; 2<sup>nd</sup> ed.; Twigg, M. V.; Wolfe Publishing, London, **1989**.
- (6) Hammer G.; Lubcke, T.; Kettner, R.; Pillarella, M. R.; Recknagel, H.; Commichau, A.; Neumann, H. J.; Paczynska-Lahme, B. Natural Gas. In *Ullmann's Encyclopedia of Industrial Chemistry*; Wiley-VCH, Verlag GmbH & Co. KGaA: Weinheim, **2012**, 23, 739 –792.
- (7) Hammond, C.; Conrad, S.; Hermans, I. Oxidative Methane Upgrading. *ChemSusChem* **2012**, 5, 1668-1686.
- (8) Yvon-Durocher, G.; Allen, A. P.; Bastviken, D.; Conrad, R.; Gudas, C.; St-Pierre, A.; Thanh-Duc, N.; del Giorgio, P. A. Methane fluxes show consistent temperature dependence across microbial to ecosystem scales. *Nature* **2014**, 507, 488-491.

- (9) <https://www.iea.org/reports/flaring-emissions>.
- (10) Hutchings, G. J.; Scurrell, M. S.; Woodhouse, J. R. Partial oxidation of methane using oxide catalysts. *Chem. Soc. Rev.* **1989**, 18, 251-283.
- (11) Hargreaves, J. S. J.; Hutchings, G. J.; Joyner, R. W. Control of product selectivity in the partial oxidation of methane. *Nature* **1990**, 348, 428-429.
- (12) Periana, R. A.; Taube, D. J.; Gamble, S.; Taube, H.; Satoh, T.; Fujii, H. Platinum catalysts for the high-yield oxidation of methane to a methanol derivative. *Science* **1998**, 280, 560-564.
- (13) Palkovits, R.; Antonietti, M.; Kuhn, P.; Thomas, A.; Schüth, F. Solid Catalysts for the Selective Low - Temperature Oxidation of Methane to Methanol. *Angew. Chemie. Int. Ed.* **2009**, 48, 6909-6912.
- (14) Tomkins, P.; Ranocchiari, M.; van Bokhoven, J. A. Direct Conversion of Methane to Methanol under Mild Conditions over Cu-Zeolites and beyond. *Acc. Chem. Res.* **2017**, 50, 418-425.
- (15) Olivos-Suarez, A. I.; Szécsényi, Á.; Hensen, E. J. M.; Ruiz-Martinez, J.; Pidko, E. A.; Gascon, J. Strategies for the Direct Catalytic Valorization of Methane Using Heterogeneous Catalysis: Challenges and Opportunities. *ACS Catal.* **2016**, 6, 2965-2981.
- (16) Groothaert, M. H.; Smeets, P. J.; Sels, B. F.; Jacobs, P. A.; Schoonheydt, R. A. Selective oxidation of methane by the bis( $\mu$ -oxo)dicopper core stabilized on ZSM-5 and mordenite zeolites. *J. Am. Chem. Soc.* **2005**, 127, 1394-1395.
- (17) Patrick, T.; Mansouri, A.; Bozbag, S. E.; Krumeich, F.; Bum Park, M.; Alayon, E. M. C.; Ranocchiari, M.; van Bokhoven, J. A. Isothermal cyclic conversion of methane into methanol over copper- exchanged zeolite at low temperature. *Angew. Chem. Intl. Ed.* **2016**, 55, 5467-5471.
- (18) Grundner, S.; Markovits, M. A. C.; Li, G.; Tromp, M.; Pidko, E. A.; Hensen, E. J. M.; Jentys, A.; Sanchez-Sanchez, M.; Lercher, J. A. Single-site trinuclear copper oxygen clusters in mordenite for selective conversion of methane to methanol. *Nature Comm.* **2015**, 6, 7546-7555.

- (19) Sushkevich, V. L.; Palagin, D.; Ranocchiari, M.; van Bokhoven, J. A. Selective anaerobic oxidation of methane enables direct synthesis of methanol. *Science* **2017**, 356, 523-527.
- (20) Sorokin, A. B.; Kudrik, E. V.; Bouchu, D. Bio-inspired oxidation of methane in water catalyzed by N-bridged diiron phthalocyanine complex. *Chem. Commun.* **2008**, 2562-2564.
- (21) Sorokin, A. B.; Kudrik, E. V.; Alvarez, L. X.; Afansiev, P.; Millet, J. M. M.; Bouchu, D. Oxidation of methane and ethylene in water at ambient conditions. *Catal. Today* **2010**, 157, 149-154.
- (22) Forde, M. M.; Bezzu, C.; Grazia, R.; Armstrong, R. L.; Jenkins, Ab Rahim, M. H.; Carley, A. F.; Dimitratos, N.; Lopez-Sanchez, J. A.; Taylor, S. H.; McKeown, N. B.; Hutchings, G. J. Methane oxidation using silica-supported N-bridged di-iron phthalocyanine catalyst. *J. Catal.* **2012**, 290, 177–185.
- (23) <https://cen.acs.org/articles/86/i4/Dow-Awards-Methane-Challenge-Grants.html>.
- (24) Edwards, J. K.; Freakley, S. J.; Carley, A. F.; Kiely, C. J.; Hutchings, G. J. Strategies for designing supported gold-palladium bimetallic catalysts for the direct synthesis of hydrogen peroxide. *Acc. Chem. Res.* **2013**, 47, 845–854.
- (25) Pritchard, J.; Piccinini, M.; Tiruvalam, R.; He, Q.; Dimitratos, N.; Lopez-Sanchez, J. A.; Morgan, D. J.; Carley, A. F.; Edwards, J. K.; Kiely, C. J.; Hutchings, G. J. Effect of heat treatment on Au–Pd catalysts synthesized by sol immobilisation for the direct synthesis of hydrogen peroxide and benzyl alcohol oxidation. *Catal. Sci. Technol.* **2013**, 3, 308–317.
- (26) Ab Rahim, M. H.; Forde, M. M.; Jenkins, R. L.; Hammond, C.; He, Q.; Dimitratos, N.; Lopez-Sanchez, J. A.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Murphy, D. M.; Kiely, C. J.; Hutchings, G. J. Oxidation of methane to methanol with hydrogen peroxide using supported gold-palladium alloy nanoparticles. *Angew. Chemie. Int. Ed.* **2013**, 12, 1318–1322.
- (27) Edwards, J. K.; Solsona, B.; Landon, P.; Carley, A. F.; Herzing, A.; Kiely, C. J.; Hutchings, G. J. Direct synthesis of hydrogen peroxide from H<sub>2</sub> and O<sub>2</sub> using TiO<sub>2</sub>-supported Au-Pd catalysts. *J. Catal.* **2005**, 236, 69-79.

- (28) Edwards, J. K.; Solsona, B.; Ntainjua, E. N.; Carley, A. F.; Herzing, A. A.; Kiely, C. J.; Hutchings, G. J. Switching Off Hydrogen Peroxide Hydrogenation in the Direct Synthesis Process. *Science* **2009**, 323, 1037-1041.
- (29) Freakley, S.; Piccinini, M.; Edwards, J. K.; Ntainjua, E. N.; Moulijn, J. A.; Hutchings, G. J. Effect of Reaction Conditions on the Direct Synthesis of Hydrogen Peroxide with a AuPd/TiO<sub>2</sub> Catalyst in a Flow Reactor. *ACS Catal*, **2013**, 3, 487-501.
- (30) Williams, C.; Carter, J. H.; Dummer, N. F.; Chow, Y. K.; Morgan, D. J.; Yacob, S.; Serna, P.; Willock, D. J.; Meyer, R. J.; Taylor, S. H.; Hutchings, G. J. Selective oxidation of methane to methanol using supported AuPd catalysts prepared by stabilizer-free sol-immobilization. *ACS Catal*. **2018**, 8, 2567–2576.
- (31) Kesavan, L.; Tiruvalam, R.; Ab Rahim, M. H.; bin Saiman, M. I.; Enache, D. I.; Jenkins, R. L.; Dimitratos, N.; Lopez-Sanchez, J. A.; Taylor, S. H.; Knight, D. W.; Kiely, C. J.; Hutchings, G. J. Solvent-free oxidation of primary carbon-hydrogen bonds in toluene using Au-Pd alloy nanoparticles. *Science* **2011**, 331, 195–199.
- (32) Hammond, C.; Forde, M. M.; Ab Rahim, M. H.; Thetford, A.; He. Q.; Jenkins, R. L.; Dimitratos, N.; Lopez-Sanchez, J. A.; Dummer, N. F.; Murphy, D. M.; Carley, A. F.; Taylor, S. H.; Willock, D. J.; Stangland, E. E.; Kang, J.; Hagen, H.; Kiely, C. J.; Hutchings, G. J. Direct catalytic conversion of methane to methanol in an aqueous medium by using copper-promoted Fe-ZSM-5. *Angew. Chemie. Int. Ed*. **2012**, 51, 5129–5133.
- (33) Xu, J.; Armstrong, R. D.; Shaw, G.; Dummer, N. F.; Freakley, S. J.; Taylor, S. H.; Hutchings, G. J. Continuous selective oxidation of methane to methanol over Cu- and Fe-modified ZSM-5 catalysts in a flow reactor. *Catal. Today* **2016**, 270, 93-100.
- (34) Agarwal, N.; Freakley, S. J.; McVicker, R. U.; Althahban, S. M.; Dimitratos, N.; He. Q.; Morgan, D. J.; Jenkins, R. L.; Willock, D. J.; Taylor, S. H.; Kiely, C. J.; Hutchings, G. J. Aqueous Au-Pd colloids catalyze selective CH<sub>4</sub> oxidation to CH<sub>3</sub>OH with O<sub>2</sub> under mild conditions. *Science* **2017**, 358, 223–227.
- (35) Shan, J.; Li, M.; Allard, L. F.; Lee, S.; Flytzani-Stephanopoulos, M. Mild oxidation of methane to methanol or acetic acid on supported isolated rhodium catalysts. *Nature* **2017**, **551**, 605-608.

- (36) Jin, R.; Peng, M.; Li, A.; Deng, Y.; Jia, Z.; Huang, F.; Ling, J.; Yang, F.; Fu, H.; Xie, J.; Han, X.; Xiao, D.; Jiang, Z.; Liu, H.; Ma, D. Low Temperature Oxidation of Ethane to Oxygenates by Oxygen over Iridium-Cluster Catalysts. *J. Am. Chem. Soc.* **2019**, 141, 18921–18925.
- (37) Narsimhan, K.; Iyoki, K.; Dinh, K.; Román-Leshkov, Y. Catalytic oxidation of methane into methanol over copper-exchanged zeolites with oxygen at low temperature. *ACS Central Sci.* **2016**, 2, 424-429.
- (38) Dinh, K.T.; Sullivan, M. M.; Narsimhan, K.; Serna, P.; Meyer, R.J.; Dinca, M.; Roman-Leshkov, Y. Continuous partial oxidation of methane to methanol catalyzed by diffusion-paired copper dimers in copper-exchanged zeolites. *J. Amer. Chem. Soc.* **2019**, 141, 11641–11650.
- (39) Koishybay, A.; Shantz, D. F. Water is the oxygen source for methanol produced in partial oxidation of methane in a flow reactor over Cu-SSZ-13. *J. Amer. Chem. Soc.* **2020**, 142, 11962–11966.
- (40) Noceti, R. P.; Taylor, C. E.; D'Este, J. R. Photocatalytic conversion of methane. *Catal. Today* **1997**, 33, 199–204.
- (41) Tomita, A.; Nakajima, J.; Hibino, T. Direct oxidation of methane to methanol at low temperature and pressure in an electrochemical fuel cell. *Angew. Chem. Int. Ed.* **2008**, 47, 1462–1464.