



ALMA MATER STUDIORUM  
UNIVERSITÀ DI BOLOGNA

ARCHIVIO ISTITUZIONALE  
DELLA RICERCA

## Alma Mater Studiorum Università di Bologna Archivio istituzionale della ricerca

Effect of manufacturing process on the microstructural and rheological properties of milk chocolate

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

*Published Version:*

V. Glicerina, F. Balestra, M. Dalla Rosa, S. Romani (2015). Effect of manufacturing process on the microstructural and rheological properties of milk chocolate. JOURNAL OF FOOD ENGINEERING, 145(January 2015), 45-50 [10.1016/j.jfoodeng.2014.06.039].

*Availability:*

This version is available at: <https://hdl.handle.net/11585/372550> since: 2018-02-07

*Published:*

DOI: <http://doi.org/10.1016/j.jfoodeng.2014.06.039>

*Terms of use:*

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).  
When citing, please refer to the published version.

(Article begins on next page)

## Accepted Manuscript

Effect of manufacturing process on the microstructural and rheological properties of milk chocolate

Virginia Glicerina, Federica Balestra, Marco Dalla Rosa, Santina Romani

PII: S0260-8774(14)00288-X  
DOI: <http://dx.doi.org/10.1016/j.jfoodeng.2014.06.039>  
Reference: JFOE 7855

To appear in: *Journal of Food Engineering*

Received Date: 7 May 2014  
Revised Date: 26 June 2014  
Accepted Date: 28 June 2014

Please cite this article as: Glicerina, V., Balestra, F., Rosa, M.D., Romani, S., Effect of manufacturing process on the microstructural and rheological properties of milk chocolate, *Journal of Food Engineering* (2014), doi: <http://dx.doi.org/10.1016/j.jfoodeng.2014.06.039>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2014 Elsevier. This manuscript version is made available under the Creative Commons Attribution-NonCommercial-NoDerivs (CC BY-NC-ND) 4.0 International License (<https://creativecommons.org/licenses/by-nc-nd/4.0>)

1       **EFFECT OF MANUFACTURING PROCESS ON THE MICROSTRUCTURAL AND**  
2       **RHEOLOGICAL PROPERTIES OF MILK CHOCOLATE**

3  
4  
5       Virginia Glicerina<sup>a\*</sup>, Federica Balestra<sup>a</sup>, Marco Dalla Rosa<sup>a</sup>, Santina Romani<sup>ab</sup>

6       <sup>a</sup>*Interdepartmental Centre for Agri-Food Industrial Research, Alma Mater Studiorum, University of*

7       *Bologna, Piazza Goidanich 60, Cesena (FC)*

8       <sup>b</sup>*Alma Mater Studiorum, University of Bologna, Department of Agro - Food Science, Campus of*

9       *Food Science, Piazza Goidanich, 60, 47521 Cesena, Italy*

10       \*Corresponding author: TEL: +390547/338120; FAX: +390547/382348;

11       [virginia.glicerina2@unibo.it](mailto:virginia.glicerina2@unibo.it)

12

13 **Abstract**

14

15 The effect of different process steps on microstructural, rheological and visual properties of milk  
16 chocolate was studied. Each process step affects the microstructural characteristics of milk  
17 chocolate, involving modifications on its macroscopic properties, such as rheological attributes.  
18 Milk chocolate samples were obtained at each phase of the manufacture process: mixing, pre-  
19 refining, refining, conching and tempering. Microstructural properties (network structure and  
20 particle size) and rheological parameters (yield stress, apparent viscosity, thixotropy,  $G'$  and  $G''$ )  
21 were evaluated by using respectively an environmental scanning electron microscope (ESEM), and  
22 a controlled strain–stress rheometer. Colorimetric analyses ( $L^*$ ,  $h^\circ$  and  $C^*$ ) were also performed.  
23 ESEM analysis revealed important changes in the network structure during process, with a  
24 reduction in particle size and an increase in the voids between aggregates, from the mixing to the  
25 refining step. Moreover, an increase of all rheological analyzed parameters from mixed sample to  
26 the refined one was found. Samples obtained from the conching and tempering steps were  
27 characterized by the lowest statistically significantly values of all rheological parameters. This  
28 could be related to the changes in the structure aggregation evidenced by ESEM analysis. From  
29 colour results, the samples with the finest particles appeared lighter and more saturated than those  
30 with coarse particles.

31

32 *Keywords:* Milk Chocolate; Manufacture steps; Microstructure; Rheology; Appearance.

33

34

35

36

37

38

39

40 **1. Introduction**

41 Milk chocolate is a complex rheological system having solid particles (cocoa, milk powder and  
42 sugar) dispersed in cocoa butter, which represent the fat phase (Pajin et al., 2013). Milk powder is  
43 one of the main ingredient of milk chocolate (being used at about 20% w/w in the formulation); this  
44 ingredient affects the sensory characteristics of the final product, the processing behaviour and the  
45 rheological properties of the fluid chocolate mass (Franke and Heilzmann, 2008; Taylor et al.,  
46 2009). The determination of the rheological properties of chocolate is important during  
47 manufacturing processes in order to obtain high quality products with well-defined characteristics  
48 (Servais et al., 2002; Gonçalves and Lannes, 2010). The rheological characteristics of milk  
49 chocolate (pseudoplastic flow with yield stress, apparent viscosity, thixotropy and viscoelasticity)  
50 are in fact influenced by formulation (amount of fat, amount and type of emulsifiers) as well as by  
51 processing steps (mixing, pre-refining, refining, conching and tempering) (Tscheuschner and  
52 Wunsche, 1979; Vavreck, 2004; Schantz and Rohm, 2005). The processing of milk chocolate  
53 involves, during each single step (mixing, pre-refining, refining, conching and tempering),  
54 modifications in its final quality and attributes, influencing in a strong way the microstructure of the  
55 product (aggregation, de-aggregation, reduction of particle size, immobilization of cocoa butter,  
56 etc.) (Afoakwa et al., 2009a; Aguilera et al., 2000). In particular, milk powder with its own physical  
57 characteristics and inner porosity may have a significant impact on the chocolate processing  
58 conditions and on the physical and organoleptic properties of the final product (Liang and Hartel,  
59 2004).

60 To our knowledge no papers are available in literature regarding the influence of the single process  
61 step on microstructural, rheological and appearance properties of milk chocolate.

62 In our opinion, in order to improve the final quality of milk chocolate it would be interesting to  
63 study in depth the evolution of these important quality characteristics during the different process  
64 phases (mixing, pre- refining, refining, conching and tempering). For this purpose in the present

65 work the influence of each process phase on microstructural, rheological and colorimetric properties  
66 of milk chocolate were evaluated during the overall manufacturing process.

## 67 **2. Materials and methods**

### 68 2.1. Materials

69 Milk chocolate samples were produced in an Italian confectionery factory by using an industrial  
70 plant (Buhler, Malmo, Sweden) provided of mixer, pre-refiner, refiner, conching and tempering  
71 machine, and equipped to produce 6000 kg of chocolate at every production cycle. Milk chocolate  
72 production was made up by different steps as shown in Fig. 1. The ingredients used in the chocolate  
73 formulation were: sugar (47%), cocoa butter (25%), whole milk powder (21%) and cocoa liquor  
74 (18%). The experimental samples were taken after each production phase: mixing (A), pre-refining  
75 (B), refining (C), conching (D) and tempering (E). In particular, the refining step was realized by  
76 using a five-roll refiner, that consists of a vertical array of four hollow cylinders temperature  
77 controlled by internal water flow, held together by hydraulic pressure. The temperatures of the five  
78 cylinders used to press particles were: 1<sup>st</sup> and 2<sup>nd</sup> cylinder 28°C; 3<sup>th</sup> 44°C, 4<sup>th</sup> 49°C and 5<sup>th</sup> 30°C.  
79 Samples were stored in plastic bucket (1 kg capacity) at room temperature until the analytical  
80 determinations. Before performing the analysis the samples were melted in a microwave (Stortz and  
81 Marangoni, 2013) at 150 watt for 25 minutes. The melting parameters were chosen after  
82 preliminary experiments in order to avoid changes in the chocolate properties.

83

### 84 2.2. Methods

#### 85 2.2.1. Microstructure analysis

86 Samples microstructure was observed using an environmental scanning electron microscope ESEM  
87 (Evo 50 EP, Zeiss, Germany) equipped with a microprobe (EDS Mod. 350, Oxford Instrument,  
88 UK). The detector used was a backscatter electron detector (QBSE) that provided good  
89 compositional contrast imaging at 20 kV and in low vacuum mode with 100 Pascal at 500x  
90 magnification. These parameters were chosen after preliminary trials and according to Dahlenborg

91 et al. (2010), in order to cause minimal damage on the chocolate surface and in order to optimize  
92 the images quality. By using this kind of instrument ESEM, samples are not coated and the images  
93 are more dependent on sample rather than coating characteristics, in this way the true structure can  
94 be analyzed (Rousseau, 2007). Ten micrographs for each chocolate sample were taken. The  
95 acquired images were subsequently elaborated using the software Image Pro-plus 6.0 (Media  
96 Cybernetics Inc Bethesda, USA).

97

### 98 2.2.2. Fundamental properties

99 Measurements were carried out at 40°C using a controlled strain-stress rheometer (MCR 300,  
100 Physica/ Anton Paar, Ostfildern, Germany) equipped respectively with a bob and cup geometry and  
101 with a plate-plate system to perform analysis in steady state conditions and the dynamic tests  
102 respectively. In steady state conditions, after a pre-shearing of 500 s at 2 s<sup>-1</sup>, apparent viscosity was  
103 measured as function of increasing shear rate from 2 to 50 s<sup>-1</sup> (ramp up) within 180 s, then  
104 decreasing from 50 to 2 (ramp down), within each ramp 18 measurements were taken (ICA, 2000).  
105 Chocolate rheological flow curves are usually fitted (Afoakwa et.al., 2008, 2009b; Taylor et al.,  
106 2009) by using the Casson model, that is a well-known rheological model to describe the non-  
107 Newtonian flow behaviour of fluids with a yield stress (Joye, 2003). In particular, some fluid  
108 products, like chocolate, are well described by this model because of their non linear yield-stress-  
109 pseudoplastic nature. According to Chevalley (1991) curve points represent a case for a better fit to  
110 chocolate data, if the exponent is taken as 0.6 rather than 0.5.

111 For this reason, in this study the obtained flow curves were evaluated and fitted according to the  
112 rheological model of Casson, modified by Chevalley (1991), in order to obtain a better fit of the  
113 chocolate samples. The model used is represented in the following equation (1):

$$114 \tau^{0.6} = \tau_0^{0.6} + n_{PL} y^{0.6} \quad (1)$$

115 where  $\tau_0$  is the yield stress and  $\eta_{PL}$  is the so-called “plastic viscosity”. In order to measure the  
116 goodness of fit, the determination coefficient ( $R^2$ ) was determined. The yield stress and the apparent

117 viscosity were obtained according to ICA (2000), Servais et al., (2004) and Afoakwa et al., (2008),  
118 evaluating the shear stress respectively at 5 and 40 s<sup>-1</sup>. In particular, the apparent viscosity evaluated  
119 at the shear stress of 40 s<sup>-1</sup> according to Do et al., (2007), reflects the microstructure of the sample  
120 taking into account the presence of aggregates.

121 The samples thixotropy was evaluated according to Servais et al., (2004), from the difference  
122 between apparent viscosity measured at 40 s<sup>-1</sup> during ramp up and ramp down. The thixotropy  
123 values represent in very close way the value of the hysteresis area between the apparent viscosity  
124 curves during the ramp up and the ramp down. The loop area designates the energy required to  
125 break down the structure not recovered during the experimentation period (Roopa and  
126 Bhattacharya, 2009) and represents the rate of the internal breakdown of matrix (Dolz et al., 2000).

127 In dynamic conditions, oscillatory tests by using a plate-plate geometry were performed in order to  
128 investigate the viscoelastic properties of samples and to evaluate the storage (G') and the loss (G'')  
129 modulus. In order to identify the linear viscoelastic range (LVR), in which the viscoelastic  
130 properties are independent from the stress conditions, strain sweep tests were applied. Frequency  
131 sweep tests were carried out in the viscoelastic linear region at the constant deformation amplitudes  
132 of 0.12%, previously evaluated with the strain sweep test, in the range from 1 to 100 Hz.

133

### 134 2.2.3. Colorimetric measurements

135 Colour of chocolate samples was measured using a colour spectrophotometer mod. Colorflex  
136 (Hunterlab, USA), equipped with a sample holder (diameter 64 mm). Colour was measured in the  
137 CIE L\*a\*b\* scale using the D65 illuminant. The instrument was calibrated with a white tile (L\* =  
138 98.03, a\* = - 0.23, b\* = 2.05) and the calibration was also validated with a green standard tile (L\* =  
139 53.14, a\* = - 26.23, b\* = 12.01) before the measurements.

140 Numerical values of a\* and b\* were converted into hue angle (h°) and Chroma (C\*) that represent  
141 the hue and the saturation index:  $C^* = [(a^*)^2 + (b^*)^2]^{1/2}$ ,  $h^\circ = [\arctang(b^*/a^*)/2 \pi]^* 360$  (Mc Guire,  
142 1992).



143

144

### 145 **2.3. Statistical analyses**

146 All the analysis were carried out in triplicate for each chocolate sample.

147 Analyses of variance (ANOVA) and the test of mean comparison according to Fisher Least  
148 Significant Difference (LSD) were conducted on all obtained data. Level of significance was  $P \leq$   
149 0.05.

150 The statistical software used was STATISTICA, version 8.0. (StatSoft, Tulsa, Oklahom).

151

## 152 **3. Results and discussion**

### 153 3.1. Microstructural properties of milk chocolate

154 In Fig. 2 (a, b, c, d, e) micrographs of milk chocolate samples obtained by ESEM analysis are  
155 shown.

156 ESEM was employed in order to evaluate the main microstructural modifications occurred on  
157 chocolate samples during the different process steps, concerning sugar crystalline networks,  
158 particle-particle interactions, presence of voids and particle-fat behaviour (Afoakwa, et al., 2009).

159 In table 1 are reported the size diameters of the largest particles measured on chocolate samples,  
160 being those that underwent the main modifications during process. Microstructure examination,  
161 highlighted different structures between samples obtained from the manufacturing steps.

162 ESEM micrographs showed a decrease in the particle size from sample obtained after mixing (A) to  
163 the one taken after refining (C) (Table 1), parallel to an increase in the presence of large voids  
164 between aggregates (Fig. 2 a, b, c). The reduction of the particles diameter causes an increase in the  
165 particles number, parallel to an increase in the contact points between them, due to chemical and  
166 mechanical interactions (Afoakwa et al., 2009; Servais et al., 2004). The increase of particle  
167 interactions from sample obtained after mixing (A) to the one taken after refining (C), due to the  
168 raise of their specific surface area, involves a reduction of the particles mobility, due to their high

169 aggregation (Bayod, 2008a; Bayod et al. 2008b). On the other side, the presence of large voids  
170 between aggregates (filled with cocoa butter) involves an immobilization of a part of cocoa butter  
171 that can not contribute to the continuous fluid phase flow. According with the studies of Windhab  
172 (2000), the effective immobilized fluid fraction ( $\phi_{eff}$ ) in the particle aggregates can be considered as  
173 an increase of solid volume, as explained in the following equation:

$$174 \quad \phi_{eff} = \phi_s + \phi_{sif} + \phi_{vif} + \phi_{hifi} \quad (2)$$

175 Where  $\phi_s$  = is the volume occupied by solid particles,  $\phi_{sif}$  = is the volume of the fluid immobilized  
176 by surface,  $\phi_{vif}$  = is the volume of fluid immobilized in particle cavities and into inner voids in  
177 particle aggregates and  $\phi_{hifi}$  = is the part of fluid immobilized when particles or aggregates move  
178 within the continuous phase such as in rotation.

179 For this reason in order to know the effective solid content in a dispersion, all the parameters  
180 presents in the equation (2) must be taken into account. In particular, the cocoa butter immobilized  
181 in large voids can have a significant impact on the rheological behaviour of the milk chocolate  
182 system (Windhab, 2000).

183 The micrographs of Fig. 2 (d, e), related to the samples after conching and tempering steps, show a  
184 further reduction in the particle size coupled to a reduction of the larger voids between aggregates,  
185 that leads to a reduction of the fluid immobilization. In the conching step a destruction of the  
186 previous obtained agglomerates and a re-distribution of cocoa butter between particles was noted,  
187 according to Attaie et al., (2003). Cocoa butter in fact, due to its free-moving lubricating plastic  
188 flow, coats particles and reduces forces and aggregation between solid particles (Beckett, 2000),  
189 thus improving their mobility (Aguilera et al., 2004).

190

### 191 3.2. Fundamental rheological properties

192 In Fig. 3 the flow curves of the milk chocolate samples, obtained increasing the shear rate from 2 to  
193  $50 \text{ s}^{-1}$ , are reported.

194 The apparent viscosity ( $\eta$ ) against shear rate ( $\dot{\gamma}$ ) was used to represent the rheological behaviour of  
195 milk chocolate; it is evident that the apparent viscosity decreases increasing the shear rate, which  
196 proves the pseudoplastic or shear thinning nature of chocolate.

197 According to Juszczak, et al., (2004) this behaviour can be attributed to the breakdown of the inner  
198 structure dispersions, in fact the increase of shear rate causes the drop in the apparent viscosity of  
199 the molecules orientating along the flow lines.

200 As illustrated in Fig. 3, sample C achieved after the refining step, had the highest apparent viscosity  
201 with initial values ranging around 60 Pa s, followed by sample B, taken after the pre-refining step  
202 with initial apparent viscosity values between 20 and 30 Pa s and sample A obtained from the first  
203 step, with values between 10 and 20 Pa s. D and E samples, obtained from the last two steps of the  
204 manufacture process, had the lowest apparent viscosity values, ranging from 0 to 10 Pa s.

205 In order to better explain the rheological values obtained by the flow curves, the *Casson yield value*  
206 and the *Casson plastic viscosity* parameters were calculated applying the Casson model modified by  
207 Chevalley (1991), moreover yield stress and apparent viscosity values were obtained according to  
208 Afoakwa et al., (2008) and ICA (2000). All these data are reported in Table 2 for each chocolate  
209 sample.

210 All data were well fitted by the *Casson* model, providing high determination coefficients ( $R^2$ ) that  
211 varied from 0.75 to 0.99. A significantly increase in both *Casson* obtained parameters was  
212 highlighted from sample (A) obtained after mixing to the one taken after refining (C). This could be  
213 attributed to the increase of the contact point between particles, that need of a major amount of  
214 stress to initiate the flow, and to the presence of large void spaces that immobilized cocoa butter  
215 between aggregates. In this state the fat can not contribute to the flow as lubricant (Franke and  
216 Heinzelmann, 2008). Samples after conching (D) and tempering (E) were characterized by the  
217 lowest and significantly similar values of both *Casson* parameters. In particular, the obtained values  
218 of plastic apparent viscosity are in agreement with the results of Wichchukit et al., (2004), that  
219 showed that *Casson viscosity* of milk chocolate with 20% of cocoa butter, ranged from 7 to 48 Pa s

220 and led to decrease with the adding of lubricant. In the samples studied in this research work the  
221 highest value of *Casson* apparent viscosity was lower (25.7 Pa s), than the one obtained in the study  
222 of Wichchukit et al., (2004), probably due to a higher amount of cocoa butter used in formulation  
223 (25%), that caused a greater lubricating effect and a reduction of particle–particle interactions  
224 (Vernier, 1998).

225 The yield stress and apparent viscosity parameters, exhibited the same trends of the *Casson yield*  
226 *value* and of the *Casson Plastic Viscosity* in milk chocolate samples. According to the studies of Do  
227 et al., (2007) in fact an increase in the apparent viscosity, as from sample after mixing (A) to the  
228 one after refining (C), also in this case indicates an higher degree of particles aggregation, while a  
229 decrease of this parameter, as for samples after conching (D) and after tempering (E), underlines a  
230 lower degree of interactions, as confirmed by microstructural analysis results.

231 Thixotropy results are shown in Fig. 4. It is possible to notice how C and B samples obtained  
232 respectively after the refining and pre-refining steps, that had the most aggregate structure,  
233 presented also the significantly highest thixotropy values, related to a more damaged structure. This  
234 result according to Afoakwa et al., (2008) could be attributed to the high aggregation of the  
235 particulate system and to an elevate number of interactions between particles. Sample A taken  
236 after the mixing was characterized by an intermediate thixotropic value, between B-C and D-E  
237 ones, strictly related with the results obtained from microstructural examination, that reflects the  
238 presence of coarse particles and a weak solid structure compared to B and C samples obtained from  
239 the pre-refining and refining phase. The lowest significantly values of thixotropy were showed by  
240 chocolate samples D, after conching and E, after tempering. According with literature (Afoakwa et  
241 al., 2008) in fact, a well conched and tempered chocolate should not be thixotropic and hence  
242 should not have a very aggregate structure. Anyway, it is very unusual to have not any thixotropy.

243 The results of frequency sweep test in terms of storage and loss modulus, evaluated respectively at a  
244 frequency of 1 Hz, are reported in Table 3. The response of all samples to the imposed deformation

245 is the stored potential energy, characterized by the predominance of the elastic modulus ( $G'$ ) over  
246 the viscous one ( $G''$ ) (Ahmed and Ramaswamy, 2006; Bayod & Tornberg, 2011).

247 B and C samples, obtained from pre-refining and refining steps, were characterized by a relative more  
248 elastic structure compared to that of the other samples (A, D and E, taken after mixing, conching  
249 and tempering). As reported in previous studies (Johansson and Bergensthåll, 1992; Glicerina et al.,  
250 2013) high values of  $G'$  are related to a high level of interactive forces between particles; this  
251 confirms the high amount of stress necessary to pre-refining (B) and refining (C) samples to start  
252 flow.

253 The significantly lowest values of  $G'$  and  $G''$  were found for the samples after conching (D) and  
254 after tempering (E), constituted by a weakly structure.

### 255 3.3. Colorimetric measurements

256 The lightness ( $L^*$ ) and hue angle ( $h^\circ$ ) values of A – E milk chocolate samples are shown in Fig. 5.

257 A similar trend of lightness and hue angle values was observed in all samples. A and B samples,  
258 taken from the first two steps and characterised by coarser particles, had the lowest significantly  
259 values of both colour parameters. As known (Voltz and Beckett, 1997; Afoakwa et al., 2008), the  
260 human eye detects colour according to how the light is reflected from the surface, thus the size of  
261 the both non-fat solid and crystalline fat particles affects the colour of chocolate. In particular, in a  
262 dense packed medium, light scattering factors are inversely related with particle diameters (Saguy  
263 & Graf, 1991; Afoakwa et al., 2008), for this C, D and E samples, (obtained respectively from the  
264 refining, conching and tempering steps) having finer particles and a large specific surface area,  
265 tended to scatter more light, appearing lighter than A and B samples, that had larger particles. At the  
266 same time the highest hue angle values were found in C, D and E samples, that had a more  
267 yellonish-brown hue than A and B ones.

268

## 269 4. Conclusions

270 The modifications in the microstructure of milk chocolate during the different processing steps  
271 involve deep changes in the rheological and colorimetric parameters of product.

272 In particular, the decrease in particle size detected from sample A taken from the mixing step to C  
273 obtained from the refining one, simultaneously to an increase in the void spaces that immobilize  
274 cocoa butter, involves an increase in all rheological analyzed parameters. The re-distribution of  
275 cocoa butter during the conching step, led to a decrease in all rheological values in D and E samples  
276 obtained after the conching and tempering steps, probably because of the reduction in particle-  
277 particle interactions due to the cocoa butter that, wrapping particles, reduces forces between them.  
278 At the same time, colorimetric characteristics were also affected by the different microstructure of  
279 samples.

280 From results obtained in this work it can be concluded that the knowledge of the influence of  
281 process parameters on the milk chocolate microstructure becomes very important in order to  
282 modify, improve and/or optimize the rheological and colorimetric properties of final product.

283

## 284 **References**

285 Afoakwa, E., Paterson, A., & Fowler, M. (2008). Effects of particle size distribution and  
286 composition on rheological properties of dark chocolate. *European Food Research and Technology*,  
287 226, 1259-1268.

288 Afoakwa, E., Paterson, A., Fowler, M., & Vieira, J. (2009a). Microstructure and mechanical  
289 properties related to particle size distribution and composition in dark chocolate. *International*  
290 *Journal of Food Science and Technology*, 44, 111–119.

291 Afoakwa, E. O., Paterson, A., Fowler, M., & Vieira, J. (2009b). Comparison of rheological models  
292 for determining dark chocolate viscosity. *International Journal of Food Science and Technology*,  
293 44(1), 162–167.

- 294 Aguilera, J.M., & Stanley, D.W. (1999). Examining Food Microstructure. In Springer (Eds.),  
295 *Microstructural Principles of Food Processing and Engineering* 2<sup>nd</sup> Ed. (pp.1-43), Aspen  
296 Publishers Inc, Gaithersburg, MD.
- 297 Aguilera J.M., Stanley D.W., & Baker K. (2000). New Dimensions in Microstructure of Food  
298 Products. *Trends in Food Science Technology*, 11, 3-9.
- 299 Aguilera J.M., Michel, M. & Mayor, G. (2004). Fat Migration in Chocolate: Diffusion or Capillary  
300 Flow in a Particulate Solid? —A Hypothesis Paper. *Journal of Food Science*, 69, 167-174.
- 301 Ahmed, J., & Ramaswamy, H. S. (2006). Viscoelastic properties of sweet potato puree infant food.  
302 *Journal of Food Engineering*, 74, 376-382.
- 303 Attaie, H., Breitschuh, B., Braun, P., & Windhab E. J. (2003). The functionality of milk powder and  
304 its relationship to chocolate mass processing, in particular the effect of milk powder manufacturing  
305 and composition on the physical properties of chocolate masses. *International Journal of Food  
306 Science and Technology*, 38, 325–335.
- 307 Babin, H. (2005). *Colloidal properties of sugar particle dispersions in food oils with relevance to  
308 chocolate processing*. Doctoral Thesis - Procter Department of Food Science, University of Leeds-  
309 UK.
- 310 Bayod, E. (2008a). *Microstructural and Rheological Properties of Concentrated Tomato  
311 Suspensions during Processing*. Doctoral Thesis – Division of Food Engineering, Department of  
312 Food Technology, Engineering and Nutrition, Lund University – Sweden.
- 313 Bayod, E. Willers, E.P. & Tornberg E. (2008b). Rheological and structural characterization of  
314 tomato paste and its influence on the quality of ketchup. *LWT*, 41, 1289-1300.
- 315 Bayod, E. & Tornberg E. (2011). Microstructure of highly concentrated tomato suspensions on  
316 homogenization and subsequent shearing. *Food Research International* 44, 755-764.
- 317 Chevalley J. (1991). An adaptation of the Casson equation for the rheology of chocolate. *Journal of  
318 Texture Studies*, 22, 219-229.

- 319 Dahlenborg, H., Millqvist-Fureby, A., Bergenståhl, B., & Kalnin, D. J. E. (2010). Investigation of  
320 Chocolate Surfaces Using Profilometry and Low Vacuum Scanning Electron Microscopy. *Journal*  
321 *of the American Oil Chemists' Society*, 88, 773-783.
- 322 Do, T.-A.L., Hargreaves, J. M., Wolf, B., & Mitchell, J. R. (2007). Impact of particle Size  
323 Distribution on Rheological and Textural Properties of Chocolate Models with Reduced Fat  
324 Content. *Journal of Food Science*, 72, 541-552.
- 325 Dolz, M., González, F., Delegido, J., Hernández, M.J., & Pellicer, J., (2000). A time dependent  
326 expresión for thixotropic areas. Application to aerosol 100 hydrogels. *Journal of Pharmaceutical*  
327 *Sciences*, 89, 790-797.
- 328 Joye, D.D. (2003). Shear rate and viscosity corrections for a Casson fluid in cylindrical (Couette)  
329 geometries. *Journal of food Colloid and interface Sciences*, 267, 204-210.
- 330 Franke, K., & Heinzelmann K. (2008). Structure improvement of milk powder for chocolate  
331 processing. *International dairy Journal*, 18, 928-931.
- 332 Glicerina, V., Balestra, F., Dalla Rosa M., Romani, S., (2013). Rheological, textural and  
333 calorimetric modifications of dark chocolate during process, *Journal of Food Engineering*, 119,  
334 173-179.
- 335 Gonçalves E. V & Lannes S. C. S., (2010). Chocolate rheology. A Review. *Ciência e Tecnologia de*  
336 *Alimentos* 30, 840-841.
- 337 International Confectionery Association (ICA), (2000). Viscosity of cocoa and chocolate products.  
338 Analytical Method 46. Available from CAOBISCO, rue Defacqz 1, B-1000 Bruxelles, Belgium.
- 339 Johansson, D., & Bergenthal, B. (1992). The Influence of Food Emulsifier on Fat and Sugar  
340 Dispersions in Oils. I Adsorption, sedimentation. *Journal of the American Oil Chemists' Society*.  
341 69, 705-717.
- 342 Juszczak, L, Witczak, M., Fortuna, T., Banys, A., (2004). Rheological properties of commercial  
343 mustards. *Journal of Food Engineering*, 63, 209-271.



- 344 Liang, B., & Hartel, R. W. (2004). Effects of Milk Powders in Milk Chocolate. *Journal of Dairy*  
345 *Science*, 87, 20–31.
- 346 Mc Guire, R.G. (1992). Reporting of objective color measurements. *HortScience*, 27, 1254-1255.
- 347 Pajin B., Dokic L., Zaric, D., Šoronja-Simovic, D., Loncarevic, I., & Nikolic, I. (2013).  
348 Crystallization and rheological properties of soya milk chocolate produced in a ball mill. *Journal of*  
349 *Food Engineering*, 114, 70-74.
- 350 Roopa, B.S., & Bhattacharya, S. (2009). Characterisation and modelling of time-independent and  
351 time-dependent flow behaviour of sodium alginate dispersions. *International Journal of Food*  
352 *Science and Technology*, 44, 2583– 2589.
- 353 Rousseau, D. (2007). The microstructure of chocolate. In D.J McClements (Eds), *Understanding*  
354 *and controlling the microstructure of complex foods*. (pp. 648-690). Woodhead Publishing:  
355 Cambridge.
- 356 Saguy, S., & Graf, E. (1991). Particle size effects on the diffuse reflectance of a sucrose –caramel  
357 mixture, *Journal of Food Science*, 56, 1117-1120.
- 358 Schantz, B., & Rohm, H., (2005). Influence of lecithin-PGPR blends on the rheological properties  
359 of chocolate. *LWT-Food Science and Technology*, 38, 41-45.
- 360 Servais, C., Jones, R., & Roberts, I. (2002). The influence of particle size distribution on the  
361 processing of food. *Journal of Food Engineering*, 51, 201-208.
- 362 Servais, C., Ranch, H., & Roberts, I. (2004). Determination of chocolate viscosity. *Journal of*  
363 *Texture Studies*, 34, 467-497.
- 364 Stortz, T., A., & Marangoni, A., (2013). Ethylcellulose solvent substitution method of preparing  
365 heat resistant chocolate. *Food Research International*, 51, 797-803.
- 366 Taylor, J. E., Van Damme, I., Johns, M. L., Routh, A. F., & Wilson, D. I. (2009). Shear rheology of  
367 molten crumb chocolate. *Journal of Food Science*, 74(2), 55–61.

- 368 Tscheuschner, H. D., & Wunsche, D. (1979). Rheological properties of chocolate masses and the  
369 influence of some factors. In P. Sherman (Ed.), *Food Texture and Rheology* (pp. 355–368). New  
370 York: Academic Press.
- 371 Vavreck, A. N. (2004). Flow of molten milk chocolate from an efflux viscometer under vibration at  
372 various frequencies and displacements. *International Journal of Food Science and Technology*,  
373 39(4), 465–468 .
- 374 Vernier, F. (1998). Influence of emulsifier on the rheology of chocolate and suspension of cocoa  
375 and sugar particles in oil. Doctoral Thesis- Department of Chemistry, University of Reading-UK
- 376 Voltz, M. & Beckett, S.T. (1997). Sensory of chocolate. *The Manufacturing Confectioner*. In proc.  
377 of DS Chocolate Technology Conference. pp. 49. Anuga FoodTec
- 378 Windhab, E. J., (2000). Fluid immobilization – a structure-related key mechanism for the viscous  
379 flow behavior of concentrated suspension systems. *Applied Rheology* 10, (3) 134-144
- 380 Wichchukit, S., Mccarthy M, J., & Mccarthy K, L. (2004). Flow Behaviour of Milk Chocolate Melt  
381 and the Application to Coating Flow. *Journal of Food Science*, 70, 165-171.

382

383

384

385

386

387

388

389

390

391


392

393

394

395

396

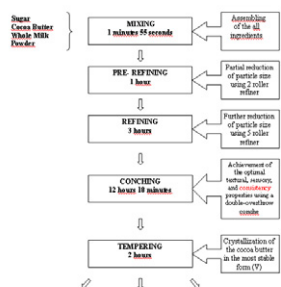

397

398

399

400

401

402

403

404

405

406

407

408

409

410


411

412


413

414

415




416

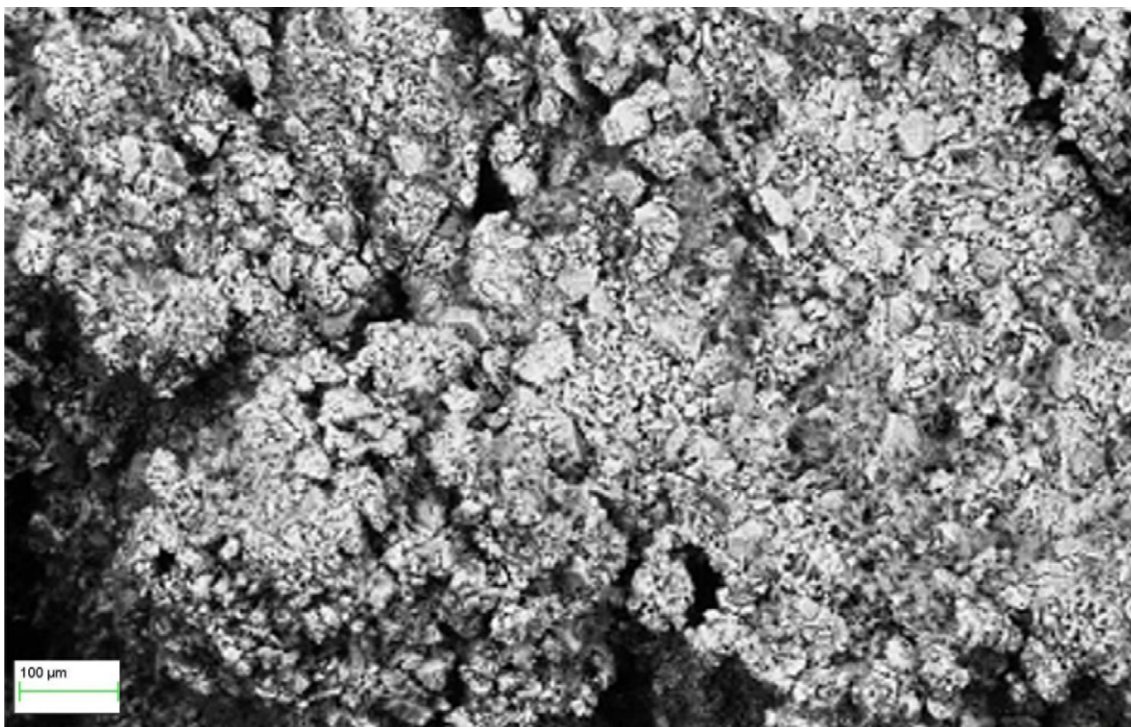


417




418

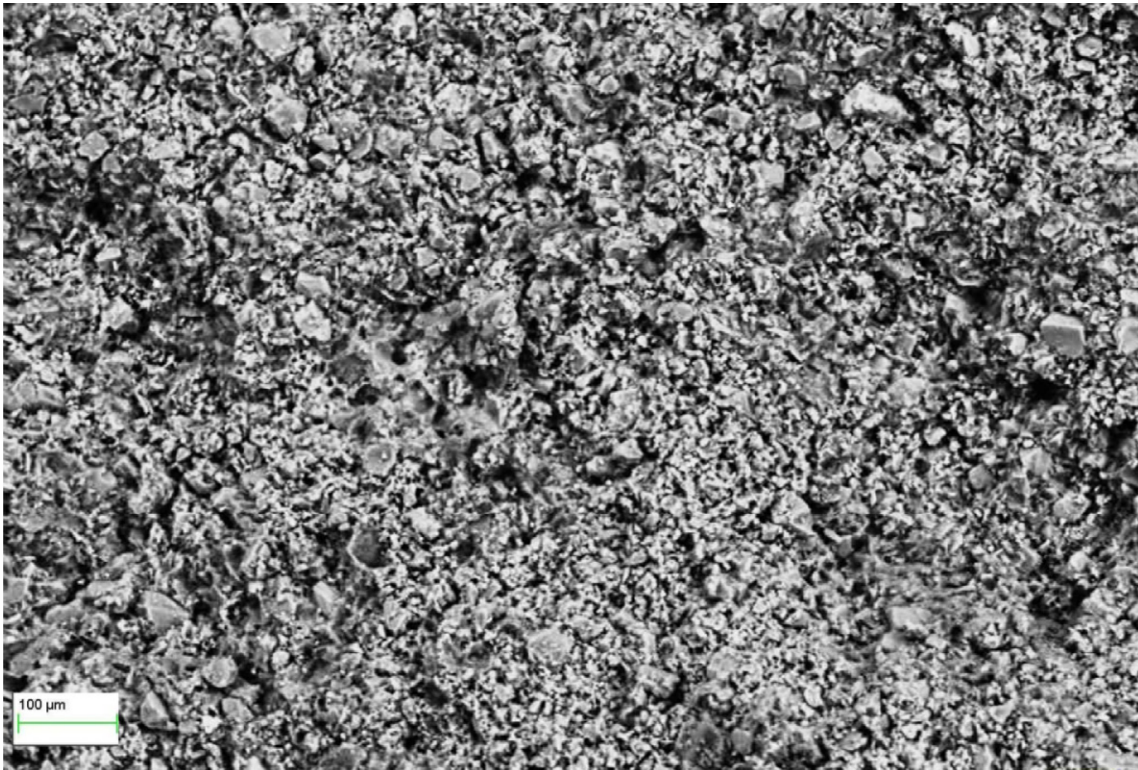

419

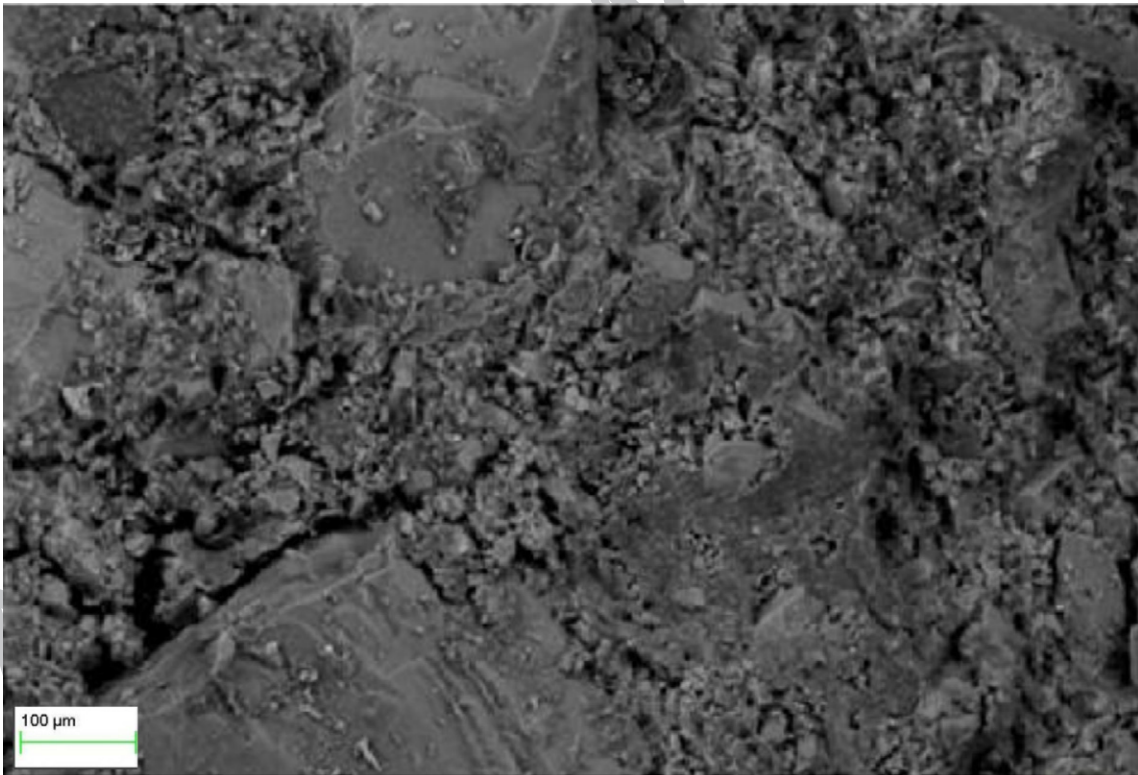

420

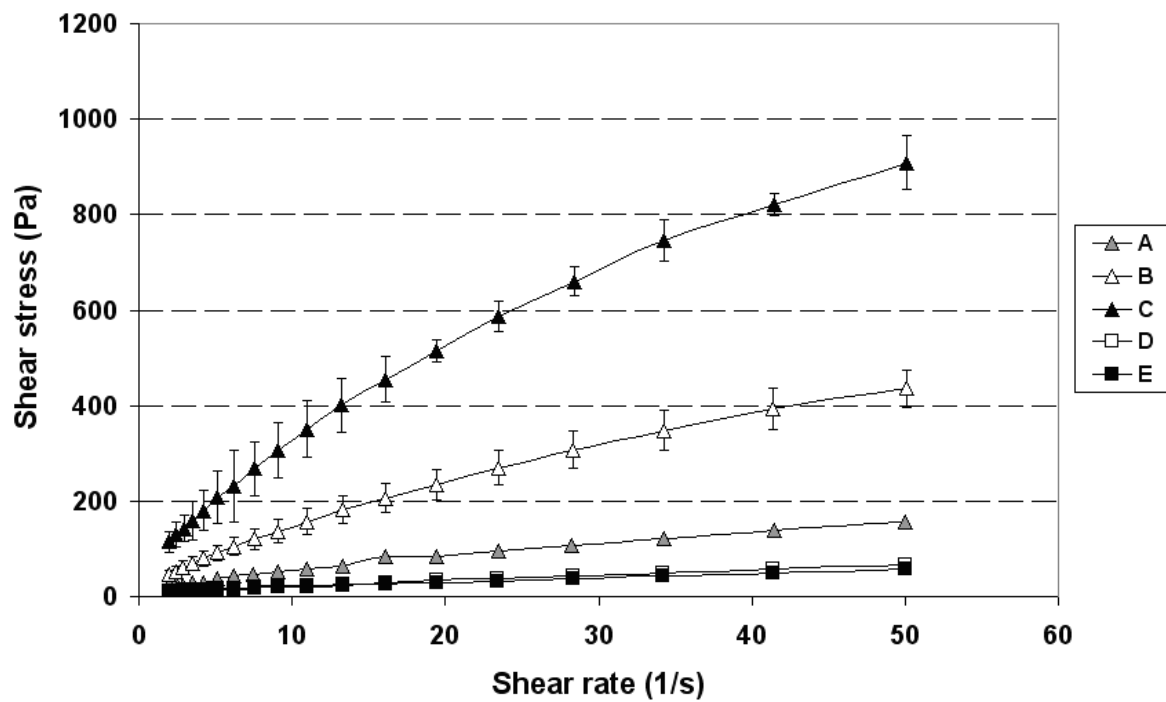

421

422

423

424

425

426

427

428

429

430

431


432

433

434

435

436

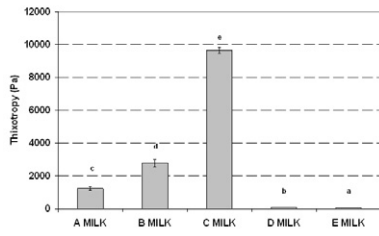

437

438

439

440

441

442

443

444

445

446

447

448

449

450

451

452

453


454

455

456

457

458

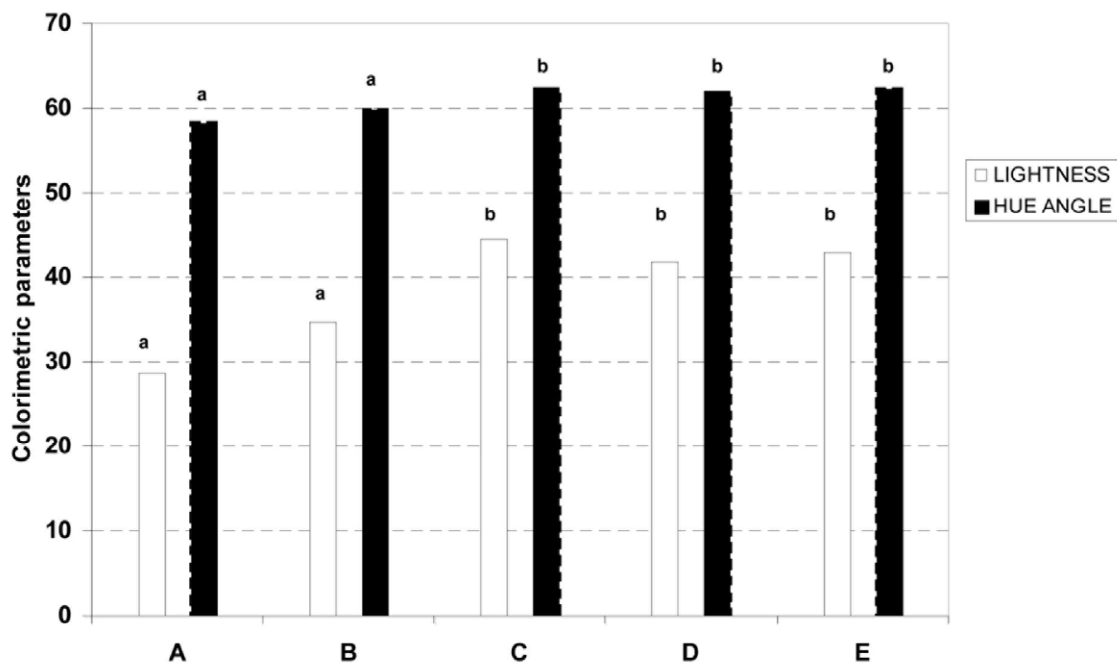

459

460

461

462

463

464

465

466

467

468

469

470

471

472

473

474



475

476

477

478

479 Legends to Figures

480

481 Fig. 1. Scheme of chocolate manufacturing process (adapted from Babin, H. 2005).

482

483 Fig.2. Micrographs of milk chocolate after different processing steps: (a) mixing, (b) pre-refining,  
484 (c) refining, (d) conching and (e) tempering.

485

486 Fig.3. Changes of apparent viscosity (Pa s) of milk chocolate samples, during mixing (A), pre-  
487 refining (B), refining (C), conching (D) and tempering (E) steps, evaluated at 40°C.

488

489 Fig. 4. Changes of thixotropy of milk chocolate samples during mixing (A), pre-refining (B),  
490 refining (C), conching (D) and tempering (E) steps.

491

492 Fig. 5. Lightness ( $L^*$ ) and hue angle ( $h^\circ$ ) colorimetric parameters of milk chocolate samples during  
493 mixing (A), pre-refining (B), refining (C), conching (D) and tempering (E) steps.

494

495

496

497

498

499

500

501

502

503

504

505

506

507

508

509 **Highlights**

510 -Milk chocolate quality is affected by particles characteristics and from the process.

511 -Influence of single steps on structural properties are useful, to improve the rheological ones.

512 -Microstructure and rheology are key parameters to optimize final properties of milk chocolate.

513

514

515

516

517

518

519

520

521

522

523

524

525

526

527 **Table 1.** Microstructural analysis of the milk chocolate.

Samples	Particle size
	(Ferret diameter)
$A_{\text{mixing}}$	$103.00^a \pm 2.57$
$B_{\text{pre-refining}}$	$67.00^b \pm 3.54$
$C_{\text{refining}}$	$29.00^c \pm 2.37$
$D_{\text{conching}}$	$22.00^c \pm 2.56$
$E_{\text{tempering}}$	$17.91^c \pm 3.73$

528 <sup>a-c</sup> values in the same column followed by different letters differ significantly at  $p < 0.05$  level

529

530

531

532

533

534

535

536

537

538

539

540

541

542

543

544

545

546 **Table.2.** Casson yield values, Casson Plastic Viscosity, Yield stress and Apparent Viscosity of milk  
 547 Chocolate samples.

<b>Samples</b>	<b>Casson Yield value (Pa)</b>	<b>Casson Plastic Viscosity (Pa*s)</b>	<b>Yield stress (Pa)</b>	<b>Apparent Viscosity (Pa*s)</b>
A <sub>mixing</sub>	6.82±0.63 <sup>b</sup>	4.38±0.30 <sup>b</sup>	37.10±3.14 <sup>b</sup>	3.84±0.11 <sup>b</sup>
B <sub>pre-refining</sub>	11.97±0.58 <sup>c</sup>	7.82±0.83 <sup>c</sup>	91.10±5.95 <sup>c</sup>	10.84±1.39 <sup>c</sup>
C <sub>refining</sub>	35.70±4.70 <sup>d</sup>	15.36±2.30 <sup>d</sup>	209.33±8.14 <sup>d</sup>	23.23±2.15 <sup>d</sup>
D <sub>conching</sub>	2.75±0.23 <sup>a</sup>	1.55±0.35 <sup>a</sup>	16.93±2.17 <sup>a</sup>	1.53±0.13 <sup>a</sup>
E <sub>tempering</sub>	1.95±0.04 <sup>a</sup>	0.21±0.00 <sup>a</sup>	14.56±1.45 <sup>a</sup>	1.32±0.12 <sup>a</sup>

548 a-d values in the same column followed by different letters differ significantly at  $p < 0.05$  level.

549  
550

551

552

553

554

555

556

557

558

559

560

561

562

563 **Table 3.** Storage and loss modulus of milk chocolate samples evaluated at 1 Hz and at 40°C.

<b>Samples</b>	<b>G'</b> <b>(Pa)</b>	<b>G''</b> <b>(Pa)</b>
A <sub>mixing</sub>	8416±125 <sup>b</sup>	1281±32 <sup>b</sup>
B <sub>pre-refining</sub>	13673±644 <sup>c</sup>	2357±24 <sup>c</sup>
C <sub>refining</sub>	72746±890 <sup>d</sup>	16873± <sup>d</sup>
D <sub>conching</sub>	3983±112 <sup>a</sup>	807±34 <sup>a</sup>
E <sub>tempering</sub>	2873±97 <sup>a</sup>	798±84 <sup>a</sup>

564 a-d values in the same column followed by different letters differ significantly ( $p < 0.05$ ).

565