



ALMA MATER STUDIORUM
UNIVERSITÀ DI BOLOGNA

ARCHIVIO ISTITUZIONALE
DELLA RICERCA

Alma Mater Studiorum Università di Bologna Archivio istituzionale della ricerca

Shear strengthening of masonry wallettes resorting to structural repointing and FRCM composites

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

Published Version:

Shear strengthening of masonry wallettes resorting to structural repointing and FRCM composites / Casacci S.; Gentilini C.; Di Tommaso A.; Oliveira D.V.. - In: CONSTRUCTION AND BUILDING MATERIALS. - ISSN 0950-0618. - ELETTRONICO. - 206:(2019), pp. 19-34. [10.1016/j.conbuildmat.2019.02.044]

Availability:

This version is available at: <https://hdl.handle.net/11585/689520> since: 2019-06-15

Published:

DOI: <http://doi.org/10.1016/j.conbuildmat.2019.02.044>

Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).
When citing, please refer to the published version.

(Article begins on next page)

This is the final peer-reviewed accepted manuscript of:

[Susanna Casacci, Cristina Gentilini, Angelo Di Tommaso and Daniel V. Oliveira. Shear strengthening of masonry wallettes resorting to structural repointing and FRCC composites. Construction and Building Materials. Vol. 206C, pp. 19-34, 2019]

The final published version is available online at:
[<https://doi.org/10.1016/j.conbuildmat.2019.02.044>]

Rights / License:

The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

1 Shear strengthening of masonry wallettes resorting to structural repointing and 2 FRCM composites

3 Susanna CASACCI^{1,a}, Cristina GENTILINI^{2,b*}, Angelo DI TOMMASO^{1,b}, and Daniel V.

4 OLIVEIRA^{3,d}

5 ¹*Department of Civil, Chemical, Environmental and Materials Engineering – DICAM*
6 *University of Bologna, Viale del Risorgimento 2, 40136 Bologna, Italy*

7 ²*Department of Architecture – DA*

8 *University of Bologna, Viale del Risorgimento 2, 40136 Bologna, Italy*

9 ³*ISISE, University of Minho, Department of Civil Engineering, Guimarães, Portugal*

10 ^asusanna.casacci@unibo.it; ^bcristina.gentilini@unibo.it; ^cangelo.ditommaso@unibo.it; ^ddanvco@civil.uminho.pt

11 *corresponding author

13 Abstract

14 Results of an experimental campaign conducted on plain and reinforced masonry wallettes subjected to
15 diagonal compression tests are presented in this paper. The masonry panels were reinforced by means of two
16 strengthening techniques: structural repointing achieved by inserting basalt bars in the mortar bed joints and
17 fiber reinforced cementitious matrix (FRCM) composite, obtained by applying a single-ply glass mesh on the
18 sides of the specimens. The structural effects of symmetric and asymmetric strengthening configurations are
19 investigated. The main mechanical parameters, such as shear capacity, ductility and shear modulus, are
20 compared and discussed introducing a calibrated reinforcement ratio. Further, analytical procedures presented
21 in the codes and in literature are followed to predict the shear capacity of the unstrengthened and strengthened
22 wallettes and, finally, compared to the values obtained experimentally.

24 **Keywords:** Repointing; masonry; diagonal compression test; lime-based matrix; basalt bars; FRCM; glass
25 mesh.

27 Nomenclature list

Symbol	Definition
A_b	Average bond area between the matrix and the bar
A_{FRCM}	Area of FRCM reinforcement by unit width in both directions (horizontal and vertical)
A_{BAR}	Cross-sectional area of the bar
A_m	Interface loading area between the steel shoe and the wall
A_n	Net cross-sectional area of the wallette
E	Elastic modulus
EB	Externally bonded
E_{BAR}	Elastic modulus of the bar
E_{FRCM}	Elastic modulus of the FRCM
E_m	Elastic modulus of masonry

f_{cb}	Compressive strength of the bricks
f_{cm}	Compressive strength of the mortar
f_{fm}	Flexural strength of the mortar
f_i	Force carried by i -th bar
f'_m	Compressive strength of masonry
$f_{t,BAR}$	Tensile strength of the bar
$f_{t,FRCM}$	Tensile strength of the FRCM
f'_t	Tensile strength of masonry
FRCM	Fiber reinforced cementitious matrix
FRP	Fiber reinforced polymer
ϕ_{BAR}	Diameter of the bar
g	Gage length
G	Shear modulus
h	Height of the brick
H	Height of the masonry panel
L_e	Effective length of the bar
L_i	Effective bond length of the i -th bar
n	Percentage of the gross area of the unit brick that is solid
n_{layer}	Number of layer of fabric
NSM	Near surface mounted
PBO	Polyparaphenylene benzobisoxazole
P	Applied load
P_{max}	Maximum applied load
P_{max}^{UNR}	Maximum applied load for the unreinforced specimen
P_{max}^R	Maximum applied load for the reinforced specimen
R_{BAR}	Radius of the bar
RF-A	Specimen reinforced by single-ply asymmetric FRCM system
RF-S	Specimen reinforced by single-ply symmetric FRCM system
RR-A	Specimen reinforced by asymmetric structural repointing
RR-S	Specimen reinforced by symmetric structural repointing
t	Thickness of the brick
t_m	Thickness of the mortar joint
T	Thickness of the masonry panel
u	Horizontal displacement
URM	Unreinforced masonry specimen
v	Vertical displacement
V_n	Shear capacity
V_c	Shear capacity due to toe crushing failure
V_{dt}	Shear capacity due to diagonal tension failure

V_f	Contribution of reinforcement to shear capacity of the specimen
V_m	Shear capacity of the unreinforced masonry wall
V_{sf}	Shear capacity due to shear friction failure
V_{ss}	Shear capacity due to shear sliding failure
w	Width of the brick
W	Width of the masonry panel
θ	Angle between horizontal and the main diagonal of the wall
μ	Pseudo-ductility
μ_m	Modified coefficient of internal shear friction in mortar joint
μ_0	Coefficient of internal friction in the mortar joints
γ	Shear strain
ε_{BAR}	Breaking elongation of the bar
ε_{FRCM}	Ultimate tensile strain of the FRCM
Δ	Structural enhancement achieved in terms of P_{max} by using reinforcement
Δu	Horizontal extension of the specimen
Δv	Vertical shortening of the specimen
ρ_f	Calibrated reinforcement ratio
τ	Shear stress
τ_{el}	Shear stress in the elastic branch
τ_{max}	Maximum shear stress
τ_b	Average shear bond strength between the matrix and the bar
τ_0	Shear bond strength of mortar joints
$\tau_{0,m}$	Modified shear bond strength of mortar joints

28

29 **1. Introduction**

30 Masonry buildings constitute the greatest part of the building stock in Europe. It is well known that masonry
31 structures suffer from several structural deficiencies. Low ductility, low mechanical properties (in particular,
32 a poor tensile strength), as well as weak connections between structural elements, are among the causes of the
33 high vulnerability against out-of-plane loads and of the fragile collapse of masonry structures [1-3]. For these
34 reasons, strengthening interventions are often necessary to improve the mechanical performance of masonry
35 structures [4, 5]. Innovative materials, as externally bonded (EB) textiles such as FRPs (fiber reinforced
36 polymers) have been used for repairing and strengthening both modern and historic constructions and structural
37 components [6, 7]. The composite materials are used to: (i) provide tensile strength to masonry elements; (ii)
38 modify the mechanical behaviour and the collapse mechanisms of the structure and (iii) increase the structure
39 displacement capacity, [8].

40 Recently, fiber reinforced cementitious matrix (FRCM) composites have been introduced in order to overcome
41 well-known drawbacks of FRP composites such as low compatibility with masonry substrates, low
42 reversibility of the interventions, low vapor permeability and durability issues against environmental factors,

43 [9]. FRCC composites are a combination of inorganic matrices and high-strength fibers namely steel, carbon,
44 polyparaphenylene benzobisoxazole (PBO), basalt or glass [10-12]. The inorganic matrix exhibits significant
45 heat resistance, can be applied at low temperatures or on wet surfaces and allows vapor permeability [13].
46 Additionally, FRCC composites can be easily removed in case they need to be substituted [14].
47 In the case of masonry façades or elements with fair-faced bricks, the use of EB composites for retrofitting
48 interventions may not represent a viable solution, because it can violate aesthetic and conservation requirements.
49 For this reason, the so-called reinforced repointing technique has been developed, being minimally invasive and
50 respectful of the aesthetic of fair-faced masonry elements, [15-18]. The reinforced repointing technique involves
51 the application of materials having high tensile strength such as glass or steel bars, carbon wires, steel textile
52 sheets or composite thin pultruded laminae, to reduce the vulnerability of masonry structures against in-plane
53 actions and long-term high-level dead loads, [19-21]. The technology is also called near surface mounted (NSM)
54 reinforcement [22], because the reinforcing material is embedded with a filler (typically epoxy paste or cement
55 grout) in the horizontal bed joints of a wall previously grooved for few centimetres, usually by means of a grinder.
56 In order to check for the structural effectiveness of FRCC composites and NSM bars applied to masonry for in-
57 plane loading, reinforced masonry panels are commonly subjected to diagonal compression tests. In the last
58 decade, several studies have been published on masonry reinforced with EB FRCC systems subjected to diagonal
59 compression. In [23], masonry panels reinforced with a carbon fiber mesh embedded in a cementitious mortar
60 matrix were subjected to both monotonic and cyclic in-plane loading. The strengthening system provided an
61 increase of both shear strength and energy dissipation. Incerti et al. [24] performed diagonal compression tests
62 on brick double-wythe masonry panels characterized by different textures, as flemish bond and header bond.
63 The panels were reinforced using the same strengthening system, i.e. a basalt bi-directional grid coupled with
64 a lime-based mortar matrix. Results confirmed the efficiency of FRCC composites in improving the shear
65 behavior of masonry panels.

66 In [25], masonry walls reinforced with glass FRCC (GFRCC) were tested. The GFRCC compounds were
67 able to increase the load capacity of the walls and demonstrated a high bond with the masonry surface, reducing
68 the need of transversal ties. An investigation of the in-plane behavior of single- and double-sided strengthened
69 masonry wall panels with a multi-axial hybrid glass-polypropylene fabric coated in a natural hydraulic lime-
70 based mortar was undertaken in [26]. The experimental program considered both solid clay-bricks and hollow
71 clay-blocks as masonry substrate. Recently, different attempts were made to employ natural fibers instead of
72 synthetic ones, as in [27], where the behaviour of tuff masonry specimens strengthened with a textile made
73 with hemp fibers embedded in a lime-based mortar matrix loaded under diagonal compression was
74 investigated. Sisal fibers were employed to strengthen masonry panels against in-plane loading in [28].

75 From the brief literature review carried out above, walls strengthened with FRCC evidenced significant
76 improvements in strength and ductility. However, it emerges that FRCC composites can be applied using a great
77 number of different fiber types (synthetic or natural) embedded in inorganic matrices of different nature (e.g.
78 cementitious-based or lime-based), as well as using different strengthening layouts (symmetric or asymmetric

79 configuration), on different masonry typologies (single or double-wythe, made of solid bricks or hollow blocks,
80 employing natural stones or artificial bricks).

81 Due to the growing interest for FRCM composites and the extremely high combination of variables associated
82 with its use, a wide experimental and analytical research activity is needed to quantify their contribution to load
83 carrying capacity and ductility enhancement as a function of the typology of the substrate, as well as of the mortar
84 matrix and fiber types.

85 Additionally, studies on masonry panels reinforced with basalt NSM bars embedded in a lime-based matrix, as
86 the one herein proposed, are very limited, since the available research programs were carried out on masonry
87 walls made of concrete blocks reinforced using carbon or glass bars (see Section 2).

88 It should also be noted that FRCM and NSM composites usually exhibit scattered results. The variability is due
89 to several factors: the built-in variability of the masonry and of the matrix, and as a consequence, its mechanical
90 behavior is strongly dependent on casting and curing conditions, as well as on substrate conditions. This aspect
91 represents a limit for this class of composites with respect to FRPs, where the variability is mainly related to the
92 masonry substrate. For these reasons, experimental works on masonry reinforced with FRCM composites or
93 NSM bars are necessary to fully characterize their mechanical behaviour. The aim of the present work is to
94 contribute in deepening the knowledge on this topic by enriching the limited existing literature.

95 Given the context above, the present paper discusses the results of an experimental program involving small
96 masonry specimens made of fire-clay bricks and lime-based mortar subjected to diagonal compression loading.
97 After curing, specimens were reinforced using two different strengthening solutions: a group of specimens was
98 strengthened with basalt bars by using the NSM reinforcement technique. To the second group of specimens,
99 a FRCM system, consisting of a 1-ply glass mesh and hydraulic lime-based mortar was applied. Symmetrical
100 and asymmetrical configurations were considered for both retrofitting techniques in order to observe the
101 influence of the reinforcement eccentricity: this condition is important in in-field applications, since most of
102 the times only one side of the wall can be strengthened. Results are presented in terms of load capacity, shear
103 modulus as well as ductility. In order to compare the results obtained from the experimental tests, a calibrated
104 reinforcement ratio is defined. Finally, analytical procedures presented in the codes and in literature are
105 followed to predict the shear capacity of the unreinforced specimens. The shear contribution of the NSM bars
106 is calculated following a modified approach presented in [29], while for the FRCM system contribution, ACI
107 549 Standard [30] is adopted.

108 The paper is organised as follows. Section 2 presents a brief summary on previous diagonal tests conducted
109 on NSM strengthened masonry walls. Materials, specimens and test set-up employed in the experimental
110 program are presented in Section 3. Results of the experimental campaign are collected and discussed in
111 Section 4. In Section 5, analytical procedures to compute shear capacities of both unreinforced and reinforced
112 specimens are presented and compared to the experimental values. Some final considerations conclude the
113 paper.

114

115 **2. Previous tests on NSM bars in masonry subjected to diagonal compression**

116 In this section, the main recent results of experimental campaigns conducted on masonry specimens reinforced
117 by means of NSM bars and subjected to diagonal compression are reported. Results are collected in Table 1 in
118 terms of slenderness ratio, defined as the ratio between the height and the thickness of the panel, masonry and
119 reinforcement properties, shear capacity and increase in shear capacity with respect to the unreinforced
120 specimens. In order to compare the results, a calibrated reinforcement ratio ρ_f , which represents the ratio
121 between the axial stiffness of the reinforcement and that of masonry, is introduced [31, 32]:

122

$$123 \rho_f = \frac{A_{rein f} E_{rein f}}{A_n E_m} 100\% \quad (1)$$

124

125 where $A_{rein f}$ is the area of the reinforcement, A_n is the net masonry area, while $E_{rein f}$ and E_m are the moduli
126 of elasticity of the reinforcing material and masonry, respectively.

127 To the authors' knowledge, the most recent contribution on this topic is the work by Yu et al. [33], which
128 tested eight concrete masonry specimens strengthened with prestressed GFRP bars. The bars were inserted
129 in the mortar joints by means of epoxy paste, following different schemes. The main aspects investigated in
130 the paper were the effect of the bar prestress level and the reinforcement ratio on the load carrying capacity of
131 the specimens. Results showed an increase of the shear capacity of the reinforced walls with prestressed bars
132 with respect to both URM control specimens and specimens reinforced with NSM bars without prestress. URM
133 walls were characterized by a stair-stepped central crack, while the presence of the bars changed the failure
134 mode from shear friction to a combination of shear sliding and friction, or to shear sliding along a single bed
135 joint. It is shown that an increase of the reinforcement ratio or of the level of prestress in the bars did not lead
136 to a proportional increment in the load carrying capacity.

137 Dizhur et al. [34] tested clay brick wall panels reinforced using NSM CFRP strips. NSM strips were inserted
138 vertically or following a cross pattern in the specimens, thus they were not inserted in the mortar bed joints.
139 This solution resulted in an improved structural performance of the retrofitted masonry panels when compared
140 to the control units. However, this application is not interesting to the aim of the present study, since in general,
141 the vertical insertion of the bars does not represent an acceptable solution in the case of historic or monumental
142 buildings due to strict preservation criteria that have to be usually observed.

143 Ismail et al. [35] investigated the diagonal shear behavior of 17 masonry wallettes strengthened using NSM
144 helical steel bars. Both single and double-wythe panels were tested, considering horizontal, vertical and grid
145 patterns of reinforcement. Three out of 17 specimens were reinforced embedding the steel bars in the mortar
146 bed joints that were inserted in the slots employing a cementitious grout. Results showed that single-wythe
147 thick wallettes reinforced with the horizontal NSM bars registered a decrease in shear strength. This was
148 attributed to the fact that the masonry bond strength for these specimens resulted significantly lower with
149 respect to the series average value. However, even if no shear strength increase was recorded, a large increment
150 in pseudo-ductility was observed with respect to URM walls.

151 Mahmood and Ingham [36] performed diagonal compression tests on 17 double-wythe solid clay brick
152 masonry wallettes. Some wallettes were retrofitted by applying EB glass fabrics and others by using NSM
153 CFRP rectangular bars. Also in this campaign, vertical, horizontal and a combination of horizontal and vertical
154 bars were considered among the different retrofitting solutions. CFRP bars were embedded in the slots by
155 means of an epoxy paste. Results showed that symmetric and asymmetric applications of NSM horizontal bars
156 lead to a similar increase in shear strength, even if the symmetrically reinforced panel was characterized by a
157 ρ_f that was double with respect the asymmetric one.

158 In the paper by Tumialan et al. [37] six walls made of hollow concrete blocks and reinforced with glass FRP
159 (GFRP) bars embedded into an epoxy-based paste were tested. A remarkable increase in shear capacity,
160 ranging between 30% and 80%, was achieved. The wall specimen, where only one face was strengthened,
161 showed the same increase in shear strength as the one with the same amount of reinforcement ratio but
162 symmetrically distributed, while the wall with half amount of reinforcement registered less than half of increase
163 in load carrying capacity. The authors stated that the results obtained for the concrete walls should not be
164 generalized for walls with clay bricks, which are characterized by different mechanical and geometrical
165 properties.

166 Turco et al. [38] present experimental results of different applications of NSM bars for the shear reinforcement
167 of masonry walls. Different strengthening combinations were considered: smooth and sand-coated glass FRP
168 bars as reinforcement, epoxy paste and latex modified cementitious paste as groove filling materials. All the
169 retrofitted specimens registered an increase in shear capacity (up to 120%) and ductility. Some specimens
170 showed an out-of-plane phase during failure, in particular the walls strengthened by using the sand-coated bars
171 with epoxy paste due to the high stiffness of the reinforcement. No out-of-plane component was observed for
172 the specimens where low-bond systems were employed: the lower stiffness of reinforcement allowed some
173 slip and, consequently, a better redistribution of stresses was possible.

174 It should be noted that in almost all the studies considered above, only one specimen per type was tested (in
175 few exceptions two panels per type were tested) and only few studies deal with NSM bars inserted in mortar-
176 filled grooves. Additionally, it can be observed that a lot of variables are involved in the case of NSM bar
177 strengthening of masonry: the masonry substrate typology, the reinforcement type, the groove filling material
178 type, the bar cross-sectional shape, the presence of prestress in the reinforcement as well as the pattern
179 distribution of the reinforcement. This large number of parameters requires extensive laboratory
180 characterization and testing to get insight in the mechanical behaviour, to assess existing analytical procedures
181 and to address new design provisions.

Table 1. Summary of recent diagonal compression tests on masonry panels reinforced by using NSM bars.

Reference	Masonry panel properties				NSM reinforcement				Shear capacity [KN]	Shear strength increase with respect to URM (%)	
	Material	Dimensions [mm] (W × H × T)	Slenderness ratio [l]	Number of tested panels for each type	Material	Filling material	Pattern	Reinforcement ratio ρ_f (%)			
Yu et al. [33]	Hollow concrete blocks	W1, W2	1630 × 1630 × 150	10.87	2	/	/	/	0	112.3	/
		W3				1	3 GFRP bars ($\phi 6$)	Two-component general purpose epoxy resin	Horizontal (1 face)	0.40	187.7
		W4			7 GFRP bars ($\phi 6$)		0.93			224.2	100
		W5			2 Prestressed GFRP bars ($\phi 6$)		0.27			195.7	74
		W6			3 Prestressed GFRP bars ($\phi 6$)		0.40			210.8	88
		W7			4 Prestressed GFRP bars ($\phi 6$)		0.53			210.8	88
		W8			7 Prestressed GFRP bars ($\phi 6$)		0.93			234.9	109
		Ismail et al. [35]			New solid clay bricks	W1C-1	1200 × 1200 × 110	10.91	1	/	/
W1S-7, W1S-8	2		7 High strength twisted stainless steel bars ($\phi 6$)	Thixotropic injectable grout		Horizontal (2 faces)			0.19	114.5	-27
Salvaged solid clay bricks	W2C-3		1200 x 1200 x 220	5.45	1	/	/	/	0	51.0	/
	W2S-14					2 High strength twisted stainless steel bars ($\phi 6$)	Thixotropic injectable grout	Horizontal (1 face)	0.08	71.6	40
Mahmood and Ingham [36]	Solid clay bricks	AP8	1170 × 1175 × 225	4.78	1	/	/	/	0	37.0	/
		WTC8				5 CFRP rectangular bars (1.2 mm x 15 mm)	Two-component epoxy resin	Horizontal (1 face)	0.74	65.0	76
		WTC9				10 CFRP rectangular bars (1.2 mm x 15 mm)		Horizontal (2 faces)	1.48	67.0	81
Tumialan et al. [37]	Hollow concrete blocks	Wall 1	1625 × 1625 × 152	10.69	1	/	/	/	0	108.09	/
		Wall 2				14 GFRP bars ($\phi 6.25$)	Epoxy-based paste	Horizontal (1 face)	0.82	197.5	82
		Wall 3				6 GFRP bars ($\phi 6.25$)		Horizontal (2 faces)	0.82	194.83	80
		Wall 4						Horizontal (1 face)	0.35	139.23	28
Turco et al. [38]	Concrete blocks	Control	1600 × 1600 × 150	10.6	1	/	/	/	0	108	/
		E-6CG-1HJ				7 sand coated GFRP bars ($\phi 6.35$)	Epoxy-based paste	Horizontal (1 face)	n.d.(*)	198.9	84
		E-5SG-1HJ				7 smooth GFRP bars ($\phi 5$)				241.1	123
		C-6CG-1HJ				7 sand coated GFRP bars ($\phi 6.35$)	Latex modified cementitious paste	184.1	70		
		E-6CG-2HJ				4 sand coated GFRP bars ($\phi 6.35$)	Epoxy-based paste	195	81		
		E-5SG-2HJ				4 smooth GFRP bars ($\phi 5$)		190.4	76		
		E-6CG-2HJB				8 sand coated GFRP bars ($\phi 6.35$)		Horizontal (2 faces)	189	75	

n.d.(*). not deducible from the paper since some data are missing

182 3. Materials and methods

183 3.1. Bricks and mortars

184 Standard tests were performed to characterize the mechanical properties of the materials used in the
185 experimental campaign. Portuguese solid clay bricks having nominal size of $200 \times 100 \times 50 \text{ mm}^3$ were used
186 for manufacturing the wallettes. Brick compressive strength in flatwise direction was obtained according to
187 EN 772-1 [39] on six 40 mm cubic specimens.

188 Two different types of commercial pre-mixed mortars were used for the preparation of the specimens. A lime-
189 based mortar (mortar A), classified as M5 according to EN 998-2 [40], was used to build the specimens. The
190 mortar was prepared following the instructions provided by the manufacturer, i.e. mixing 4 liters of clean water
191 with 25 kg of powder, [41]. From the same batch of mortar used for the joints, 26 prismatic samples of nominal
192 size $40 \times 40 \times 160 \text{ mm}^3$ were cast and cured at laboratory conditions for two months. After curing, prismatic
193 samples were tested in order to determine compressive and flexural strengths according to EN 1015-11 [42].
194 The testing age of the mortar was approximately the same as the one of the wallettes.

195 The mortar employed for the strengthening operations (referred as mortar B throughout this paper) was a bi-
196 component commercially available, based on natural hydraulic lime and pozzolanic fraction, and classified as
197 M15 according to EN 998-2 [40]. The mixing ratio was a drum of component two for every 25 kg of component
198 one [43]. Using mortar B, Dalalbashi et al. [44] performed compressive and flexural tests according to [42, 45]
199 on five prismatic specimens, at different ages. Tests were performed in a universal testing machine at a rate of
200 10 N/s. The compressive and flexural strengths at 28 days of curing are reported in this paper, since changes
201 in the mechanical properties after the first 30 days were not significant.

202 In Table 2, mechanical properties of bricks and mortars are listed in terms of brick compressive strength f_{cb} , as
203 well as compressive f_{cm} and flexural strength f_{fm} of mortars A and B. The elastic modulus E of mortar B
204 provided by the manufacturer is reported as well.

205

206 3.2. Basalt bars and glass mesh

207 In order to assess the mechanical properties of the basalt bars used to strengthen the specimens, direct tensile
208 tests were performed, Fig. 1a. An anchorage system consisting of steel pipes filled with a thixotropic bi-
209 component epoxy resin was employed. The dimension of the specimens was derived according to ASTM
210 D7205 [46]. The specimens, with a total length of 1000 mm, were provided with two anchoring systems of
211 300 mm long each. Diameter ϕ_{BAR} and cross-sectional area A_{BAR} resulted equal to 5.50 mm (CoV=1%) and
212 23.76 mm^2 , respectively.

213 A universal testing machine was used for the tests. The top end pipe was encased in a steel frame connected
214 to the top jaw of the machine. The gripping mechanism of the upper frame, as shown in Fig. 1b, allowed for
215 torsional rotation to avoid the negative effects of possible eccentricity and misalignments of the specimens.
216 The bottom end pipe was encased in a steel frame fixed to the lower grip of the testing machine. Each specimen
217 was provided with a clip gauge (length equal to 100 mm) placed in the central position of the bar to record the
218 elongation and the load was applied at a constant speed of 2 mm/min until the failure of the specimen. A total

219 of four bars were tested. In Fig. 1c, a bar at failure is reported, while in Fig. 1d, the stress-strain curves for the
 220 tested bars are shown. Stress-strain curves are linear till the peak load, showing a brittle failure of the bars. In
 221 Table 2, the tensile strength $f_{t,BAR}$, elastic modulus E_{BAR} , and breaking elongation ε_{BAR} , as obtained from the
 222 tests, are reported.


223 The mesh used to strengthen the specimens consisted of an alkali-resistant pre-primed glass fiber mesh,
 224 characterized by a 25×25 mm² grid spacing, [47]. Equivalent thickness of the fiber grid and fiber area per
 225 unit width are equal to 0.035 mm and 35.27 mm²/m, respectively [47]. Its linear tensile strength, modulus of
 226 elasticity and elongation at failure are reported in Table 2. Leone et al. [48] tested FRCM coupons in order to
 227 obtain the stress-strain curve and the main mechanical properties of the composite according to the test method
 228 presented in [49]. Coupons with different sizes and testing ages were tested. Due to the variability of the results,
 229 average experimental values were reported in this study. The cracked elastic modulus of the FRCM E_{FRCM} , the
 230 ultimate tensile strain ε_{FRCM} , and the ultimate tensile stress $f_{u,FRCM}$ that have to be used in the analytical
 231 calculations are reported in Table 2.

232
 233 Table 2. Mechanical properties of the materials used in the experimental tests.

Sub-system	Material	Mechanical property	Average value	CoV (%)
Walette	Fire-clay brick	Compressive strength f_{cb} [MPa]	14.3	4
	Bedding mortar (mortar A)	Compressive strength f_{cm} [MPa]	5.8	27
		Flexural strength f_{fm} [MPa]	2.6	24
Strengthening	Matrix (mortar B)	Compressive strength f_{cm} [MPa]	7.07 ^a	10.5
		Flexural strength f_{fm} [MPa]	4.71 ^a	7.8
		Elastic modulus E [MPa]	8000 ^b	-
	Basalt bar	Tensile strength $f_{t,BAR}$ [MPa]	777.3	2
		Elastic modulus E_{BAR} [MPa]	34180	2
		Breaking elongation ε_{BAR} [%]	2.1	6
	Glass mesh	Linear tensile strength [kN/m]	45 ^b	-
		Elastic modulus [MPa]	72000 ^b	-
		Breaking elongation [%]	1.8 ^b	-
	FRCM coupon	Elastic modulus in the cracked phase E_{FRCM} [MPa]	40500 ^c	-
Ultimate tensile strain ε_{FRCM}		0.0098 ^c	-	
Ultimate tensile stress $f_{u,FRCM}$ [MPa]		853.5 ^c	-	

234 ^avalue from [44], ^bvalue provided by the manufacturer, ^cvalue from [48]

235
 236
 237

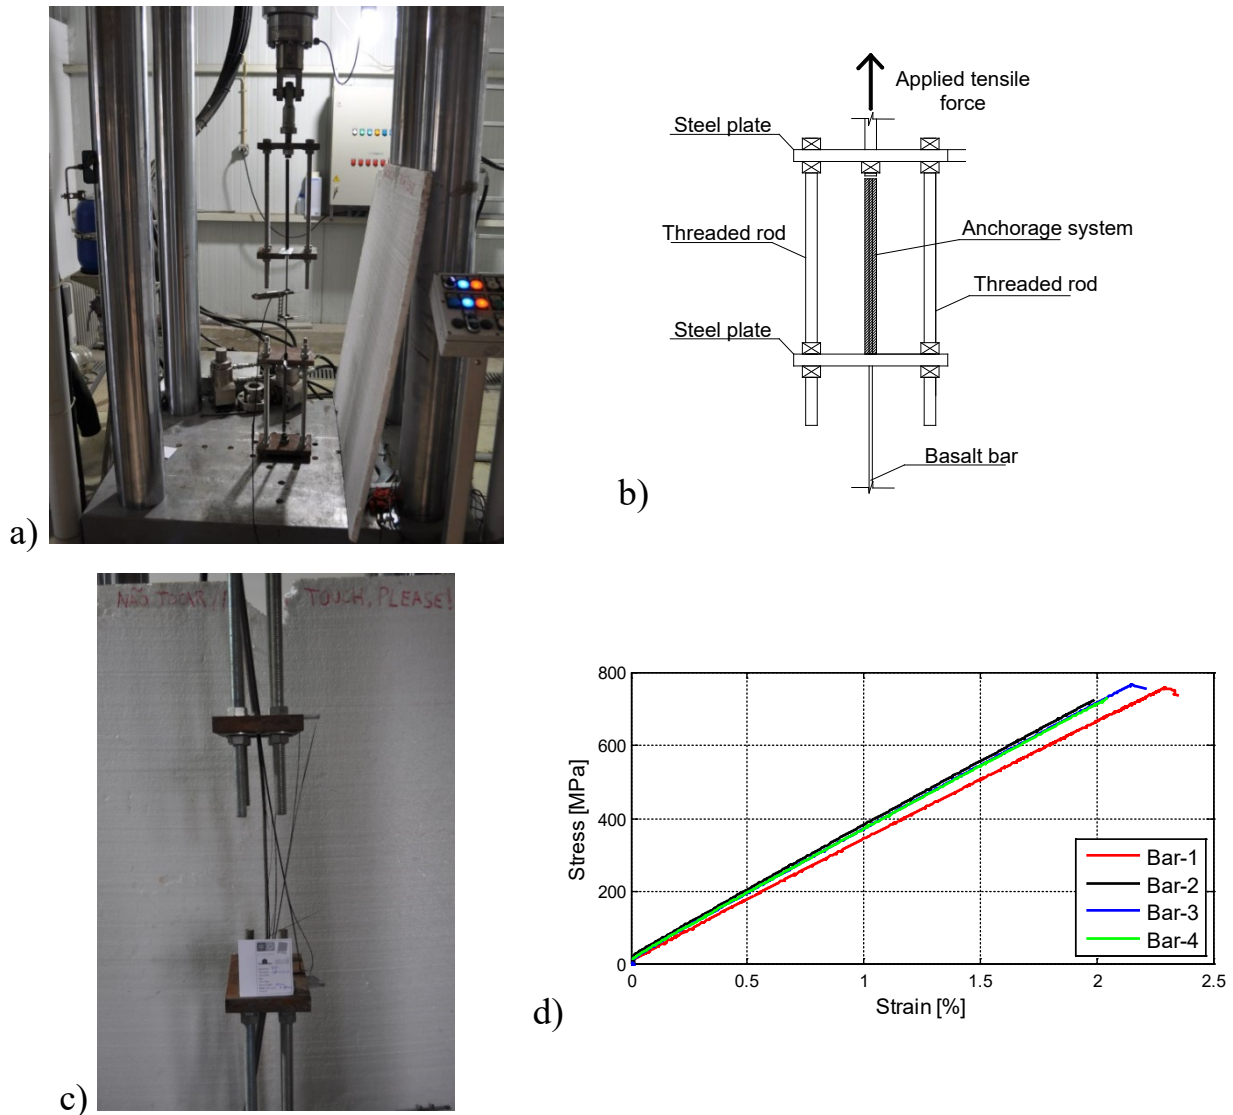

238 Fig. 1. Basalt bars: a) direct tensile test, b) detail of the top gripping mechanism of the bar, c) failure mode;
 239 d) stress-strain curves.

240

241 3.3. Masonry wallettes

242 Each masonry specimen was built with nine courses of bricks and eight 10 mm thick mortar layers, and had a
 243 nominal total size equal to $520 \times 530 \times 100 \text{ mm}^3$, see Fig. 2. The dimensions of the specimens were defined
 244 taking into account their weight, handling procedures and acceptable slenderness in order to avoid instability
 245 issues, which in this case was equal to 5.3 [24, 50]. In particular, five types of specimens were prepared, as
 246 follows:

- 247 *i)* reference unreinforced specimens hereinafter denoted as URM, Fig. 2;
- 248 *ii)* strengthened specimens with asymmetric structural repointing obtained by inserting one basalt bar in the
 249 third and in the sixth mortar joints for a total of two bars, hereinafter denoted as RR-A, Fig. 3;
- 250 *iii)* strengthened specimens with symmetric structural repointing obtained by inserting two basalt bars in the
 251 third and two in the sixth mortar joints for a total of four bars, hereinafter denoted as RR-S, Fig. 3;

252 iv) strengthened specimens with asymmetric FRCM obtained applying a 1-ply glass mesh on one side of the
253 specimen, hereinafter denoted with RF-A, Fig. 4;

254 v) strengthened specimens with symmetric FRCM obtained applying a 1-ply glass mesh on each side of the
255 specimen (characterized by an amount of reinforcement that is twice with respect to RF-A), hereinafter denoted
256 as RF-S, Fig. 4.

257 Strengthening operations were carried out after 28 days of curing of the wallettes at laboratory conditions. The
258 main phases of the repointing process consisted in the preparation of the grooves in the selected mortar joints
259 for a depth around 20 mm from the edges by means of a grinder. The grooved joints were cleaned with an air
260 gun and wet manually with a sprinkler. They were partially filled with structural mortar (mortar B) and the
261 bars were placed and pushed in the mortar such that the mortar surrounded the bars. Afterwards, the grooves
262 were completely filled with a second layer of structural mortar, finally restoring the wall original appearance,
263 Fig. 3.

264 For the application of the FRCM composite, the following operations were conducted:

265 1) the surfaces of the panels to be reinforced with FRCM composite were manually wet by means of a sprinkler;
266 2) after the wetting of the surface, mortar B was thrown manually with a metallic trowel on the surface in order
267 to increase the surface roughness and consequently the adhesion between the surface of the wall and the first
268 mortar layer used to apply FRCM composite;



269 3) afterwards, a uniform layer of mortar B (approximately 4-5 mm-thick) was applied manually on the surface
270 using a flat trowel;

271 4) while the product was still fresh, the glass mesh was pressed lightly on it with a flat trowel so that it adhered
272 perfectly to the mortar;

273 5) then, a second uniform layer of mortar B (approximately 4-5 mm-thick) was applied manually using a flat
274 trowel in order to completely cover the glass mesh;


275 6) the surface was smoothed while still fresh.

276 All the NSM and FRCM reinforced wallettes were left to cure till the time of testing. Table 3 summarizes the
277 different masonry specimens that were built. Three wallettes for each category were prepared, thus totalizing
278 15 specimens.

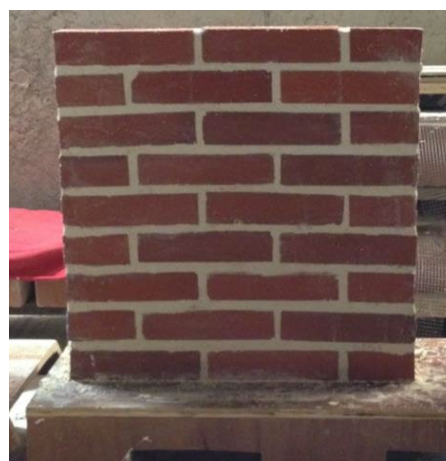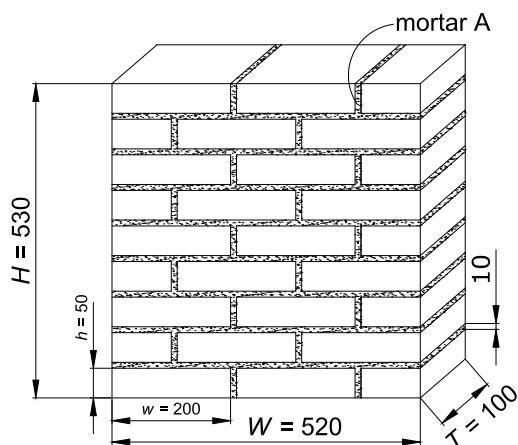


279
280 Fig. 2. Unreinforced masonry specimens (URM). Sizes in mm.

281

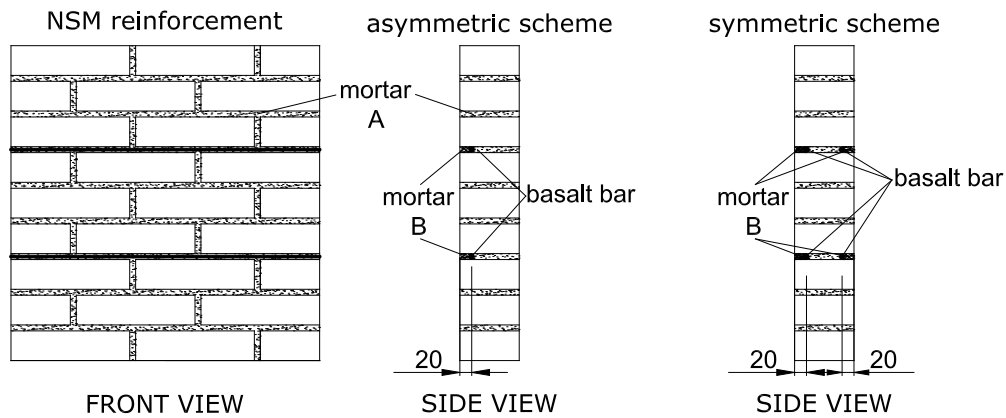

282

283 Fig. 3. Reinforced masonry wallettes with NSM basalt bars: asymmetric reinforcement scheme (RR-A
 284 specimens) and symmetric reinforcement scheme (RR-S specimens). Sizes in mm.

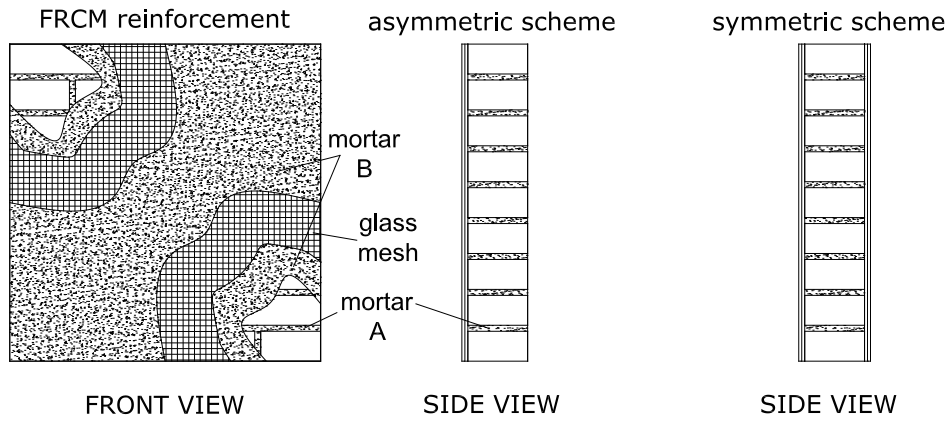

285

286 Fig. 4. Reinforced masonry wallettes with FRCM technique: asymmetric reinforcement scheme (RF-A
 287 specimens) and symmetric reinforcement scheme (RF-S specimens). Sizes in mm.

288

289 Table 3. Specimen labels and description.

Specimen label	Description	Number of tested specimens
URM	Unreinforced specimen (Fig. 2)	3
RR-A	Reinforced specimen: 2 basalt bars inserted asymmetrically in the mortar joints (Fig. 3)	3
RR-S	Reinforced specimen: 4 basalt bars inserted symmetrically in the mortar joints (Fig. 3)	3
RF-A	Reinforced specimen: 1-ply glass-based FRCM composite applied asymmetrically on one side (Fig. 4)	3
RF-S	Reinforced specimen: 1-ply glass-based FRCM composite applied symmetrically on both sides (Fig. 4)	3


290

291 3.4. *Test set-up and instrumentation*

292 After curing, all wallette specimens were subjected to a diagonal compression test [51], see also Fig. 5a. The
 293 load was applied through steel shoes with dimensions of $115 \times 115 \times 15 \text{ mm}^3$ placed at diagonally opposing
 294 bottom and top corners. All specimens were tested in a universal testing machine of 500 kN load capacity
 295 operated under displacement control at a rate equal to $2 \text{ }\mu\text{m/s}$.

296 In Fig. 5b and Fig. 5c, the instrumentation of the specimens is shown. During the test, the values of the applied
 297 load and of the diagonal displacements were recorded. The displacements were measured by four LVDTs: two
 298 applied on the front face (LVDT_{c,f} and LVDT_{t,f}), and two on the back face, (LVDT_{c,b} and LVDT_{t,b}). In
 299 particular, LVDT_{c,f} and LVDT_{c,b} were vertically oriented along the force line to measure the wall shortening,
 300 while LVDT_{t,f} and LVDT_{t,b} were placed horizontally, perpendicular to the force line to record the crack
 301 opening. A load cell was used to measure the force, P , along the loaded diagonal.

302

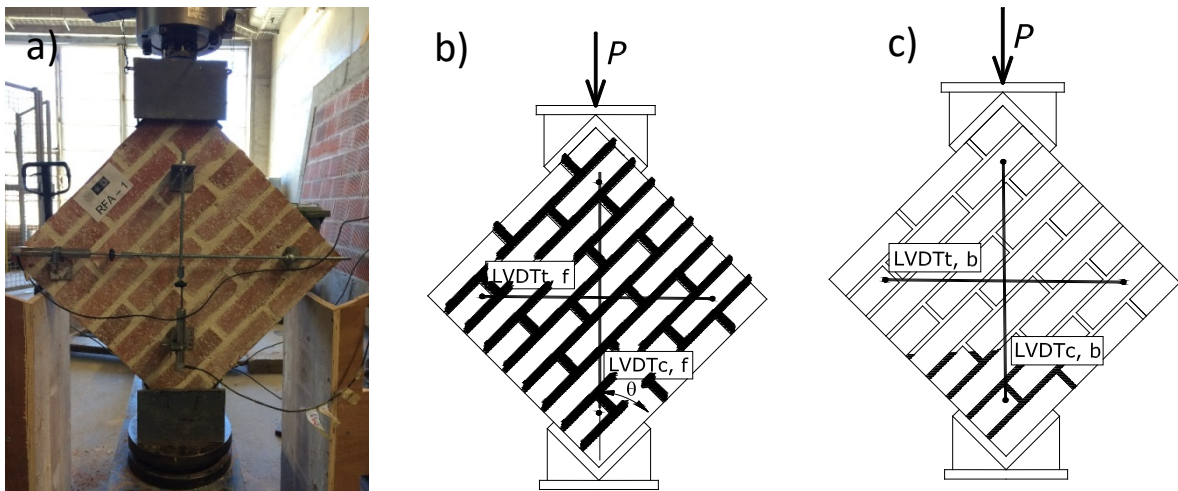

303 Fig. 5. Diagonal compression test: a) set-up, b) instrumentation of the front face; c) instrumentation of the
 304 back face.

305

306 **4. Experimental results**

307 4.1. *Shear stress-strain curves*

308 In the following, results obtained from the tests conducted on the specimens are presented. In particular, results
 309 are given in terms of shear stress (τ) versus shear strain (γ). Following ASTM E519 [51], τ is computed
 310 assuming that is equal to both tensile and compression principal stresses, as follows:

311

$$312 \tau = \frac{P \cos \theta}{A_n} \tag{2}$$

313

314 where θ is the angle between the horizontal and the main diagonal of the wall, A_n is the net area of the masonry
 315 specimen calculated as:

316

$$A_n = \left(\frac{W+H}{2}\right) Tn \quad (3)$$

318

319 with W , H , and T the width, height, and thickness of the specimen, respectively, and n is the percentage of the
 320 gross area of the unit that is solid, expressed as a decimal [52]. In this study, the value of n is equal to 1. The
 321 shear strain γ is calculated as:

322

$$\gamma = \frac{\Delta v + \Delta u}{g} \quad (4)$$


324

325 where Δv is the average vertical shortening (in mm) measured by the horizontal LVDTs, Δu is the average
 326 horizontal extension (in mm) measured by the vertical LVDTs, Fig. 5, and g is the vertical gage length (in
 327 mm), which in this study is 500 mm.


328 Referring to shear stress–strain curves for the URM specimens displayed in Fig. 6a, an approximately linear
 329 behavior until the end of the test can be identified. As soon as the crack appeared at the brick/mortar interface
 330 and the peak stress was reached, specimens collapsed in a brittle way. It should be noted that results related to
 331 specimen URM-3 are not reported due to an anomalous behaviour of the wallette during the testing procedure.
 332 The shear stress–strain curves for specimens strengthened by NSM bars are represented in Fig. 6b, as well as
 333 the curves for the URM specimens for comparison purposes. Curves for the RR-A specimens show a similar
 334 slope in the initial part. On average, the maximum shear stress is similar between asymmetrically reinforced
 335 specimens and URM walls, whereas displacement capacity is higher. Wallettes with twice the amount of
 336 reinforcement (RR-S) behave in a linear elastic manner at low load values, then a non-linear behavior is
 337 observed till the peak load. Initial cracking is delayed by the presence of the reinforcement and the shear
 338 modulus increases with the presence of the bars. RR-S-1 wallette shows an anomalous behaviour in the initial
 339 part characterized by a low rigidity: a possible reason of this behaviour can be related to the strengthening
 340 operations and it will be discussed in the next section.

341 Curves for RF-A and RF-S specimens are shown in Fig. 6c. Results are less dispersed with respect to RR
 342 specimens and a clear and consistent trend can be envisaged. The curves are steeper in the first part with a
 343 substantial increase for the shear modulus with respect to URM curves. As expected, the highest peak stresses
 344 are reached by the specimens reinforced symmetrically (RF-S). However, a remarkable increment in peak
 345 stress is also registered for specimens reinforced on only one side (RF-A). FRCM composite applied on the
 346 face of the specimens restrained the opening of diagonal cracks allowing the wallettes to undergo larger
 347 displacements (shear strain higher than 1 cm/m) and substantially increased the shear stiffness of the masonry
 348 specimens.


349

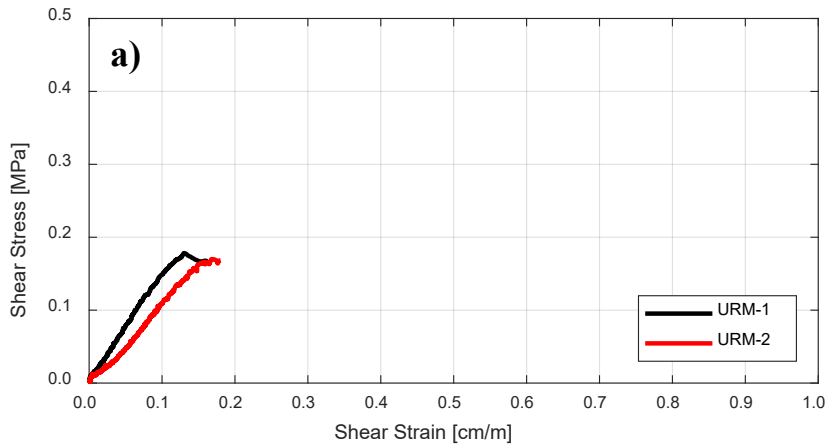

350

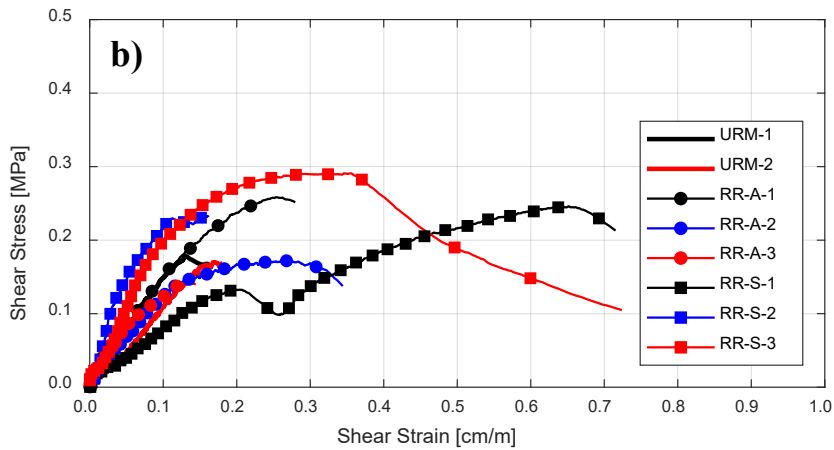

351

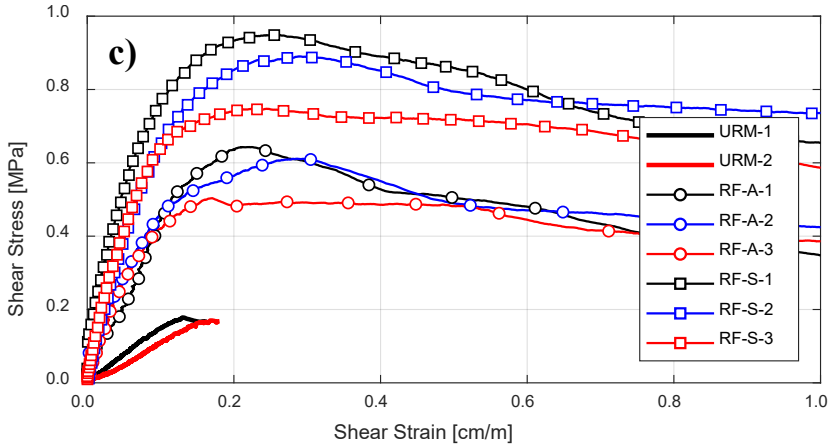

352

353 Fig. 6. Shear stress-strain curves for the tested specimens: a) URM specimens; b) strengthened specimens by
 354 using NSM bars; c) strengthened specimens by using FRCM system.

355

356 *4.2. Crack pattern and failure mode*

357 It was observed that URM specimens collapsed in a brittle way, in which a main crack developed within the
 358 mortar joints, and sliding occurred due to detachment at the brick/mortar interface: bonding between the
 359 masonry units and mortar controlled the failure, as shown in Fig. 7a and Fig. 7b.


360 In the case of RR-A and RR-S wallettes, the presence of the bars did not change the failure mode with respect
 361 to URM specimens, which still was sliding along the unreinforced mortar joints, see Fig. 8a - Fig. 8f. In some

362 repointed specimens, failure occurred due to sliding at the brick/mortar interface partially involving the
363 strengthened joints (e.g. RR-A-2 and RR-A-3 specimens). Specimen RR-S-1, symmetrically repointed, as
364 already noted in the previous section, showed an anomalous behaviour: the crack that led to the collapse of the
365 specimen propagated from the upper reinforced joint, see Fig. 8d. This behaviour may be attributed to the
366 repointing operations, as the slots in the joints were made with a grinder after the curing of the panels. This
367 procedure may have caused an initial damage in the joint, creating a weak plane, which led consequently to
368 the collapse of the specimen involving that joint. It is believed that this effect would be less relevant for thicker
369 walletes, which is the case of real buildings. Additionally, in specimens RR-A-2, RR-A-3 and RR-S-1
370 debonding of the bar from the surrounding mortar was visible, Fig. 8d. This behaviour usually is not detected
371 in the case of NSM bars embedded with epoxy resin [29], where the epoxy paste and the bar do not detach one
372 with respect to the other, while the bond at the paste/masonry interface controls failure. In the development of
373 the analytical approach presented in Section 5.2, this aspect will be taken into account.

374 Referring to the failure mode of RF-A specimens, Fig. 9a - Fig. 9c, once the peak load was attained, vertical
375 cracks started to appear in the central area, clearly visible on the specimen side not covered by the FRCM
376 composite, involving both the joints and the bricks, see Fig. 9a. As the cracking pattern developed and the
377 cracks got wider, the specimen started to tilt towards the reinforced side as already noted in other experimental
378 campaigns [29]. This behavior was neither detected in the symmetrically FRCM reinforced panels nor in the
379 case of NSM reinforced panels. This out-of-plane effect did not result in a ductility reduction. Cracks kept
380 evolving along the compressed diagonal, between the two loading shoes, leaving the outer corners unaffected.
381 Finally, FRCM debonded from the masonry and the specimens failed due to diagonal tension.

382 Failure mode of RF-S specimens, Fig. 9d - Fig. 9f, was characterized by vertical cracks that appeared in the
383 mid part of the specimen body. The cracking pattern developed within the two loading shoes, and a diagonal
384 tension failure occurred in the specimens. At failure, the FRCM layers debonded from the masonry on both
385 sides. It is thus believed that the use of anchorage systems may further increase the load and displacement
386 capacities, but this topic is outside the scope of the present study. A summary of the cracking patterns of the
387 retrofitted walls is given in Fig. 10.


388

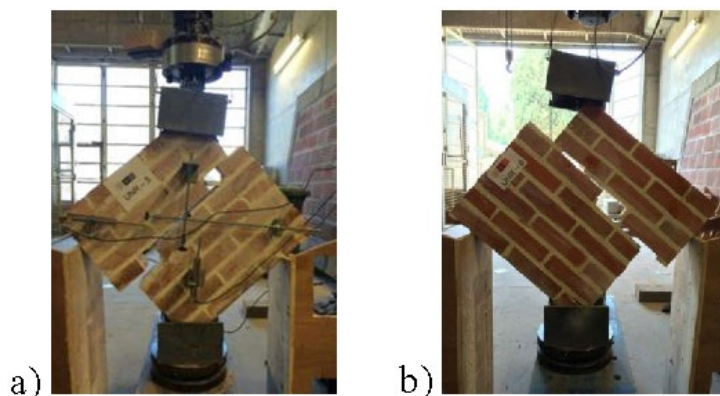

389


390

Fig. 7. Failure mode of unreinforced specimens: a) UMR-1; b) URM-2.

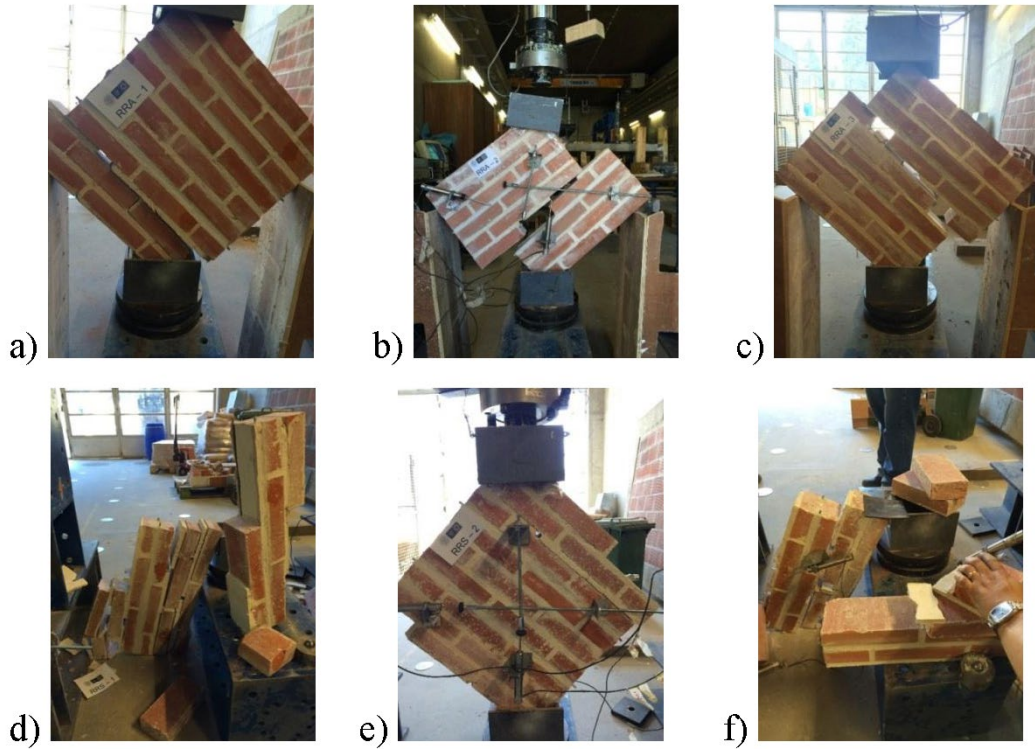

391
392
393

Fig. 8. Failure mode of RR specimens: a) RR-A-1, b) RR-A-2, c) RR-A-3, d) RR-S-1, e) RR-S-2 and f) RR-S-3.

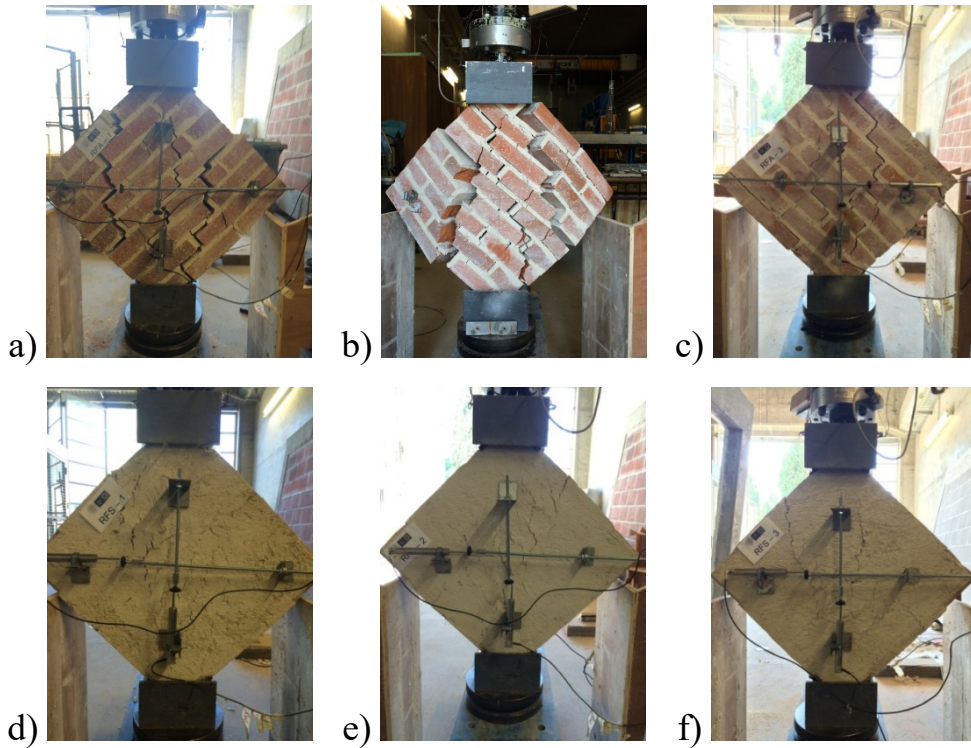

394
395

Fig. 9. Failure mode of RF specimens: a) RF-A-1, b) RF-A-2, c) RF-A-3, d) RF-S-1, e) RF-S-2 and f) RF-S-3.

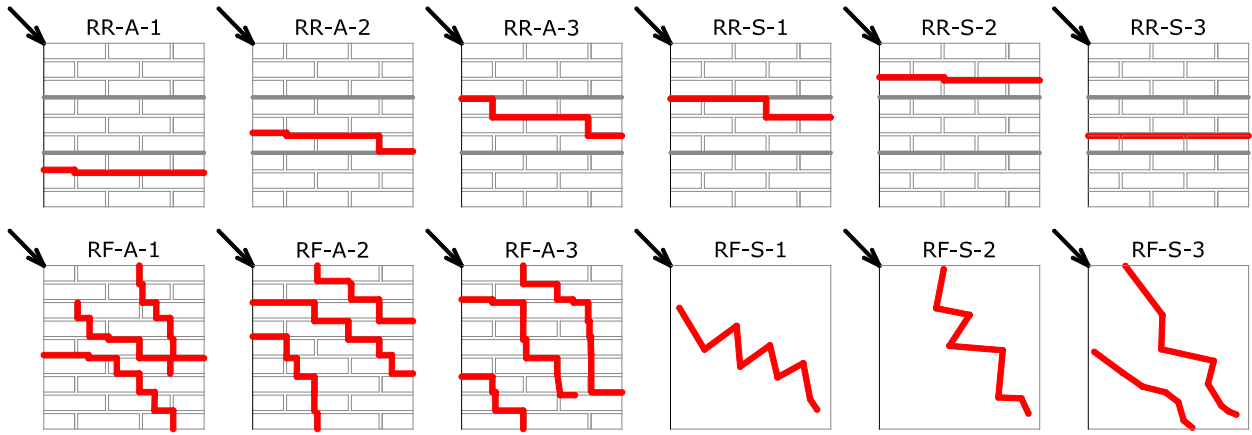


Fig. 10. Cracking patterns of the retrofitted wallettes.

4.3. Summary results

A summary of the relevant mechanical parameters obtained from the diagonal compression tests in terms of average values and coefficients of variation is given in Table 4. The peak load and shear stress values (P_{max} , τ_{max}) are also listed. The strength enhancement in terms of maximum force, Δ , achieved by using reinforcements, is calculated as follows:

$$\Delta = \left(\frac{\bar{P}_{max}^R - \bar{P}_{max}^{URM}}{\bar{P}_{max}^{URM}} \right) 100\% \quad (5)$$

where \bar{P}_{max}^R and \bar{P}_{max}^{URM} are the average peak forces for the reinforced specimens (RR-A, RR-S, RF-A and RF-S) and unreinforced specimens (URM), respectively. The elastic shear modulus is derived as:

$$G = \frac{\tau_{el}}{\gamma_{el}} \quad (6)$$

where τ_{el} is the shear stress in the elastic branch and γ_{el} is the corresponding shear strain. The displacement ductility of the considered retrofitting solutions, μ , is here evaluated as:

$$\mu = \min \left(\frac{\Delta u_u}{\Delta u_{max}}; \frac{\Delta v_u}{\Delta v_{max}} \right) \quad (7)$$

where Δu_u and Δv_u are the horizontal elongation and vertical shortening corresponding to the ultimate conditions, respectively, while Δu_{max} and Δv_{max} are the horizontal elongation and vertical shortening corresponding to the maximum load, respectively. In particular, in the case of repointing strengthening, the ultimate displacements are taken at failure, whereas for the FRCM strengthening, the ultimate condition is considered to occur when the post-peak load reaches the 80% of its maximum value, as in [10, 36, 53]. A masonry panel that experiences inelastic deformations without substantial load-carrying capacity reduction is characterized by a high value of μ .

423 Finally, in order to compare the two retrofitting solutions, the parameter ρ_f , Eq. (1), representing the calibrated
 424 reinforcement ratio, is reported as well.

425 From Table 4, by comparing the results for URM and RR-A specimens in terms of peak load, the increment Δ
 426 reaches 8%, whereas for RR-S specimens it attains 44%. Moreover, an increment in the shear modulus,
 427 \bar{G} , moving from URM specimens to RR is registered. In terms of ductility, it is worth noting that μ is lower
 428 for RR-S with respect to RR-A. As stated before, an induced initial damage may have been caused during the
 429 strengthening operation. Additionally, also due to the brittle failure of the specimens, the values of
 430 displacements at ultimate conditions employed to calculate the ductility value, Eq. (7), were not easy to
 431 identify.

432 Comparing the results for URM and RF-A specimens in terms of \bar{P}_{max} , the increment is double, whereas
 433 between URM and RF-S, the increment is three times higher. An increment in shear modulus, \bar{G} , is achieved
 434 moving from URM to RF specimens. The ductility μ is twice when compared to the one obtained for the
 435 reinforced specimens with the repointing technique. In fact, the presence of the FRCM reinforcement modifies
 436 the mode of failure from sliding (URM and RR specimens) to diagonal tension (RF specimens). Application
 437 of the FRCM only on one side of the panel leads to a substantial increment in the load capacity and pseudo-
 438 ductility value, and this increment is even more marked for the symmetric retrofitting solution.

439

440 Table 4. Summary of the main experimental results (the coefficient of variation is given inside parentheses).

Specimen label	P_{max} [kN]	\bar{P}_{max} [kN]	τ_{max} [MPa]	$\bar{\tau}_{max}$ [MPa]	Δ [%]	G [MPa]	\bar{G} [MPa]	μ [/]	$\bar{\mu}$ [/]	ρ_f [%]
URM-1	12.99	13.32	0.17	0.18	-	141.03	173.09 (26%)	-	-	-
URM-2	13.65	(4%)	0.18			205.15				
RR-A-1	11.07	14.62 (30%)	0.15	0.20	8.0	297.60	253.02 (32%)	-	1.21 (8%)	0.46
RR-A-2	13.18		0.18			159.90		1.28		
RR-A-3	19.60		0.26			301.58		1.14		
RR-S-1	18.65	19.48 (12%)	0.25	0.26	44.0	155.21	403.92 (54%)	1.18	1.09 (8%)	0.92
RR-S-2	17.71		0.24			559.56		1.00		
RR-S-3	22.09		0.30			497.00		1.08		
RF-A-1	45.83	43.96 (12%)	0.62	0.59	224.8	773.09	672.78 (17%)	1.57	2.09 (44%)	0.75
RF-A-2	48.11		0.65			693.37		1.55		
RF-A-3	37.95		0.51			551.88		3.14		
RF-S-1	66.61	64.45 (12%)	0.90	0.87	376.2	1696.50	2050.25 (35%)	2.79	2.82 (21%)	1.50
RF-S-2	70.91		0.95			2881.46		2.24		

RF-S-3	55.84		0.75			1572.80		3.44		
--------	-------	--	------	--	--	---------	--	------	--	--

441

442 Furthermore, it can be noted that even if the reinforcement ratio is not negligible in the case of repointed panels,
443 the corresponding load carrying capacity increment with respect to the control specimens is not so substantial.
444 As expected, the FRCM symmetric and asymmetric application lead to a peak increment and pseudo-ductility
445 increment that are higher. As already noted in other experimental campaigns [33, 35], an increment of the
446 reinforcement ratio does not always lead to a proportional increment in shear capacity and ductility. However,
447 in the cases where EB textiles cannot be applied in façades of masonry structures or monuments due to
448 preservation criteria, it is shown that structural repointing provides additional resources of ductility and energy
449 absorption capacity to masonry.

450 The most remarkable change highlighted in the specimens retrofitted with the bars with respect to URM panels
451 is the increment in displacement capacity. As expected, a more evident structural enhancement in the wall
452 panels is registered using the FRCM system, resulting in a clear increment of both shear strength and
453 displacement capacity.

454

455 5. Analytical investigation

456 The analytical procedure presented in ACI 549 [30] to predict the nominal shear capacity of unreinforced
457 masonry walls is followed in this section and analytical results are compared with the corresponding
458 experimental ones.

459 Considering a reinforced masonry panel subjected to a diagonal compression load P , the nominal shear
460 capacity of the panel, V_n , can be computed as the sum of two contributions:

461

$$462 V_n = V_m + V_f \quad (8)$$

463

464 where V_m and V_f are the contributions of the masonry panel and the reinforcement, respectively.

465

466 5.1. URM specimens

467 In a diagonal compression test, four types of failure mechanisms are identified, depending on physical and
468 mechanical properties of the wall [29, 31]. The specimen fails when the shear load reaches the minimum
469 shear capacity, V_m , as follows:

470

$$471 V_m = \min\{V_{SS}, V_{Sf}, V_{dt}, V_c\} \quad (9)$$

472

473 The shear capacity due to shear sliding failure, V_{SS} , is given by:

474

$$475 V_{SS} = \frac{\tau_0}{1 - \mu_0 \tan \theta} A_n \quad (10)$$

476

477 where τ_0 is the shear bond strength between mortar and bricks, μ_0 is the coefficient of internal shear friction
478 in mortar joints, and A_n is calculated by using Eq. (3). Parameters τ_0 and μ_0 can be experimentally determined
479 by means of the triplet test, as described in [54].

480 The shear capacity due to shear friction failure, V_{Sf} , is equal to:

481

$$482 \quad V_{Sf} = \frac{\tau_{0,m}}{1 - \mu_m \tan \theta} A_n \quad (11)$$

483

484 where $\tau_{0,m}$ and μ_m are the modified shear bond strength in the mortar joints and the modified coefficient of
485 internal shear friction in the mortar joints, respectively, calculated as

486

$$487 \quad \tau_{0,m} = \frac{\tau_0}{1 + 1.5 \mu_0 \frac{h}{w}} \quad (12)$$

488

489 and

490

$$491 \quad \mu_m = \frac{\mu_0}{1 + 1.5 \mu_0 \frac{h}{w}} \quad (13)$$

492

493 with w and h being the width and height of the brick, respectively.

494 The shear capacity due to the diagonal tension failure, V_{dt} , results in:

495

$$496 \quad V_{dt} = \frac{tg\theta + \sqrt{21.26 + tg^2\theta}}{10.58} f'_t A_n \quad (14)$$

497

498 where the tensile strength of masonry f'_t is considered equal to $0.67\sqrt{f'_m}$ for clay bricks, with f'_m being the
499 compressive strength of masonry.

500 Finally, the shear capacity due to toe crushing failure at the loaded end, V_c is given by:

501

$$502 \quad V_c = \frac{2wf'_m}{3h + 2wtg\theta} A_m \quad (15)$$

503

504 where A_m is the interface loading area between the steel shoe and the wall along the horizontal direction [31].

505


506 5.2. RR-A and RR-S specimens: NSM bar contribution

507 In order to calculate the V_f contribution given by the basalt bars, a modified version of the approach presented
508 by [29] is followed here. In [29], diagonal compression tests on unreinforced masonry concrete walls
509 strengthened with glass fiber-reinforced polymer bars were presented. The glass bars were embedded in the

510 mortar joints by means of an epoxy paste and a latex modified cementitious paste. In all the tests, neither
 511 debonding of FRP bars from the paste nor tensile failure of the bars were observed. Thus, in calculating the
 512 contribution of the FRP bars to the shear capacity of the walls, a perfect bond between the bar and the epoxy
 513 paste was considered. As a consequence, the shear resistance of the reinforcing bars was limited by bond failure
 514 between epoxy paste and the surrounding original mortar.

515 In the present study, after the failure of the walls reinforced by means of repointing, it was observed that the
 516 basalt bars were in some parts detached from the surrounding structural mortar. For this reason, the approach
 517 in [29] was modified taking into account that the shear resistance of the basalt bars is controlled by bond failure
 518 between the structural mortar and the bar itself.

519

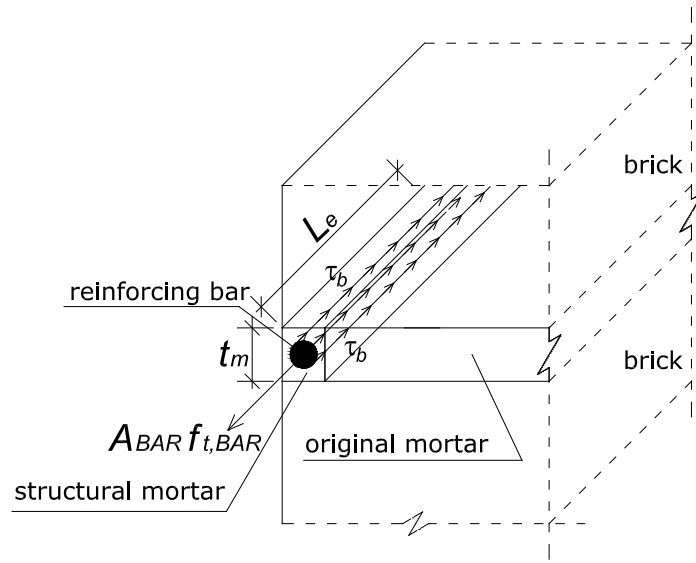

520

521 Fig. 11. Distribution of the stresses along a bar embedded in the mortar joint.

522

523 In the analysis, the bond stress between structural mortar and the bar is assumed to be uniform along the
 524 effective length of the bar at failure, Fig. 11. From equilibrium conditions, the tensile force developed in the
 525 bar should be equal to the bond strength between the structural mortar and the bar:

526

$$527 \quad \tau_b A_b = f_{t, BAR} A_{BAR} \quad (16)$$

528

529 where τ_b and A_b are the average bond strength and average bond area between the bar and the structural mortar,
 530 $f_{t, BAR}$ is the tensile stress of the NSM bar and A_{BAR} is the cross-sectional area of the bar. The average bond
 531 area A_b is equal to

532

$$533 \quad A_b = 2\pi R_{BAR} L_e \quad (17)$$

534

535 where R_{BAR} is the nominal radius of the bar and L_e is the effective length of the bar in masonry.

536 Substituting Eq. (17) in Eq. (16), the effective length results

537

538
$$L_e = \frac{f_{t,BAR} R_{BAR}}{2\tau_b} \quad (18)$$

539

540 Following [29], it is assumed that: *i*) in the masonry wall during the diagonal test, a shear crack with a constant
541 inclination angle of 45 degrees is considered; *ii*) each bar intersected by the crack is divided into two parts at
542 the two sides of the crack. The shear resistance provided by the bars, V_f , is computed as the sum of the forces
543 resisted by the bars intersecting the diagonal crack. The force carried by each bar is calculated as the product
544 of the average bond strength and the surface area of the bond between bar and structural mortar according to
545 the effective bond length of the bar, which is the shortest part of the bar intersected by the diagonal crack.
546 Therefore, V_f reads

547

548
$$V_f = \sum_{i=1}^N A_{BARi} f_i = \tau_b 2\pi R_{BAR} \sum_{i=1}^n L_i \quad L_i \leq L_e \quad (19)$$

549

550 where f_i is the force carried by i -th reinforcing bar, N is the total number of bars intersected by the diagonal
551 crack and L_i is the effective bond length of the i -th bar intersecting the diagonal crack.

552

553 5.3. RF-A and RF-S specimens: FRCM contribution

554 The contribution of FRCM composite to the shear capacity, V_f , is calculated following [31] as:

555

556
$$V_f = 2n_{layer} A_{FRCM} W f_{t,FRCM} \quad (20)$$

557

558 where n_{layer} is the number of layers of fabric, A_{FRCM} is the area of fabric reinforcement by unit width in both
559 horizontal and vertical directions, $f_{t,FRCM}$ is the tensile strength in the FRCM reinforcement calculated as:

560

561
$$f_{t,FRCM} = E_{FRCM} \varepsilon_u \quad (21)$$

562

563 where E_{FRCM} and ε_u are the tensile modulus of elasticity of the cracked FRCM and the tensile strain in the
564 FRCM reinforcement, respectively. Parameter ε_u coincides with the ultimate tensile strain ε_{FRCM} if the latter
565 value is smaller than 0.004 according to [30]. All the calculations to determine the shear capacities of the
566 unreinforced and reinforced wallettes tested in this research program are given in Appendix A.

567

568 5.4. Summary results

569 A comparison between the experimental and the analytical results in terms of shear capacity is listed in Table
570 5. The contribution of the reinforcement separated from the contribution to the shear capacity of URM panels
571 is reported as well. It can be observed that the strength of the unreinforced panels is not accurately predicted,
572 since the ratio between experimental and analytical result is 0.77. This may be due to the fact that the shear

573 friction capacity found analytically assumes at failure a stepped crack through the diagonal wall, while in the
574 case of the two walls tested in this experimental campaign, the crack pattern involved a smaller surface. For
575 specimens reinforced on one or both sides with repointing technique, analytical results overestimate the
576 strength, while for the case of FRCM composites, the formula from [30] provides a large safety margin against
577 the results obtained experimentally. Isolating the contribution of the reinforcement, it can be noted that in the
578 case of asymmetric repointing the contribution of the bars is overestimated from the analytical approach, while
579 the ratio between the experimental and analytical value is around one in the case of symmetric configuration
580 of strengthening. In the case of FRCM, the contribution of the composite found experimentally is almost three
581 times higher than the one determined analytically. The discrepancies between experimental and analytical
582 values in the case of NSM reinforcement can be ascribed to different factors. The analytical procedure
583 employed to calculate the enhancement of shear capacity given by NSM bars is based on several hypotheses.
584 The procedure is an adaptation of the method employed for NSM bars embedded with epoxy paste in masonry
585 joints: the failure mode between the two compared systems (grout-based and epoxy-based) is different, since
586 in the case of grout-filled grooves, failure is controlled by the bond between the grout and the bar, differently
587 from the case of epoxy-filled grooves where the governing factor is the bond between the epoxy paste and the
588 substrate material. Further, in the analytical approach a uniform distribution of the shear stress along the
589 embedment length of the bars is considered. The analytical model employed to calculate the contribution of
590 the bar reinforcement requires further improvements and additional validations considering data from other
591 experimental campaigns.

592

593 Table 5. Comparison between experimental and analytical results in terms of shear capacity.

	Strength (exp.)	Strength (ana.)	Ratio (exp./ana.)	Contribution of the reinforcement (exp.)	Contribution of the reinforcement (ana.)	Ratio considering only the contribution of the reinforcement (exp./ana.)
URM [kN]	9.42	12.15	0.77	/	/	/
RR-A [kN]	10.34	14.27	0.72	0.92	2.12	0.43
RR-S [kN]	13.77	16.39	0.84	4.35	4.24	1.03
RF-A [kN]	31.08	18.09	1.72	21.66	5.94	3.64
RF-S [kN]	45.57	24.03	1.90	36.15	11.88	3.04

594

595 6. Conclusions

596 An experimental campaign on diagonal compression tests conducted on clay brick masonry panels
597 strengthened by two different techniques was presented in this paper. In particular, the investigated
598 strengthening systems were: (a) structural repointing by inserting basalt bars in the mortar joints in a symmetric
599 and asymmetric configuration; (b) FRCM composites by applying a glass mesh on one or both sides of the
600 specimens.

601 Diagonal compression tests allowed to investigate the shear load capacity as well as the ductility of the tested

602 specimens. In particular, an increase in maximum load, shear stiffness and ductility was registered for both
603 retrofitting solutions. However, the increment in shear capacity and ductility is not proportional to the
604 reinforcement ratio, highlighting that an increment of reinforcement does not necessarily correspond to a better
605 structural performance, as pointed out in literature. The failure mode in the case of repointing was sliding along
606 the interface between bricks and mortar as observed in URM specimens, while in the case of FRCM
607 strengthened panels, the mode of failure was diagonal cracking. In the case of asymmetric FRCM
608 reinforcement, the panels bent towards the reinforced side.

609 Analytical procedures showed to be effective in predicting conservative values of shear capacities of reinforced
610 specimens with FRCM. However, some built-in variabilities of URM and repointed panels justify differences
611 between theoretical and experimental results. Additionally, it should be considered that analytical results
612 depend on the values chosen for the parameters, thus for a more reliable prediction of the shear strength, it is
613 recommended that the required parameters are derived by means of experimental tests on the same materials
614 adopted in the program.

615

616 **Acknowledgments**

617 This work was partly financed by FEDER funds through the Operational Programme Competitiveness Factors
618 (COMPETE) and by national funds through the Foundation for Science and Technology (project POCI-01-
619 0145-FEDER-007633). The collaboration of Mr. Mattia Girolomini and the support of the technical staff from
620 the Structural Laboratory of University of Minho during the experimental campaign are gratefully
621 acknowledged. Authors are also grateful to MagmaTech Ltd for kindly providing the basalt bars.

622

623 **Appendix A**

624 *A.1 Masonry properties*

625 Width of the brick: $w = 200$ mm

626 Height of the brick: $h = 50$ mm

627 Thickness of the brick $t = 100$ mm

628 Width of the specimen: $W = 520$ mm

629 Height of the specimen: $H = 530$ mm

630 Thickness of the specimen: $T = 100$ mm

631 Thickness of the mortar joint: $t_m = 10$ mm

632 Net area of the specimen: $A_n = 52500$ mm²

633 Compressive strength of brick: $f_{cb} = 14.3$ MPa

634 Compressive strength of mortar A: $f_{cm} = 5.8$ MPa

635 Compressive strength of masonry: $f'_m = K f_{cb}^{0.7} f_{cm}^{0.3} = 0.55 \cdot 14.3^{0.7} \cdot 5.8^{0.3} = 6.00$ MPa (according to EN
636 1996-1-1 [55] assuming masonry made by general purpose mortar)

637 Tensile strength of masonry: $f'_t = 0.67 \sqrt{f'_m} = 1.64$ MPa

638 Elastic modulus of masonry: $E_m = 1000 f'_m = 6000$ MPa (from [56])

639 Shear bond strength of mortar joint: $\tau_0 = 3\% f'_m = 0.180$ MPa (from [31])
640 Coefficient of internal shear friction in mortar joints: $\mu_0 = 0.30$ (from [31, 57])
641 Modified shear bond strength of mortar joint: $\tau_{0,m} = 0.169$ MPa
642 Modified coefficient of internal shear friction in mortar joints: $\mu_m = 0.270$
643 Average bond strength between the bar and the structural mortar: $\tau_b = 0.5$ MPa (in [29], τ_b is assumed equal
644 to 1.74 MPa. However, this value is referred to triplet tests performed on masonry made by concrete blocks
645 and joints made by epoxy paste. In this study, no triplets tests were conducted to identify the average bond
646 strength between the bar and the mortar, as a consequence the value τ_b is taken from literature on similar
647 materials [58, 59]).

648

649 *A.2 Basalt bar properties*

650 Diameter of the bar: $\phi_{BAR} = 5.5$ mm
651 Cross-sectional area of the bar: $A_{BAR} = 23.76$ mm²
652 Elastic modulus of the bar: $E_{BAR} = 34182$ MPa
653 Maximum tensile strength of the bar: $f_{t,BAR} = 777.27$ MPa

654

655 *A.3 FRCM properties*

656 Area of FRCM reinforcement by unit width in both directions: $A_{FRCM} = 35.27$ mm²/m
657 Elastic modulus of FRCM (cracked): $E_{FRCM} = 40500$ MPa

658

659 *A.4 Masonry contribution (V_m)*

660 (a) Shear capacity due to shear sliding failure, V_{SS} :

$$661 \quad V_{SS} = \frac{\tau_0}{1 - \mu_0 \tan \theta} A_n = \frac{0.180}{1 - 0.30 \cdot 1} 52500 = 13500 \text{ N} = 13.5 \text{ kN}$$

662 (b) Shear capacity due to shear friction failure, V_{Sf} :

$$663 \quad V_{Sf} = \frac{\tau_{0,m}}{1 - \mu_m \tan \theta} A_n = \frac{0.169}{1 - 0.270 \cdot 1} 52500 = 12154 \text{ N} = 12.15 \text{ kN}$$

664 (c) Shear capacity due to the diagonal tension failure, V_{dt} :

$$665 \quad V_{dt} = \frac{\tan \theta + \sqrt{21.26 + \tan^2 \theta}}{10.58} f'_t A_n = \frac{1 + \sqrt{21.26 + 1}}{10.58} 1.64 \cdot 52500 = 46533 \text{ N} = 46.53 \text{ kN}$$

666 (d) Shear capacity due to toe crushing failure at the loading end, V_c :

$$667 \quad V_c = \frac{2wf'_m}{3h + 2w \tan \theta} A_m = \frac{2 \cdot 200 \cdot 6.00}{3 \cdot 50 + 2 \cdot 200 \cdot 1} \cdot 100 \cdot 100 = 43636 \text{ N} = 43.64 \text{ kN}$$

668 Finally, URM shear capacity is calculated by using Eq. (8) as:

$$669 \quad V_m = \min\{V_{SS}, V_{Sf}, V_{dt}, V_c\} = \min\{13.5, 12.15, 46.53, 43.64\} \text{ kN} = 12.15 \text{ kN}$$

670

671 *A.5 Bars contribution (V_f)*

672
$$L_e = \frac{f_{t,BAR} R_{BAR}}{2\tau_b} = \frac{777.27 \text{ MPa} \cdot 2.25 \text{ mm}}{2 \cdot 0.5 \text{ MPa}} = 2137.49 \text{ mm} = 2.1 \text{ m}$$

673
$$V_f = \tau_b 2\pi R_{BAR} \sum_{i=1}^n L_i \quad L_i \leq L_e$$

674 asymmetric reinforcement: $V_f = 0.5 \text{ MPa} \cdot 2 \cdot \pi \cdot 2.25 \text{ mm} \cdot (200 + 100) \text{ mm} = 2.12 \text{ kN}$

675 symmetric reinforcement: $V_f = 0.5 \text{ MPa} \cdot 2 \cdot \pi \cdot 2.25 \text{ mm} \cdot (200 \cdot 2 + 100 \cdot 2) \text{ mm} = 4.24 \text{ kN}$

676

677 *A.6 FRCM contribution (V_f)*

678 From technical data, the ultimate tensile strain ε_u of FRCM is equal to 0.0098, thus higher than 0.004 that
679 represents the admissible value according to ACI 549 [30]. As a consequence, ε_u is considered equal to 0.004.

680 $f_{t,FRCM} = E_{FRCM} \varepsilon_u = 40500 \cdot 0.004 = 162 \text{ MPa}$

681 $V_f = 2n_{layer} A_{FRCM} W f_{t,FRCM}$

682 asymmetric reinforcement: $V_f = 2 \cdot 1 \cdot 35.27 \text{ mm}^2 / 1000 \text{ mm} \cdot 520 \text{ mm} \cdot 162 \text{ N/mm}^2 = 5942.3 \text{ N} =$

683 5.94 kN

684 symmetric reinforcement: $V_f = 2 \cdot 2 \cdot \frac{35.27 \text{ mm}^2}{1000 \text{ mm}} \cdot 520 \text{ mm} \cdot \frac{162 \text{ N}}{\text{mm}^2} = 11884.6 \text{ N} = 11.88 \text{ kN}$

685

686 *A.6.1 Limitations*

687 Following ACI 549 [30], the summation of the masonry and FRCM shear contributions should be checked
688 against the substrate toe crushing capacity:

689 $V_n = \min(V_m + V_f; V_c) = \min(12.15 + 5.94; 43.64) = 18.09 \text{ kN}$

690

691 **References**

- 692 [1] Boscato, G., Pizzolato, M., Russo, S. (2014) ‘Seismic behavior of a complex historical church in l’Aquila’,
693 *International Journal of Architectural Heritage*, Vol. 8, pp. 718-757.
- 694 [2] Franzoni, E., Gentilini, C., Graziani, G., Bandini, S. (2015) ‘Compressive behaviour of brick masonry
695 triplets in wet and dry conditions’, *Construction and Building Materials*, Vol. 82, pp. 45-52.
- 696 [3] Xu, H., Gentilini, C., Yu, Z., Wu, H., Zhao, S. (2018) ‘A unified model for the seismic analysis of brick
697 masonry structures’, *Construction and Building Materials*, Vol. 184, pp. 733-751.
- 698 [4] Viskovic, A. (2016) ‘Seismic retrofitting for masonry historical buildings: Design philosophy and hierarchy
699 of interventions’, *Civil and Environmental Engineering: Concepts, Methodologies, Tools, and
700 Applications*, Vol. 1, pp. 480-503 (Book Chapter).
- 701 [5] Maddaloni, G., Di Ludovico, M., Balsamo, A., Maddaloni, G., Prota, A. (2018) ‘Dynamic assessment of
702 innovative retrofit techniques for masonry buildings’, *Composites Part B: Engineering*, Vol. 147, pp.
703 147-161.
- 704 [6] Vaculik, J., Visintin, P., Burton, N.G., Griffith, M.C., Seracino, R. (2018) ‘State-of-the-art review and
705 future research directions for FRP-to-masonry bond research: Test methods and techniques for

- 706 extraction of bond-slip behavior', *Construction and Building Materials*, Vol. 183, pp. 325-345.
- 707 [7] Foraboschi, P. (2016) Effectiveness of novel methods to increase the FRP-masonry bond capacity,
708 *Composites Part B: Engineering*, Vol. 107, pp. 214-232.
- 709 [8] Valluzzi, M. R., Tinazzi, D., Modena, C. (2002) 'Shear behavior of masonry panels strengthened by FRP
710 laminates', *Construction and Building Materials*, Vol. 16, pp. 409-416.
- 711 [9] Babatunde, S.A. (2017) 'Review of strengthening techniques for masonry using fiber reinforced polymers',
712 *Composite Structures*, Vol. 161, pp. 246-255.
- 713 [10] Gattesco, N., Boem, I. (2015) 'Experimental and analytical study to evaluate the effectiveness of an in-
714 plane reinforcement for masonry walls using GFRP meshes', *Construction and Building Materials*,
715 Vol. 88, pp. 94-104.
- 716 [11] Marcari, G., Basili, M., Vestroni, F. (2017) 'Experimental investigation of tuff masonry panels reinforced
717 with surface bonded basalt textile-reinforced mortar', *Composites Part B: Engineering*, Vol. 108, pp.
718 131-142.
- 719 [12] Cevallos, O.A., Olivito, R.S., Codispoti, R., Ombres, L. (2015) 'Flax and polyparaphenylene
720 benzobisoxazole cementitious composites for the strengthening of masonry elements subjected to
721 eccentric loading', *Composites Part B: Engineering*, Vol. 71, pp. 82-95.
- 722 [13] Franzoni, E., Gentilini, C., Santandrea, M., Carloni, C. (2018) 'Effects of rising damp and salt
723 crystallization cycles in FRCM-masonry interfacial debonding: Towards an accelerated laboratory test
724 method', *Construction and Building Materials*, Vol. 175, pp. 225-238.
- 725 [14] Valluzzi, M.R., Modena, C., de Felice, G. (2014) 'Current practice and open issues in strengthening
726 historical buildings with composites', *Materials and Structures*, Vol. 47, pp. 1971-1985.
- 727 [15] Tinazzi, D., Modena, C., Nanni, A. (2000) 'Strengthening of masonry assemblages with FRP rods and
728 laminates', *International Meeting on Composite Materials, PLAST 2000, Proceedings, Advancing with
729 Composites 2000*, pp. 411-418.
- 730 [16] Valluzzi, M. R., Binda, L., Modena, C. (2005) 'Mechanical behaviour of historic masonry structures
731 strengthened by bed joints structural repointing', *Construction and Building Materials*, Vol. 19, pp.63-
732 73.
- 733 [17] Turco, V., Secondin, S., Morbin, A., Valluzzi, M.R., Modena, C. (2006) 'Flexural and shear strengthening
734 of un-reinforced masonry with FRP Bars', *Composites Science and Technology*, Vol. 66, pp.289-296.
- 735 [18] Casacci, S., Di Tommaso, A., Gentilini, C. (2015) 'Crack propagation in compression and mounted
736 arrestors', *Key Engineering Materials*, Vol. 624, pp. 595-602.
- 737 [19] Borri, A., Castori, G., Corradi, M., Speranzini, E. (2011) 'Shear behavior of unreinforced and reinforced
738 masonry panels subjected to in situ diagonal compression tests', *Construction and Building Materials*,
739 Vol. 25, pp. 4403-4414.
- 740 [20] Akhaveissy, A.H., Milani, G. (2013) 'A numerical model for the analysis of masonry walls in-plane loaded
741 and strengthened with steel bars', *International Journal of Mechanical Sciences*, Vol. 72, pp.13-27.
- 742 [21] Casacci, S., di Tommaso, A., Gentilini, C. (2016) 'Experimental investigation on pre-cracked masonry

- 743 specimens repaired by bed joints structural repointing', *Brick and Block Masonry: Trends, Innovations*
744 *and Challenges - Proceedings of the 16th International Brick and Block Masonry Conference, IBMAC,*
745 pp. 2047-2054.
- 746 [22] De Lorenzis, L., Teng, J.G. (2007) 'Near-surface mounted FRP reinforcement: An emerging technique for
747 strengthening structures', *Composites Part B: Engineering*, Vol. 38, pp. 119-143.
- 748 [23] Almeida, J.A.P.P., Pereira, E.B., Barros, J.A.O. (2015) 'Assessment of overlay masonry strengthening
749 system under in-plane monotonic and cyclic loading using the diagonal tensile test', *Construction and*
750 *Building Materials*, Vol. 94, pp. 851-865.
- 751 [24] Incerti, A., Tilocca, A.R., Ferretti, F., Mazzotti, C. (2019) 'Influence of Masonry Texture on the Shear
752 Strength of FRCM Reinforced Panels', RILEM Bookseries, Vol. 18, pp. 1623-1631.
- 753 [25] Benedetti, A. (2019) 'Diagonal Compression Behaviour of Masonry Walls Reinforced with FRM
754 Coatings', in: Aguilar R., Torrealva D., Moreira S., Pando M.A., Ramos L.F. (eds) *Structural Analysis*
755 *of Historical Constructions*. RILEM Bookseries, Vol 18. Springer, Cham.
- 756 [26] Giaretton, M., Dizhur, D., Garbin, E., Ingham, J.M., Da Porto, F. (2018) 'In-Plane Strengthening of Clay
757 Brick and Block Masonry Walls Using Textile-Reinforced Mortar', *Journal of Composites for*
758 *Construction*, Vol. 22, art. no. 04018028.
- 759 [27] Menna, C., Asprone, D., Durante, M., Zinno, A., Balsamo, A., Prota, A. (2015) 'Structural behaviour of
760 masonry panels strengthened with an innovative hemp fibre composite grid', *Construction and*
761 *Building materials*, Vol. 1, pp. 111 – 121.
- 762 [28] De Carvalho Bello, C.B., Cecchi, A., Meroi, E., Oliveira, D.V. (2017) 'Experimental and numerical
763 investigations on the behaviour of masonry walls reinforced with an innovative sisal FRCM system'
764 *Key Engineering Materials*, Vol. 747, pp. 190-195.
- 765 [29] Li, T., N., Tumialan, J.G., Nanni, A. (2005) 'Analysis of unreinforced masonry concrete walls strengthened
766 with glass fiber-reinforced polymer bars', *ACI Structural Journal*, Vol. 102, pp.569-577.
- 767 [30] ACI 549 (2013). Design and construction guide of externally bonded FRCM system for concrete and
768 masonry repair and strengthening.
- 769 [31] Babaeidarabad, S., De Caso, F., Nanni, A. (2013) 'URM walls strengthened with fabric-reinforced
770 cementitious matrix composite subjected to diagonal compression', *Journal of Composites for*
771 *Constructions*, Vol. 18:04013045.
- 772 [32] Babaeidarabad, S., Arboleda, D., Loreto, G., Nanni, A. (2014) 'Shear strengthening of un-reinforced
773 concrete masonry walls with fabric-reinforced-cementitious-matrix', *Construction and Building*
774 *Materials*, Vol. 65, pp.243-253.
- 775 [33] Yu, P., Silva, P., Nanni, A. (2017) 'In-plane Performance of unreinforced concrete masonry strengthened
776 with prestressed GFRP bars', *Journal of Composites for Construction*, Vol. 21 (1), art. no. 04016064.
- 777 [34] Dizhur, D., Griffith, M., Ingham, J. (2013) 'In-plane shear improvement of unreinforced masonry wall
778 panels using NSM CFRP strips', *Journal of Composites for Construction*, Vol. 17, art. no. 04013010.
- 779 [35] Ismail, N., Petersen, R.B., Masia, M.J., Ingham, J.M. (2011) 'Diagonal shear behaviour of unreinforced

- 780 masonry wallettes strengthened using twisted steel bars', *Construction and Building Materials*, Vol.
781 25, pp. 4386-4393.
- 782 [36] Mahmood, H., Ingham, J. M. (2011) 'Diagonal compression testing of FRP-retrofitted unreinforced clay
783 brick masonry wallettes', *Journal of Composites for Construction*, Vol. 15, pp. 810-820.
- 784 [37] Tumialan, J.G., Morbin, A., Nanni, A., Modena, C. (2001) 'Shear strengthening of masonry walls with FRP
785 composites', *COMPOSITES 2001 Convention and Trade Show, Composites Fabricators Association*,
786 Tampa (FL), October 3-6, 2001, 6 pp., CD-ROM.
- 787 [38] Turco, V., Secondin, S., Morbin, A., Valluzzi, M.R., Modena, C. (2006) 'Flexural and shear strengthening
788 of un-reinforced masonry with FRP bars', *Composites Science and Technology*, Vol. 66, pp. 289-296.
- 789 [39] EN 772-1 (2011). Methods of test for masonry units – Part 1: Determination of compressive strength.
- 790 [40] EN 998-2 (2016). Specification for mortar for masonry - Part 2: Masonry mortar.
- 791 [41] Technical sheet (2018). [https://www.mapei.com/it/it/prodotti-e-soluzioni/prodotti/dettaglio/mape-antique-
792 mc](https://www.mapei.com/it/it/prodotti-e-soluzioni/prodotti/dettaglio/mape-antique-
792 mc)
- 793 [42] EN 1015-11 (1999). Methods of test for mortar for masonry. Determination of flexural and compressive
794 strength of hardened mortar.
- 795 [43] Technical sheet (2018). <http://www.mapei.com/public/COM/products/1071-planitophdmrestauro-gb.pdf>.
- 796 [44] Dalalbashi, A., Ghiassi, B., Oliveira, D.V., Freitas, A. (2018) 'Fiber-to-mortar bond behavior in TRM
797 composites: Effect of embedded length and fiber configuration', *Composites Part B: Engineering*, Vol.
798 152, pp. 43-57.
- 799 [45] ASTM C109 (2005). Standard test method for compressive strength of hydraulic cement mortars.
- 800 [46] ASTM D7205 (2016). Standard test method for tensile properties of fiber reinforced polymer matrix
801 composite bars.
- 802 [47] Technical sheet (2018). [https://www.mapei.com/it/en/products-and-solutions/products/detail/mapegrid-g-
803 220](https://www.mapei.com/it/en/products-and-solutions/products/detail/mapegrid-g-
803 220)
- 804 [48] Leone, M., Aiello, M.A., Balsamo, A., Carozzi, F.G., Ceroni, F., Corradi, M., Gams, M., Garbin, E.,
805 Gattesco, N., Krajewski, P., Mazzotti, C., Oliveira, D., Papanicolaou, C., Ranocchiali, G., Roscini, F.,
806 Saenger, D. (2017) 'Glass fabric reinforced cementitious matrix: Tensile properties and bond
807 performance on masonry substrate', *Composites Part B: Engineering*, Vol. 127, pp. 196-214.
- 808 [49] Brameshuber, W., et al. (2016) 'Recommendation of RILEM TC 232-TDT: test methods and design of
809 textile reinforced concrete: Uniaxial tensile test: test method to determine the load bearing behavior of
810 tensile specimens made of textile reinforced concrete', *Materials and Structures/Materiaux et
811 Constructions*, Vol. 49, pp. 4923-4927.
- 812 [50] Kalali, A., Kabir M. Z. (2012) 'Experimental response of double-wythe masonry panels strengthened with
813 glass fiber reinforced polymers subjected to diagonal compression tests', *Engineering Structures*, Vol.
814 39, pp.24-37.
- 815 [51] ASTM E519M (2015). Standard test method for diagonal tension (shear) in masonry assemblages.
- 816 [52] RILEM TC 76 – LUM (1991). Diagonal tensile strength tests of small wall specimens.

- 817 [53] Tomazevic, M. (1999). 'Earthquake-resistant design of masonry buildings', A. S. Elnashai & P. J. Dowling,
818 eds., Imperial College Press.
- 819 [54] EN 1052-3. Methods of test for masonry. Part 3: Determination of initial shear strength; 2007.
- 820 [55] EN 1996-1-1. Eurocode 6 – Design of Masonry Structures – Part 1-1: General rules for reinforced and
821 unreinforced masonry structures.
- 822 [56] D.M. 14 Gennaio 2008. Norme tecniche per le costruzioni (In Italian).
- 823 [57] Gentilini, C., D'Altri, A.M., Amato, M., Zanotti, P., Favaro, F., De Miranda, S. (2017) 'Salt attack effects
824 on the shear behavior of masonry: Preliminary results of an experimental campaign', *Key Engineering*
825 *Materials*, Vol. 747, pp. 512-517.
- 826 [58] Capozucca, R. (2011) 'Shear behaviour of historic masonry made of clay bricks', *Open Construction and*
827 *Building Technology Journal*, Vol. 5, pp. 89–96.
- 828 [59] Vasconcelos, G., Lourenço, P.B. (2009) 'Experimental characterization of stone masonry in shear and
829 compression', *Construction and Building Materials*, Vol. 23, pp. 3337-3345.
- 830
- 831