



ALMA MATER STUDIORUM  
UNIVERSITÀ DI BOLOGNA

## ARCHIVIO ISTITUZIONALE DELLA RICERCA

### Alma Mater Studiorum Università di Bologna Archivio istituzionale della ricerca

Photoinduced reversible switching of porosity in molecular crystals based on star-shaped azobenzene tetramers

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

*Published Version:*

*Availability:*

This version is available at: <https://hdl.handle.net/11585/520981> since: 2022-02-15

*Published:*

DOI: <http://doi.org/10.1038/nchem.2304>

*Terms of use:*

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).  
When citing, please refer to the published version.

(Article begins on next page)

This is the final peer-reviewed accepted manuscript of:

Photoinduced reversible switching of porosity in molecular crystals based on star-shaped azobenzene tetramers

Massimo Baroncini, Simone d'Agostino, Giacomo Bergamini, Paola Ceroni, Angiolina Comotti, Piero Sozzani, Irene Bassanetti, Fabrizia Grepioni, Taylor M. Hernandez, Serena Silvi, Margherita Venturi and Alberto Credi

Nature Chemistry, **2015**, 7, 634–640

The final published version is available online at: [DOI: 10.1038/NCHEM.230](https://doi.org/10.1038/NCHEM.230)

Rights / License:

The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

***When citing, please refer to the published version.***

# Photoinduced reversible switching of porosity in molecular crystals based on star-shaped azobenzene tetramers

Massimo Baroncini,<sup>1\*</sup> Simone d'Agostino,<sup>1</sup> Giacomo Bergamini,<sup>1</sup> Paola Ceroni,<sup>1</sup> Angiolina Comotti,<sup>2\*</sup> Piero Sozzani,<sup>2</sup> Irene Bassanetti,<sup>2</sup> Fabrizia Grepioni,<sup>1\*</sup> Taylor M. Hernandez,<sup>1</sup> Serena Silvi,<sup>1</sup> Margherita Venturi<sup>1</sup> and Alberto Credi<sup>1\*</sup>

<sup>1</sup> Dipartimento di Chimica "G. Ciamician", Università di Bologna, via F. Selmi 2, 40126 Bologna, Italy

<sup>2</sup> Dipartimento di Scienza dei Materiali, Università di Milano-Bicocca, via R. Cozzi 55, 20125 Milano, Italy

\* e-mail: massimo.baroncini@unibo.it, angiolina.comotti@mater.unimib.it, fabrizia.grepioni@unibo.it, alberto.credi@unibo.it.

**The development of solid materials that can be reversibly interconverted by light between forms with different physico-chemical properties is of high interest for separation, catalysis, optoelectronics, holography, mechanical actuation, and solar energy conversion. Here we describe a series of shape-persistent azobenzene tetramers that form porous molecular crystals in their *E*-configuration, whose porosity can be tuned by changing the peripheral substituents on the molecule. Efficient *E*→*Z* photoisomerization of the azobenzene units takes place in the solid state and converts the crystals into a non-porous amorphous melt phase. Crystallinity and porosity are restored upon *Z*→*E* isomerization promoted by visible light irradiation or heating. We demonstrate that the photoisomerization enables reversible on/off switching of optical properties, such as birefringence, and of the capture of carbon dioxide from the gas phase. The linear design, the structural versatility and the synthetic**

**accessibility make this new family of materials potentially interesting for technological applications.**

Photochromic compounds are highly appealing for science and technology because they enable the implementation of light-induced functions within molecular, supramolecular and macromolecular species, biological constructs and bulk materials<sup>1,2</sup>. Azobenzene is one of the most attractive photochromes because of its easy functionalization and its clean, fast and reversible photoisomerization between two isomers (*E* and *Z*) exhibiting some significantly different physico-chemical properties<sup>3</sup>. Current and prospective applications of research on azobenzene photoisomerization include holographic information storage<sup>4</sup>, optoelectronic devices<sup>5</sup>, magnetic memories,<sup>6</sup> nanomachines,<sup>7</sup> control of chemical reactivity<sup>8</sup>, responsive surfaces<sup>9</sup> and materials,<sup>10,11</sup> energy conversion<sup>12</sup>, and drug design<sup>13</sup>.

In view of these applications azobenzene photoisomerization in the solid state is attracting much interest, but the relatively large free volume change associated with this reaction<sup>14,15</sup> poses a considerable challenge to its practical realization<sup>16,17</sup>. The *E*→*Z* photoisomerization of azobenzene derivatives is well documented for azobenzene-containing polymers<sup>18</sup>, liquid crystals<sup>9,18–24</sup>, thin films<sup>25–27</sup> and crystals at the solid-liquid interface<sup>28</sup>, whilst a limited number of examples are reported in porous materials<sup>29–33</sup> (e.g. metal-organic and covalent organic frameworks) and in molecular crystalline forms in which the azobenzene moiety is functionalized with polar substituents<sup>34–36</sup>. Our strategy is based on the use of molecules containing a central node which imparts a star-like 3D arrangement to azobenzene moieties for the fabrication of molecular crystals endowed with permanent porosity capable of promoting the reversible *E/Z* isomerization in the solid state. Microporous molecular crystals<sup>37–40</sup> may show substantial advantages in terms of preparation, processability, structural diversification and functional flexibility in comparison with porous metal-organic<sup>41</sup> and covalent<sup>42</sup> frameworks. Moreover, the novel molecular crystals exhibit

extrinsic porosity (that is, porosity resulting solely from the solid-state molecular packing) which is uncommon and of challenging design<sup>37-40</sup>.

As an embodiment of these concepts we describe the preparation, structure, and reversible photoisomerization in the solid state of porous tetra(azobenzene)methane compounds, consisting of four azobenzene units covalently linked to a tetrahedral carbon atom. We envisaged that the extended branches of the *E*-azobenzene units and the rigid tetrahedral structure of the molecule could prevent a tightly packed arrangement<sup>43</sup>, resulting in a porous crystal structure in which the gained free volume, combined with the occurrence of weak van der Waals interactions, may allow photoswitching of the azobenzene units in the solid state.

## Results and discussion

### ***Synthesis and spectroscopic analysis in solution***

Compounds *E*<sub>4</sub>-**1a-c** (Fig. 1a) having the four azobenzene units in the *E* configuration, and hydrogen, methyl and *tert*-butyl peripheral substituents, respectively, were synthesized in 70% yield by Mills coupling of tetra(4-aminophenyl)methane with four equivalents of the appropriately *para*-substituted nitrosobenzene in acetic acid. The products were isolated from the reaction mixture by filtration and easily purified by recrystallization (Figs. S1-S6 in the ESI).

The absorption spectra of *E*<sub>4</sub>-**1a-c** in CH<sub>2</sub>Cl<sub>2</sub> (Figs. S14-S16) show the typical features of *E*-azobenzene and are consistent with the presence of four such units, although they do not exactly correspond to the sum of the respective individual spectra. For example, the  $\pi\pi^*$  band of *E*<sub>4</sub>-**1c** ( $\lambda_{\text{max}} = 345 \text{ nm}$ ) is red-shifted by  $750 \text{ cm}^{-1}$  in comparison with that of the 1,1'-dimethyl-*E*-azobenzene model *E*-**2**, suggesting that the four units are not fully independent from an electronic point of view, possibly because of homoconjugation effects. Irradiation of *E*<sub>4</sub>-**1c** at 365 nm causes the *E*→*Z* isomerization (Fig. 1b) with an initial quantum yield for azobenzene unit  $\Phi_{EZ} = 0.18$  (for

*E*-**2**,  $\Phi_{EZ} = 0.17$ ). The fact that isosbestic points in the absorption spectra are not precisely maintained and that the *E*→*Z* photoisomerization quantum yield decreases throughout the irradiation indicates that the four azobenzene units of **1c** exhibit similar but not identical photophysical and photochemical properties. Nevertheless, the *E*→*Z* conversion upon exhaustive irradiation at 365 nm in CH<sub>2</sub>Cl<sub>2</sub> amounts to >95%. <sup>1</sup>H NMR analysis of the photostationary state (PSS) obtained in C<sub>6</sub>D<sub>6</sub> under the same conditions shows that the composition is 89% *Z*<sub>4</sub>-**1c**, 6% *E*<sub>1</sub>*Z*<sub>3</sub>-**1c**, 3% *E*<sub>2</sub>*Z*<sub>2</sub>-**1c**, <1% *E*<sub>3</sub>*Z*<sub>1</sub>-**1c** and <1% starting material, corresponding to an overall *E*→*Z* conversion of 97%. For the sake of simplicity, hereafter we will refer to the PSS obtained upon 365-nm irradiation of *E*<sub>4</sub>-**1c** in CH<sub>2</sub>Cl<sub>2</sub> as *Z*<sub>4</sub>-**1c**. Compounds **1a,b** exhibit a similar behaviour, as reported in the ESI (Figs. S7-S11 and S14-S16).

### **Structure of the molecular crystalline solids**

Compounds *E*<sub>4</sub>-**1a–c** crystallize in the tetragonal system (see Table S2 and Figs. S21-S30). In all solids the tetrahedral node lies on a -4 crystallographic axis, and the four azobenzene units are all mutually related by symmetry. The main structural motif observed in crystalline *E*<sub>4</sub>-**1a–c** is the interlocking of adjacent molecules along the four-fold rotoinversion axes, which run parallel to the crystallographic *c*-axis direction (Fig. 2b). This corresponds to the direction of maximum crystal growth, and is apparent both in the ideal and experimental morphology of the crystals obtained from solution or constituting the deposited thin films (Fig. S32). The “open” molecular geometry determined by the four tetrahedrally arranged *E*-azobenzene units (Fig. 2a) combined with the presence of the bulky substituents, especially *tert*-butyl groups in *E*<sub>4</sub>-**1c**, makes it particularly difficult to achieve an efficient space occupation in the solid state, as evidenced by a packing coefficient value of 0.59.

The molecular piles are placed side-by-side in the crystal, with shape taking control of the self-assembly. The resulting crystal packing (Fig. 2c) is characterized in *E*<sub>4</sub>-**1c** by the presence of empty

channels along the *c*-axis direction, with a 10.4 % porosity (calculated as the ratio between the accessible volume by a 1.2 Å probe and the cell volume). A channel-like porosity is also observed, though less pronounced, in *E*<sub>4</sub>-**1b** (8.1%), while for *E*<sub>4</sub>-**1a** the porosity (6.7%) is confined to discrete, non-communicating regions along the pile (Fig. S25). In the case of *E*<sub>4</sub>-**1c**, the shape of the channels responsible for crystal porosity shows the periodic presence of necks (Fig. 2d); this feature is unique to *E*<sub>4</sub>-**1c**. A closer inspection of the structure reveals that the necks along the channels arise from the terminal *tert*-butyl substituents, while the largest sections of the channels are delimited by benzene moieties (Fig. S33). <sup>13</sup>C Magic-angle spinning (MAS) NMR spectra of *E*<sub>4</sub>-**1b** and *E*<sub>4</sub>-**1c** show respectively 10 and 11 resonances, in accordance with the highly symmetric arrangement of the molecule in the crystal structure (Figs. S12-S13). No solvent molecules are observed in the spectra, as independently confirmed by thermogravimetric analysis (Fig. S31).

### ***Solid-state photoreactivity and photoinduced phase transitions***

To investigate the photoreactivity in the solid state, powders of *E*<sub>4</sub>-**1a–c** were subjected to 365-nm irradiation for 6 h in an NMR tube. <sup>1</sup>H NMR spectroscopic analysis performed on the irradiated solid dissolved in C<sub>6</sub>D<sub>6</sub> showed indeed the presence of *Z*-azobenzene units (Fig. S11). Quantitative information on the photoisomerization reaction was obtained from irradiation experiments carried out on dry films of **1a–c** deposited on a quartz slide by spin coating or drop casting from a solution. The X-ray powder diffraction (XRPD) pattern measured on drop casted films of *E*<sub>4</sub>-**1a–c** is superimposable to the pattern calculated on the basis of single crystal data (Fig. 3a and S26-S29), thus indicating that the layer contains crystalline particles. In the following we will describe in detail the properties of **1c**, as compounds **1a,b** exhibit a very similar behaviour (Table S1, Figs. S19-S20 and S34-S35).

The quality and homogeneity of the spin coated thin films enabled characterization by transmission UV-visible absorption spectroscopy. The absorption spectra of *E*<sub>4</sub>-**1c** (Fig. 3c) and *Z*<sub>4</sub>-**1c** (Fig. 3d) in

the solid film are similar to those recorded in solution, and show the typical  $\pi\pi^*$  (ca. 350 nm) and  $n\pi^*$  (ca. 450 nm) bands of azobenzene.

Irradiation of the  $E_4$ -**1c** film at 365 nm brings about spectral changes (Fig. 3c) almost identical to those found in solution, indicating an efficient  $E \rightarrow Z$  isomerization. From a comparison of the spectra it can be estimated that at the photostationary state about 32% of the azobenzene unit of **1c** are converted to the  $Z$  configuration. Conversely, no effect is detected when the same experiment is performed on a film of  $E$ -**2**, indicating that the rigid tetrahedral arrangement of the azobenzene moieties is crucial for their photoisomerization in the solid. Exposure of the irradiated sample, or a film of previously prepared  $Z_4$ -**1c**, to light of 436 nm causes  $Z \rightarrow E$  photoisomerization and a photostationary state enriched in  $E$ -azobenzene units is obtained (Fig. 3d). The absorption spectrum recorded before any irradiation is fully restored by heating the film at 130 °C for 10 min (Fig. 3cd), indicating that (i) thermal  $Z \rightarrow E$  isomerization occurs, (ii)  $E_4$ -**1c** is the thermodynamically stable form of **1c** in the solid state, and (iii) the photoreaction is a clean process (Fig. 3b).

The XRPD pattern obtained after 48 h irradiation of the film still corresponds to the pattern of  $E_4$ -**1c**, while the intensity of all peaks decreases and disappear after prolonged irradiation, indicating that the material has become amorphous (Fig. 3a). Notably, the XRPD signals of the  $E_4$ -**1c** crystals are recovered upon heating the irradiated film, showing that the phase change is reversible (Fig 3a) and correlated to the  $E/Z$  interconversion. To gain more insight into the effect of light on solid  $E_4$ -**1c** we imaged the crystals with a polarizing optical microscope. The crystals of  $E_4$ -**1c** exhibit a significant optical birefringence under cross-polarized light illumination (Fig. 4ab), confirming an ordered arrangement of the molecules in the solid that gives rise to anisotropic crystals. It is important to note that the high yield of  $E \rightarrow Z$  photoconversion for crystals of this size (roughly 1  $\mu\text{m}$ ) implies that the photoisomerization of  $E_4$ -**1c** upon irradiation in the 350-360 nm region is not limited to surface layers. Efficient bulk photoisomerization of azobenzene solid crystals is made possible, besides the high inherent photoreactivity of the material, because the  $E \rightarrow Z$  conversion



causes a decrease in the optical density at the irradiation wavelength (Fig. 3c), thus enabling photons to reach the core of the crystals. To our best knowledge, substantial  $E \rightarrow Z$  photoisomerization of azobenzene-containing crystals was described only in two latest reports on azobenzene cyclophanes bearing long alkyl substituents<sup>23,24</sup>.

Upon near-UV irradiation of the crystals on the microscope slide, both the crystal morphology (Fig. 4c) and the optical birefringence (Fig. 4d) disappear. Indeed, the crystals appear to be melt and the material assumes the consistency of a viscous liquid (Fig. S36). It is likely that the mixture of  $E$ - and  $Z$ -isomers leads to the formation of an eutectic<sup>16,24,44</sup>; consequently, the photogenerated material is amorphous in agreement with XRPD data. Again, control experiments performed on  $E$ -**2** crystals do not show light-induced effects. Birefringent crystals are formed upon annealing of the irradiated sample at 160 °C for 20 min as a consequence of  $Z \rightarrow E$  thermal isomerization (Fig. 4ef). The formation of larger crystals in comparison with starting ones is consistent with crystallization from a melt phase under slow cooling. These findings also rule out the possibility that the transformation observed under UV irradiation is caused by local thermal effects and confirms that the observed phenomenon is in fact an isothermal photoinduced crystal-amorphous phase transformation taking place at ambient temperature<sup>19,23,24,45</sup>. The photoinduced amorphisation and thermal recrystallization can be repeated on the same sample without degradation of the material (Figs. 3d, S18, S34, S38).

A detailed examination of the effect of light on the  $E_4$ -**1c** crystals reveals an even more interesting behavior, not observed for previously investigated azobenzene-containing crystals<sup>23,24,45</sup>: exposure to UV light for a short time causes no significant change in morphology but affords a dramatic decrease of the birefringence, which is fully restored by heating (Fig. S38). In other words, the loss of optical anisotropy does not require complete amorphisation of the material. Such an observation supports the view, suggested by the XRPD and optical absorption results discussed above, that crystallinity is substantially maintained upon partial  $E \rightarrow Z$  isomerization of  $E_4$ -**1c**. We hypothesize

that  $E \rightarrow Z$  isomerization in a relatively small population of **1c**, such as that afforded in the initial stages of the irradiation, increases the lattice disorder throughout the entire sample to an extent sufficient to disrupt long-range structural anisotropy, thus causing the loss of optical birefringence<sup>46</sup>. The solid, however, remains mostly ordered and the crystal structure and morphology are not affected, as confirmed by the complete regeneration of the film upon thermal annealing (Fig. S38).

Such a behavior is interesting for optical information storage because the thin film behaves as a one-input ternary switch under threshold control. Irradiation with a light dose below the threshold converts state “0”, crystalline and birefringent (Figs. 4a,b and S38a,b), to state “1” which is still crystalline but no longer birefringent (Fig. S38c,d). Continued irradiation (that is, exposure to a dose of photons above the threshold) places the film into state “2” characterized by an amorphous structure (Fig. 4c,d). Clean and reversible switching among the three states can be performed by appropriate light and heat stimulation.

### ***Gas adsorption experiments***

The microporosity of the molecular crystals was demonstrated by gas adsorption measurements (see Figs. S39-S41). While  $E_4$ -**1a** exhibits negligible gas uptake properties, the CO<sub>2</sub> isotherm of  $E_4$ -**1c** at 195 K shows a Langmuir type-I profile which reaches the value of 52 cm<sup>3</sup>(STP)/g at 1 bar, highlighting the open and accessible free-volume in the compound (Fig. 5a). The maximum CO<sub>2</sub> uptake corresponds to the occupancy of four molecules per unit cell (i.e. 2 molecules per cavity) and is consistent with the empty space as estimated from the crystallographic structure, suggesting a complete filling of the cavities by gas diffusion in the permeable crystal. Similarly, the maximum CO<sub>2</sub> sorption of  $E_4$ -**1b** compound results in a full loading of the available space (Fig. 5a, inset). In sharp contrast, the CO<sub>2</sub> adsorption isotherms of  $Z_4$ -**1b** and  $Z_4$ -**1c** samples obtained by precipitation from UV-irradiated solutions exhibit a negligible CO<sub>2</sub> uptake, demonstrating that the all-Z isomers

are not porous. However, upon heating, the samples are converted back to the porous forms, as shown in the inset of Fig. 5a. Therefore, a reversible switching between the porous and non porous forms was realized<sup>47</sup>, taking advantage of photoirradiation and thermal relaxation of the *E*- and *Z*-azobenzene moieties.

It is worth noting that very few cases of molecular solids in which porosity can be switched on and off reversibly have been reported<sup>48,49</sup>. Such materials consist of cage or bowl-shaped molecules (that is, they exhibit intrinsic porosity)<sup>37-40</sup> and their switching mechanism is based on solvation-desolvation effects, making them highly interesting under a structural viewpoint but less appealing for practical applications.

The porosity of the molecular crystals was further checked by CO<sub>2</sub> and N<sub>2</sub> adsorption measurements under mild conditions of temperature and up to 10 bar. The maximum CO<sub>2</sub> uptake values of 41 cm<sup>3</sup>/g and 32 cm<sup>3</sup>/g were found for the *E*<sub>4</sub>-**1c** species at 10 bar and temperatures of 273 and 298 K, respectively (Fig. 5b). The pore size of about 7 Å guarantees an excellent interaction with the gas molecules: in fact, the compound exhibits isosteric heat of adsorption ( $Q_{st}$ ) equal to 28 kJ/mol, indicating the occurrence of favourable interactions of CO<sub>2</sub> with the aromatic groups exposed to the inner surface of the crystalline channels. Instead, N<sub>2</sub> adsorption experiments collected at 273 and 298 K for both *E*<sub>4</sub>-**1b** and *E*<sub>4</sub>-**1c** showed very limited uptake values even at high pressures, indicating a low affinity of the absorbent for nitrogen (Figs. 5b and S39). This observation can be exploited for the selective capture of carbon dioxide in a mixture with nitrogen: in fact, IAST calculations indicated a CO<sub>2</sub>/N<sub>2</sub> selectivity as high as 80 for the *E*<sub>4</sub>-**1b** compound. It is worth noting that this value exceeds the performances of most molecular crystals endowed with permanent porosity<sup>50</sup>. Collectively, the gas adsorption data support the view that *E*<sub>4</sub>-**1a-c** molecules pack inefficiently with one another because of their rigid star-like shape and the presence of bulky groups at the periphery. These features generate a large free-volume in the crystal which enables the *E*→*Z* photoconversion in the solid state.

## Conclusions

A series of compounds based on a tetra(azobenzene)methane-type moiety with diversified end groups (H, Me or *t*-Bu) has been developed. The star-like shape and rigidity of the molecules prevent a close-packed arrangement in the crystals and promote low density molecular self-assembly, affording porous molecular crystals in which azobenzene *E*→*Z* photoisomerization occurs in the solid state. The porosity of the crystals increases on increasing the size of the terminal substituents introduced in the four azobenzene units. The porous crystals of *E*<sub>4</sub>-**1b,c** adsorb CO<sub>2</sub> from the gas phase selectively with respect to N<sub>2</sub>, whereas the corresponding *Z*-isomers, obtained by light irradiation at room temperature, are not porous; crystallinity and porosity are restored upon *Z*→*E* isomerization promoted by visible light irradiation or heating. These compounds – in particular **1b,c** – possess a number of valuable features, including synthetic accessibility, solution processability, high photoreactivity and tunability of the physico-chemical properties. Such properties are key requirements for materials apt for technological applications as photoswitchable catalysts and membranes, solid-state photonic switches, substrates for holography and photolithography, and photoresponsive adhesives.

The present study contributes to the design of novel microporous molecular solids in which photoreactive groups can be converted by light to high-energy molecular configurations, as the crystal porosity provides the space required for the photoinduced structural changes. It also paves the way for a better understanding of solid-state photochemical reactions and photoinduced phase transitions. The unique combination of porosity and photoactive moieties opens up intriguing perspectives in the field of responsive materials involving light irradiation, molecular movements and chemical stimuli.

## Acknowledgments

This work was supported by MIUR (PRIN 2010CX2TLM “InfoChem” and FIRB 2010RBAP11C58Y “Nanosolar”), MAECI (DGSP n. 0075740), Fondazione Cariplo 2012-0921, and the University of Bologna. M. B. thanks R. Zamboni (ISOF-CNR Bologna) for support.

### **Authors contributions**

M. B., A. C. and An. C. conceived the project. M. B. and T. M. H. synthesized and characterized the compounds; S. d’A. and F. G. performed crystal growth experiments and X-ray diffraction studies; S. S. and M. B. carried out the spectroscopic, photochemical and microscopy experiments; I. B., An. C. and P. S. performed gas adsorption experiments, solid-state NMR spectra, and preparation and characterization of the polymorphs; G. B., P. C., M. V. and all other authors analyzed the data; A. C. wrote the paper.

### **Additional information**

Supplementary information is available in the online version of the paper. Reprints and permissions information is available online at [www.nature.com/reprints](http://www.nature.com/reprints). Correspondence and request for materials should be addressed to A.C.

### **Competing financial interests**

The authors declare no competing financial interests.

### **References**


1. Kobatake, S., Takami, S., Muto, H., Ishikawa, T. & Irie, M. Rapid and reversible shape changes of molecular crystals on photoirradiation. *Nature* **446**, 778–781 (2007).
2. Szymanski, W., Beierle, J. M., Kistemaker, H. A. V, Velema, W. A. & Feringa, B. L. Reversible photocontrol of biological systems by the incorporation of molecular photoswitches. *Chem. Rev.* **113**, 6114–6178 (2013).

3. Bandara, H. M. D. & Burdette, S. C. Photoisomerization in different classes of azobenzene. *Chem. Soc. Rev.* **41**, 1809–1825 (2012).
4. Bruder, F.-K., Hagen, R., Rölle, T., Weiser, M.-S. & Fäcke, T. From the surface to volume: concepts for the next generation of optical-holographic data-storage materials. *Angew. Chem. Int. Ed.* **50**, 4552–4573 (2011).
5. Raimondo, C. *et al.* Optically switchable organic field-effect transistors based on photoresponsive gold nanoparticles blended with poly(3-hexylthiophene). *Proc. Natl. Acad. Sci. U. S. A.* **109**, 12375–12380 (2012).
6. Venkataramani, S. *et al.* Magnetic bistability of molecules in homogeneous solution at room temperature. *Science* **331**, 445–448 (2011).
7. Ragazzon, G., Baroncini, M., Silvi, S., Venturi, M. & Credi, A. Light-powered autonomous and directional molecular motion based on a dissipative self-assembling system. *Nat. Nanotechnol.* **10**, 70–75 (2015).
8. Stoll, R. S. & Hecht, S. Artificial light-gated catalyst systems. *Angew. Chem. Int. Ed.* **49**, 5054–5075 (2010).
9. Kausar, A., Nagano, H., Ogata, T., Nonaka, T. & Kurihara, S. Photocontrolled translational motion of a microscale solid object on azobenzene-doped liquid-crystalline films. *Angew. Chem. Int. Ed.* **48**, 2144–2147 (2009).
10. Yanai, N. *et al.* Guest-to-host transmission of structural changes for stimuli-responsive adsorption property. *J. Am. Chem. Soc.* **134**, 4501–4504 (2012).
11. Brown, J. W. *et al.* Photophysical pore control in an azobenzene-containing metal–organic framework. *Chem. Sci.* **4**, 2858–2864 (2013).
12. Kucharski, T. J. *et al.* Templated assembly of photoswitches significantly increases the energy-storage capacity of solar thermal fuels. *Nat. Chem.* **6**, 441–447 (2014).
13. Velema, W. a *et al.* Optical control of antibacterial activity. *Nat. Chem.* **5**, 924–928 (2013).
14. Naito, T., Horie, K. & Mita, I. Photochemistry in polymer solids. 11. The effects of the size of reaction groups and the mode of photoisomerization on photochromic reactions in polycarbonate film. *Macromolecules* **24**, 2907–2911 (1991).
15. Evans, R. a *et al.* The generic enhancement of photochromic dye switching speeds in a rigid polymer matrix. *Nat. Mater.* **4**, 249–253 (2005).
16. Tsuda, M. & Kuratani, K. Isomerization of cis-azobenzene in the solid phase. *Bull. Chem. Soc. Jpn.* **37**, 1284–1288 (1964).
17. Bushuyev, O. S., Tomberg, A., Friščić, T. & Barrett, C. J. Shaping crystals with light: crystal-to-crystal isomerization and photomechanical effect in fluorinated azobenzenes. *J. Am. Chem. Soc.* **135**, 12556–12559 (2013).
18. Bléger, D., Yu, Z. & Hecht, S. Toward optomechanics: maximizing the photodeformation of individual molecules. *Chem. Commun.* **47**, 12260–12266 (2011).
19. Lee, S. *et al.* Stimulus-responsive azobenzene supramolecules: fibers, gels, and hollow spheres. *Langmuir* **29**, 5869–5877 (2013).
20. Yu, Y., Maeda, T., Mamiya, J.-I. & Ikeda, T. Photomechanical effects of ferroelectric liquid-crystalline elastomers containing azobenzene chromophores. *Angew. Chem. Int. Ed.* **46**, 881–883 (2007).
21. Norikane, Y., Hirai, Y. & Yoshida, M. Photoinduced isothermal phase transitions of liquid-crystalline macrocyclic azobenzenes. *Chem. Commun.* **47**, 1770–1772 (2011).


22. Akiyama, H. & Yoshida, M. Photochemically reversible liquefaction and solidification of single compounds based on a sugar alcohol scaffold with multi azo-arms. *Adv. Mater.* **24**, 2353–2356 (2012).
23. Uchida, E. *et al.* Control of the orientation and photoinduced phase transitions of macrocyclic azobenzene. *Chem. Eur. J.* **19**, 17391–17397 (2013).
24. Hoshino, M. *et al.* Crystal melting by light: X-ray crystal structure analysis of an azo crystal showing photoinduced crystal-melt transition. *J. Am. Chem. Soc.* **136**, 9158–9164 (2014).
25. Nakano, H., Seki, S. & Kageyama, H. Photoinduced vitrification near the surfaces of single crystals of azobenzene-based molecular materials with glass-forming ability. *Phys. Chem. Chem. Phys.* **12**, 7772–7774 (2010).
26. Yan, X., Wang, F., Zheng, B. & Huang, F. Stimuli-responsive supramolecular polymeric materials. *Chem. Soc. Rev.* **41**, 6042–6065 (2012).
27. Harada, A., Takashima, Y. & Nakahata, M. Supramolecular polymeric materials via cyclodextrin-guest interactions. *Acc. Chem. Res.* **47**, 2128–2140 (2014).
28. Ichimura, K. Reversible photoisomerisability and particle size changes of mill-dispersed azobenzene crystals in water. *Chem. Commun.* **45**, 1496–1498 (2009).
29. Brown, J. W. *et al.* Photophysical pore control in an azobenzene-containing metal–organic framework. *Chem. Sci.* **4**, 2858 (2013).
30. Patel, H. a *et al.* Unprecedented high-temperature CO<sub>2</sub> selectivity in N<sub>2</sub>-phobic nanoporous covalent organic polymers. *Nat. Commun.* **4**, 1357 (2013).
31. Lyndon, R. *et al.* Dynamic photo-switching in metal-organic frameworks as a route to low-energy carbon dioxide capture and release. *Angew. Chem. Int. Ed.* **52**, 3695–3698 (2013).
32. Park, J., Sun, L.-B., Chen, Y.-P., Perry, Z. & Zhou, H.-C. Azobenzene-functionalized metal-organic polyhedra for the optically responsive capture and release of guest molecules. *Angew. Chem. Int. Ed.* **53**, 5842–5846 (2014).
33. Patel, H. a *et al.* Directing the structural features of N<sub>2</sub>-phobic nanoporous covalent organic polymers for CO<sub>2</sub> capture and separation. *Chem. Eur. J.* **20**, 772–780 (2014).
34. Koshima, H., Ojima, N. & Uchimoto, H. Mechanical motion of azobenzene crystals upon photoirradiation. *J. Am. Chem. Soc.* **131**, 6890–6891 (2009).
35. Koshima, H. & Ojima, N. Photomechanical bending of 4-aminoazobenzene crystals. *Dyes Pigm.* **92**, 798–801 (2012).
36. Bushuyev, O. S., Singleton, T. a & Barrett, C. J. Fast, reversible, and general photomechanical motion in single crystals of various azo compounds using visible light. *Adv. Mater.* **25**, 1796–800 (2013).
37. Holst, J. R., Trewin, A. & Cooper, A. I. Porous organic molecules. *Nat. Chem.* **2**, 915–920 (2010).
38. McKeown, N. B. Nanoporous molecular crystals. *J. Mater. Chem.* **20**, 10588–10597 (2010).
39. Sozzani, P., Bracco, S., Comotti, A., Ferretti, L. & Simonutti, R. Methane and carbon dioxide storage in a porous van der Waals crystal. *Angew. Chem. Int. Ed.* **44**, 1816–1820 (2005).
40. Mastalerz, M. & Oppel, I. M. Rational construction of an extrinsic porous molecular crystal with an extraordinary high specific surface area. *Angew. Chem. Int. Ed.* **51**, 5252–5255 (2012).

41. Zhou, H.-C. & Kitagawa, S. Metal–Organic Frameworks (MOFs). *Chem. Soc. Rev.* **43**, 5415–5418 (2014).
42. Feng, X., Ding, X. & Jiang, D. Covalent organic frameworks. *Chem. Soc. Rev.* **41**, 6010–6022 (2012).
43. Aujard, I. *et al.* Tetrahedral onager crosses for solubility improvement and crystallization bypass. *J. Am. Chem. Soc.* **123**, 8177–8188 (2001).
44. Uyama, A. *et al.* Reversible photocontrol of surface wettability between hydrophilic and superhydrophobic surfaces on an asymmetric diarylethene solid surface. *Langmuir* **27**, 6395–6400 (2011).
45. Norikane, Y., Hirai, Y. & Yoshida, M. Photoinduced isothermal phase transitions of liquid-crystalline macrocyclic azobenzenes. *Chem. Commun.* **47**, 1770–1772 (2011).
46. Palmer, B. a *et al.* X-ray birefringence imaging. *Science* **344**, 1013–1016 (2014).
47. Luo, F. *et al.* Photoswitching CO<sub>2</sub> capture and release in a photochromic diarylethene metal-organic framework. *Angew. Chem. Int. Ed.* **53**, 9298–9301 (2014).
48. Thallapally, P. K., Dalgarno, S. J. & Atwood, J. L. Frustrated organic solids display unexpected gas sorption. *J. Am. Chem. Soc.* **128**, 15060–15061 (2006).
49. Jones, J. T. a *et al.* On-off porosity switching in a molecular organic solid. *Angew. Chem. Int. Ed.* **50**, 749–753 (2011).
50. Comotti, A. *et al.* Porous dipeptide crystals as selective CO<sub>2</sub> adsorbents: experimental isotherms vs. grand canonical Monte Carlo simulations and MAS NMR spectroscopy. *CrystEngComm* **15**, 1503–1507 (2013).




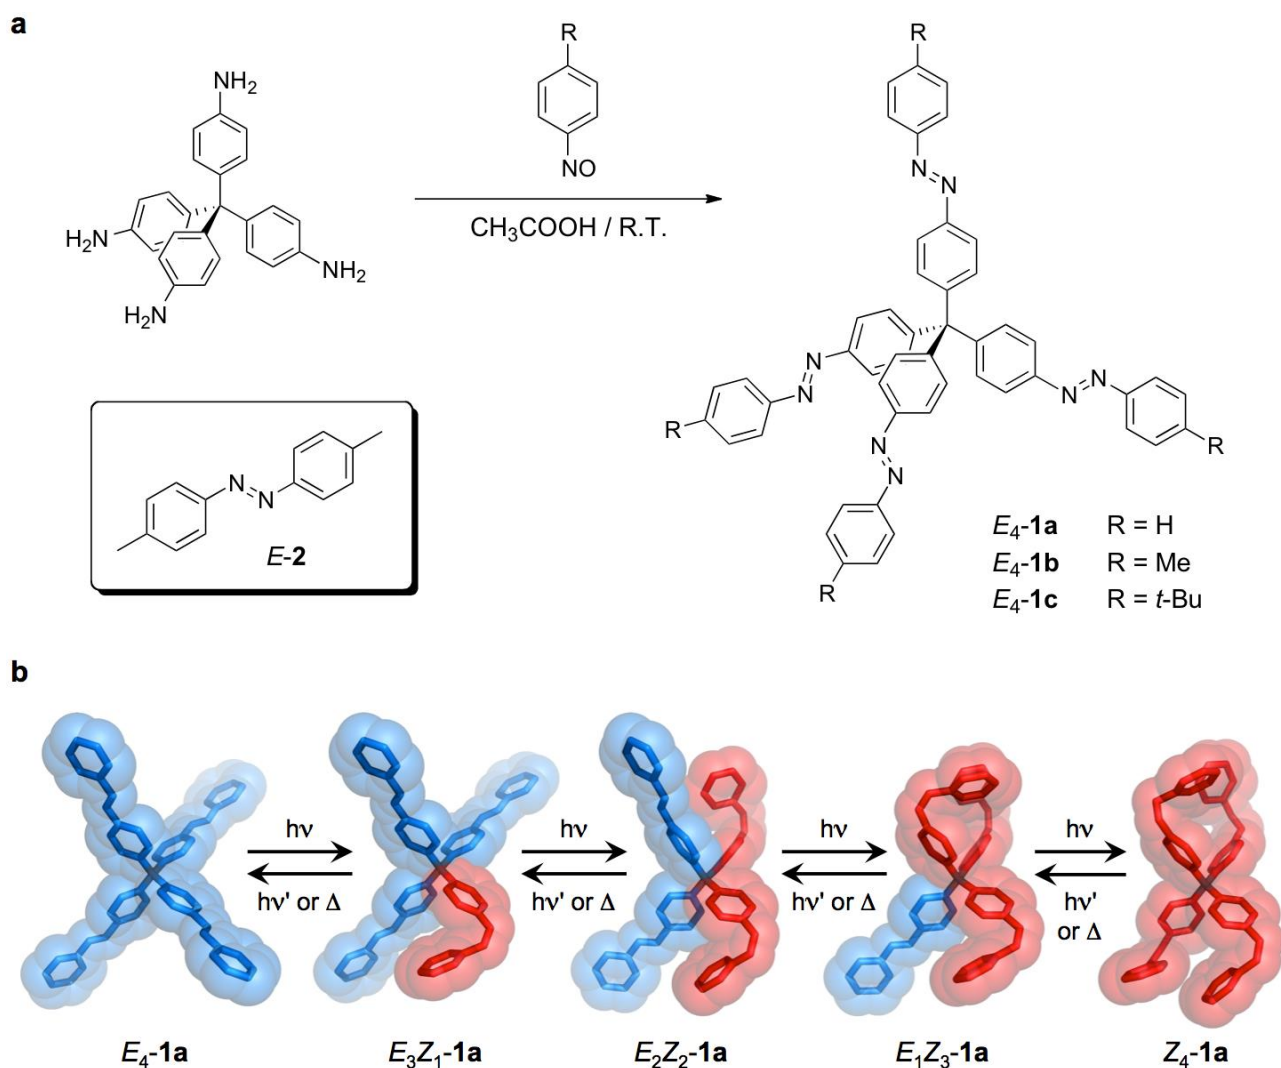


**Fig. 1 | Star-shaped azobenzene tetramers and their photochemical transformations.** (a) Synthetic route and molecular formula of  $E_4\text{-1a-c}$  and of model compound  $E\text{-2}$ . (b) MM3 Optimized molecular structure of the interconverting  $E/Z$  stereoisomers of  $\mathbf{1a}$ .  $E$ - and  $Z$ -azobenzene units are colored in blue and red, respectively, and hydrogen atoms are omitted for clarity. Compounds  $\mathbf{1b}$  and  $\mathbf{1c}$  exhibit a similar behaviour.

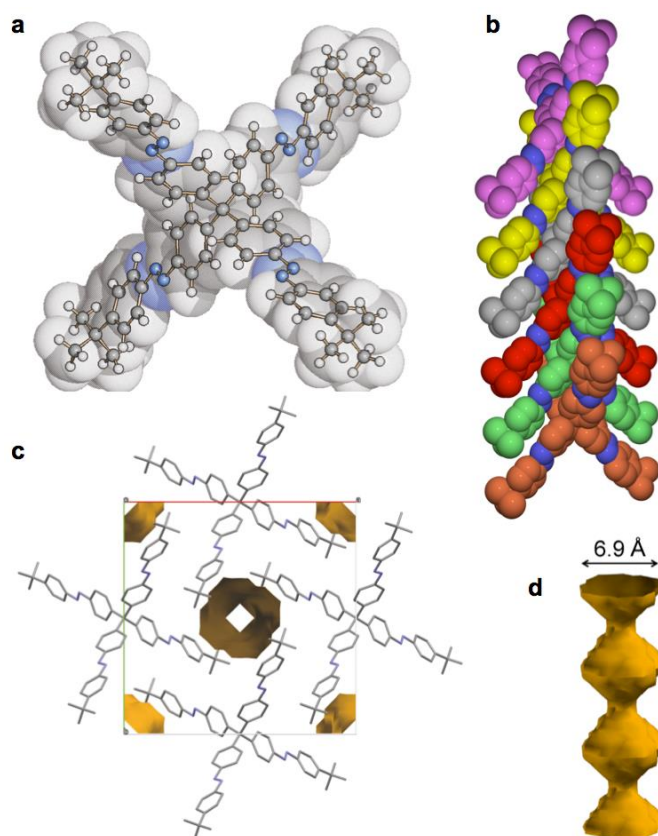


**Fig. 2 | Structural properties of  $E_4-1c$  in the crystalline state.** (a) Ball-and-stick and space filling representations of the molecular structure of  $E_4-1c$  as observed in its crystals (colour code: blue, nitrogen; black, carbon; white, hydrogen). The four azobenzene units are all equivalent by symmetry. (b) Space filling view of the interlocking of adjacent molecules along the  $c$ -axis direction. For the sake of clarity, hydrogen atoms are omitted, and carbon atoms in different molecules are displayed with different colours. (c) Relative arrangement of molecular piles in crystalline  $E_4-1c$  and representation of the empty channels extending along the  $c$ -axis direction. (d) Side view of a channel portion.

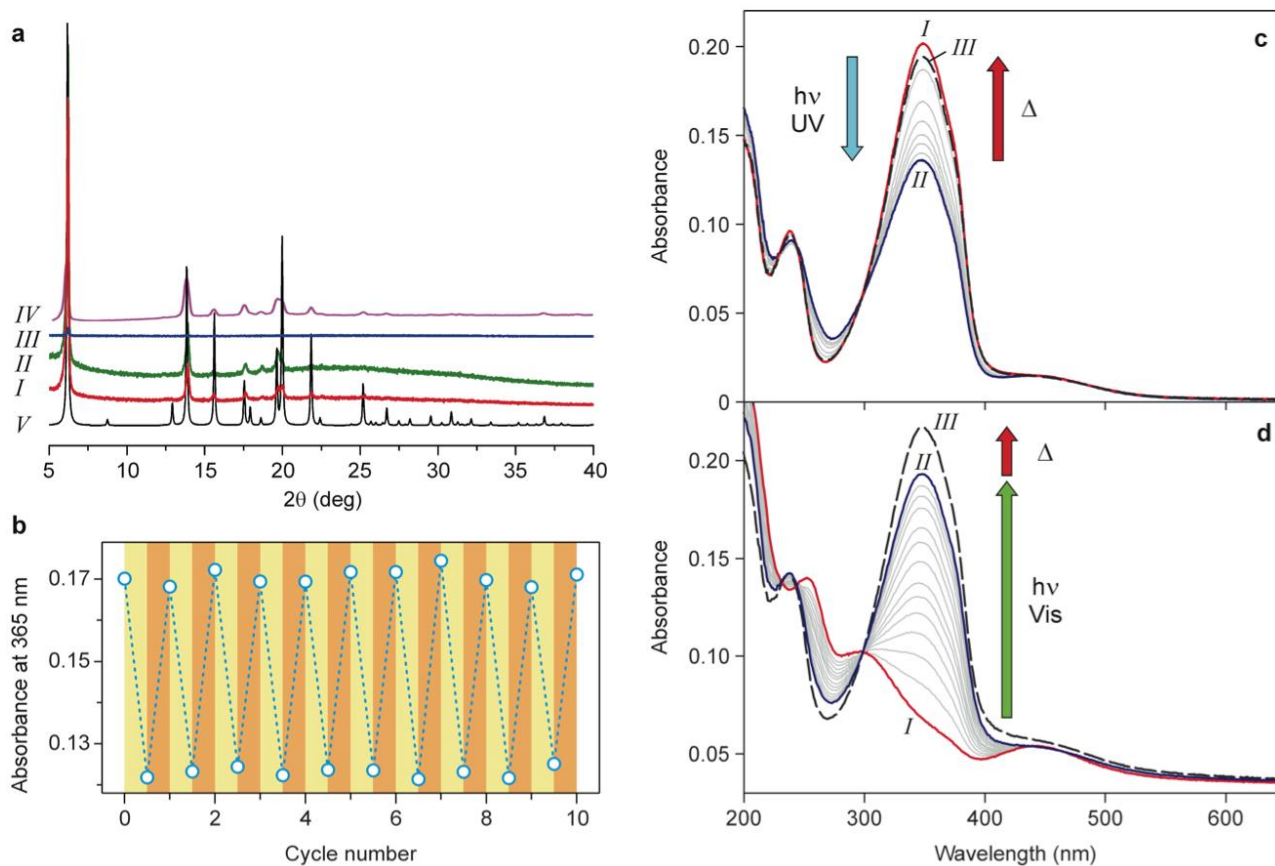

**Fig. 3 | Observation of the photoisomerization of **1c** in a thin solid film by XRPD and UV-vis absorption spectroscopy.** (a) XRPD patterns obtained before (*I*) and after 48 h (*II*) and 96 h (*III*) of irradiation of a drop casted film of *E*<sub>4</sub>-**1c** at 365 nm. Curve *III* shows that crystallinity is lost upon prolonged irradiation. Curve *IV* is the pattern obtained after annealing of the irradiated film at 130 °C for 10 min and indicates that crystallinity is regained upon heating. The pattern calculated on the basis of single crystal data (*V*) is also shown. (b) Absorbance changes measured at 365 nm of a spin coated thin film of *E*<sub>4</sub>-**1c** subjected to UV-irradiation and heating cycles. Light yellow areas: irradiation at 365 nm for 20 min; light orange areas: heating at 180° C for 20 min. The complete absorption spectra are reported in Fig. S18. (c) Absorption spectra of a spin coated thin film of *E*<sub>4</sub>-**1c** before (*I*) and after (*II*) irradiation at 365 nm for 6 min (photostationary state); spectra taken at intermediate times are shown in light grey. Curve *III* is the spectrum obtained after heating the film at 130 °C for 10 min. (d) Absorption spectrum of a *Z*<sub>4</sub>-**1c** thin film before (*I*) and after (*II*) irradiation at 436 nm for 34 min (photostationary state); spectra taken at intermediate times are shown in light grey. Curve *III* (dashed line) is the spectrum obtained after heating the film at 130 °C for 10 min.

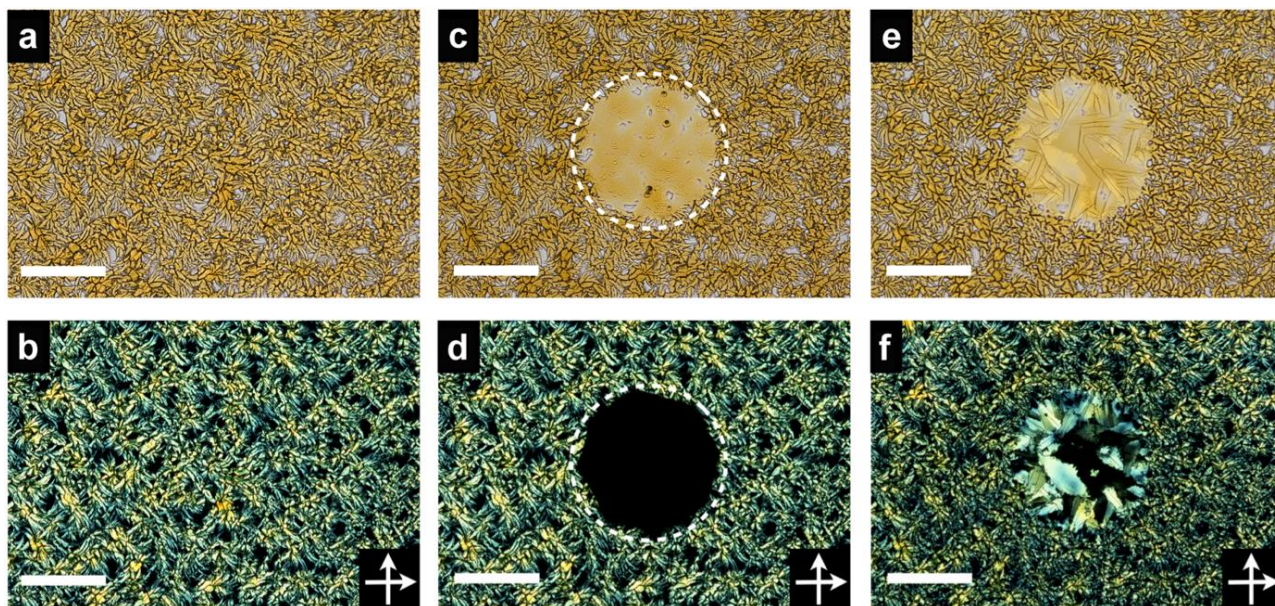

**Fig. 4 | Effect of photochemical and thermal stimulation on the 1c crystals.** Polarizing optical photomicrographs of solid  $E_4$ -1c under bright field (top) and cross-polarized (bottom) light illumination, before (a, b) and after (c, d) near-UV irradiation (330-380 nm) in a central spot (dashed line) for 10 min. (e, f). Recrystallization of the irradiated sample is observed upon thermal annealing at 160 °C for 20 min. Scale bar is 100  $\mu\text{m}$ . The white arrows in b, d and f represent the relative orientation of the polarizer and analyzer.

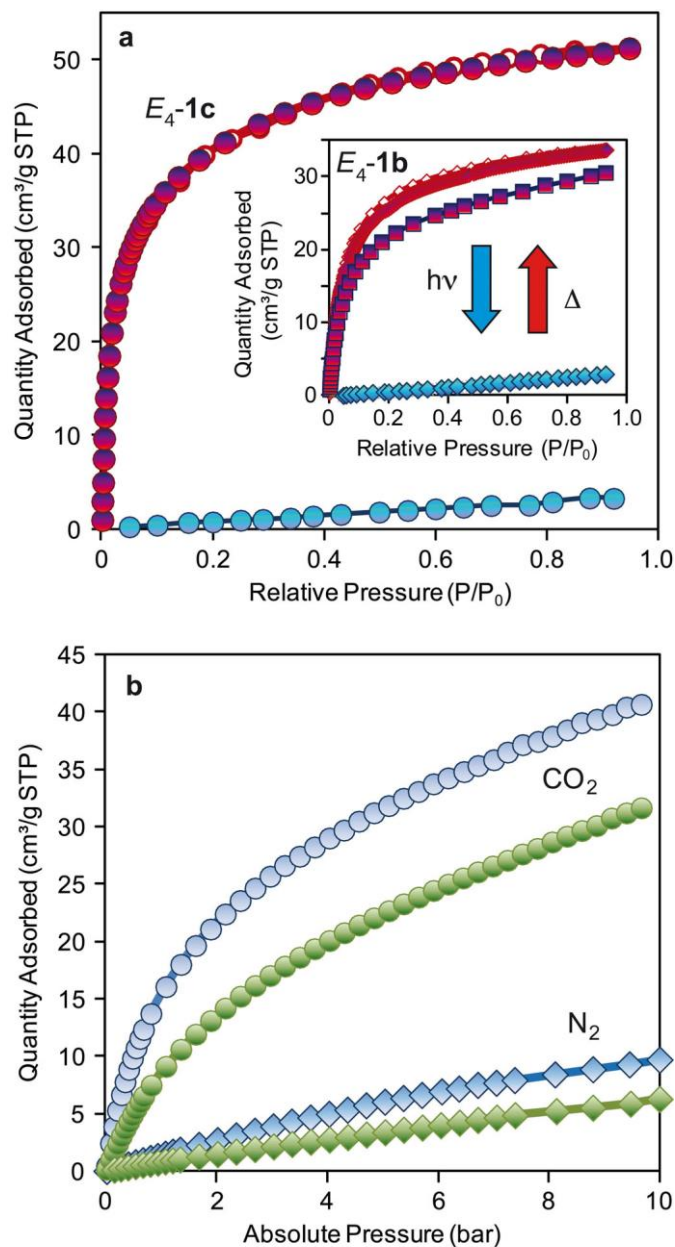

**Fig. 5 | Switching of gas adsorption properties and observation of CO<sub>2</sub>/N<sub>2</sub> selectivity.** (a) CO<sub>2</sub> adsorption isotherms of E<sub>4</sub>-1c (red circles) and Z<sub>4</sub>-1c (blue circles) at 195 K. The inset shows the CO<sub>2</sub> adsorption isotherms at 195 K of E<sub>4</sub>-1b (red diamonds), Z<sub>4</sub>-1b (blue diamonds), and the Z<sub>4</sub>-1b sample after heating at 160 °C for 2 hours (red squares). (b) CO<sub>2</sub> (circles) and N<sub>2</sub> (diamonds) adsorption isotherms of E<sub>4</sub>-1c at 298 K (green) and 273 K (blue).