

Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: P. Ratajczyk, S. Sobczak, M. Andrzejewski, F. Marin, M. Marchini, L. Maini and A. Katrusiak, *J. Mater. Chem. C*, 2025, DOI: 10.1039/D5TC00809C.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Pressure- and temperature-driven transitions and conformational conversions of n-hexyl substituted perylene diimide (PDI-C₆) crystalsReceived 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Paulina Ratajczyk,^a Szymon Sobczak,^a Michał Andrzejewski,^b Francesco Marin,^c Marianna Marchini,^c Lucia Maini,^{*c} Andrzej Katrusiak^{*a}

Perylene diimides (PDIs) are organic semiconductors with properties suitable for applications in electronic devices. This study presents a comprehensive investigation of PDI-C₆, a perylene diimide modified with an n-hexyl alkyl chain at the imide position, under non-ambient conditions, with a focus on the rich diagram of structurally varying phases and their anisotropic strain. Five distinct polymorphs of PDI-C₆ have been found. The ambient phase I transforms to phase II at 465 K, which at 521 K transforms to phase III. The perylene cores arranged in parallel stacks in phase I rotate in the scissor-opening motion by 33° in phase II. Under high pressure, phase I transforms to phase IV at 1.22 GPa and to phase V at 1.50 GPa. The transitions between phases I, IV and V stepwise modify the conformation of the n-hexyl substituents. Surprisingly, all five polymorphs are of space-group type $P\bar{1}$, which is unprecedented as the symmetry of phases usually involve the space-group changes. These findings significantly enhance our understanding of the structural transformations of the next-generation electronic materials and highlight the role of the crystal engineering in constructing novel organic semiconductors with high sensitivity to the environmental stimuli.

Introduction

Organic charge-transfer complexes and π -conjugated compounds are prospective materials for efficiently harvesting solar energy, proposed in response to the pressing demand for new environment-friendly sustainable energy sources. Presently, the mass production of silicon and hybrid-perovskite solar photovoltaic (SPV) panels poses significant drawbacks. Silicon panels are expensive and energy-demanding in production, their disposal is environment polluting and recycling difficult and expensive; the main problems connected to the presently innovative hybrid perovskites, such as [CH₃NH₃]PbI₃ (MAPbI₃), are their contents of metals, often poisonous and contaminating the environment both at the production and disposal stages, not to mention a relatively high susceptibility to humidity, temperature changes and stress. The mass production of Si-based panels threatens the environment and biosphere and more environment-friendly materials are intensely sought.^{1,2}

Organic materials are attractive due to their practically infinite ways of modifications and tuning properties,

production and disposal. π -Conjugated molecular materials have recently attracted a significant attention in the field of organic electronics due to their potential for practical applications, driven by the promising combination of superior charge carrier mobility and robust stability.³ Recent extensive research has focused on designing and synthesizing new materials, understanding their structures, properties and emerging opportunities for developing innovative devices.⁴ Compared to their inorganic counterparts, organic semiconductors offer not only high efficiency of the photoelectric conversion, but also new qualities, including high flexibility and light weight, making them attractive for the next-generation electronic devices,^{5,6} such as photovoltaic tapes and foils for highly flexible photovoltaic panels and tissues, apart from substituting the roof and other panels. The envisaged applications for the organic photovoltaics (OPVs) panels can be similar to those already witnessed for similar organic light-emitting diodes (OLEDs) and organic thin-film transistors (OTFTs).^{7–10}

Thermal expansion, compressibility and polymorphism are key issues for organic semiconductors, because different crystal forms of a compound vary in properties and they are additionally modified by the temperature and pressure-induced strain.^{11,12} Molecular engineering through chemical synthesis is a direct method to tailor the optoelectronic properties of materials,^{13,14} but they may be enhanced or deteriorated by the monotonic changes and phase transitions. The synthesis process is usually time-consuming, labor-intensive and expensive, but the polymorphism of products

^a Faculty of Chemistry, Adam Mickiewicz University, Uniwersytetu Poznańskiego 8, 61-614 Poznań, Poland. E-mail: katran@amu.edu.pl

^b Paul Scherrer Institute, Forschungsstrasse 111, Villigen CH-5232, Switzerland

^c Department of Chemistry "G. Ciamician", University of Bologna, via Selmi 2, 40126 Bologna, Italy. E-mail: l.maini@unibo.it

† Supplementary Information available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x




can improve or diminish envisaged applications.^{15,16} Most organic semiconductors crystallize in two or more polymorphic forms with different molecular packings in solid state,^{17–21} leading to different properties.^{22,23} The electronic, optical, mechanical, and charge transport properties of organic materials are heavily dependent on the molecular packing, which is governed by various types of strong and weak intermolecular interactions.^{24,25} Thus, investigating and controlling crystal structures and polymorphism is crucial for tailoring optical and electrical properties of organic semiconductors. Application of pressure and high- or low-temperature efficiently modifies intermolecular interactions and reveal the polymorphic behaviour of molecular compounds.^{26,27} Including this important physical variables in the study of organic materials opens new exciting opportunities for investigating and developing high-performance semiconductors for optoelectronic devices.^{28–30}

Perylene-3,4,9,10-tetracarboxydiimides, commonly known as perylene diimides (PDIs) are a class of compounds with polyaromatic π -conjugated flat molecules. PDIs offer a number of attractive characteristics, including high photo- and thermal-stability along with chemical inertness,³¹ and have been extensively studied as semiconductors for OFETs,^{32–35} and OPVs.^{36–38} The properties of these *n*-type semiconducting materials can be efficiently modified through appropriate functionalization of the PDI core, achieved either by introducing different substituents at the imide N-atom or by modifying the core at the *bay* or *ortho* positions.³⁹ Such substitutions effectively alter crystal packing and solubility, influencing the optical and electrochemical properties.^{36,40} Particularly effective, in the context of enhanced solubility, is the imide-site substitution by long alkyl chains. Several PDI systems with different alkyl chain length are known, but their polymorphic behaviour remains underinvestigated.^{41–44}

Here, we present our study on *N,N'*-dihexyl-3,4,9,10-perylenedicarboximide (denoted as PDI-C₆), a commercially available PDI derivative functionalized with a hexyl alkyl moiety at the imide position (Scheme 1). The UV-Vis spectrum shows the high absorbance (Figure S1) characteristic of highly efficient photovoltaic materials. Although two high-temperature transitions of PDI-C₆ were reported,^{32–35} they have not been thoroughly investigated, and the structures of those phases remain unknown. Recently, Madhu and coworkers reported the crystal structure of PDI-C₆ phase I at 173 K, revealing its one-dimensional (1D) columns, characteristic of PDI alkyl derivatives, stabilized by π - π stacking and C–H...O hydrogen bonding interactions.⁴⁵ Some of PDIs, such as PDI-C₅, have been studied at both room and high temperature, showing intriguing phase transitions, including polymorph obtained at 494 K that is characterized by a criss-cross arrangement of the aromatic cores.^{46,47} However, high-pressure studies of perylene diimides, and other organic photovoltaic (OPV) materials remain exceptionally rare.^{9,48–53} To fill this gap, we explored the polymorphism of PDI-C₆ at various temperatures and high pressure by combining multiple techniques, including synchrotron and in-lab X-ray diffraction, as well as differential scanning calorimetry (DSC).

Scheme 1. Structural formula of *N,N'*-dihexyl-3,4,9,10-perylenedicarboximide (PDI-C₆).
View Article Online
DOI: 10.1039/D5TC00809C

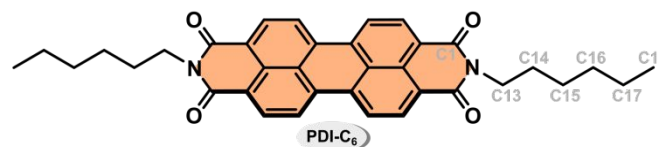

Results and discussion

Previous calorimetric studies of PDI-C₆ revealed two phase transitions during heating, occurring around 464 and 519 K, and two during cooling, at 494 and 409 K,³⁴ but they were not further investigated. To maintain consistent labelling with that previously introduced for PDI-C₅,⁴⁷ a PDI derivative with an *n*-pentyl chain, we will refer to the form stable under room conditions (296 K/0.1 MPa) as phase I, with subsequent phases labelled according to their order of appearance.

PDI-C₆ at room conditions

At room conditions, PDI-C₆ phase I crystallizes in the triclinic space group $P\bar{1}$, with the PDI-C₆ molecule located on an inversion center ($Z' = 0.5$). This observation agrees with the structure reported by Madhu et al. at 173 K (CSD refcode: TIXTUS).⁴⁵ In this structure, the molecules π -stacked into columns along the [100] crystal direction (Figure S2). The distance between π -stacked molecular cores ($d_{\pi-\pi}$) at room conditions is 3.3809(15) Å, somewhat shorter than the typical range 3.4–3.6 Å usually reported for π -stacked aggregates.⁵⁴

The perylene core of the PDI molecules is planar, while the alkyl chains protrude off the plane in *trans* conformation. The inclination of the *n*-hexyl chain in the respect to the perylene core can be described by torsion angle C1–N1–C13–C14 (τ_1), while the conformation of the alkyl chains is characterized by four torsion angles (Scheme 1): N1–C13–C14–C15 (τ_2), C13–C14–C15–C16 (τ_3), C14–C15–C16–C17 (τ_4) and C15–C16–C17–C18 (τ_5). In analogy to the ethane-like molecules, the hexyl chain conformers can be represented using four-letter descriptors.⁵⁵ In phase I, the alkyl chains adopt *anti-anti-anti-anti* conformation denoted by descriptor AAAA, corresponding to angles τ_2 , τ_3 , τ_4 , τ_5 all approaching 180°. The conformations involving *gauche*⁺ and *gauche*[−] torsions (60° and −60°, respectively), present in subsequent phases, are denoted e.g. G⁺AG[−]A. The *eclipsed* conformation (E) describes a molecular arrangement in which adjacent methylene or methyl groups are in close proximity, with the torsion angles between 0° and $\pm 30^\circ$, or close to 120°. The overall packing consists of alternating layers, with interdigitated alkyl chains and layers composed of rigid aromatic cores.

Temperature effect on PDI-C₆



The thermal behaviour of PDI-C₆ has been investigated by several complementary techniques, including differential scanning calorimetry (DSC); thermogravimetric analysis (TGA); hot-stage microscopy (HSM); variable-temperature synchrotron X-ray powder diffraction (VT-PXRD) and in-lab single-crystal X-ray diffraction (VT-SCXRD). These methods allowed us to explore a broad temperature range from 100 K up to the decomposition at 823 K with TGA (in a N₂ atmosphere, Figure S3 in Supporting Information) or at 673 K using VT-PXRD (in air).

During the heating cycle, according to the DSC thermogram, phase I transforms to phase II at $T_{I \rightarrow II} = 465$ K, and at $T_{II \rightarrow III} = 521$ K phase II transforms to phase III (Figure 1). These transitions are consistent with the VT-SCXRD and HSM. The thermograms collected for the PDI-C₆ cooled at a rate of 20 K min⁻¹ indicate that the transitions from phase III to phase II and from phase II to phase I are reversible, as previously reported.³⁴

The HSM revealed intriguing behaviour during the heating and cooling of the crystals related to the transition between phases I and II. The transitions occurred at slightly different temperatures for individual crystals, which is characteristic of 1st-order reconstructive transitions. The phase I to phase II transition observed upon heating was characterized by clearly visible propagating fronts that induced wrinkle formation on the crystal surface (as visible for crystal 1 in Figures 2a and 2b). A different behaviour was observed upon cooling, at approx. 392 K, all the PDI-C₆ needles elongated (Figure 2c,d), leading to the movement, jumping and bending of some crystals (Figure S18e,f). Similar polymorphism and thermomechanical behaviour were observed for other organic semiconducting materials.^{56,57} This macroscopic changes in single-crystal morphology can be attributed to the mutual rotation of the perylene cores, where the transformation of stress accumulated due to molecular rearrangement is converted into mechanical force.⁴⁷

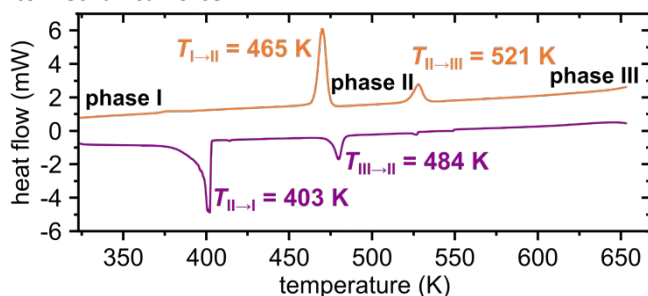


Figure 1. Differential scanning calorimetry (DSC) thermogram of PDI-C₆ in the heating (top) and cooling (bottom) cycles. Temperatures of phase transitions are indicated.

Our VT-PXRD analysis shows that, on approaching the transition to phase II, simultaneously the reflections of both phases II and III appear, while above $T_{II \rightarrow III}$, at 538 K only phase III is present (Figure 3). The coexistence of phases II and III is evident from two distinct peaks at 2θ below 1.25° in the PXRD pattern collected at 475 K (Figure S4). Because the transition from phase I to phase II is accompanied by a strong deformation, the unexpected appearance of phase III at 469 K can be associated with this strong mechanical effect, 'pulling'



Figure 2. Hot stage microscopy of PDI-C₆ crystals during the heating cycle: (a) phase I at 470 K, (b) transition from phase I to phase II at 473 K; and during cooling cycle: (c) phase II at 423 K, (d) transition from phase II to phase I at 363 K, reshaping the crystals. Additional images are provided in Figures S18 and S19 of the SI.

small portions of the crystals into the adjacent higher-temperature phase III. The observation of phases outside their stability regions are occasionally experienced for other compounds, too, e.g. resorcinol or benzimidazole.^{58,59} This recourse of a portion of the fine-powder sample to phase III at 469 K contrasts with all our experiments on single crystals and DSC measurements, all of which transformed to phase II, as expected. Upon cooling, phase III demonstrates strong hysteresis, persisting up to 353 K, when a simultaneous transition into phases II and I occurs (Figure S9). This extended hysteresis of phase III in the cooling run may result from a substantial thermal contraction, as indicated by thermal-expansion tensor plot (Table S7), potentially hindering the spatial reorganization of molecules during the transition to phases II/I. Notably, a significant difference is observed in the phase transition temperature across different thermal analyses (cf. Figure S8). This suggests that crystal morphology, particularly crystal size, plays a crucial role in influencing the kinetics of phase transition events, as it was observed for other materials.⁶⁰

In order to better understand the structural changes and the temperature effect on PDI-C₆ crystals, we performed a series of VT-SCXRD experiments up to 470 K. Heating phase I from 100 K to $T_{I \rightarrow II}$, gradually elongates the unit-cell parameters a_i and c_i (the index indicates the phase). Parameter b_i initially elongates up to 338 K; on further heating to 430 K this trend is reversed and b_i shortens; and between 430 K and 465 K, b_i hardly changes with temperature (Figure 4a). This unexpected behaviour can be attributed to the conformational changes of the n-hexyl chains. The π -conjugated stacking columns of PDI-C₆ molecules aligned along direction a_i in phase I, can be described by the *pitch and roll inclinations* relative to the ideal cofacial π -stack, as reported by Curtis et al.⁶¹ In this analysis, the *pitch* (P) angle corresponds to the displacement caused by the shift of adjacent molecules along the long molecular axis, whereas the *roll* (R) angle refers to the relative shift between adjacent molecules perpendicular to the long axis of the molecule (or along its short molecular axis). As the temperature increases in phase I, the P angle decreases from 42.88(6)° at 100 K to 42.31(4)° at 440 K, while the R angle slightly increases from 20.49(7)° to 21.11(5)° over



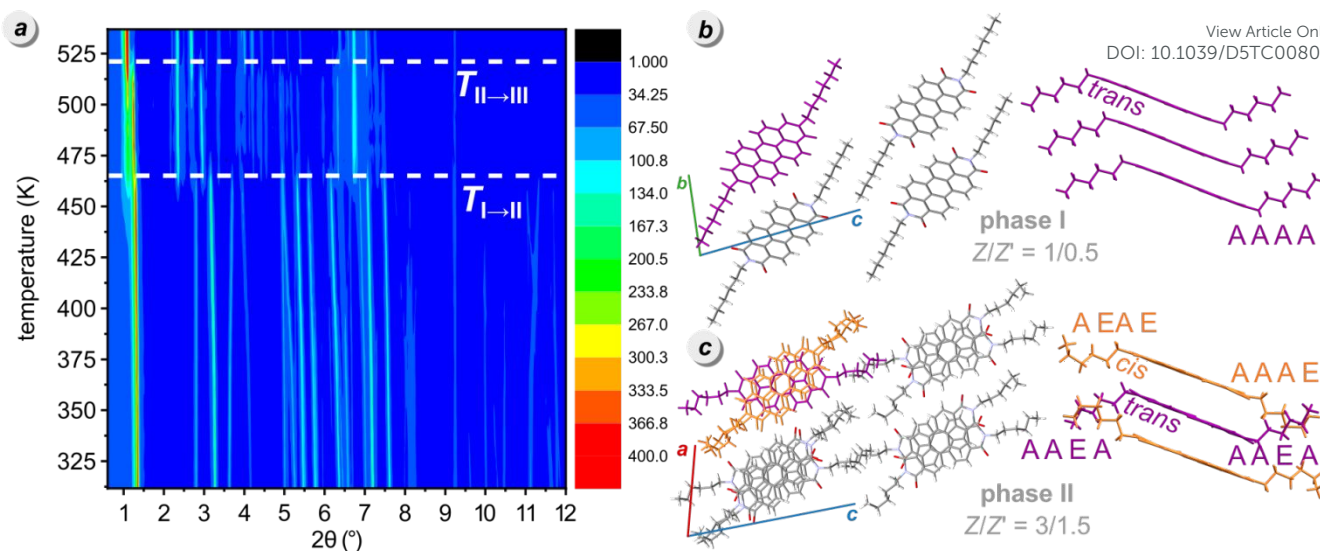


Figure 3. Temperature-resolved powder X-ray diffractograms of PDI-C₆ upon heating (left). The dashed lines indicate the transition temperatures identified in the DSC measurement: $T_{I \rightarrow II} = 465$ K and $T_{II \rightarrow III} = 521$ K. The color scale represents intensity variations. Crystal structures of PDI-C₆ phase I (b) and II (c) showing: the packing arrangement along the 1D columnar alignment (left) and the columnar stacking, including conformer descriptors (right). Molecules located at the inversion center with a *trans* conformation are depicted in purple, while those in general positions with a *cis* conformation are shown in orange.

the same temperature range (Figure 5a). The distance between π -stacked molecular planes ($d_{\pi-\pi}$) increases from 3.321(2) Å at 100 K up to 3.4397(13) Å at 440 K (Table S2). The calculated volumetric thermal expansion coefficient (α_v) in the 100–354 K range, is $162 \cdot 10^{-6} \text{ K}^{-1}$, which is close to the typical value of $170 \cdot 10^{-6} \text{ K}^{-1}$ observed for organic compounds.⁶² However, between 368 K and 461 K, the α_v increases sharply, reaching $446 \cdot 10^{-6} \text{ K}^{-1}$, which is nearly three times the value observed in the previous temperature range (see the Supporting Information for more details).

The phase transition from phase I to phase II fractures the single crystals, which complicated the accurate determination of high-temperature structures. Despite these difficulties, we successfully solved the structure of phase II at 470 K, revealing its triclinic symmetry of space group $P\bar{1}$. The unit-cell parameters of PDI-C₆ phase II closely resemble those of high-temperature phase III of PDI-C₅ ($a = 11.624$ Å, $b = 11.617$ Å, $c = 17.415$ Å, $\alpha = 98.21^\circ$, $\beta = 71.25^\circ$, $\gamma = 116.06^\circ$, CSD refcode: DICMUX01) and its number of molecules in the unit cell ($Z = 3$) is the same.⁴⁷ These similarities extend to the molecular packing and in PDI-C₆ phase II one molecule lies at an inversion center, while the other occupies a general position. The alkyl chains of the C_i -symmetric molecule are in *trans* conformation (i.e. they protrude to the opposite sides of PDI core), whereas the alkyl chains in the molecule at general position are *cis* (they protrude to the same side). The *trans*-molecule adopts the AAEA conformation, while the *cis* molecule has AAEE and AEAE conformers (Figure 3c). Within the columns, every two parallel *cis*-molecules are followed by a *trans*-molecule, whose perylene core is rotated by approximately 33° about the column axis and slightly tilted relative to the *cis* molecules. This results in an alternating sequence of two molecules *cis*, criss-cross π -stacked to one molecule *trans*, followed by two molecules *cis*, etc. Above 521 K, the strong reconstructive

transition occurs, which hampered our attempts to determine the structure of PDI-C₆ phase III. The unit-cell parameters of phase III are reported in Table 1.

PDI-C₆ under pressure

High-pressure single-crystal X-ray diffraction measurements were performed on PDI-C₆ at room temperature, up to 4.61 GPa. The discontinuities in the unit-cell dimensions as well as the doubling of parameter b at 1.22 GPa and its subsequent halving at 1.52 GPa evidence two pressure-induced phase transitions (Figure 4b). Phase I is stable up to 1.05 GPa and then transforms to phase IV, which at 1.52 GPa transforms to phase V. The high-pressure phases IV and V are of the same triclinic space group type $P\bar{1}$ as phases I, II and III. In phases I and V, the asymmetric part of the unit cell comprises half of the PDI-C₆ molecule, while $Z' = 1$ in phase IV. The crystallographic information are summarized in Table 1 and the crystal and experimental data are detailed in Table S16 in SI.

The compression of the phase I significantly reduces a_1 and c_1 dimensions, which is associated with decreased π - π distances and deformations of the alkyl chains. The parameter b_1 is hardly affected by the pressure and upon the compression to 0.73 GPa, it decreases by only -0.14%. Interestingly, at 1.05 GPa, just before the transition to phase IV, the b_1 is approximately +0.01% longer compared to its length at 0.1 MPa. These changes correlate with variations in the shortest hydrogen bond CH4...O2, which shortens from 2.4752(15) Å at 0.1 MPa to 2.37(3) Å at 0.73 GPa, before lengthening slightly to 2.39(2) Å at 1.05 GPa. At 0.1 MPa, the P angle is 42.53° and the R angle is 20.75° . The compression of phase I from 0.1 MPa to 1.05 GPa of PDI-C₆ has a small impact



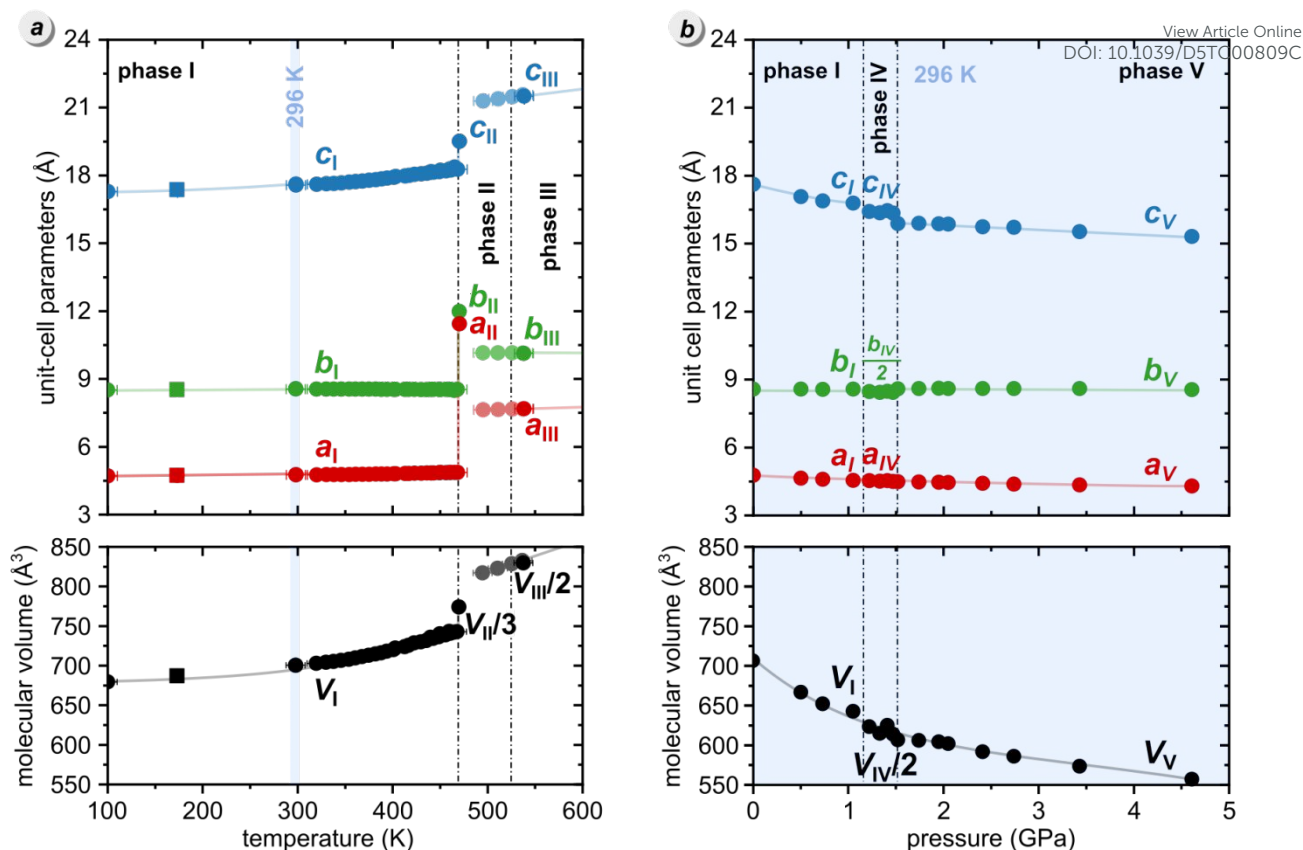


Figure 4. Temperature (a) and pressure (b) dependence of the unit-cell dimensions a , b , c (top) and molecular volume ($V_m = V/Z$, bottom) of PDI- C_6 . Estimated standard deviations (ESDs) are smaller than plotted symbols. The data at 173 K (squares) were taken from Madhu et al.⁴⁵ The unit-cell parameters of phase III determined during the cooling cycle are marked with a lighter color. The data measured at 296 K is highlighted in blue. Lines joining the points are for guiding the eye only. The triclinic angles are plotted in Figure S21.

Table 1. Selected crystallographic data of PDI- C_6 phases I, II, III, IV and V (cf. Table S16 and S17 in SI for details).

p (GPa)/ T (K)	Phase	Unit cell						V (\AA^3)	Z/Z'	$d_{\pi-\pi}$ (\AA)
		a (\AA)	b (\AA)	c (\AA)	α ($^\circ$)	β ($^\circ$)	γ ($^\circ$)			
0.0001/298	I	4.7568(10)	8.5487(16)	17.576(2)	81.678(14)	84.850(15)	83.169(16)	700.3(2)	1/0.5	3.3809(15)
0.0001/470	II	11.443(7)	11.988(8)	19.506(9)	96.05(5)	73.16(5)	114.90(6)	2323(3)	3/1.5	3.579(8)
0.0001/537	III	7.676(2)	10.148(1)	21.559(2)	84.35(2)	83.34(4)	90.52(3)	1665.5(5)	2/1	–
1.41/296	IV	4.5308(1)	16.9532(3)	17.887(1)	66.484(3)	95.489(2)	96.287(1)	1250.21(8)	2/1	3.2643(6) 3.2044(5)
1.95/296	V	4.4643(1)	8.6151(1)	15.8664(8)	90.750(3)	92.236(3)	97.490(1)	604.46(3)	1/0.5	3.2049(6)

on the P angle, reducing it by only 0.33° . In contrast, the changes of the R angle and π - π stacking distance ($d_{\pi-\pi}$) are much more pronounced. The compression to 1.05 GPa, decreases the R angle by 1.75° and shortens the $d_{\pi-\pi}$ distance to 3.278(6) \AA from 3.3882(4) \AA measured at 0.1 MPa (Figure 5b).

The unit cell of phase IV clearly corresponds to that of phase I, as evident from compression of parameters (Figure 4b) and the structural comparison presented in Figure 6. The nearly monotonic compression of a reflects the gradual contraction of π - π stacking distance between adjacent PDI- C_6 molecules within the stacks. The unit-cell vectors of phases I

(a_I , b_I , c_I) and IV (a_{IV} , b_{IV} , c_{IV}) are related by the following equation (1):

$$\begin{pmatrix} a_{IV} \\ b_{IV} \\ c_{IV} \end{pmatrix} = \begin{pmatrix} -1 & 0 & 0 \\ 0 & -2 & 0 \\ 0 & -1 & 1 \end{pmatrix} \begin{pmatrix} a_I \\ b_I \\ c_I \end{pmatrix} \quad (1)$$

Apart from doubling of the b parameter ($b_{IV} = 2b_I$), the transition from phase I to IV leads to an abrupt reduction of the c'_{IV} parameter by -2.20% , which can be recalculated in relation to the c_I parameter of phase I with the Equation (2):

$$c'_{IV} = \sqrt{c_{IV}^2 + b_{IV}^2/4 - c_{IV}b_{IV}\cos\alpha_{IV}} \quad (2)$$



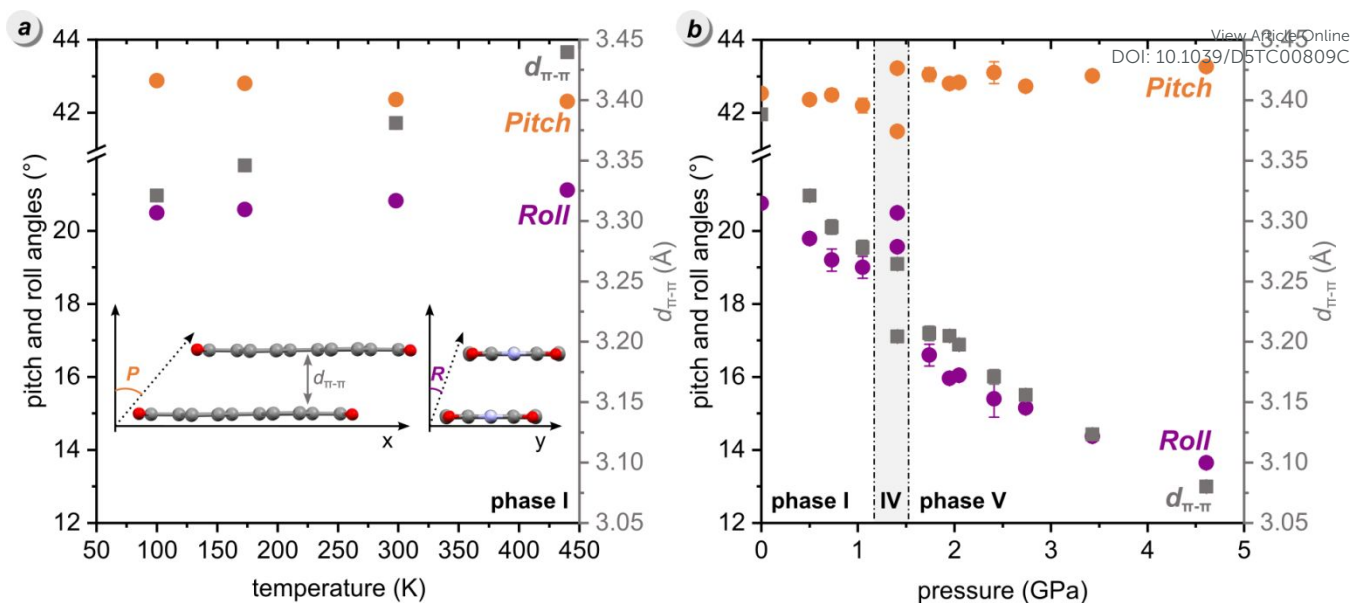


Figure 5. Temperature (a) and pressure (b) effects on the π -stacking of PDI-C₆ molecules under pressure: orange and purple symbols represent the *pitch* and *roll* angles and grey squares mark the distance between π -stacked molecules ($d_{\pi-\pi}$).⁶¹ Inset: graphical representation of P , R and $d_{\pi-\pi}$. The alkyl substituents and H-atoms are skipped for clarity. The corresponding numerical values can be found in Tables S2 and S10 of the SI.

The transformation to phase IV releases the structural strain accumulated during compression by lowering the crystal symmetry and doubling the number of independent molecules. As a result, due to conformational alternation of the *n*-hexyl chains, the Z' in phase IV increases from 0.5 to 1. One of the molecules retains C_i symmetry, maintaining the AAAA conformation of alkyl chains, as observed before in phase I, with τ_2 - τ_5 torsion angles close to 180°. The other molecule adopts a *gauche*⁺/*gauche*⁻ (G⁺/G⁻) conformation, where τ_3 and τ_5 remain near 180°, while τ_2 and τ_4 twist to approximately $\pm 60^\circ$. Consequently, the conformers descriptors for two independent molecules present in phase IV are AAAA/AAAA and G⁺AG⁻A/G⁻AG⁺A (Figure 7). The discrimination of molecules into two independent conformers affects their π -stacking in phase IV and significantly impacts the elastic response of the crystal. The pressure-induced deformation of the AAAA stacks follow the trends observed in phase I, with the P angle decreasing by 0.71°, and $d_{\pi-\pi}$ by 0.42% compared to their values at 1.05 GPa. Under the same conditions, the R angle increases by 1.5°. The accommodation of new conformers G⁺AG⁻A/G⁻AG⁺A requires the P angle to increase by 1.73° and R angle to decrease by 0.93°, compared to AAAA conformer at 1.41 GPa. As a result, the enhanced flexibility of G⁺AG⁻A/G⁻AG⁺A conformers allows for more efficient packing and the $d_{\pi-\pi}$ distance shorter by 1.84% compared to that between conformers AAAA at 1.41 GPa.

At 1.5 GPa, a drop in the parameter c length and the halving of the parameter b mark another phase transition, changing the unit-cell vectors to resemble those of phase I:

$$\begin{pmatrix} a_V \\ b_V \\ c_V \end{pmatrix} = \begin{pmatrix} -1 & 0 & 0 \\ 0 & -1/2 & 0 \\ 0 & -1/2 & 1 \end{pmatrix} \begin{pmatrix} a_{IV} \\ b_{IV} \\ c_{IV} \end{pmatrix} \quad (3)$$

In phase V, the Z' number is reduced back to 0.5, and all molecules adopt the G⁺AG⁻A/G⁻AG⁺A conformation (Figure 7). As the pressure increases from 1.74 to 4.61 GPa, the a_V parameter shortens by -4.12%, and c_V by -3.62%, while parameter b_V is hardly reduced (-0.48%). This unusual effect results from the preserved characteristic motif of π -stacking into columns, similarly as in phase I. The G⁺AG⁻A/G⁻AG⁺A conformation effectively accommodates compression, as evidenced by a negligible change in $d_{\pi-\pi}$ distance up to 2.1 GPa. Above this pressure, $d_{\pi-\pi}$ decreases significantly with compression, by 9.09% at 4.61 GPa compared to 0.1 MPa. The deformation of the π -stacked columns in phase V becomes more pronounced, with the P angle increasing by 0.22° and the R angle decreasing by 2.95° between 1.74 and 4.61 GPa (Table S10).

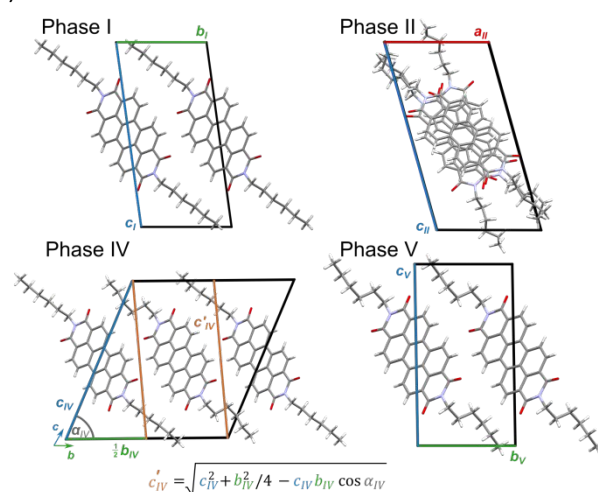


Figure 6. Lattice relations between phases I (0.1 MPa/298 K), II (0.1 MPa/470 K), IV (1.41 GPa/296 K), and V (1.95 GPa/296 K) in PDI-C₆, illustrated for maintained orientations of the π -stacked molecules; the orange axes in phase IV indicate the corresponding directions in phases I and V.



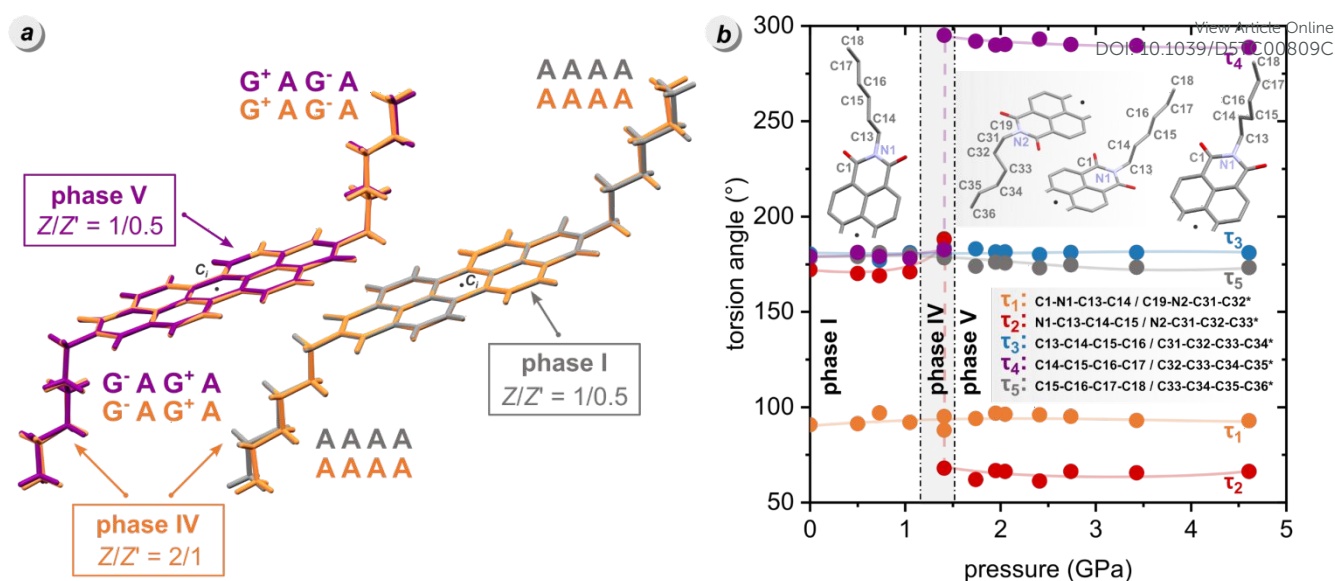


Figure 7. Conformational changes in PDI-C₆ molecules in phases I (grey), IV (orange) and V (violet) illustrated by (a) superimposing fragment of the perylene core, and (b) torsion angles τ_{1-5} plotted as a function of pressure. In the description of the torsion angles, asterisks refer to the atoms in phase IV. Hydrogen atoms are omitted for clarity.

Conclusions

We comprehensively investigated the solid-state phase transitions of the semiconductor PDI-C₆, employing a combination of differential scanning calorimetry, hot-stage microscopy, and X-ray diffraction under high pressure and various temperatures. Our research highlights an unprecedented polymorphic diversity of PDI-C₆, identifying reversible transformations between five distinct polymorphic forms. This includes two high-temperature polymorphs, previously observed only through DSC analysis, and two new high-pressure phases. Notably, all identified polymorphs crystallize in the same triclinic space-group type $P\bar{1}$.

The transition from phase I to phase II involves a scissor-like rotation of the perylene cores, accompanied by a significant conformational rearrangement of the alkyl chains. However, the structure retains its 1D columnar stacking and the interdigitation of the alkyl chains. PDI-C₆ phase II is isomorphic to phase III of PDI-C₅. The close structural relationship is further evidenced by similar mechano-responsive behaviour of crystals upon cooling from phase II back to phase I, which is characterized by moving, jumping and reshaping of single crystals. Due to the reconstructive phase transition, the structure of phase III could not be determined; however, we were able to establish the unit-cell parameters and characterize its thermal contraction upon cooling. This significant thermal strain may hinder the spatial rearrangement of molecules, leading to a high hysteresis upon cooling as observed in the VT-PXRD.

The volume changes observed in PDI-C₆ phase I on lowering the temperature from 298 to 100 K, on average, correspond to the compression from ambient pressure to ca. 0.5 GPa, fulfilling pressure–temperature corespondance rule.⁶³ Conversely, in the temperature range from 100 to 440 K, the

PDI-C₆ phase I follow the rule of the inverse relation of the thermal expansion and compressibility, exemplified by thermal expansion along [z], which corresponds to the strongest compressibility in the same direction. While the thermal phase transition from phase I to II is dominated by the rotation of the aromatic core, the experimental and theoretical computations consistently indicate that the conformational flexibility of the n-hexyl substituents at the imide position is the driving factor of pressure-induced phase transitions. The stepwise emergence of conformers G⁺AG⁻A/G⁻AG⁺A during compression in phase IV, where half of the molecules preserve the conformation AAAA/AAAA, while in phase V all molecules adopt the G⁺AG⁻A/G⁻AG⁺A conformation, indicates that such conformational conversion facilitates more efficient molecular packing and thus effectively reduces the π -stacking distance by 9.09% between 0.1 MPa and 4.61 GPa.

Experimental Methods

Crystallization

PDI-C₆ was purchased from Aldrich and used without additional purification. Crystals of PDI-C₆ were obtained using a solvothermal reactor. The process involved preparing a supersaturated solution of the PDI-C₆ in toluene, p-xylene, CH₂Cl₂, or CHCl₃, heating it to 453 K (or 373 K for chlorinated solvents) overnight, and then gradually cooling it to room temperature.

Differential Scanning Calorimetry (DSC)

The DSC measurement was performed with PerkinElmer PyrisDiamond DSC-7 equipped with a PII intracooler, in N₂ atmosphere and a scanning speed of 20 K min⁻¹. The



temperatures of phase transitions were determined using the method of intersecting slope and baseline lines.

Hot-Stage Microscopy (HSM)

The HSM analysis was performed using an OLYMPUS BX41 microscope equipped with a VISICAM 5.0 and a NIKON DS F13 camera. A Linkam TMS-94 stage was used for the temperature control. The images were taken under polarized light to highlight modifications in the crystals due to solid-state transition, with a 40× magnification.

Variable-Temperature Single-Crystal X-ray Diffraction (VT-SCXRD)

The single-crystal measurements were performed on Xcalibur diffractometers with microfocus sources ($\text{CuK}\alpha = 1.54178 \text{ \AA}$ and $\text{MoK}\alpha = 0.71073 \text{ \AA}$) and an Oxford Cryojet attachment. For data collection and processing, the CrysAlisPro software was employed. The crystal structures were initially solved using SHELXT and subsequently refined using SHELXL within the Olex2 suite.^{64,65} All non-H atoms were refined with anisotropic thermal parameters. H atoms were located in the difference Fourier map and from the molecular geometry. All crystal structures were analysed and compared using the software Mercury.⁶⁶ We conducted measurements at 100, 298, 440 and 470 K. Additionally, we determined the unit-cell parameters between 450 and 465 K from quick-experiments. The final crystal data are summarized in Table 1 and have been deposited in the CCDC with numbers 2421994, 2422224, 2412030 and 2421130.

Variable Temperature X-ray Powder Diffraction (VT-PXRD)

VT-PXRD experiments were conducted in the 312–537 K range at the ALBA Synchrotron and Powder Diffraction beamline BL04-MSPD equipped with the High-throughput Position Sensitive Detector (PSD) MYTHEN and an FMB Oxford hot air blower. Indexing of the high-temperature phases was achieved using a 30-second X-ray exposure, $\lambda = 0.41235(1) \text{ \AA}$, over the 2θ range of 0.8° – 15° . Figure 3a presents the VT-PXRD patterns obtained upon heating the material, while Figure S9 contains a temperature-resolved diffractogram collected during cooling the PDI-C₆ powder. Indexing of the PXRD data collected at 499 K was hampered. However, we successfully indexed the data collected at 537 K, which allowed the determination of the triclinic primitive unit-cell parameters of high-temperature polymorph III of PDI-C₆. Furthermore, the data for PDI-C₆ phase III at 537 K were refined using Pawley fitting in Topas-Academic V5 (TOPAS).⁶⁷ The final crystallographic data are summarized in Table 1.

High-Pressure Single-Crystal X-ray Diffraction

All high-pressure experiments were conducted using a modified Merrill-Bassett diamond anvil cell (DAC) with diamond anvils supported on steel discs.⁶⁸ The diamond culets were 0.8 mm in diameter. The gasket was made of 0.3 mm thick tungsten foil with spark-eroded holes 0.4 mm in diameter. Strongly elongated thin plate crystals were prepared

by cutting them to the dimensions required for the experimental chamber. The DAC chamber was loaded with the single-crystal sample and a ruby chip. Daphne Oil 7575 was used as the pressure-transmitting medium to maintain hydrostatic conditions.^{69,70} Subsequently, the DAC was closed and compressed. Pressure was generated by controlled tightening of three screws. The experimental details are shown in Figure S20 of the supporting information. Pressure was calibrated before and after the measurement using the ruby fluorescence method with the Photon Control spectrometer, affording an accuracy of 0.02 GPa.^{71,72} Single-crystal X-ray diffraction measurements were conducted on a 4-circle diffractometer equipped with a CCD detector and $\text{MoK}\alpha$ X-ray source ($\lambda = 0.71073 \text{ \AA}$) and with synchrotron radiation (see below Synchrotron X-ray Diffraction Measurements for details). The DAC chamber was centered using the gasket-shadowing method.⁷³ The CrysAlisPro software (ver. 43.98a) was used for the data collection, reduction and absorption correction. The structures were solved with direct methods using SHELXS and refined using least-squares methods with SHELXL, all within the Olex2 software suite.^{65,74} Anisotropic displacement parameters were applied to all non-hydrogen atoms. The hydrogen atoms were initially identified through different Fourier maps and recalculated based on the molecular geometry after each refinement cycle. The isotropic displacement parameters (U_{iso}) of H atoms were fixed at 1.5 $U_{\text{eq}}(\text{C})$ for methyl groups, and at 1.2 $U_{\text{eq}}(\text{C})$ for methylene and aromatic H atoms. In-lab X-ray diffraction measurements were conducted at pressures of 1.05, 1.74 and 2.41 GPa. Additionally, quick experiments were carried out at 1.22, 1.33, 1.47, and 1.52 GPa, where only the unit-cell parameters were determined. All reference images collected during the diffraction measurements were consistent, testifying that no transformations took place during these experiments.

Synchrotron X-ray Diffraction Measurements

X-ray diffraction measurements were performed at the Materials Science beamline of the Swiss Light Source⁷⁵ using synchrotron radiation of approx. 0.4920 \AA , focused and collimated to $150 \mu\text{m}$ (exact wavelengths were placed in Table S16). High-pressure diffraction data was collected for single crystals of the PDI-C₆ systems placed in a DAC in a steel gasket (thickness $\sim 90 \mu\text{m}$ and a hole diameter $250 \mu\text{m}$). A ruby fluorescent method was used to determine pressure inside the DAC. Daphne Oil 7575 was used as a pressure transmitting medium. We conducted measurements at 0.1 MPa, 0.5, 0.73, 1.41, 1.95, 2.05, 2.74, 3.43, and 4.61 GPa. The final crystal data from high-pressure measurements are summarized in Table 1 (cf. Table S16) and have been deposited in CIF format in the Cambridge Crystallographic Database with numbers CCDC 2412018–2412029 (from in-lab and synchrotron measurements).

Author contributions



Sample preparation: F.M., L.M., investigation and analysis of high-pressure and high-temperature SCXRD: P.R., S.S., M.A., F.M., A.K.; investigation and analysis of DSC, HSM, VT-PXRD: F.M., M.M., L.M.; theoretical investigation: M.A.; funding acquisition: P.R., L.M., A.K.; visualization: P.R., supervision: S.S., L.M., A.K.; original draft preparation: P.R., S.S., L.M., A.K.; review and editing: all authors. All the authors have given their approval to the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We are grateful to Dr. Nicola Casati for providing access to the synchrotron at PSI, Villigen. PR is grateful to the Polish Ministry of Education and Science (Diamentowy Grant DI2019/0160/49) for their financial support.

Notes and references

- 1 S. Preet and S. T. Smith, *J. Clean. Prod.*, 2024, **448**, 141661.
- 2 X. Wang, X. Tian, X. Chen, L. Ren and C. Geng, *Sol. Energy Mater. Sol. Cells*, 2022, **248**, 111976.
- 3 W. Wu, Y. Liu and D. Zhu, *Chem. Soc. Rev.*, 2010, **39**, 1489–1502.
- 4 A. B. Koren, M. D. Curtis, A. H. Francis and J. W. Kampf, *J. Am. Chem. Soc.*, 2003, **125**, 5040–5050.
- 5 L. Zang, Y. Che and J. S. Moore, *Acc. Chem. Res.*, 2008, **41**, 1596–1608.
- 6 S. Park, T. Kim, S. Yoon, C. W. Koh, H. Y. Woo and H. J. Son, *Adv. Mater.*, 2020, **32**, 1–29.
- 7 C. Wang, H. Dong, W. Hu, Y. Liu and D. Zhu, *Chem. Rev.*, 2012, **112**, 2208–2267.
- 8 H. Dong, X. Fu, J. Liu, Z. Wang and W. Hu, *Adv. Mater.*, 2013, **25**, 6158–6183.
- 9 P. Ratajczyk, S. Sobczak, P. Woźny, A. Wcisło, T. Poręba and A. Katrusiak, *J. Mater. Chem. C*, 2023, **11**, 11055–11065.
- 10 G. Zhang, F. R. Lin, F. Qi, T. Heumüller, A. Distler, H. J. Egelhaaf, N. Li, P. C. Y. Chow, C. J. Brabec, A. K. Y. Jen and H. L. Yip, *Chem. Rev.*, 2022, **122**, 14180–14274.
- 11 Y. G. Zhen, H. L. Dong, L. Jiang and W. P. Hu, *Chinese Chem. Lett.*, 2016, **27**, 1330–1338.
- 12 M. Mas-Torrent and C. Rovira, *Chem. Rev.*, 2011, **111**, 4833–4856.
- 13 M. Zambianchi, L. Favaretto, M. Durso, C. Bettini, A. Zanelli, I. Manet, M. Gazzano, L. Maini, D. Gentili, S. Toffanin, F. Gallino, M. Muccini, M. Cavallini and M. Melucci, *J. Mater. Chem. C*, 2015, **3**, 121–131.
- 14 L. Maini, F. Gallino, M. Zambianchi, M. Durso, M. Gazzano, K. Rubini, D. Gentili, I. Manet, M. Muccini, S. Toffanin, M. Cavallini and M. Melucci, *Chem. Commun.*, 2015, **51**, 2033–2035.
- 15 D. Liu, C. Li, S. Niu, Y. Li, M. Hu, Q. Li, W. Zhu, X. Zhang, H. Dong and W. Hu, *J. Mater. Chem. C*, 2019, **7**, 5925–5930.
- 16 J. Bernstein, *Polymorphism in molecular crystals*, Oxford University Press: New York, 2002.
- 17 H. Chung and Y. Diao, *J. Mater. Chem. C*, 2016, **4**, 3915–3933.
- 18 Y. Diao, K. M. Lenn, W. Y. Lee, M. A. Blood-Forsythe, J. Xu, Y. Mao, Y. Kim, J. A. Reinspach, S. Park, A. Aspuru-Guzik, G. Xue, P. Clancy, Z. Bao and S. C. B. Mannsfeld, *J. Am. Chem. Soc.*, 2014, **136**, 17046–17057.
- 19 C. Wang, Y. Yu, Z. Chai, F. He, C. Wu, Y. Gong, M. Han, Q. Li and Z. Li, *Mater. Chem. Front.*, 2019, **3**, 32–38.
- 20 P. Pandey, N. Demetri, L. Gigli, A. M. James, F. Devaux, Y. H. Geerts, E. Modena and L. Maini, *Cryst. Growth Des.*, 2022, **22**, 1680–1690.
- 21 I. de Oliveira Martins, F. Marin, E. Modena and L. Maini, *Faraday Discuss.*, 2022, **235**, 490–507.
- 22 C. Cappuccino, L. Catalano, F. Marin, G. Dushaq, G. Raj, M. Rasras, R. Rezgui, M. Zambianchi, M. Melucci, P. Naumov and L. Maini, *Cryst. Growth Des.*, 2020, **20**, 884–891.
- 23 C. Cappuccino, S. Canola, G. Montanari, S. G. Lopez, S. Toffanin, M. Melucci, F. Negri and L. Maini, *Cryst. Growth Des.*, 2019, **19**, 2594–2603.
- 24 G. R. Desiraju, *Crystal engineering: the design of organic solids*, Elsevier Science Publishers B.V., Amsterdam, 1989.
- 25 C. Gao, X. Li, Y. Qu, R. Dai, Z. Wang, H. Li and Z. Zhang, *J. Phys. Chem. C*, 2019, **123**, 8731–8739.
- 26 E. V. Boldyreva, *Acta Crystallogr. Sect. A Found. Crystallogr.*, 2008, **64**, 218–231.
- 27 A. Katrusiak, *Cryst. Res. Technol.*, 1991, **26**, 523–531.
- 28 Y. S. Guan, Z. Zhang, J. Pan, Q. Yan and S. Ren, *J. Mater. Chem. C*, 2017, **5**, 12338–12342.
- 29 M. Szafranski and A. Katrusiak, *J. Phys. Chem. Lett.*, 2017, **8**, 2496–2506.
- 30 M. Szafranski and A. Katrusiak, *J. Phys. Chem. Lett.*, 2016, **7**, 3458–3466.
- 31 A. Datar, K. Balakrishnan and L. Zang, *Chem. Commun.*, 2013, **49**, 6894–6896.
- 32 T. B. Singh, S. Erten, S. Günes, C. Zafer, G. Turkmen, B. Kuban, Y. Teoman, N. S. Sariciftci and S. Icli, *Org. Electron.*, 2006, **7**, 480–489.
- 33 R. Centore, L. Ricciotti, A. Carella, A. Roviello, M. Causà, M. Barra, F. Ciccullo and A. Cassinese, *Org. Electron.*, 2012, **13**, 2083–2093.
- 34 L. I. Kuznetsova, A. A. Piryazev, D. V. Anokhin, A. V. Mumyatov, D. K. Susarova, D. A. Ivanov and P. A. Troshin, *Org. Electron.*, 2018, **58**, 257–262.
- 35 J. Mei, Y. Diao, A. L. Appleton, L. Fang and Z. Bao, *J. Am. Chem. Soc.*, 2013, **135**, 6724–6746.
- 36 E. Kozma and M. Catellani, *Dye. Pigment.*, 2013, **98**, 160–179.
- 37 C. Li and H. Wonneberger, *Adv. Mater.*, 2012, **24**, 613–636.
- 38 W. S. Shin, H. H. Jeong, M. K. Kim, S. H. Jin, M. R. Kim, J. K. Lee, J. W. Lee and Y. S. Gal, *J. Mater. Chem.*, 2006, **16**, 384–390.
- 39 C. Huang, S. Barlow and S. R. Marder, *J. Org. Chem.*, 2011, **76**, 2386–2407.
- 40 F. Marin, A. Zappi, D. Melucci and L. Maini, *Mol. Syst. Des.*



- Eng., 2023, **8**, 500–515.
- 41 H. Langhals, S. Demmig and T. Potrawa, *J. für Prakt. Chemie*, 1991, **333**, 733–748.
- 42 A. J. McKerrow, E. Buncel and P. M. Kazmaier, *Can. J. Chem.*, 1993, **71**, 390–398.
- 43 M. Carmen Ruiz Delgado, E. G. Kim, D. A. Da Silva Filho and J. L. Bredas, *J. Am. Chem. Soc.*, 2010, **132**, 3375–3387.
- 44 Y. Geng, H. Bin Li, S. X. Wu and Z. M. Su, *J. Mater. Chem.*, 2012, **22**, 20840–20851.
- 45 J. Pitchaimani, A. Kundu, S. P. Anthony, D. Moon and V. Madhu, *ChemistrySelect*, 2020, **5**, 2070–2074.
- 46 E. Hadicke and F. Graser, *Acta Cryst*, 1986, **42**, 189–195.
- 47 F. Marin, S. Tombolesi, T. Salzillo, O. Yaffe and L. Maini, *J. Mater. Chem. C*, 2022, **10**, 8089–8100.
- 48 P. Ratajczyk, A. Katrusiak, W. Bogdanowicz, Krzysztof A. Przybył, P. Krysiak, A. Kwak and A. Iwan, *Mater. Adv.*, 2022, **3**, 2697–2705.
- 49 K. A. Bogdanowicz, S. Lalik, P. Ratajczyk, A. Katrusiak, P. Krysiak, A. I. Pawłowska, M. Marzec and A. Iwan, *Sci. Rep.*, 2023, **13**, 13240.
- 50 W. Shi, T. Deng, G. Wu, K. Hippalgaonkar, J. S. Wang and S. W. Yang, *Adv. Mater.*, 2019, **31**, 1–8.
- 51 M. Knaapila and S. Guha, *Reports Prog. Phys.*, 2016, **79**, 066601.
- 52 S. Bergantin, M. Moret, G. Buth and F. P. A. Fabbiani, *J. Phys. Chem. C*, 2014, **118**, 13476–13483.
- 53 R. Li, M. Wang, H. Zhao, Z. Bian, X. Wang, Y. Cheng and W. Huang, *J. Phys. Chem. Lett.*, 2020, **11**, 5896–5901.
- 54 R. Thakuria, N. K. Nath and B. K. Saha, *Cryst. Growth Des.*, 2019, **19**, 523–528.
- 55 A. Pórolniczak, S. Sobczak and A. Katrusiak, *J. Mater. Chem. C*, 2023, **11**, 16992–17002.
- 56 M. Dharmarwardana, R. P. Welch, S. Kwon, V. K. Nguyen, G. T. McCandless, M. A. Omary and J. J. Gassensmith, *Chem. Commun.*, 2017, **53**, 9890–9893.
- 57 M. Dharmarwardana, S. Pakhira, R. P. Welch, C. Caicedo-Narvaez, M. A. Luzuriaga, B. S. Arimilli, G. T. McCandless, B. Fahimi, J. L. Mendoza-Cortes and J. J. Gassensmith, *J. Am. Chem. Soc.*, 2021, **143**, 5951–5957.
- 58 F. Safari and A. Katrusiak, *J. Phys. Chem. C*, 2021, **125**, 23501–23509.
- 59 W. Zieliński and A. Katrusiak, *Cryst. Growth Des.*, 2013, **13**, 696–700.
- 60 A. Katrusiak, M. Rusek, M. Dušek, V. Petříček and M. Szafranski, *J. Phys. Chem. Lett.*, 2023, **14**, 3111–3119.
- 61 M. D. Curtis, J. Cao and J. W. Kampf, *J. Am. Chem. Soc.*, 2004, **126**, 4318–4328.
- 62 A. van der Lee and D. G. Dumitrescu, *Chem. Sci.*, 2021, **12**, 8537–8547.
- 63 M. Kaźmierczak, E. Patyk-Kaźmierczak and A. Katrusiak, *Cryst. Growth Des.*, 2021, **21**, 2196–2204.
- 64 G. M. Sheldrick, *Acta Crystallogr. Sect. C Struct. Chem.*, 2015, **71**, 3–8.
- 65 O. V. Dolomanov, L. J. Bourhis, R. J. Gildea, J. A. K. Howard and H. Puschmann, *J. Appl. Crystallogr.*, 2009, **42**, 339–341.
- 66 C. F. MacRae, I. Sovago, S. J. Cottrell, P. T. A. Galek, P. McCabe, E. Pidcock, M. Platings, G. P. Shields, J. S. Stevens, M. Towler and P. A. Wood, *J. Appl. Crystallogr.*, 2020, **53**, 226–235. DOI: 10.1039/D5TC00809C
- 67 A. A. Coelho, *J. Appl. Crystallogr.*, 2018, **51**, 210–218.
- 68 L. Merrill and W. A. Bassett, *Rev. Sci. Instrum.*, 1974, **45**, 290–294.
- 69 D. Staško, J. Prchal, M. Klicpera, S. Aoki and K. Murata, *High Press. Res.*, 2020, **40**, 525–536.
- 70 K. Murata and S. Aoki, *Rev. High Press. Sci. Technol. No Kagaku To Gijutsu*, 2016, **26**, 3–7.
- 71 G. J. Piermarini, S. Block, J. D. Barnett and R. A. Forman, *J. Appl. Phys.*, 1975, **46**, 2774–2780.
- 72 H. K. Mao, J. Xu and P. M. Bell, *J. Geophys. Res.*, 1986, **91**, 4673.
- 73 A. Budzianowski and A. Katrusiak, *High-Pressure Crystallogr.*, 2004, **140**, 101–112.
- 74 G. M. Sheldrick, *Acta Crystallogr. Sect. A Found. Crystallogr.*, 2008, **64**, 112–122.
- 75 P. R. Willmott, D. Meister, S. J. Leake, M. Lange, A. Bergamaschi, M. Böge, M. Calvi, C. Cancellieri, N. Casati, A. Cervellino, Q. Chen, C. David, U. Flechsig, F. Gozzo, B. Henrich, S. Jäggi-Spielmann, B. Jakob, I. Kalichava, P. Karvinen, J. Krempasky, A. Lüdeke, R. Lüscher, S. Maag, C. Quitmann, M. L. Reinle-Schmitt, T. Schmidt, B. Schmitt, A. Streun, I. Vartiainen, M. Vitins, X. Wang and R. Wulfschleger, *J. Synchrotron Radiat.*, 2013, **20**, 667–682.



ARTICLE

Open Access Article. Published on 04 June 2025. Downloaded on 6/4/2025 6:05:38 PM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Data for this article,

Pressure- and temperature-driven transitions and conformational conversions of n-hexyl substituted perylene diimide (PDI-C6) crystals

By Paulina Ratajczyk, Szymon Sobczak, Michał Andrzejewski, Francesco Marin, Marianna Marchini, Lucia Maini,* Andrzej Katrusiak* for publication as a paper in J. Mat. Chem. C.

Have been included as part of the Supplementary Information, and

The crystallographic data for compound PDI-C6 has been deposited at the CCDC with numbers 2421994, 2422224, 2412030 and 2421130 (varied-temperature data) and 2412018-2412029 (high-pressure data) and can be obtained in the form of CIF files from <https://www.ccdc.cam.ac.uk/>.

