



ALMA MATER STUDIORUM  
UNIVERSITÀ DI BOLOGNA

ARCHIVIO ISTITUZIONALE  
DELLA RICERCA

## Alma Mater Studiorum Università di Bologna Archivio istituzionale della ricerca

Sensitivity of direct metal laser sintering Maraging steel fatigue strength to build orientation and allowance for machining

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

*Published Version:*

Sensitivity of direct metal laser sintering Maraging steel fatigue strength to build orientation and allowance for machining / Croccolo, Dario; De Agostinis, Massimiliano; Fini, Stefano; Olmi, Giorgio; Robusto, Francesco; Ćirić-Kostić, Snezana; Morača, Slobodan; Bogojević, Nebojsa. - In: FATIGUE & FRACTURE OF ENGINEERING MATERIALS & STRUCTURES. - ISSN 8756-758X. - STAMPA. - 42:1(2019), pp. 374-386. [10.1111/ffe.12917]

*Availability:*

This version is available at: <https://hdl.handle.net/11585/645831> since: 2019-04-05

*Published:*

DOI: <http://doi.org/10.1111/ffe.12917>

*Terms of use:*

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).  
When citing, please refer to the published version.

(Article begins on next page)

This is the peer reviewed version of the following article:

Croccolo, Dario; De Agostinis, Massimiliano; Fini, Stefano; Olmi, Giorgio; Robusto, Francesco; Ćirić-Kostić, Snezana; Morača, Slobodan; Bogojević, Nebojsa, Sensitivity of direct metal laser sintering Maraging steel fatigue strength to build orientation and allowance for machining, «FATIGUE & FRACTURE OF ENGINEERING MATERIALS & STRUCTURES», 2019, 42, pp. 374 - 386.

which has been published in final form at <https://doi.org/10.1111/ffe.12917>.

This article may be used for non-commercial purposes in accordance with Wiley Terms and Conditions for Use of Self-Archived Versions.

# **SENSITIVITY OF DMLS MACHINING STEEL FATIGUE STRENGTH TO BUILD ORIENTATION AND ALLOWANCE FOR MACHINING**

<sup>1</sup> Department of Industrial Engineering (DIN), University of Bologna, Bologna, Italy

<sup>2</sup> Faculty of Mechanical and Civil Engineering in Kraljevo, University of Kragujevac,  
Serbia

## **ABSTRACT**

This work derives its motivations from the increasing interest towards Additive Manufacturing and the lack of studies, mainly in the field of fatigue. The effect of build orientation and of allowance for machining on DMLS produced Maraging Steel MS1 has been assessed. The experimental results, properly set up by tools of Design of Experiment, have been statistically processed and compared. The outcomes were that, probably due to effect of the thermal treatment, machining and material properties, the aforementioned factors do not have a significant impact on the fatigue response. This made it possible to work out a global curve that accounts for all the results, consisting in a high amount of data points. This can be regarded as one of the most generable and reliable fatigue models being currently available in the literature. Fracture surfaces have been carefully studied as well, individuating the initiation points being usually located at sub-surface porosities. Micrographies along the stacking direction and the build plane have been performed as well.

**Keywords:** Additive Manufacturing, DMLS, Maraging Steel, Rotating Bending Fatigue, Build orientation, Allowance for Machining.

## NOMENCLATURE

<i>AM</i>	Additive Manufacturing
<i>ANOVA</i>	Analysis of Variance
<i>CAD</i>	Computer Aided Design
<i>CTE</i>	Coefficient of thermal expansion
<i>DMLS</i>	Direct Metal Laser Sintering
<i>FL</i>	Fatigue Limit [MPa]
<i>R</i>	Stress Ratio (fatigue tests)
<i>f</i>	Frequency (fatigue tests) [Hz]
<i>R<sub>a</sub></i>	Roughness Average [ $\mu\text{m}$ ]
<i>S<sub>i</sub></i>	10-base logarithm of $\sigma_i$
$\bar{S}_{..}$	Overall mean (for ANOVA)
<i>SLM</i>	Selective Laser Melting
<i>S-N curve</i>	Maximum Bending Stress vs. Life Cycles curve in the finite life domain
<i>SSBC</i>	Sum of Squares between Columns (for ANOVA)
<i>SSE</i>	Sum of Squares Error (for ANOVA)
<i>SSI</i>	Sum of Squares Interaction (for ANOVA)
<i>SSBR</i>	Sum of Squares between Rows (for ANOVA)
<i>UTS</i>	Ultimate Tensile Strength [MPa]
$\sigma_i$	Finite life fatigue strength for the (i- th) sample set

## INTRODUCTION

Nowadays, Additive Manufacturing (AM) technologies are attracting a remarkable interest from industry, civil constructions and academia, considering its great potentials and its large applications. AM makes it possible to achieve the production of even much complicated geometries directly from three-dimensional CAD (computer aided design) models in a short time <sup>1</sup>, thus remarkably reducing the time from conception to market. Moreover, through a full exploitation of metal AM technique, lighter parts can be obtained: the capability of building even highly complicated shapes, which would not be affordable by conventional production methods, makes it possible to significantly increase the strength to weight ratio. This technique is more and more used in many strategic fields, e.g. automotive, aerospace, as well in the biomedical and injection molds industries <sup>1-2</sup>.

The most widely used techniques of AM for metals are Selective Laser Melting (SLM) that emphasizes the use of a laser as energy source, and Direct Metal Laser Sintering (DMLS) that makes use of a laser to selectively sinter some solid areas of the cross section of the built part. Nowadays, these two techniques can be regarded as being basically the same, according to <sup>3-6</sup>. Both have the capability of building metal parts layer-by-layer, starting from a highly controlled metal powder <sup>7-8</sup>. The CAD 3D model is initially split into several slices, individuating the cross sections corresponding to each slice. This makes it possible to convert a 3D problem into a 2D one. Afterwards, a high power laser is used to selectively fuse metallic powder particles, by some scans with controlled direction, which generate the solid shape of the part. After the consolidation of one powder layer, a new powder layer is stacked, the base plate is moved downwards, and the aforementioned processed is repeated until the completion of the component. During this building process, a large part of metal powder is generally unused, but can then be recycled, which makes it possible to strongly reduce the waste of raw material.

However, AM techniques also have some drawbacks arising from their typical cast structure, involving high surface roughness, presence of pores or sometimes oxides and thermal tensile residual stresses. These are due to remarkably steep temperature gradients affecting the layers and significant cooling rates. Despite these outcomes, previous studies in the literature, as well as data sheets by powder producers, indicate that their

monotonic properties can be well comparable to those of wrought material, with an isotropic response regardless of the build orientation during the stacking process. Anyway, a further issue with AM processed parts arises from the lack of a sufficiently high amount of studies dealing with their fatigue properties, considering that this is the most frequent state of load in the previously mentioned application fields. According to the literature<sup>9</sup> the fatigue limit is often coarsely estimated as the 50% of the ultimate tensile strength (UTS) of the material, considering conventional subtractive manufacturing. The determination of a correct fatigue limit to UTS ratio for additively produced parts is still under investigation.

Maraging steels are particularly suitable to powder bed fusion manufacturing techniques, such as DMLS or SLM<sup>10</sup>. Moreover, they exhibit a high performance in terms of UTS (close to 2,000 MPa, following aging treatment, regardless of the build orientation<sup>11</sup>) and of fracture toughness, which makes them promising materials in many fields. However, a possible issue is that a lack of studies, dealing with the fatigue response of this material, can be still observed in the scientific literature. A previous research<sup>12</sup> investigated the fatigue response (in terms of both the fatigue strength in the finite life domain and the fatigue limit) of Maraging steel MS1 (also reported as 18% Ni Maraging 300 or AISI 18Ni300). An experimental campaign was aimed at the investigation of the potential impact of the build orientation on fatigue, following heat aging treatment and machining with 0.5 mm allowance. The outcome was that the results were consistent for the three considered build orientation and the estimated fatigue limit was around 590 MPa, corresponding to 29% of the UTS. Consequently, the post manufacture treatments (aging and machining) proved to be able to remove any source of anisotropy. The determined fatigue limit to UTS ratio was also consistent with those of the experimental campaigns described in<sup>13-17</sup> that dealt with Maraging steels in wrought conditions. A recent study<sup>18</sup> has been focused on the effect of the laser scan speed on both static and fatigue performance, as well as on the porosities induced in the microstructure. However, the tests were conducted under subsequent blocks with different stress range and are therefore not comparable to the previous ones. Moreover, one build orientation only (vertical with respect to the powder bed) has been considered. Other studies, e.g.<sup>2</sup>, are mainly focused on the static properties or on the effect of the process parameters on the achieved microstructure of AM processed Maraging steel parts<sup>19</sup>. An interesting and particularly recent study is presented in<sup>1</sup>, where AISI 18Ni300 samples were involved in a quite extensive low-cycle fatigue campaign. However, this study was more oriented to the elasto-

plastic behaviour in the low-cycle fatigue domain, rather than to the fatigue response in the nominally elastic field and to its dependence on build or post-process parameters.

The subject of the present study consists in an extension of the outcomes of <sup>12</sup>: it aims at investigating the build orientation effect for increased allowance for machining, and then to better investigate the potential effect of allowance on the fatigue strength of the built and then machined components. The parts have all been produced by DMLS using a commercial machine by EOS. These two goals have been tackled by designing a suitable experimental campaign that completes and integrates the previous one described in <sup>12</sup>. Regarding the study on allowance, motivations stem from some recent researches <sup>20-22</sup>, which are starting to focus on the so called “size effect”, i.e. the effect of the amount of material to be removed after sintering on mechanical properties. The here reported results indicate a remarkably slower crack growth rate, following machining from oversized blocks. The fatigue performance of machined Ti-6Al-4V samples with suitable selection of allowance has also been the topic of the study <sup>23</sup>, which confirms the general interest in this point. A recent study <sup>3</sup> has studied the effect of allowance on fatigued 15-5 PH Stainless steel, reporting a beneficial effect of the incremented allowance. This is presumably due to the removal of the surficial layers around the contour, where the concentration of voids is statistically higher, and to the drop of residual stresses.

## **EXPERIMENTAL**

The experimental campaign involved Maraging steel MS1 (also reported as 18% Ni Maraging 300 or AISI 18Ni300), whose chemical composition is provided in Table 1. The material powder was supplied by EOS GmbH – Electro Optical Systems, Krailling/Munich, Germany). Fatigue testing was carried out under rotating bending, following the ISO 1143. Specimen geometry was chosen accordingly, with reference to the cylindrical smooth shape with uniform cross section at gage. The samples were manufactured with 6 mm diameter at gage and 10 mm diameter at the heads as a good compromise to reduce production costs, while ensuring agreement with the Standard.

**Table 1:** Chemical composition of Maraging steel MS1



The specimens were manufactured by EOSINT M280 system (EOS GmbH - Electro Optical Systems, Krailling/Munich, Germany), equipped with Ytterbium fibre laser with 200W power and emitting 0.2032mm thickness and 1064nm wavelength infrared light beam. The process takes place in an inert environment in a working space with  $250 \times 250$  mm dimensions on the horizontal plane and a maximum height of 325 mm. The layer thickness was set to 40  $\mu\text{m}$  and a parallel scan strategy with alternating scan direction was adopted. This direction was rotated by  $70^\circ$  at every layer, to get a better structure uniformity. Moreover, a contour line was scanned at every layer to better define the external shape.

The experimental campaign was arranged according to Table 2 that takes two parameters into account: build orientation and allowance. In particular, three levels were considered for the first factor: horizontal, vertical and slanted ( $45^\circ$  inclined) with reference to the inclination of the sample main axis of inertia with respect to the horizontal base plate during the deposition process with vertical stacking direction. Regarding the allowance factor, it refers to the allowance accounted during the machining task at every sample gage. Five levels were considered: 0.5, 1, 2, 3 and 4 mm. For the sake of clarity, consistently with the study <sup>3</sup>, a double notation has been used: the sample Sets have been identified by both their sequential number and a letter (H for horizontal, V for vertical, and S for slanted), followed by a number indicating the entity of allowance. It is worth mentioning that this study must be regarded as a follow-up of the previous one included in <sup>12</sup>: in particular, the sets with numbers 1-3 were included in that previous research. The current one has dealt with sets #4 to #9, to investigate the effect of the build orientation at incremented (3 mm) allowance and to then deepen the study on allowance for fixed (vertical) build orientation. The blank boxes indicate not investigated treatment combinations, due to their reduced interest for production and design purposes.

**Table 2:** Design of the experimental campaign

After the building process and before machining all the samples underwent the recommended surface and heat treatments by the powder producer. In particular, they were treated by micro-shot-peening, in order to close the pores that may be induced by laser sintering. Afterwards, an aging heat treatment, consisting in age-hardening at  $490^\circ\text{C}$  for 6 hours <sup>11</sup> was conducted. This treatment, which is aimed at reducing the tensile residual stresses, arising from the stacking process, was performed with the samples being still connected to their

supports. Finally, the specimens underwent machining and refining by grinding with the aim of accomplishing the roughness and dimensional specifications and of improving the fatigue performance.

The fatigue testing was aimed at the determination of the S-N curves and the fatigue limits (FLs). An abbreviated staircase method was applied to determine the FL, according to the Dixon method <sup>24-27</sup>. A life duration of  $10^7$  cycles was set as run-out, as suggested by the literature and in accordance with <sup>12</sup>. A confidence analysis (90% confidence level) was also performed based on the standard deviation of FL (scattering of the experimental results) and on the size of the sequence that led to its computation. The data in the finite life domain were processed according to the Standard ISO 12107 <sup>28</sup>: both the linear and the quadratic model have been worked out and the general linear test has then been applied, to assess the significance of the improvements arising from the latter. Lower and upper bounds to be wrapped around the curves have been determined, considering failure probabilities of 10% and 90% and with a 90% confidence level. The fatigue tests were performed under rotating bending (load ratio  $R=-1$ , frequency,  $f=60\text{Hz}$ ), so that each sample was loaded under a four point-bending configuration with constant bending moment at gage.

The experimentation was preceded by dimensional checks and roughness measurements that involved every sample. For this purpose, a micrometer screw gage, a digital caliper (both with the resolution of 0.01mm) and a portable surface roughness tester (with the resolution of 0.01  $\mu\text{m}$ , Handysurf E-30A; Carl Zeiss AG, Oberkochen, Germany) were used. Measurements were carried out with 4 replications at each head and with 6 replications at gage. The sample diameter was measured along  $90^\circ$  angled direction. As for roughness,  $R_a$  was retrieved considering again  $90^\circ$  angled spots, averaging the roughness profiles over a 4 mm tester shift. Measurements related to the Set #6 are collected in Table 3. Some roughness measurements at the gage are missing, when the related sample survived the fatigue testing: in this cases  $R_a$  at heads only was retrieved, due to the impossibility to correctly align the roughness tester at the gage for unbroken samples. At the end of the fatigue testing, crack surfaces were carefully analysed for the individuation of the crack nucleation point and of internal defects, oxides or porosities. For this purpose, a Stemi 305 stereo-microscope (by ZEISS, Oberkochen, Germany) as well as an Optiphot-100 optical microscope (by Nikon, Melville, NY, United States) have been utilized. Micrographies have also been performed, performing cuts of the samples along the cross section and along their longitudinal direction, thus individuating the microstructure along the build direction and on the deposition plane. After proper surface texturing, chemical etching (for 1 min 20 s at room

temperature) has been performed, according to the following recipe: 150ml H<sub>2</sub>O, 50ml HCl, 25ml HNO<sub>3</sub>, 1g CuCl<sub>2</sub>. The samples have then been observed by the aforementioned optical microscope.

**Table 3:** Dimensional and roughness (R<sub>a</sub>) measurements with regard to the samples of Set #6

## RESULTS

The results of the fatigue tests for samples Sets #4 to #9 are collected in Tables 4-9: in particular, sample identifier, the applied load (in terms of stress at the gage) and the observed life are provided. As mentioned above, the fatigue curve in the finite lifespan domain were processed according to ISO 12107<sup>28</sup> through the determination of both the linear and the quadratic models. The general linear test always led to the outcome that the improvements yielded by the latter were not significant. Therefore, the linear model proved to be the most suitable to process all the results. The fatigue curves can be expressed as in Eq. (1) or Eq. (2), the related coefficients are expressed in Table 10 for each sample Set.

**Table 4:** Results of the fatigue tests on the samples of Set #4

**Table 5:** Results of the fatigue tests on the samples of Set #5

**Table 6:** Results of the fatigue tests on the samples of Set #6

**Table 7:** Results of the fatigue tests on the samples of Set #7

**Table 8:** Results of the fatigue tests on the samples of Set #8

**Table 9:** Results of the fatigue tests on the samples of Set #9

**Fig. 1:** S-N curves in the finite life domain for Sets #1<sup>12</sup> to #6

**Table 10:** Coefficients of the determined S-N curves, according to the linear model of<sup>28</sup>, with reference to

Eq.s (1-2)

$$\text{Log}(N) = b_0 + b_1 \cdot \text{Log}(\sigma_i) \quad (1)$$

$$\sigma_i = 10^{\frac{b_0}{b_1}} \cdot N^{\frac{1}{b_1}} \quad (2)$$

The fatigue curves for Sets #1 to 6, considering also the results in <sup>12</sup> are depicted in Fig. 1. The comparison of these curves makes it possible to account for the potential joint effect of build orientation and of allowance. The fatigue curves for Sets #1, 6, 7, 8, 9 are conversely plotted in Fig. 2. The analysis of this graph makes it possible to compare the fatigue responses at different allowance levels.

**Fig. 2:** S-N curves in the finite life domain for Sets #1, 6, 7, 8 and 9

## DISCUSSION

The results have been statistically processed, to assess if the differences among the curves were significant with respect to the observed scattering affecting the experimental data. For this purpose, the ANOVA-based methodology introduced and described in <sup>3, 29</sup> was applied. The S-N curves related to the sets #1 to 6 were compared, regarding the related plan as a two-factor design. Conversely, the fatigue curves with regard to Sets #1, 6, 7, 8, 9 have been compared, considering a one-factor design, to evaluate the impact of allowance for machining. The first analysis was conducted as in <sup>3</sup>, through the calculation of mean fatigue curves and of a grand mean fatigue curve. Then an “SSBR” term, i.e. a “Sum of squares between rows” related to the differences among the responses for different build orientation was computed. At the same way an “SSBC” term, i.e. a “Sum of squares between Columns” related to the effect of allowance has then estimated, to assess the difference between the fatigue responses for 0.5 and 3 mm allowance. Then, “SSI” term, related to the interaction between the two factors was determined. All the values were converted into scalars, by calculating their integral mean over the reference life span. The error-related term (SSE) was finally determined as the sum of the squares of the residuals between the actual experimental data and the predicted ones based on the interpolating S-N curves. All the determined yields were subsequently processed in a conventional two-factor

ANOVA, provided that the aforementioned squared terms were scaled and made comparable one another by division by the related degrees of freedom. The analysis was conducted, considering both an interval between  $10^5$  and  $10^7$  cycles and a more reduced span between  $10^6$  and  $10^7$ . The results in both cases were that all the differences are negligible, meaning that the two factors are not significant and that no interaction occurs. The ANOVA table regarding the first one is reported in Table 11.

**Table 11:** ANOVA Table for the two-factor design (lifespan between  $10^5$  and  $10^7$ )

The one-factor ANOVA was developed as in <sup>29</sup>, however, considering that in this reference the analysis had been applied to a Low Cycle Fatigue study, some details are provided below for the sake of clarity. A grand mean curve  $\bar{S}_{..}$  has initially been computed as in Eq. (3), where S indicates the 10-base logarithm of the stress corresponding to a generic fatigue life and the subscript refers to the Set number.

$$\bar{S}_{..} = \frac{S_1 + S_6 + S_7 + S_8 + S_9}{5} \quad (3)$$

Then, an “SSBC” term, being related to the effect of allowance, has been determined as in Eq. (4). This takes the differences among the fatigue curves for different allowance levels into account.

$$SSBC = \left[ (S_1 - \bar{S}_{..})^2 + (S_6 - \bar{S}_{..})^2 + (S_7 - \bar{S}_{..})^2 + (S_8 - \bar{S}_{..})^2 + (S_9 - \bar{S}_{..})^2 \right] \quad (4)$$

As above, the error (SSE) was estimated as the sum of the squares of the residuals between the experimental yields and the predicted ones, according to the interpolating fatigue curves. Scalar terms were the worked out by the integral means of the aforementioned terms. The analysis proceeded as a conventional one-factor ANOVA, provided the scalar terms were made comparable, rationalizing them by their degrees of freedom. The study was repeated for the same intervals that have been mentioned above with regard to the analysis with two factors. The outcome for the interval between  $10^5$  and  $10^7$  is provided in Table 12, in both cases the statistical test proved that the allowance does not have any effect.

**Table 12:** ANOVA Table for the one-factor design (lifespan between  $10^5$  and  $10^7$ )

This outcome is also confirmed by the computation of the fatigue limits for infinite life, considering the aforementioned run-out of  $10^7$  cycles. The nominal values along with their confidence intervals at the 95.5% confidence level are displayed in the bar graph in Fig. 3. They are all quite close, with overlapped bands, except for that for Set # 7 that is a bit lower. The average value of the fatigue limit, involving the nine sets, is 581 MPa, corresponding to 38% the UTS of the studied material, following the aging treatment.

**Fig. 3:** Fatigue limits for 10 million cycle run-out with regard to samples #4 to 9. The results for Sets #1 to 3<sup>12</sup> are also appended for comparison purposes.

This result indicates that Maraging Steel has an isotropic behaviour, moreover its response does not exhibit variation for incremented allowance. In other words, this material has a particularly robust response that yields all consistent results even in different production conditions. This outcome also confirms the remarks in<sup>3</sup>. The build process of a Maraging Steel is performed with a doubled layer thickness ( $40\mu\text{m}$  instead of  $20\mu\text{m}$ ) with respect to the manufacturing of a Stainless steel. Moreover, it leads to a much more reduced tensile residual stress field, due to the lower coefficient of thermal expansion (CTE). In particular, the CTE of Maraging steel is approximately 10% lower than that for Stainless steel and the lower CTE, the lower the induced residual stresses<sup>3, 30</sup>. The doubled value of layer thickness also affects the induced residual stress. In fact, with approximately one-half stacked layers, the state of heating/cooling is made more uniform along the part height, and the thermal gradient as well as the residual stress state are reduced.

Incremented allowance proved to have a beneficial effect for Stainless Steel, as machining was able to remove the external surface layers, thus promoting a remarkable drop of the detrimental residual stresses. For Maraging steels, residual stresses already keep a much more reduced value, therefore this beneficial effect turns to be negligible.

Moreover, due to the higher number of layers, Stainless Steel proved to be sensitive to the notch effect in case of missing scans and to the number of defects per layer due to the limited perpendicularity between the laser path and the surface. Slanted orientation proved to be the best for that material as a good compromise between a not high notch effect and a not too extended build area, which made it possible to get a good perpendicularity with the laser path. Maraging Steel, with one-half layers, is less sensitive to the described effects; therefore, the build orientation is also completely ineffective. Moreover, like in <sup>12</sup>, the present results confirm that the post-manufacture heat treatment and machining are able remove any possible cause of anisotropy.

**Fig. 4:** Global S-N curve in the finite life domain accounting for all the 56 data

Considering the aforementioned outcomes and the statistical evidence of not significant differences among the fatigue responses of the nine sets (also including those tested in <sup>12</sup>), a global fatigue curve was determined. This curve has been yielded by the regression of all the data for all the studied sets and can be regarded as the most general and reliable description of the response of the studied Maraging Steel in the current state of the art. This model is likely to have many applications in the field of machine design, as it simultaneously accounts for the issues of build orientation and machining and related allowance. The fatigue curve was worked out, based on ISO 12107 <sup>28</sup>, by the linear model, like for all the sample sets. The confidence band at the 90% confidence level, with lower and upper bounds respectively corresponding to 10% and 90% failure probabilities, has been determined as well. The curve and the related band, along with dots corresponding the 56 experimental data that were involved in the interpolation, is plotted in Fig. 4. The analytical equations of the nominal curve at the 50% failure probability, to be used for life prediction, are provided in Eq.s (5-6).

$$\text{Log}(N) = 23.91 + 6.31 \cdot \text{Log}(S) \quad (5)$$

$$S = 7940 \cdot N^{-0.163} \quad (6)$$

The study was finally completed by fractography. Some fracture surfaces along with details of the crack initiation points are shown in Fig. 5. It can be remarked that almost the totality of failures was triggered by sub-surface porosities or voids with average dimension (diameter) and distance from the edge of respectively 50 $\mu$ m and 80 $\mu$ m. The area of initial propagation is also clearly visible due to its bright aspect. The outcomes of the carried out micrographies are shown in the pictures in Fig. 6 with reference to samples of Set #4 that were horizontally stacked with a 3 mm allowance. The deposited layers are visible in Fig. 6 (a): this image was recorded, considering a cut along the sample cross section. The laser scans along the build plane are then visible in Fig. 6 (b): this picture was taken, following a cut along a plane containing the sample longitudinal axis, i.e. along the deposition plane.

**Fig. 5:** Fractographic analysis of the fracture surface of sample 8.4: detail at the right side with crack initiation from a sub-surface porosity

**Fig. 6:** Micrographies on samples of Set #4 (H,3): (a) stacked layers with highlighted build direction: (b) laser scans, with emphasized inclusions by red circles

## CONCLUSIONS

The motivations for this study arose from the lack of a sufficient amount of data regarding the fatigue response of Maraging steel MS1 (also reported as 18% Ni Maraging 300 or AISI 18Ni300). Moreover, a further interest has been addressed to the possible effect of build orientation (even in presence of post-manufacture heat treatment and machining) and of the allowance for machining. Regarding this point, previous studies in the literature and by the same research group had indicated the possibility of a size effect (for parts machined from oversized blocks) in some conditions.

The aforementioned goals have been tackled experimentally, running fatigue tests under rotating bending, involving aged Maraging steel MS1 (also reported as 18% Ni Maraging 300 or AISI 18Ni300). Six sample sets have been tested in the present campaign, thus investigating the effects of build orientation and of allowance, according to an extensive experimental plan. The results, statically processed, have indicated that



the two mentioned factors do not have any impact on the fatigue response, including both the behaviour in the finite life domain and that for infinite life. In particular, the averaged fatigue limit, including all the performed tests, is 581 MPa, corresponding to 38% of the Ultimate Tensile Strength. This completely isotropic response is due to the beneficial effect of aging and machining, to the higher layer thickness (with respect, for instance to Stainless Steels) and to material properties, especially a not high coefficient of thermal expansion, which lead to a quite small residual stress field arising from the stacking process.

The analysis has been completed by the determination of a global fatigue curve that can be regarded as one of the most general and reliable models for fatigue life prediction being currently available in the literature. The curve, along with its confidence band (for 10% and 90% failure provability, 90% confidence level) has been determined through the interpolation of 56 experimental data, retrieved for different build orientations and different allowances, but all well consistent one another.

Finally, fractographic analyses have been conducted and have indicated that cracks usually start from sub-surface porosities having dimensions and distance from the edge of respectively 50  $\mu$ m and 80  $\mu$ m. Some inclusions have also been highlighted by micrographies conducted on the build plane and along the perpendicular build direction.

## **ACKNOWLEDGEMENTS**


The research presented in this paper has received funding from the European Union's Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie grant agreement No. 734455.

## **REFERENCES**


1. Branco R, Costa JDM, Berto F, Razavi SMJ, Ferreira JAM, Capela C, Santos L, Antunes F (2018). Low-Cycle Fatigue Behaviour of AISI 18Ni300 Maraging Steel Produced by Selective Laser Melting. *Metals*, 8, 32, 1-15.
2. Becker TH, Dimitrov D (2016). The achievable mechanical properties of SLM produced Maraging Steel 300 components. *Rapid Prototyp. J.*, 22 (3), 487-494.

3. Croccolo D, De Agostinis M, Fini S, Olmi G, Bogojevic N, Ciric-Kostic S (2018). Effects of build orientation and thickness of allowance on the fatigue behaviour of 15–5 PH stainless steel manufactured by DMLS. *Fatigue Fract. Eng. Mater. Struct.*, 41, 900-916.
4. Herderick E (2011). Additive Manufacturing of Metals: A Review. *In Proc. of Materials Science and Technology (MS&T)*, October 16-20, 2011, Columbus, Ohio, 1413-1425.
5. Lewandowski JJ, Seifi M (2016). Metal Additive Manufacturing: A Review of Mechanical Properties. *Annu. Rev. Mater. Res.*, 46, 151-186.
6. Nicoletto G (2018). Directional and notch effects on the fatigue behavior of as-built DMLS Ti6Al4V. *Int. J. Fatigue*, 106, 124-131.
7. Abe F, Osakada K, Shiomi M, Uematsu K, Matsumoto M (2001). The manufacturing of hard tools from metallic powders by selective laser melting. *J. Mater. Process. Technol.*, 111 (1-3), 210-213.
8. Santos EC, Shiomi M, Osakada K, Laoui T (2006). Rapid manufacturing of metal components by laser forming, *Int. J. Mach. Tool Manu.*, 46 (12-13), 1459-1468.
9. Niemann G, Winter H, Hohn BR (2005). *Maschinenelemente*. Springer-Verlag, Berlin, Germany.
10. Casati R, Lemke J, Vedani M (2017). Microstructural and Mechanical Properties of As Built, Solution Treated and Aged 18 Ni (300 grade) Maraging Steel Produced by Selective Laser Melting. *Metall. Ital.*, 1, 11-20.
11. [https://cdn0.scrvt.com/eos/c88047245bff2c4b/2f494ef432d0/MS-MS1-M280\\_M290\\_400W\\_Material\\_data\\_sheet\\_05-14\\_en.pdf](https://cdn0.scrvt.com/eos/c88047245bff2c4b/2f494ef432d0/MS-MS1-M280_M290_400W_Material_data_sheet_05-14_en.pdf)
12. Croccolo D, De Agostinis M, Fini S, Olmi G, Vranic A, Ciric-Kostic S (2016). Influence of the build orientation on the fatigue strength of EOS maraging steel produced by additive metal machine. *Fatigue Fract. Eng. Mater. Struct.*, 39, 637-647.
13. Karlinski W, Tacikowski J, Wojtyra K (1999). Fatigue strength of nitrided 18Ni250 and 18Ni300 grade maraging steels. *Surf. Eng.*, 15, 483-489.
14. Nagano T, Kawagoishi N, Moriyama M, Chen Q, Nagashima E (2007). Influence of shot peening on fatigue strength of maraging steels with different hardness. *J.S.M.S.*, 56, 1126-1132.
15. Wang W, Yan W, Duan Q, Shan Y, Zhang Z, Yang K (2010). Study on fatigue property of a new 2.8 GPa grade maraging steel. *Mater. Sci. Eng., B*, 527, 3057-3063.
16. Chen, Q, Nagano T, Nakamura Y, Maeda Y, Kawagoishi N (2013). Initiation and propagation behavior of a fatigue crack of maraging steel in high humidity. *In: Proc. 13th International Conference on Fracture, International Congress on Fracture (ICF)*, Beijing, China, 16–21.


17. Schuller R, Fitzka M, Irrasch D, Tran D, Pennings B, Mayer H (2015). VHCF properties of nitrided 18Ni maraging steel thin sheets with different Co and Ti content. *Fatigue Fract. Eng. Mater. Struct.*, 38, 518-527.
18. Santos LMS, Ferreira JAM, Jesus JS, Costa JM, Capela C (2016). Fatigue behaviour of selective laser melting steel components. *Theor. Appl. Fract. Mec.*, 85, 9-15.
19. Mutua J, Nakata S, Onda T, Chen Z-C (2018). Optimization of selective laser melting parameters and influence of post heat treatment on microstructure and mechanical properties of maraging steel. *Mater. Design*, 139, 486-497.
20. Zhang X, Martina F, Ding J, Wang X, Williams S (2017). Fracture toughness and fatigue crack growth rate properties in wire + arc additive manufactured Ti-6Al-4V. *Fatigue Fract. Eng. Mater. Struct.*, 40 (5), 790-803.
21. Zhang J, Wang X, Paddea S, Zhang X (2016). Fatigue crack propagation behaviour in wire+arc additive manufactured Ti-6Al-4V: effects of microstructure and residual stress. *Mater. Design*, 90, 551-561.
22. Van Hooreweder B, Moens D, Boonen R, Kruth J-P, Sas P (2012). Analysis of fracture toughness and crack propagation of Ti-6Al-4V produced by selective laser melting. *Adv. Eng. Mater.*, 14, 92-97.
23. Wycisk E, Siddique S, Herzog D, Walther F, Emmelmann C (2015). Fatigue performance of laser additive manufactured Ti-6Al-4V in very high cycle fatigue regime up to  $10^9$  cycles. *Front. Mater.*, 2, 1-8.
24. Dixon WJ, Massey F Jr. *Introduction to Statistical Analysis*. McGraw-Hill, New York, United States, 1983.
25. Olmi G, Comandini M, Freddi A (2010). Fatigue on shot-peened gears: experimentation, simulation and sensitivity analyses. *Strain*, 46 (4), 382-395.
26. Olmi G, Freddi A (2013). A new method for modelling the support effect under rotating bending fatigue: application to Ti-6Al-4V alloy, with and without shot peening. *Fatigue Fract. Eng. Mater. Struct.*, 36 (10), 981-993.
27. Van Hooreweder B, Moens D, Boonen R, Sas P (2012). The critical distance theory for fatigue analysis of notched aluminium specimens subjected to repeated bending. *Fatigue Fract. Eng. Mater. Struct.*, 35, 878-884.
28. International Organization for Standardization ISO 12107:2012. *Metallic Materials – Fatigue Testing – Statistical Planning and Analysis of Data*. International Organization for Standardization (ISO), Geneva, Switzerland, 2012.
29. Olmi G (2012). Low Cycle Fatigue Experiments on Turbogenerator Steels and a New Method for Defining Confidence Bands. *J. Test. Eval.*, 40, 4, Paper ID JTE104548.
30. Fergani O, Berto F, Welo T, Liang SY (2017). Analytical modelling of residual stress in additive manufacturing. *Fatigue Fract. Eng. Mater. Struct.*, 40, 971-978.

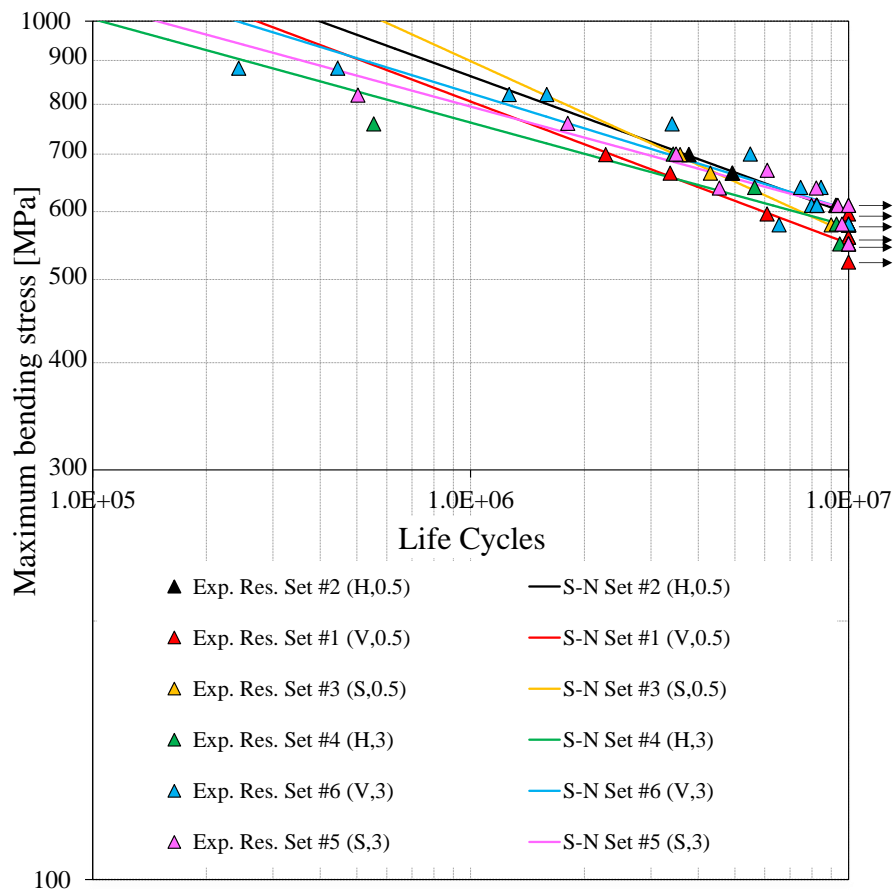

**Fig. 1:** S-N curves in the finite life domain for Sets #1<sup>12</sup> to #6

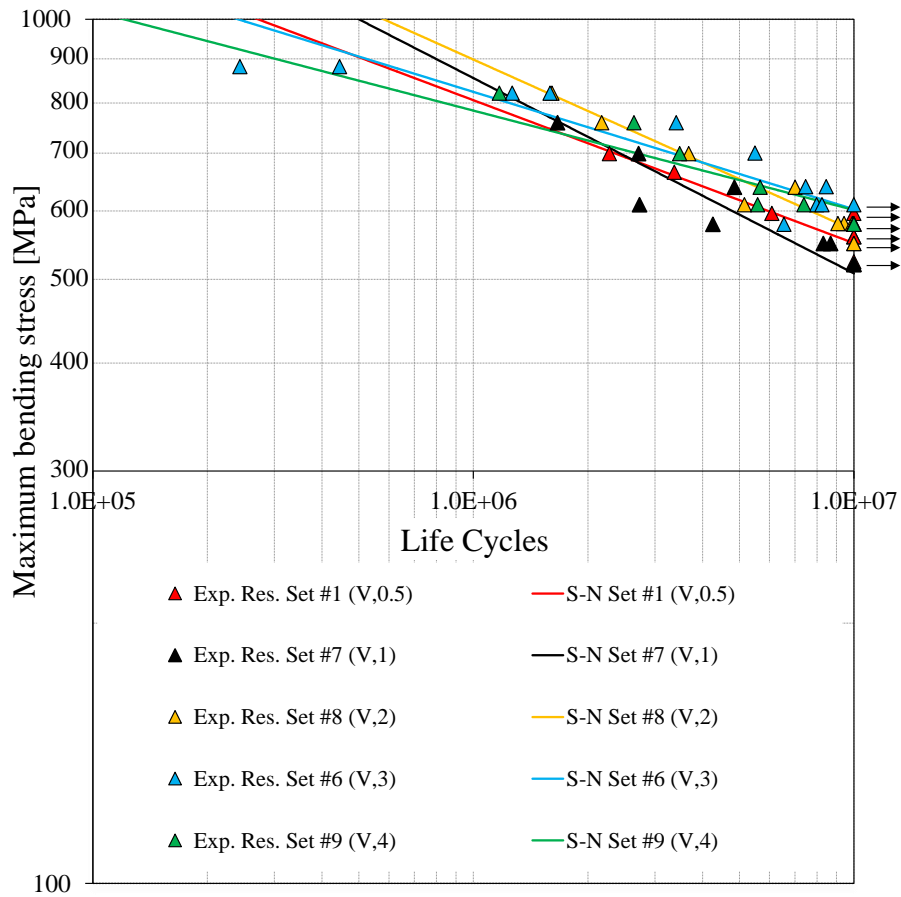


**Fig. 2:** S-N curves in the finite life domain for Sets #1, 6, 7, 8 and 9

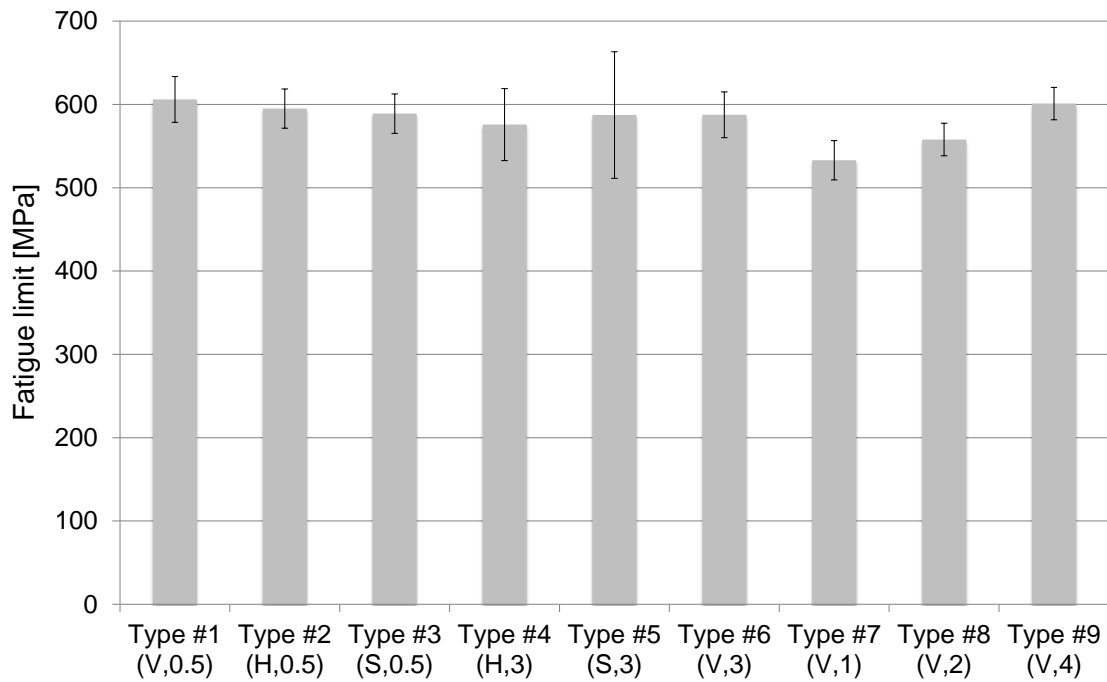


**Fig. 3:** Fatigue limits for 10 million cycle run-out with regard to samples #4 to 9. The results for Sets #1 to 3


<sup>12</sup> are also appended for comparison purposes.

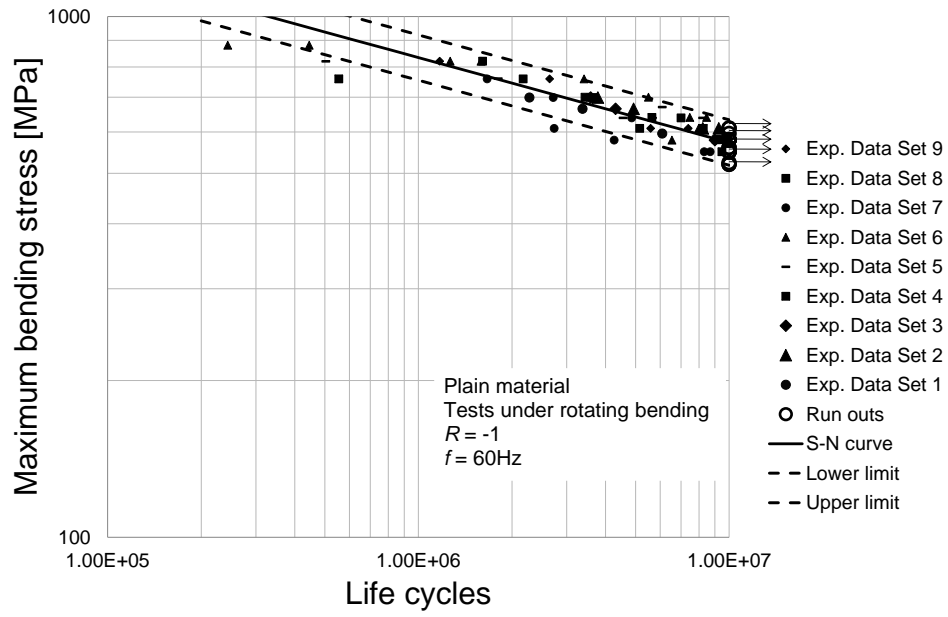

**Fig. 4:** Global S-N curve in the finite life domain accounting for all the 56 data

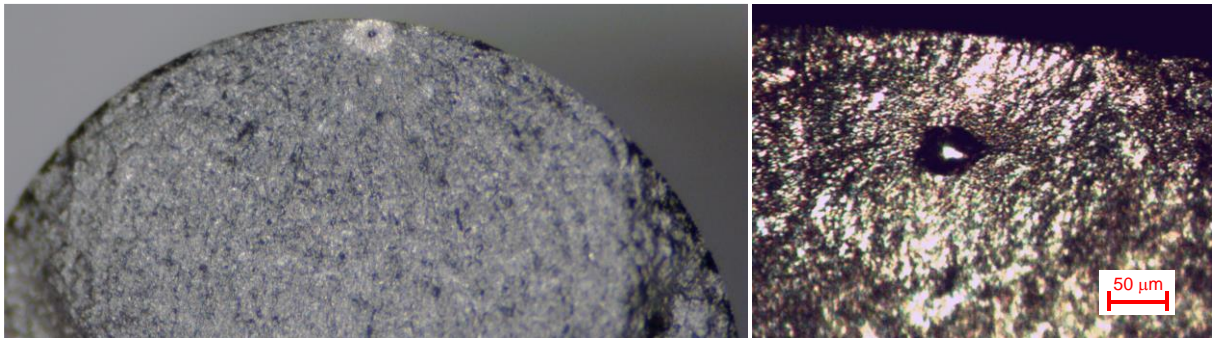

**Fig. 5:** Fractographic analysis of the fracture surface of sample 8.4: detail at the right side with crack initiation from a sub-surface porosity

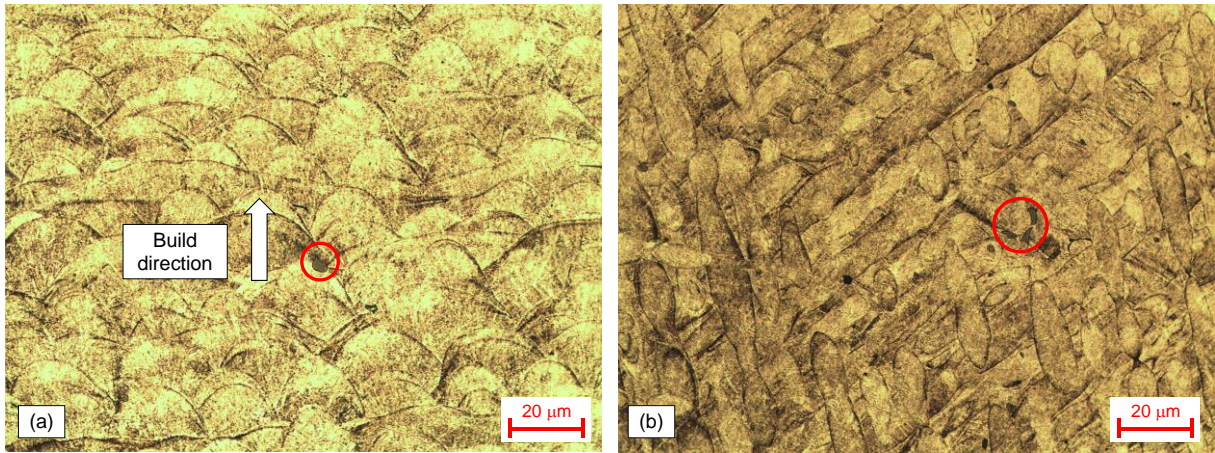

**Fig. 6:** Micrographies on samples of Set #4 (H,3): (a) stacked layers with highlighted build direction: (b) laser scans, with emphasized inclusions by red circles

**Table 1:** Chemical composition of Maraging steel MS1

Ni [%]	Co [%]	Mo [%]	Ti [%]	Al [%]	Cr [%]	Cu [%]	C [%]	Mn [%]	Si [%]	P [%]	S [%]	Fe [%]
17-19	8.5-9.5	4.5-5.2	0.6-0.8	0.05-0.15	≤ 0.5	≤ 0.5	≤ 0.03	≤ 0.1	≤ 0.1	≤ 0.01	≤ 0.01	Bal.

**Table 2:** Design of the experiment

		Allowance [mm]				
		0.5	1.0	2.0	3.0	4.0
Build orientation	Horizontal	Set #2 (H,0.5)			Set #4 (H,3)	
	Vertical	Set #1 (V,0.5)	Set #7 (V,1)	Set #8 (V,2)	Set #6 (V,3)	Set #9 (V,4)
	Slanted	Set #3 (S,0.5)			Set #5 (S,3)	



**Table 3:** Dimensional and roughness ( $R_a$ ) measurements with regard to the samples of Set #6

Specimen ID	Gage diameter			Head diameter (left side)			Head diameter (right side)		
	Mean [mm]	St. dev. [mm]	Roughness $R_a$ [ $\mu\text{m}$ ]	Mean [mm]	St. dev. [mm]	Roughness $R_a$ [ $\mu\text{m}$ ]	Mean [mm]	St. dev. [mm]	Roughness $R_a$ [ $\mu\text{m}$ ]
6.1	6.00	0.008	0.819	10.02	0.001	0.315	10.01	0.001	0.275
6.2	6.00	0.008	0.785	10.01	0.002	0.295	10.02	0.001	0.269
6.3	6.00	0.008	0.758	10.01	0.002	0.294	10.02	0.000	0.293
6.4	5.99	0.010	---	10.02	0.001	0.304	10.02	0.001	0.271
6.5	6.00	0.007	0.779	10.01	0.002	0.336	10.02	0.002	0.305
6.6	6.00	0.013	0.738	10.01	0.002	0.388	10.02	0.002	0.286
6.7	5.99	0.009	---	10.01	0.002	0.294	10.02	0.000	0.309
6.8	5.99	0.006	0.748	10.02	0.002	0.331	10.02	0.001	0.330
6.9	5.99	0.007	0.736	10.01	0.002	0.320	10.02	0.001	0.286
6.10	6.00	0.007	0.733	10.01	0.002	0.346	10.01	0.002	0.286
6.11	6.00	0.007	0.733	10.01	0.003	0.313	10.02	0.001	0.261
6.12	5.99	0.007	0.745	10.02	0.001	0.353	10.01	0.000	0.270
6.13	6.00	0.008	0.769	10.02	0.002	0.404	10.01	0.001	0.308

**Table 4:** Results of the fatigue tests on the samples of Set #4

Specimen ID	Stress [MPa]	Life [N]	Failure
4.1	759	554,382	Y
4.2	700	3,435,461	Y
4.3	670	387,562	Y
4.4	640	5,642,058	Y
4.6	580	---	N
4.7	610	8,255,277	Y
4.8	580	9,289,822	Y
4.9	550	9,472,904	Y
4.10	550	---	N

**Table 5:** Results of the fatigue tests on the samples of Set #5

Specimen ID	Stress [MPa]	Life [N]	Failure
5.1	700	3,499,346	Y
5.2	670	6,092,545	Y
5.3	639	4,554,231	Y
5.4	610	---	N
5.5	639	8,214,794	Y
5.6	610	9,367,065	Y
5.7	580	9,612,600	Y
5.8	550	---	N
5.9	760	1,807,539	Y
5.10	820	503,537	Y

**Table 6:** Results of the fatigue tests on the samples of Set #6

Specimen ID	Stress [MPa]	Life [N]	Failure
6.1	759	3,411,585	Y
6.2	700	5,499,068	Y
6.3	640	7,468,459	Y
6.4	610	---	N
6.5	640	8,456,821	Y
6.6	610	7,982,955	Y
6.7	579	---	N
6.8	610	8,247,250	Y
6.9	881	445,085	Y
6.10	881	243,461	Y
6.11	821	1,265,354	Y
6.12	821	1,591,045	Y
6.13	579	6,547,376	Y

**Table 7:** Results of the fatigue tests on the samples of Set #7

Specimen ID	Stress [MPa]	Life [N]	Failure
7.1	759	1,664,344	Y
7.2	699	2,716,753	Y
7.3	639	4,854,824	Y
7.4	610	2,733,629	Y
7.5	579	4,263,093	Y
7.6	550	8,686,316	Y
7.7	520	---	N
7.8	550	8,308,210	Y
7.9	520	---	N

**Table 8:** Results of the fatigue tests on the samples of Set #8

Specimen ID	Stress [MPa]	Life [N]	Failure
8.1	759	2,173,992	Y
8.2	699	3,681,461	Y
8.3	639	7,003,462	Y
8.4	580	9,426,902	Y
8.5	550	---	N
8.6	580	9,074,564	Y
8.7	550	---	N
8.8	580	9,901,534	Y
8.9	610	5,153,485	Y
8.10	821	1,609,415	Y

**Table 9:** Results of the fatigue tests on the samples of Set #9

Specimen ID	Stress [MPa]	Life [N]	Failure
9.1	759	2,643,707	Y
9.2	699	3,483,595	Y
9.3	639	5,671,878	Y
9.4	579	---	N
9.5	610	5,586,420	Y
9.6	579	---	N
9.8	610	7,388,578	Y
9.9	579	---	N
9.10	821	1,171,227	Y

**Table 10:** Coefficients of the determined S-N curves, according to the linear model of <sup>28</sup>, with reference to Eq.s (1-2)

Set #	$b_0$	$b_1$	$10^{\frac{b_0}{b_1}}$	$\frac{1}{b_1}$
4	29.87	-8.28	4,038	-0.121
5	30.17	-8.33	4,172	-0.120
6	27.46	-7.36	5,383	-0.136
7	18.97	-4.42	19,417	-0.226
8	20.93	-5.06	13,806	-0.198
9	21.66	-5.32	11,735	-0.188

**Table 11:** ANOVA Table for the two-factor design (lifespan between  $10^5$  and  $10^7$ )

	Sum of squares	Degrees of freedom	Failure	Fisher's ratio	p-value
SSBR: Effect of the build orientation	0.0005	2	0.0003	0.44	0.65
SSBC: Effect of the thickness of allowance for machining	0.0028	1	0.0028	4.84	0.04
SSI: Interaction	0.0016	2	0.0008	1.35	0.28
SSE: Error	0.0135	23	0.0006		

**Table 12:** ANOVA Table for the one-factor design (lifespan between  $10^5$  and  $10^7$ )

	Sum of squares	Degrees of freedom	Failure	Fisher's ratio	p-value
SSBC: Effect of the thickness of allowance for machining	0.0048	4	0.0012	1.66	0.19
SSE: Error	0.0189	26	0.0007		