



ALMA MATER STUDIORUM  
UNIVERSITÀ DI BOLOGNA

ARCHIVIO ISTITUZIONALE  
DELLA RICERCA

## Alma Mater Studiorum Università di Bologna Archivio istituzionale della ricerca

Hydrothermal Liquefaction of Enzymatic Hydrolysis Lignin: Biomass Pretreatment Severity Affects Lignin Valorization

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

*Published Version:*

Jensen, M.M., Djajadi, D.T., Torri, C., Rasmussen, H.B., Madsen, R.B., Venturini, E., et al. (2018). Hydrothermal Liquefaction of Enzymatic Hydrolysis Lignin: Biomass Pretreatment Severity Affects Lignin Valorization. ACS SUSTAINABLE CHEMISTRY & ENGINEERING, 6(5), 5940-5949 [10.1021/acssuschemeng.7b04338].

*Availability:*

This version is available at: <https://hdl.handle.net/11585/658654> since: 2019-01-30

*Published:*

DOI: <http://doi.org/10.1021/acssuschemeng.7b04338>

*Terms of use:*

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).  
When citing, please refer to the published version.

(Article begins on next page)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26

This is the final peer-reviewed accepted manuscript of:

**Hydrothermal Liquefaction of Enzymatic Hydrolysis Lignin: Biomass Pretreatment Severity Affects Lignin Valorization, Mads M. Jensen, Demi T. Djajadi, Cristian Torri, Helene B. Rasmussen, René B. Madsen, Elisa Venturini, Ivano Vassura, Jacob Becker, Bo B. Iversen, Anne S. Meyer, Henning Jørgensen, Daniele Fabbri, and Marianne Glasius. ACS Sustainable Chem. Eng. 2018, 6, 5, 5940–5949**

The final published version is available online at: [10.1021/acssuschemeng.7b04338](https://doi.org/10.1021/acssuschemeng.7b04338).

Rights / License:

The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

***When citing, please refer to the published version.***

1 **Hydrothermal Liquefaction of Enzymatic Hydrolysis Lignin – Biomass Pretreatment**  
2 **Severity Affects Lignin Valorization**

3

4

5 Mads M. Jensen<sup>1</sup>, Demi T. Djajadi<sup>2</sup>, Cristian Torri<sup>3</sup>, Helene B. Rasmussen<sup>1</sup>, René B. Madsen<sup>1</sup>, Elisa Venturini<sup>4</sup>,  
6 Ivano Vassura<sup>4</sup>, Jacob Becker<sup>1</sup>, Bo B. Iversen<sup>1</sup>, Anne S. Meyer<sup>2</sup>, Henning Jørgensen<sup>2,5</sup>, Daniele Fabbri<sup>3</sup>,  
7 Marianne Glasius<sup>1\*</sup>

8

9

10 <sup>1</sup>Department of Chemistry and iNANO, Aarhus University, Langelandsgade 140, 8000 Aarhus C, Denmark

11 <sup>2</sup>Department of Chemical and Biochemical Engineering, Technical University of Denmark, Søtofts Plads  
12 Building 229, 2800 Kgs. Lyngby, Denmark

13 <sup>3</sup>Dipartimento di Chimica “Giacomo Ciamician”, University of Bologna, Via Selmi 2, 40126 Bologna, Italy

14 <sup>4</sup>Department of Industrial Chemistry “Toso Montanari”, University of Bologna, Viale Risorgimento 4, 40146  
15 Bologna, Italy

16 <sup>5</sup>Present address: Department of Plant and Environmental Sciences, University of Copenhagen,  
17 Thorvaldsensvej 40, 1871 Frederiksberg C, Denmark

18 \*corresponding author: [glasius@chem.au.dk](mailto:glasius@chem.au.dk)

19

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

***When citing, please refer to the published version.***

## 1 Abstract

2 Alkaline hydrothermal liquefaction (HTL) of lignin-rich enzymatic hydrolysis residues (EnzHR) from wheat  
3 straw and *Miscanthus x giganteus* was performed at 255, 300, and 345 °C to investigate valorization of this  
4 side-stream from second-generation bioethanol production. HTL of EnzHR from biomass hydrothermally  
5 pretreated at two different levels of severity (190 °C, 10 min and 195 °C, 15 min) showed the most effective  
6 lignin depolymerization of the low severity EnzHR for both wheat straw and *Miscanthus*. The degree of  
7 depolymerization during HTL was temperature dependent and was not complete after 20 min at 255 °C,  
8 most distinctly for the *Miscanthus* EnzHR. The yields of 128 monomeric products quantified by gas  
9 chromatography – mass spectrometry were up to 15.4 wt% of dry matter. Principal component analysis of  
10 the quantified compounds showed that non-lignin HTL products are main contributors to the variance of  
11 the HTL products from the two biomasses. The chemically modified lignin polymer was found to have  
12 increased thermal stability after HTL. Analytical pyrolysis was applied to investigate the chemical  
13 composition of a larger fraction of the products. Analytical pyrolysis contributed with additional chemical  
14 information as well as confirming trends seen from quantified monomers. This work is relevant for future  
15 lignin valorization in biorefineries based on current second-generation bioethanol production.

16 **Keywords:** Base-catalyzed depolymerization, lignin depolymerization, hydrothermal pretreatment,  
17 analytical pyrolysis, principal component analysis, PARAFAC2

## 18 Introduction

19 Lignocellulosic side-streams from food production, paper pulp production, forestry and agriculture are  
20 good feedstock candidates for sustainable fuels and chemicals. One example is wheat, which can be utilized  
21 to produce food and straw for fuel (bioethanol)<sup>1</sup> and potentially chemicals.<sup>2</sup> Additionally, energy crops such  
22 as *Miscanthus* are candidates for production of liquid fuels and chemicals.<sup>3</sup> Lignocellulosic biomass  
23 primarily consists of cellulose, hemicelluloses, lignin, and extractives.<sup>4</sup> Lignin makes up 15–35 wt% of  
24 lignocellulosic biomass and is the largest renewable source of aromatics.<sup>5-6</sup> Only about 2% of industrially  
25 extracted lignins are used as chemicals, e.g., as dispersants.<sup>7</sup> Lignin-rich enzymatic hydrolysis residue  
26 (EnzHR) from second-generation bioethanol production is an emerging type of industrial lignin and only  
27 about 40% of this lignin side-stream is needed for internal energy use.<sup>1,6</sup>

28 Biomass in aqueous slurry can be converted into valuable products by hydrothermal liquefaction (HTL) at  
29 200–370 °C and 4–20 MPa, where the changes in the physicochemical properties of water result in unique  
30 solvation and reaction conditions.<sup>8-9</sup> The reaction chemistry of lignin HTL is dominated by ionic rather than  
31 radical reactions.<sup>10</sup> The utilization of water for HTL also means that energy-intensive drying of wet  
32 biomasses is avoided. This makes HTL an ideal match with the utilization of the wet lignin residue resulting  
33 from the ethanol production, which is currently dried and burned.<sup>1</sup> Products from HTL of lignin have been  
34 shown to have antifungal properties<sup>11</sup> and can partly substitute bisphenol A in an epoxy resin.<sup>12</sup>

35 The plant species of lignocellulosic feedstocks, lignin extraction method (kraft, soda, etc.), biomass  
36 pretreatment method (hydrothermal, dilute acid, etc.), and pretreatment severity affect the structure of  
37 the lignin, and can thus be expected to affect the HTL products.<sup>13-14</sup> Differences in lignin HTL products due  
38 to plant species are easily evident by comparing softwood lignin (guaiacol (G) type) producing  
39 phenols/guaiacols/catechols and grass lignin (*p*-hydroxyphenyl/guaiacyl/syringyl (HGS) type) also producing  
40 syringol.<sup>15-17</sup> Effects of type of pretreatment on lignin HTL products have also been investigated, e.g., choice  
41 of organosolv solvent<sup>18</sup> and mechanical pretreatment.<sup>19</sup> Hydrothermal pretreatment is used in recent  
42 second generation bioethanol plants of demonstration<sup>1</sup> and full scale.<sup>20</sup> Hydrothermal pretreatment is the

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 treatment of biomass with steam without additives.<sup>1</sup> Increasing the severity of hydrothermal pretreatment  
2 of wheat straw from a severity factor of  $\log R_0$  2.77 to 3.65 results in a large reduction of  $\beta$ -O-4 ether bonds  
3 and likely formation of new  $\beta$ -5 C-C bonds in the lignin.<sup>21</sup> Pretreatment of aspen wood with steam  
4 explosion in the  $\log R_0$  range 3.2–4.5 cause an almost linear decrease of  $\beta$ -O-4 bonds.<sup>22</sup> The change of lignin  
5 inter-unit bonding can be expected to affect subsequent valorization of the lignin in the EnzHR from  
6 second-generation bioethanol production. Yet, the effects of varying the severity of hydrothermal  
7 pretreatment have, to our knowledge, not received any attention in HTL literature.

8 In this work, we performed alkaline HTL of EnzHR from two grass species (*Miscanthus* and wheat straw)  
9 and two different and industrially relevant hydrothermal pretreatment severities ( $\log R_0$  3.65 and  $\log R_0$   
10 3.97) after initial screening of HTL temperature (255 °C, 300 °C, and 345 °C), to investigate the effects of  
11 these parameters on HTL product composition. We characterized the composition of feedstock and HTL  
12 products, small as well as polymeric compounds, using mainly size exclusion chromatography (SEC) and gas  
13 chromatography – mass spectrometry (GC-MS) combined with pyrolysis techniques. The study is  
14 subdivided into effects of varying HTL temperature for both biomasses (Part I) and effects of varying  
15 pretreatment severity for both biomasses (Part II).

## 16 Materials and methods

17 Detailed descriptions of materials and experimental methods can be found in the Supporting Information.  
18 Results are reported as mean and standard deviation of data obtained from replicate HTL experiments, i.e.,  
19 covering uncertainties of the entire procedure.

### 20 Enzymatic hydrolysis residues

21 EnzHR used as feedstocks for HTL were prepared by subjecting *Miscanthus x giganteus* stalks and wheat  
22 straw to hydrothermal pretreatment (steam pretreatment with autohydrolysis) at severity  $\log R_0$  3.65 (190  
23 °C, 10 min) or  $\log R_0$  3.97 (195 °C, 15 min) as detailed elsewhere.<sup>23</sup> The pretreated biomasses were then cut  
24 to <3 cm, knife-milling to <300  $\mu$ m, and subjected to enzymatic hydrolysis and protease treatment  
25 according to a published procedure.<sup>24</sup> The resulting solids were the *Miscanthus* (M3.65 and M3.97) and  
26 wheat straw (W3.65 and W3.97) enzymatic hydrolysis residues (EnzHR). The compositions of the EnzHR are  
27 shown in Table S1. The severity factor  $\log R_0$  is calculated according to Overend and Chornet:<sup>25</sup>

$$28 \quad \log R_0 = \log \left[ t(\text{min}) \cdot \exp \left( \frac{T(^\circ\text{C}) - 100}{14.75} \right) \right] \quad (1)$$

### 29 Hydrothermal liquefaction of enzymatic hydrolysis residues

30 Lignin-rich EnzHR containing 1 g dry matter (DM) was added to a 9 g aqueous solution of KOH giving a 10 g  
31 slurry of 10 wt% DM EnzHR and 5.6 wt% KOH. The slurry was transferred to a 20 mL stainless steel (SAE316)  
32 batch reactor and heated in an Omega Engineering FSB-4 fluidized sand bath. The reaction time was 20 min  
33 after heating for 4 min. The temperature for the start of reaction was defined as  $T_{R\text{start}} = T_1 + 0.92(T_{R\text{max}} - T_1)$ ,  
34 where  $T_1$  is the initial temperature of the slurry (ca. 25 °C) and  $T_{R\text{max}}$  is maximum reaction temperature. The  
35 reactor content was cooled to below 50 °C in less than 2 min by submersion in a water bath. The gas yield  
36 was low (<4 wt%). HTL experiments were generally performed in duplicate.

### 37 Product fractionation

38 The liquid and solid products were separated using the procedure outlined in Figure 1. The product  
39 fractionation has been shown to aid in interpretation of the complex product mixture from HTL of lignin.<sup>15</sup>

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 This is achieved by fractionation into a low molecular weight fraction (denoted liquid product, LP) and a  
2 high molecular weight fraction (denoted chemically modified lignin, CML). The product solution was  
3 acidified with 4M HCl to pH 2. The CO<sub>2</sub> evolved during acidification from dissolved carbonates was not  
4 included in the mass balance. Acidification resulted in precipitation, and solids were separated from the  
5 water phase (WP) by filtration. The solids were washed with diethyl ether (Et<sub>2</sub>O) until the filtrate appeared  
6 colorless. The WP was liquid-liquid extracted 3 times with Et<sub>2</sub>O (~1:1 ratio). The Et<sub>2</sub>O extracts were dried  
7 over Na<sub>2</sub>SO<sub>4</sub>. The liquid product (LP) was obtained as a dark orange/brown viscous oil after evaporation of  
8 the Et<sub>2</sub>O at reduced pressure. Chemically modified lignin (CML) was obtained as the tetrahydrofuran (THF)  
9 soluble solids by washing the reactor and filter retentate with THF until the filtrate appeared colorless. The  
10 CML was a dark brown/black brittle solid fraction after evaporation of the THF under reduced pressure. The  
11 solid residue (SR) remaining on the filters was oven dried at 105 °C overnight. SR caught in the sintered  
12 glass filter gave additional 0.7 wt% yield in the W3.97-300-2 experiment.

13 The yields of the dried/evaporated product fractions were calculated as DM corrected wt% using Equation  
14 (2). Monomer yields are reported on both DM (Equation (2)) and lignin basis (Equation (3)).

15 
$$Y_{product} = \frac{m_{product}}{m_{EnzHR} \cdot DM_{EnzHR}} \cdot 100\% \quad (2)$$

16 
$$Y_{aromatic\ monomer} = \frac{m_{product}}{m_{EnzHR} \cdot DM_{EnzHR} \cdot (AIL_{EnzHR} + ASL_{EnzHR})} \cdot 100\% \quad (3)$$


17 where  $m_{product}$  is the mass of the product fraction or monomer,  $m_{EnzHR}$  is the mass of added EnzHR, and  
18  $DM_{EnzHR}$ ,  $AIL_{EnzHR}$ , and  $ASL_{EnzHR}$  is the fraction of dry matter, acid insoluble lignin, and acid soluble lignin in the  
19 EnzHR, respectively.

20 The yield of the CML fraction was corrected for the 2,6-di-tert-butyl-4-methylphenol (BHT) introduced into  
21 this fraction by the use of BHT-stabilized THF.

22 The effects of slurry preparation and fractionation procedure on the biomass were accounted for by control  
23 experiments using M3.65 and W3.65 EnzHR, where the slurry was transferred to the reactor and kept at  
24 room temperature for 24 min before going through the same fractionation procedure as the HTL products.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

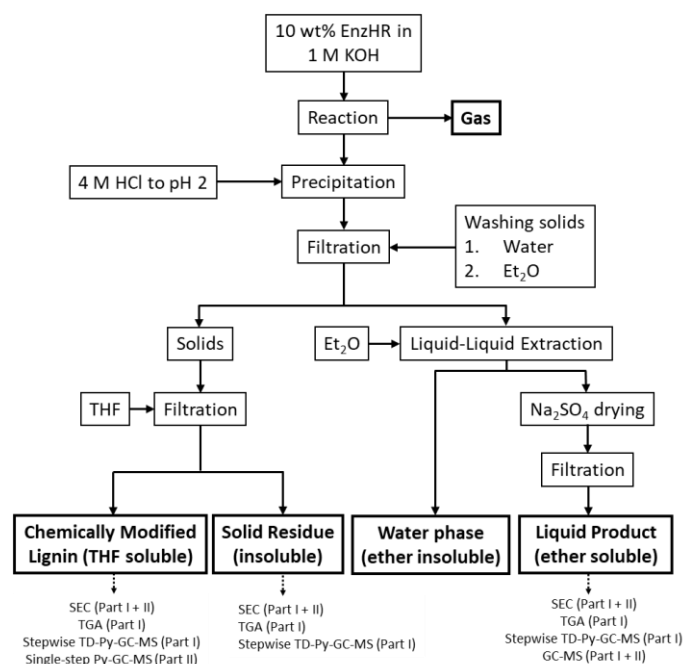

1

2 Figure 1. Procedure for hydrothermal liquefaction of enzymatic hydrolysis residues (EnzHR) and  
 3 subsequent product fractionation into liquid product (LP), chemically modified lignin (CML), and  
 4 solid residue (SR).

#### 5 Size exclusion chromatography

6 The molar mass distribution of samples was determined using size exclusion chromatography (SEC) with UV  
 7 detection at 280 nm. Compounds were separated on a Polymer Standards Service PolarSil column (300 x 8  
 8 mm, 5 µm, 100 Å) at 70 °C in a 9:1 (v/v) dimethyl sulfoxide/water eluent with 0.05 M LiBr. The molar mass  
 9 scale was calibrated using the retention times of 5 phenolic compounds in the range 152–1701 g/mol and  
 10 extrapolated using a linear regression curve of time (min) versus log(Mw).

#### 11 Quantification by GC-MS

12 Aliquots of LP were dissolved in ethyl acetate containing 4-bromotoluene and 4-bromophenol as internal  
 13 standards and were derivatized to their trimethylsilyl (TMS) derivatives. The GC-MS analyses were  
 14 performed using an Agilent system (7890B GC, 5977A MSD) equipped with an Agilent VF-5ms (60 m, 0.25  
 15 mm, 0.25 µm) column. Twenty-three compounds were quantified using authentic standards. Additional 105  
 16 compounds were semi-quantified using standards of a similar compound. Peak areas below the signal  
 17 detection limit were excluded. Deconvolution of peaks was performed with the PARAFAC2 based  
 18 Deconvolution and Identification System (PARADISE) ver. 1.1.1.<sup>26</sup> The deconvoluted mass spectra were  
 19 identified using the NIST11 library and a personal library of phenolic compounds.

#### 20 Principal component analysis

21 Principal component analysis (PCA) including data preprocessing were performed using PLS\_toolbox 8.2 in  
 22 MatLab R2017a. The deconvoluted TIC peak areas without a lower area threshold were used as input and  
 23 were mean centered and Pareto scaled.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

## 1 Thermogravimetric analysis

2 The weight loss from volatilization and pyrolysis of the LP, CML and SR was measured using  
3 thermogravimetric analysis (TGA) on a Mettler Toledo TGA/SDTA 851e. The TGA program was 25–700 °C  
4 (10 °C min<sup>-1</sup>) under a nitrogen flow of 90 mL min<sup>-1</sup>.

## 5 Stepwise thermal desorption and pyrolysis of Part I samples

6 Samples of LP, CML, and SR from the study of biomass and HTL temperature (Part I) were subjected to  
7 stepwise thermal desorption and pyrolysis on a CDS Pyroprobe 1000 prior to GC-MS analysis (TD-Py-GC-  
8 MS). Thermal desorption and pyrolysis using solid phase microextraction (SPME) sampling of desorbed  
9 compounds were performed using a procedure modified from a previous study.<sup>27</sup> Briefly, samples were  
10 heated in steps to 200, 280, 350, 420, and 500 °C at a heating rate of 0.01 °C ms<sup>-1</sup> under nitrogen flow. The  
11 temperature of each step was held for 5 min. Pyrolysates were sampled on a  
12 carboxen/polydimethylsiloxane SPME fiber (Supelco), and subjected to on-fiber derivatization using a  
13 procedure modified from a previous study.<sup>28</sup> The SPME fiber was exposed for 15 min in the headspace of a  
14 vial containing TMS-derivatization reagents and desorbed in the GC-MS inlet (Agilent 6851 GC, 5668 MSD)  
15 at 300 °C. Desorbed compounds were separated on an Agilent HP-5ms (30 m, 0.25 mm, 0.25 μm) column.  
16 The data showed repeatability poorer than the 10–30% relative standard deviation previously reported for  
17 quantitative analysis.<sup>27,29</sup> The stepwise TD-Py-GC-MS data were thus only used qualitatively.

## 18 Single-step pyrolysis of Part II samples

19 Single-step Py-GC-MS was performed using an Agilent GC-MS system (7890B GC, 5977A MSD) equipped  
20 with a Gerstel automated pyrolysis setup as described elsewhere.<sup>15</sup> CML samples from the study of biomass  
21 pretreatment severity (Part II) were analyzed in duplicate. Flash pyrolysis was performed under helium flow  
22 at 500 °C. Peak areas were obtained by deconvolution of the TIC using PARADISE and normalized to sample  
23 mass (corrected for BHT content). Peak identification was performed using authentic standards, published  
24 mass spectra, or the NIST11 libraries.<sup>30</sup> A solution of a homologous series of straight-chain alkanes was  
25 analyzed to provide Kovats retention index (RI) in the C<sub>7</sub>-C<sub>34</sub> range. Aliphatic compounds and structural  
26 isomers of aromatic compounds were identified using the NIST RI library where possible. The RI for each  
27 identified compound is reported in Table S8 and can be used for future studies to avoid incorrect  
28 identifications from relying purely on mass spectral libraries.

## 29 Results and discussion

### 30 Product fractionation

31 Initial experiments were performed to study the effect of HTL temperature (255, 300, and 345 °C) on  
32 products from *Miscanthus* and wheat straw EnzHR. The product solution was fractionated into a low  
33 molecular weight fraction (LP); a high molecular weight, THF soluble fraction (CML); and an insoluble  
34 residue (SR) in order to aid interpretation of the HTL process. The yields of the product fractions from HTL  
35 of the M3.65 and W3.65 EnzHRs (Table 1) showed increased liquefaction at higher temperature (higher LP  
36 and lower CML yields). The LP, CML, and SR fraction yields suggest that liquefaction of M3.65 and W3.65  
37 was not complete after 20 min at 255 °C.

38 The yields of the product fractions from HTL of the EnzHRs from *Miscanthus* and wheat straw pretreated at  
39 two different severity levels (M3.65-300, M3.97-300, W3.65-300, and W3.97-300, Table 1) showed few  
40 differences. The CML yield of W3.65 (16 wt%) was lower than W3.97 (22 wt%). Plotting the fraction yields  
41 against the lignin content in the EnzHR (Figure S1) showed that the LP yields correlated with the lignin  
42 content ( $r^2 = 0.87$ ,  $n = 9$ ). The HTL of EnzHR resulted in low yields of SR (Table 1) due to the concentration of

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

**When citing, please refer to the published version.**



1 alkaline base, extensive washing with THF, losses in the filter, and likely the type of lignin.<sup>19,31-32</sup> This type of  
 2 product fractionation has previously resulted in mass balances of 88–92% in the solid and extracted  
 3 fractions after HTL of high-purity organosolv and soda lignins.<sup>15,33</sup> Here, the LP, CML, and SR account for  
 4 only 55–74% of the feedstock EnzHR. The unaccounted mass from lignin HTL is likely trapped CO<sub>2</sub> and  
 5 highly volatile and water-soluble HTL products.<sup>34</sup> The mass balances correlate well with the content of  
 6 carbohydrate content of the EnzHR (Table S1). CO<sub>2</sub> is the main product from HTL of cellulose.<sup>35</sup> The KOH  
 7 used here would be able to trap CO<sub>2</sub> as carbonate in the aqueous product solution having pH > 10. This CO<sub>2</sub>  
 8 was not quantified. The control samples have mass balances of 91% and 106% showing that trapped CO<sub>2</sub>  
 9 and losses of highly volatile and water-soluble HTL products are the likely causes of the lack of mass  
 10 closure.

11 Table 1. Average yields and associated standard deviations of the product fractions from the HTL  
 12 and control experiments (20 °C) of the EnzHR.

EnzHR <sup>1</sup>	Fraction yields (% w/w DM)									
	M3.65				M3.97		W3.65			W3.97
<i>T</i> <sub>reaction</sub>	20 °C	255 °C	300 °C	345 °C	300 °C	20 °C	255 °C	300 °C	345 °C	300 °C
LP	2.0	39.1	42.8 ± 0.1	44.9 ± 0.3	48.9 ± 2.6	1.0	47.7	52.4 ± 1.3	53.5 ± 0.5	52.1 ± 0.2
CML	37.0	24.6	18.6 ± 9.3	8.7 ± 0.5	21.6 ± 1.2	68.0	24.3	15.7 ± 1.5	13.8 ± 0.3	21.9 ± 1.1
SR	52.0	6.2	1.2 ± 0.7	1.0 ± 0.2	0.5 ± 0.1	36.7	1.4	1.0 ± 0.7	1.7 ± 0.4	0.3 ± 0.2
<i>n</i> <sub>replicates</sub>	1	1	2	2	2	1	1	3	2	2

13 <sup>1</sup>M: *Miscanthus × giganteus* stalks; W: wheat straw. The numbers denote severity factor used during  
 14 biomass pretreatment: 3.65 - 190 °C 10 min; 3.97 - 195 °C 15 min.

#### 15 HTL temperature study of EnzHR conversion (Part I)


16 Molar mass distributions of the products determined by SEC (Table S3) showed that HTL of EnzHR lignin  
 17 lower the molar mass and give a more narrow molar mass distribution of the products based on comparing  
 18 the average molar masses of the LP and CML product fractions with the control experiments. This is in  
 19 contrast to previous results from HTL of Protobind 1000 soda lignin.<sup>15</sup> HTL results in both depolymerization  
 20 and repolymerization of aromatics, and the relative importance of these reactions are apparently different  
 21 for the two types of lignin.

22 Characterization of LP (Part I)Figure 2**Errore. L'origine riferimento non è stata trovata.** shows TGA-curves  
 23 for LP samples. Separate TGA-curves and differential TGA-curves are included in the electronic Supporting  
 24 Information (Figure S3). The TGA data revealed substantially different curves for the two replicates of  
 25 M3.65-345 LP, which could be due to sample heterogeneity. Consequently, only large differences in mass  
 26 losses were interpreted for the LP samples. The LP fractions from HTL at 255 °C had a lower mass loss of  
 27 volatiles during TGA than the other LP, which is consistent with the quantification of monomers. This  
 28 supports that depolymerization of the bulk biomass is not complete after 20 min at 255 °C. Note that HTL  
 29 of lignin in low concentration and volumes has shown depolymerization to be complete within seconds.<sup>36</sup>  
 30 Interestingly, introducing the on-fiber silylation to the stepwise TD-Py-GC-MS procedure resulted in  
 31 detection of a hump of decreasingly volatile compounds continuing into the dimeric range in the pyrolysis  
 32 steps of the LP (Figure S4), which indicates that volatilization of heavy compounds occurs alongside  
 33 pyrolysis. This observation shows that monomers and dimers potentially can be fractionated by distillation.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 The TGA suggested that the LP consist of about 35–48% mass, which can be detected by the GC-MS method  
2 (b.p. 120–300 °C). The 5–8% of the mass evaporating at temperatures below 120 °C likely consists of  
3 residual solvent, moisture, and products with low boiling points. The total (semi-)quantified compounds  
4 corresponds to 24–29% of the mass of the LP. Thus, it appears that GC-MS with TMS derivatization is  
5 suitable for quantification of the volatile products from HTL of lignin-rich feedstocks. The 10–20% of  
6 volatiles not quantified is likely due to a large number of compounds at low concentrations. Oligomeric  
7 products appear to be the main group of compounds comprising the remaining 45–60% mass of the LP, as  
8 based on SEC relative areas of UV detectable compounds (Figure S1). The complexity of this mass fraction  
9 appear high, based on the stepwise TD-Py-GC-MS results, and characterization of oligomer products could  
10 benefit from additional, dedicated studies.

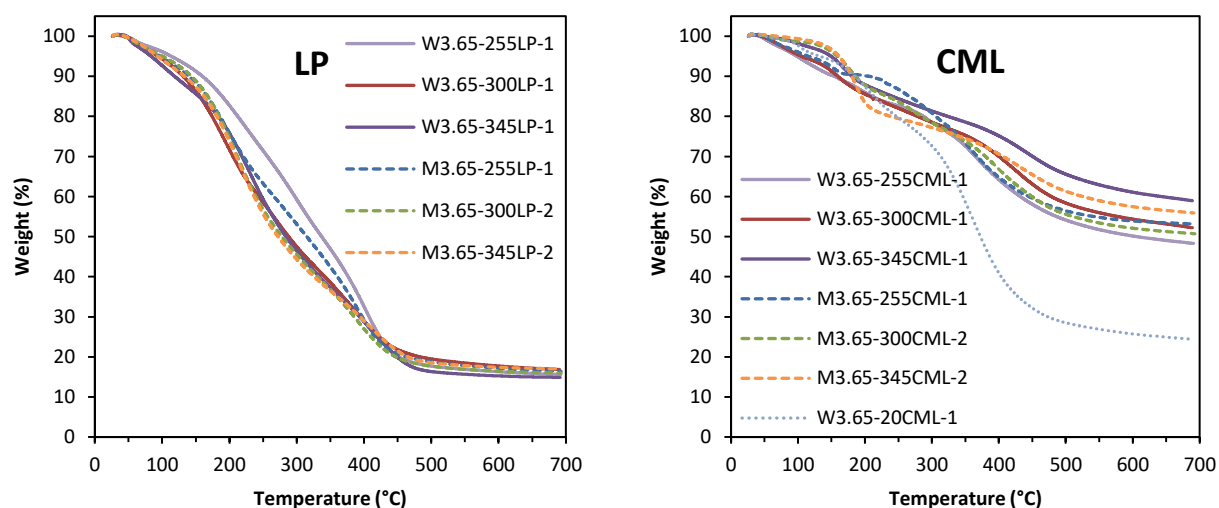

11  
12 Figure 2. Thermogravimetric curves for LP and CML fractions.


13 PCA (Figure 3 and 4) was used to visualize and explore the GC-MS results of the LP fraction prior to  
14 quantitative analysis based on groups of compounds (Figure 5). Three principal components (PC) were  
15 found to describe the model based on the scree plot of eigenvalues. Three PCs explained 93% of the total  
16 variance of the LP. The explorative PCA showed a clear grouping on principal component (PC) 1 and PC 2  
17 according to the latent variables of biomass and HTL temperature (Figure 3, left). PC 1 explained 51% of the  
18 total variance and separated samples according to HTL temperature. PC 2 explaining 21% of the total  
19 variance and primarily spanned the binary choice of biomasses. The loadings plot (Figure 3, right) shows the  
20 variables that contributed most to the separation. The compounds are colored according to main functional  
21 group. High loadings for hydroxy acids (mainly lactic acid and 2-hydroxybutanoic acid) and phenol on PC2  
22 separate *Miscanthus* from wheat straw, while catechol, an unknown catechol/benzenetriol, fatty acids and  
23 acetosyringone separate wheat straw from *Miscanthus*. The higher yield of phenol from *Miscanthus* can be  
24 partly caused by the higher carbohydrate content (Table S1), since phenol is a product of both cellulose and  
25 lignin.<sup>37</sup> The above shows that the non-lignin HTL products, and thus non-lignin biomass content, are main  
26 contributors to the variance of the products. A HTL plant producing lignin-derived aromatic chemicals can  
27 thus expect a different product if changing from *Miscanthus* to wheat straw EnzHR as feedstock. However,  
28 the product change would appear to be mostly caused by differences in non-lignin components in the  
29 feedstocks and to a lesser degree by differences in lignin structure.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 PC 3 explained 20% of the total variance and in itself separates the 300 °C samples from the rest. The  
2 compounds that cause this separation are mainly hydroxy acids, catechol and 3-methoxycatechol that have  
3 maximum yields at 300 °C regardless of biomass. Plotting the scores of PC 1 against PC 3 (Figure 4, left)  
4 resulted in grouping according to HTL temperature, with little separation according to biomass. The  
5 corresponding loadings plot (Figure 4, right) visualizes guaiacol, syringol and acetosyringone that are highly  
6 correlated to HTL at 255 °C, and 3-methylcatechol, alkylcatechols and propanoic acid that are highly  
7 correlated to HTL at 345 °C regardless of biomass.


8 The overall picture from PC1, PC2 and PC3 was that the monomeric aromatics had the most lignin-like  
9 functionalities from HTL of EnzHR lignin at 255 °C, though with syringol more correlated with *Miscanthus*  
10 than wheat straw, and acetosyringone and 3-methoxycatechol produced in higher amounts from wheat  
11 straw. The 345 °C HTL resulted in a higher abundance of most catechols, with the notable exception of  
12 catechol, the single most abundant compound, which is found at highest concentration after HTL at 300 °C.  
13 Additionally, catechol and 4-methylcatechol are produced in higher abundance from wheat straw than  
14 *Miscanthus* on DM basis. The trends of the PCA model were verified by the quantitative results (Table S4).  
15 The PCA suggests that, although some information is lost, compounds can generally be grouped according  
16 to functional groups, as the overall temperature trends are similar within each class of compounds.  
17 However for studying reaction mechanisms, some exceptions, e.g., guaiacol, syringol, catechol, and 3-  
18 methoxycatechol, should be interpreted separately.

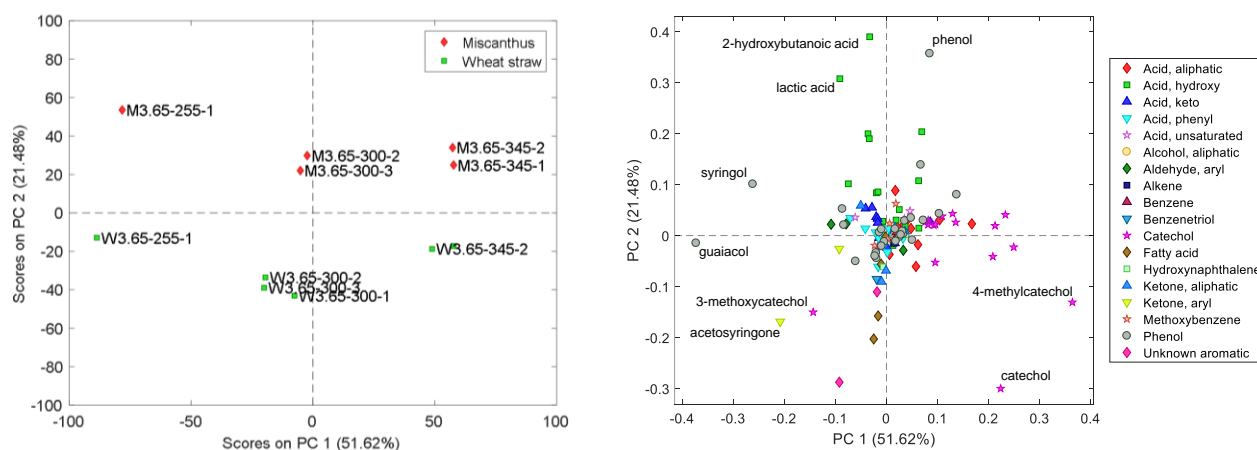

19  
20 Figure 3. Scores (left) and loadings (right) plots for PC 1 and PC 2 of PCA model for the EnzHR  
21 HTL temperature study.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

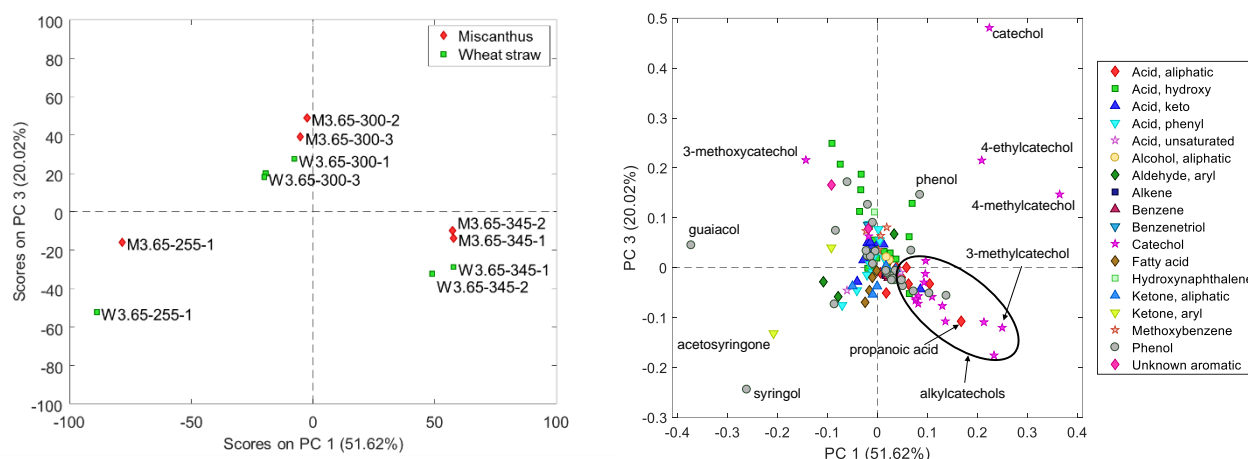

1

2 Figure 4. Scores (left) and loadings (right) plots for PC 1 and PC 3 of PCA model for the EnzHR  
 3 HTL temperature study.

4 Inter-study comparisons of monomer yields are difficult because GC-MS results are commonly reported as  
 5 relative peak areas, and when quantification of monomers is performed, it is often limited to selected  
 6 compounds that vary from study to study. Here we present a procedure for quantification of a feasible  
 7 number of compounds combined with a procedure for semi-quantification of a large number of products.  
 8 We find that this procedure has a suitable balance between cost of chemical analysis and benefit from  
 9 accuracy of quantification. Twenty-three compounds in the LP were quantified and 105 compounds were  
 10 semi-quantified using GC-MS (Table S4 on DM and S5 on lignin basis). The results are summarized in Figure  
 11 5 as grouped yields on DM basis in order to include the yields of non-lignin products (yields of aromatic  
 12 compounds are reported on the more relevant lignin basis below). The maximum yield of 71 quantified  
 13 aromatic monomers found here was 14.4 wt% on basis of lignin content. This is lower than the 21.5 wt%  
 14 (kraft lignin from Norway spruce) and 17.9 wt% (concentrated sulfuric acid hydrolysis lignin from oak) of 13  
 15 aromatics,<sup>38</sup> yet, higher than the 8.4 wt% of 9 aromatics (Indulin AT kraft lignin from mixed softwood),<sup>34</sup>  
 16 and higher than the 4.6–5.2 wt% of 22 aromatics from HTL of three different organosolv lignins from olive  
 17 tree pruning.<sup>18</sup> Despite differences in analytical procedures and HTL parameters, it would appear that the  
 18 type of lignin and plant species are major contributors to the differences in yield of aromatic monomers. A  
 19 recent summary of base-catalyzed depolymerization of lignin can be found elsewhere.<sup>38</sup>

20 Wheat straw and *Miscanthus* gave equal yields of total aromatics at 300 °C, yet quite different yields at 255  
 21 °C and 345 °C. M3.65-255 showed uniquely low total yield. This suggests that the two biomasses have  
 22 different optimal temperature for depolymerization of the lignin. The optimal HTL temperature might not  
 23 be 300 °C for either biomass and requires further investigations as it cannot be inferred from this work.

24 Vanillin is a widely used aroma compound and can be synthesized from guaiacol and catechol.<sup>39</sup> Vanillin  
 25 was produced in low yield (<0.6 wt%), though in highest yield at 255 °C. The sum of vanillin, guaiacol, and  
 26 catechol was largest for wheat straw at 300 °C (5.1 wt%). Syringaldehyde is a precursor for the synthesis of  
 27 3,4,5-trimethoxybenzaldehyde for the pharmaceutical industry.<sup>40</sup> Yet, syringaldehyde was also produced in  
 28 low yield in this study (<0.5 wt%).

29 HTL of veratraldehyde and vanillin is suggested to proceed through a set of reactions with catechol as final  
 30 product and e.g., vanillic acid, guaiacol, and 1,2-dimethoxybenzene as intermediate products, with all

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)


**When citing, please refer to the published version.**

1 intermediates present after 6 min reaction time at 350 °C.<sup>10</sup> This suggests that the observed trends in  
2 temperature-dependent concentrations of aryl aldehydes, methoxyphenols, methoxybenzenes, and  
3 catechols (Figure 5) are results of reaction kinetics rather than change in depolymerization mechanisms.  
4 The trends of lignin depolymerization into methoxyphenols and catechols observed here are in agreement  
5 with a kinetic study by Forchheim et al.<sup>41</sup>

6 Lui et al.<sup>10</sup> demonstrated that alkaline HTL of a  $\beta$ -O-4 model compound resulted in a phenol and an aryl  
7 ketone. In the present work, the quantity of aryl ketones was found to decrease with temperature,  
8 proportional to aryl aldehydes (*Miscanthus*  $r^2 = 0.96$ ,  $n = 5$ ; wheat straw  $r^2 = 0.99$ ,  $n = 6$ ). This indicates a  
9 common reaction mechanism for aryl aldehydes and aryl ketones. A common mechanism for removal of  
10 the aryl carbonyls during HTL has not yet been identified.<sup>10,33,42-43</sup>

11 However, aryl ketones have been found likely to engage in repolymerization, and aryl carbonyls in general  
12 can dimerize through aldol addition, reducing their monomer concentration.<sup>15,33,43</sup> A lower yield of total  
13 quantified monomer aromatics is observed at 345 °C compared to 300 °C, supporting repolymerization and  
14 dimerization as explanations for lower levels of aryl ketones and aryl carbonyls at higher temperatures.  
15 Note that the yields of LP increase and CML decrease from 300 °C to 345 °C, which appear to be due to  
16 increased dimerization (Figure S2) while depolymerization of the lignin/CML continues.

17 Isomerization of alkylphenols and alkylcatechols was observed at 345 °C, resulting in a more diverse and  
18 complex LP composition. Increased rate of alkylation reactions was seen at 345 °C from the large increase  
19 of “other catechols” (Table S5), which are C<sub>2</sub>-catechols (3/5-ethyl and dimethyl) and C<sub>3</sub>-catechols (3/4/5-  
20 propyl and combinations of methyls and ethyls). However, assigning isomer identification to individual  
21 alkylcatechol peaks was not possible due to very similar mass spectra. Multiple alkylated phenols and  
22 catechols were also reported from HTL of *Miscanthus* at 338 °C.<sup>46</sup> In addition, extensive  
23 demethylation/demethoxylation of aromatic methoxy groups was observed at 345 °C, as seen from the  
24 near-zero yields of methoxybenzenes, guaiacols, syringol and 3-methoxycatechol.

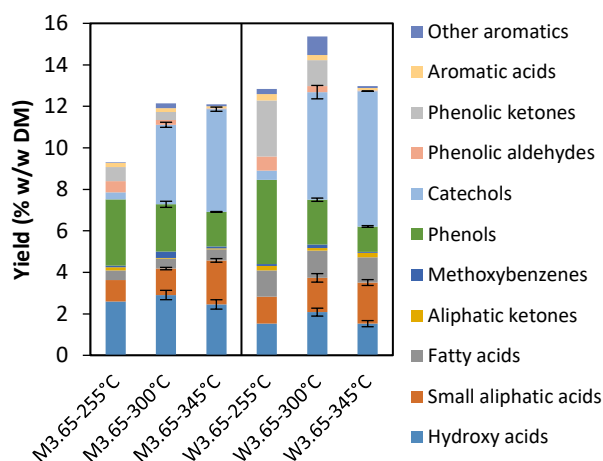

25

26 Figure 5. Yield (% w/w dry matter of EnzHR) of groups of monomeric compounds in the HTL  
27 temperature study. Standard deviations are only shown for selected groups for clarity.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

## 1 *Characterization of high molar mass fractions (Part I)*

2 The weight loss from volatilization and pyrolysis of the CML and SR was investigated using TGA.  
3 Additionally, chemical features of the volatile and thermally degradable organics of the HTL fractions were  
4 investigated by stepwise TD-Py-GC-MS. Figure 2 shows TGA-curves for a CML sample for each biomass and  
5 HTL temperature. Additionally, all CML and SR TGA-curves and differential TGA-curves are included in the  
6 electronic Supporting Information (Figure S5 and S6).

7 The pyrolytic mass loss of the CML from the control experiment W3.65-20 was significantly larger and  
8 initiated at a lower temperature than for the CMLs after HTL. Additionally, thermal stability of the CML  
9 appears to be higher after HTL at 345 °C than the lower HTL temperatures. The increased thermal stability  
10 after HTL is likely a result of a more condensed structure. Lignin requires thermal stabilization prior to  
11 pyrolytic conversion into carbon fibers.<sup>6</sup> The lignin HTL products could be candidates for feedstock for  
12 carbon fiber production. Additionally, increased thermal stability could be beneficial for using the lignin HTL  
13 products for adhesives in materials where pyrolytic conditions can occur during a fire.

14 TGA of SR was only possible for M3.65-255 and W3.65-20 due to low SR yield in the other experiments in  
15 Part I. The differential TGA-curves showed a simple mass loss pattern with a large mass loss within a narrow  
16 temperature interval with a maximum at 345 °C and a less distinct mass loss over a wider temperature  
17 interval with maximum at 410 °C. Similar mass loss characteristics are observed for extracted  $\alpha$ -cellulose  
18 and Klason lignin, respectively.<sup>47</sup> The presence of a characteristic cellulose mass loss in one or more  
19 fractions of the control experiment was expected due to the glucan content of the EnzHR. It is more  
20 surprising that cellulose appears not to have depolymerized completely during HTL at 255 °C, since  
21 carbohydrates are generally hydrolyzed above 140 °C at alkaline conditions.<sup>48</sup> Stepwise TD-Py-GC-MS found  
22 aromatic pyrolysates alongside a dominating levoglucosan (cellulose pyrolysate) presence in the SR of both  
23 M3.65-255 and W3.65-20. It would consequently appear that the SR fraction from HTL of EnzHR at 255 °C  
24 mainly contains unconverted or partly converted cellulose with a trace of lignin-like polymers.

## 25 *Effects of biomass pretreatment severity on HTL of EnzHR (Part II)*

26 The analytical approach for studying the effects of biomass pretreatment severity was focused on fewer  
27 methods based on the observations from Part I. Quantification of monomers was performed using GC-MS,  
28 molar mass distributions were determined by SEC, and chemical features of the CML fraction were  
29 investigated by single-step Py-GC-MS. HTL at 300 °C was chosen for the study of potential effects of  
30 biomass pretreatment severity on the HTL products, based on the maximum yield of total monomeric  
31 aromatics and the bifunctional catechol. Also, optimization of yields of high-value compounds (e.g. vanillin  
32 and syringaldehyde) were not pursued due to the lack of selectivity within the parameter space of Part I.

## 33 *Quantification of monomers in LP (Part II)*


34 The yields of the 128 quantified compounds are listed in Table S6 and S7 on DM and lignin basis,  
35 respectively. The higher severity of biomass pretreatment resulted in lower abundance of hydroxy acids  
36 and higher abundance of fatty acids and aromatics in the HTL product. The hydroxy acids likely derived  
37 from carbohydrates since the yields correlate with cellulose and hemicellulose content of the EnzHR (Figure  
38 S8,  $r^2 = 0.82$ ,  $n = 9$  and  $r^2 = 0.94$ ,  $n = 9$ , respectively). The higher abundance of fatty acids is likely a result of  
39 an increase in relative abundance of extractives in the EnzHR due to lower residual carbohydrate content at  
40 higher pretreatment severity. The higher yield of aromatics on DM basis at higher pretreatment severity  
41 will at least partly be a result of the higher lignin content of the EnzHR. Consequently, the yields of

*This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)*

***When citing, please refer to the published version.***

1 aromatics will in the following be discussed on lignin basis in order to explore the effects of biomass  
2 pretreatment severity on HTL of the lignin. The yields of aromatics are summarized in Figure 6 as grouped  
3 yields on lignin basis. Regardless of pretreatment severity, *Miscanthus* EnzHR produced more phenol, *p*-  
4 cresol and 4-ethylphenol than wheat straw, which in turn produced more acetosyringone than *Miscanthus*.  
5 The data from single-step Py-GC-MS (see below) indicate that it is at least partly a result of differences in H  
6 and S monolignol content. Catechols (except 3-methoxycatechol) and methoxybenzenes were found in  
7 higher yields at the low severity. The phenolic aryl carbonyls, other aromatics, and likely also phenols were  
8 not sensitive to pretreatment severity.

9 Figure 6 shows that HTL of wheat straw and *Miscanthus* EnzHRs hydrothermally pretreated at log  $R_0$  3.65  
10 resulted in higher yield of monomeric aromatics on lignin basis, and hence, more effective lignin  
11 depolymerization, than pretreated at log  $R_0$  3.97. The less effective depolymerization at log  $R_0$  3.97 is likely  
12 a result of fewer ether and more C-C bonds in the more severely pretreated lignin. This shows that lignin  
13 depolymerization is affected by changing pretreatment severity within even a narrow range. Choosing  
14 pretreatment severity would thus become a matter of whether the most effective lignin depolymerization  
15 (log  $R_0$  3.65) or a more concentrated aromatic product fraction (log  $R_0$  3.97) is best for the direct use (e.g.  
16 resin) or cost of purification of the HTL product. The aromatic monomer yield trend is in contrast to the  
17 observed lowest glucose yields by enzymatic hydrolysis for the log  $R_0$  3.65 pretreated biomasses of this  
18 study.<sup>23</sup> Furthermore, conversion of wheat-straw cellulose into ethanol increases with increased severity in  
19 the log  $R_0$  3.28–3.88 range.<sup>49</sup>

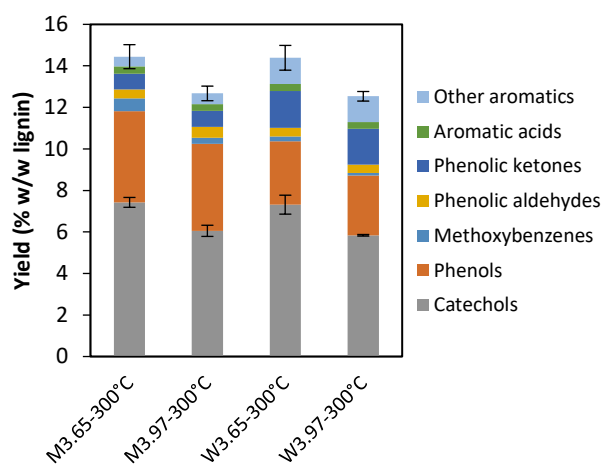

20  
21 Figure 6. Yield (% w/w lignin (AIL+ASL) of EnzHR) of compounds in the HTL study of biomass  
22 pretreatment effects. Standard deviations are shown for catechols and the total sum.

### 23 *Characterization of CML fraction (Part II)*

24 Single-step Py-GC-MS of the high molecular weight fraction, CML, (Table 2) gave additional information and  
25 confirmed trends seen from GC-MS of the LP. The higher severity of biomass pretreatment resulted in  
26 higher abundance of extractives in the HTL product, supporting the higher fatty acid content found in the  
27 LP from HTL of the log  $R_0$  3.97 pretreated biomasses. The lower yield of monomeric aromatics on lignin  
28 basis at higher pretreatment severity (Figure 6) was mirrored by a seemingly higher abundance of aromatic

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 pyrolysates in the corresponding CML fraction. However, the aromatic results are inconclusive due to the  
2 larger uncertainty of the Py-GC-MS results.

3 HTL resulted in a clear decrease in the abundance of pyrolysates produced from native biomass molecules  
4 (carbohydrates, lignols and hydroxycinnamic acids). An almost complete disappearance of native lignin  
5 structure and hydroxycinnamic acids after HTL has been reported for Protobind 1000 and Lignoboost  
6 lignins.<sup>15,50</sup> An increased abundance of aromatic nitrogen pyrolysates was observed after HTL, which  
7 requires further investigation, yet, could be a result of reaction between protein and lignocellulose.<sup>51</sup>

8 HTL could result in isomerization of aliphatic substituents on the phenyl ring of the macromolecular HTL  
9 products due to repolymerization, in addition to the isomerization of monomeric aromatics observed in  
10 Part I. A previous Py-GC-MS study in our group found that *ortho*-directed reactions are important for  
11 repolymerization during HTL.<sup>15</sup> Here HTL appears to increase the relative abundance of *o*-isomers and  
12 decrease the *p*-isomers in CML when including all types of aliphatic substituents (*ortho*-Ph% and *para*-Ph%).  
13 However, this calculation contains a much larger number of *p*-compounds than *o*-compounds due the  
14 native structure of lignin. The results are ambiguous when calculating the *o/p*-ratio using only the *o*-alkyl  
15 phenolics and their corresponding *p*-isomer (*o/p*-subgroup). The near equal *o/p*-subgroup ratios after HTL  
16 could be a result of loss of alkyl substituents followed by both *p*- and *o*-directed repolymerization after  
17 HTL.<sup>51</sup>

18 HTL of EnzHR resulted in higher H and lower S abundance of the CML fraction compared to the control  
19 CML. This could be due to more repolymerization of H units compared to G and S, as well as more efficient  
20 depolymerization of the S units that have fewer interunit C-C bonds in the native lignin.<sup>15,19</sup> *Miscanthus*  
21 CML was found to have higher H monomer content than wheat straw, both before and after HTL.  
22 Pretreatment severity did not affect the post-HTL H/G/S ratios significantly in the CML fraction.

### 23 Implications for biorefining

24 The results of this study show that plant species and pretreatment severity will affect the HTL product  
25 composition and lignin depolymerization. These parameters are important choices for processes upstream  
26 of HTL, and should consequently be considered carefully for a biorefinery concept based on lignin  
27 valorization of enzymatic hydrolysis residue by HTL. The trends seen by varying HTL temperature were  
28 generally in agreement with previous results from HTL of other biorefinery lignins.<sup>19</sup> Additional information  
29 was found on temperature dependency of non-lignin products and alkylation of aromatics. *Miscanthus* and  
30 wheat straw showed differences in temperature-dependent behavior. *Miscanthus* and wheat straw yielded  
31 on lignin basis equal amounts, yet different distributions, of monomeric aromatics at 300 °C. Lignin  
32 depolymerization during HTL was more effective for both biomasses when pretreated at log  $R_0$  3.65 than  
33 3.97. This shows that biomass pretreatment severity must be taken into account for the optimization of  
34 lignin depolymerization. Additionally, it suggests that pretreatment severity for optimal lignin  
35 depolymerization has the opposite trend compared to cellulose conversion into bioethanol. Consequently,  
36 it will be necessary in a future biorefinery to identify the overall optimal pretreatment conditions for  
37 obtaining maximum value of the entire biomass by balancing yields of ethanol and aromatics.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**



1 Table 2. Summary of results (peak areas) from single-step Py-GC-MS of CML fractions from HTL and control  
 2 experiments.

	M3.65-20°C	W3.65-20°C	M3.65-300°C	M3.97-300°C	W3.65-300°C	W3.97-300°C
<i>Pyrolysates</i>						
Carbohydrate	+	+	-	-	-	-
Lignols	+++	+++	+	+	+	+
Hydroxycinnamic acids	++++	++++	+	+	+	+
Aromatic N	+	+	+++	+++	+++	+++
Extractives	++	++++	+++	++++	+	++
Catechols	++	++	+(+)	++	+(+)	++
Phenols	++++	++++	+(+)	++	+(+)	++
Methoxybenzenes	++	+	+++(+)	++++	+++(+)	+++
Ph-aryl carbonyls	++++	++++	+	+	+	+
<i>Phenolic R-isomers</i>						
<i>meta</i> -Ph%	1.8 ± 0.1	2.4 ± 0.2	1.8 ± 0.01	1.9 ± 0.2	2.1 ± 0.2	2.1 ± 0.3
<i>ortho</i> -Ph%	2.4 ± 0.4	2.9 ± 0.7	16.2 ± 0.2	19.1 ± 0.8	16.7 ± 1.0	17.1 ± 0.5
<i>para</i> -Ph%	95.7 ± 0.5	94.7 ± 1.0	82.0 ± 0.2	79.1 ± 0.7	81.2 ± 1.1	80.9 ± 0.5
<i>o/p</i> -subgroup*	0.29 ± 0.004	0.43 ± 0.001	0.35 ± 0.004	0.38 ± 0.012	0.34 ± 0.023	0.35 ± 0.011
<i>Monomer ratios</i>						
H%	16.6 ± 1.7	11.8 ± 2.3	52.6 ± 1.5	52.8 ± 2.8	46.2 ± 2.1	42.6 ± 1.9
G%	51.6 ± 0.03	52.1 ± 0.5	44.5 ± 1.3	44.9 ± 2.5	49.3 ± 1.9	52.8 ± 0.7
S%	31.9 ± 1.7	36.1 ± 2.9	2.9 ± 0.2	2.3 ± 0.4	4.6 ± 0.6	4.7 ± 1.4

3 The symbolic scale (number of +) is based on pyrolysate peak areas and is relative within each row, i.e., ++  
 4 in phenols and catechols are not equal. Parentheses emphasize uncertainty.

5 \*Calculated as the ratio between the *o*-phenolic pyrolysates and their corresponding *p*-isomer,  $n_o = 4$ ,  $n_p =$   
 6 4.

### 7 Acknowledgements

8 This study was funded by the BioValue SPIR, Strategic Platform for Innovation and Research on value added  
 9 products from biomass, which is co-funded by The Innovation Fund Denmark, case no: 0603-00522B and  
 10 carried under the auspices of the Aarhus University Centre for Circular Bioeconomy.

### 11 Supporting Information

12 Detailed experimental procedures. BHT content of CML fractions. SEC results. Yields of quantified  
 13 monomeric compounds on both DM and lignin basis. TGA and differential TGA curves, including a figure of  
 14 combining TGA and stepwise TD-Py-GC-MS results. Linear regressions of fraction and compound yields as  
 15 functions of biopolymer contents. Results of single-step Py-GC-MS, including pyrolysate categorization and  
 16 RI for improved identification of pyrolysates.

### 17 References

- 18 1. Larsen, J.; Haven, M. O.; Thirup, L., Inbicon makes lignocellulosic ethanol a commercial reality.  
 19 *Biomass Bioenerg* **2012**, *46*, 36-45. DOI 10.1016/j.biombioe.2012.03.033
- 20 2. Deswarte, F. E. I.; Clark, J. H.; Hardy, J. J. E.; Rose, P. M., The fractionation of valuable wax products  
 21 from wheat straw using CO<sub>2</sub>. *Green Chem* **2006**, *8* (1), 39-42. DOI 10.1039/B514978A
- 22 3. Brosse, N.; Dufour, A.; Meng, X.; Sun, Q.; Ragauskas, A., Miscanthus: a fast-growing crop for biofuels  
 23 and chemicals production. *Biofuels, Bioproducts and Biorefining* **2012**, *6* (5), 580-598. DOI 10.1002/bbb.1353
- 24 4. Sjöström, E., *Wood chemistry : fundamentals and applications*. 2nd ed.; Academic Press: San Diego,  
 25 1993.
- 26 5. Azadi, P.; Inderwildi, O. R.; Farnood, R.; King, D. A., Liquid fuels, hydrogen and chemicals from lignin:  
 27 A critical review. *Renew Sust Energ Rev* **2013**, *21*, 506-523. DOI 10.1016/j.rser.2012.12.022

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

- 1 6. Ragauskas, A. J.; Beckham, G. T.; Biddy, M. J.; Chandra, R.; Chen, F.; Davis, M. F.; Davison, B. H.; Dixon,  
2 R. A.; Gilna, P.; Keller, M.; Langan, P.; Naskar, A. K.; Saddler, J. N.; Tschaplinski, T. J.; Tuskan, G. A.; Wyman, C.  
3 E., Lignin Valorization: Improving Lignin Processing in the Biorefinery. *Science* **2014**, *344* (6185), 1246843.  
4 DOI 10.1126/science.1246843
- 5 7. Gosselink, R. J. A.; de Jong, E.; Guran, B.; Abächerli, A., Co-ordination network for lignin—  
6 standardisation, production and applications adapted to market requirements (EUROLIGNIN). *Industrial*  
7 *Crops and Products* **2004**, *20* (2), 121-129. DOI 10.1016/j.indcrop.2004.04.015
- 8 8. Peterson, A. A.; Vogel, F.; Lachance, R. P.; Froling, M.; Antal, M. J.; Tester, J. W., Thermochemical  
9 biofuel production in hydrothermal media: A review of sub- and supercritical water technologies. *Energ*  
10 *Environ Sci* **2008**, *1* (1), 32-65. DOI 10.1039/b810100k
- 11 9. Kruse, A.; Dinjus, E., Hot compressed water as reaction medium and reactant - Properties and  
12 synthesis reactions. *J Supercrit Fluid* **2007**, *39* (3), 362-380. DOI 10.1016/j.supflu.2006.03.016
- 13 10. Lui, M. Y.; Chan, B.; Yuen, A. K. L.; Masters, A. F.; Montoya, A.; Maschmeyer, T., Unravelling Some of  
14 the Key Transformations in the Hydrothermal Liquefaction of Lignin. *Chemsuschem* **2017**, *10* (10), 2140-2144.  
15 DOI 10.1002/cssc.201700528
- 16 11. Dos Santos, P. S. B.; Erdocia, X.; Gatto, D. A.; Labidi, J., Bio-oil from base-catalyzed depolymerization  
17 of organosolv lignin as an antifungal agent for wood. *Wood Science and Technology* **2016**, *50* (3), 599-615.  
18 DOI 10.1007/s00226-015-0795-8
- 19 12. Chen, H. Z.; Li, Z. Y.; Liu, X. Y.; Tian, Y. M.; Yang, L.; Wang, Z. C., Depolymerization of renewable  
20 resources-lignin by sodium hydroxide as a catalyst and its applications to epoxy resin. *J Appl Polym Sci* **2015**,  
21 *132* (26). DOI 10.1002/app.42176
- 22 13. Rinaldi, R.; Jastrzebski, R.; Clough, M. T.; Ralph, J.; Kennema, M.; Bruijninx, P. C. A.; Weckhuysen, B.  
23 M., Paving the Way for Lignin Valorisation: Recent Advances in Bioengineering, Biorefining and Catalysis.  
24 *Angew Chem Int Edit* **2016**, *55* (29), 8164-8215. DOI 10.1002/anie.201510351
- 25 14. Kozliak, E. I.; Kubatova, A.; Artemyeva, A. A.; Nagel, E.; Zhang, C.; Rajappagowda, R. B.; Srnirnova, A.  
26 L., Thermal Liquefaction of Lignin to Aromatics: Efficiency, Selectivity, and Product Analysis. *Acs Sustain Chem*  
27 *Eng* **2016**, *4* (10), 5106-5122. DOI 10.1021/acssuschemeng.6b01046
- 28 15. Jensen, M. M.; Madsen, R. B.; Becker, J.; Iversen, B. B.; Glasius, M., Products of hydrothermal  
29 treatment of lignin and the importance of ortho-directed repolymerization reactions. *J Anal Appl Pyrol* **2017**,  
30 *126*, 371-379. DOI 10.1016/j.jaap.2017.05.009
- 31 16. Nguyen, T. D. H.; Maschietti, M.; Belkheiri, T.; Amand, L. E.; Theliander, H.; Vamling, L.; Olausson, L.;  
32 Andersson, S. I., Catalytic depolymerisation and conversion of Kraft lignin into liquid products using near-  
33 critical water. *J Supercrit Fluid* **2014**, *86*, 67-75. DOI 10.1016/j.supflu.2013.11.022
- 34 17. Zhang, B.; Huang, H. J.; Ramaswamy, S., Reaction kinetics of the hydrothermal treatment of lignin.  
35 *Appl Biochem Biotech* **2008**, *147* (1-3), 119-131. DOI 10.1007/s12010-007-8070-6
- 36 18. Erdocia, X.; Prado, R.; Corcuera, M. A.; Labidi, J., Base catalyzed depolymerization of lignin: Influence  
37 of organosolv lignin nature. *Biomass Bioenerg* **2014**, *66*, 379-386. DOI 10.1016/j.biombioe.2014.03.021
- 38 19. Katahira, R.; Mittal, A.; McKinney, K.; Chen, X. W.; Tucker, M. P.; Johnson, D. K.; Beckham, G. T., Base-  
39 Catalyzed Depolymerization of Biorefinery Lignins. *Acs Sustain Chem Eng* **2016**, *4* (3), 1474-1486. DOI  
40 10.1021/acssuschemeng.5b01451
- 41 20. Betarenewables website <http://betarenewables.com/en>. (accessed 11 Oct 2017).
- 42 21. Jensen, A.; Cabrera, Y.; Hsieh, C.-W.; Nielsen, J.; Ralph, J.; Felby, C., 2D NMR characterization of wheat  
43 straw residual lignin after dilute acid pretreatment with different severities. *Holzforschung* **2017**, *71* (6), 461.  
44 DOI 10.1515/hf-2016-0112
- 45 22. Li, J.; Henriksson, G.; Gellerstedt, G., Lignin depolymerization/repolymerization and its critical role  
46 for delignification of aspen wood by steam explosion. *Bioresource Technol* **2007**, *98* (16), 3061-3068. DOI  
47 10.1016/j.biortech.2006.10.018

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

- 1 23. Djajadi, D. T.; Hansen, A. R.; Jensen, A.; Thygesen, L. G.; Pinelo, M.; Meyer, A. S.; Jørgensen, H.,  
2 Surface properties correlate to the digestibility of hydrothermally pretreated lignocellulosic Poaceae biomass  
3 feedstocks. *Biotechnology for Biofuels* **2017**, *10* (1), 49. DOI 10.1186/s13068-017-0730-3
- 4 24. Rahikainen, J.; Mikander, S.; Marjamaa, K.; Tamminen, T.; Lappas, A.; Viikari, L.; Kruus, K., Inhibition  
5 of enzymatic hydrolysis by residual lignins from softwood—study of enzyme binding and inactivation on  
6 lignin-rich surface. *Biotechnol Bioeng* **2011**, *108*. DOI 10.1002/bit.23242
- 7 25. Overend, R. P.; Chornet, E., Fractionation of Lignocellulosics by Steam-Aqueous Pretreatments. *Philos*  
8 *T R Soc A* **1987**, *321* (1561), 523-536. DOI 10.1098/rsta.1987.0029
- 9 26. Johnsen, L. G.; Skou, P. B.; Khakimov, B.; Bro, R., Gas chromatography - mass spectrometry data  
10 processing made easy. *J Chromatogr A* **2017**, *1503*, 57-64. DOI 10.1016/j.chroma.2017.04.052
- 11 27. Torri, C.; Alba, L. G.; Samori, C.; Fabbri, D.; Brillman, D. W. F., Hydrothermal Treatment (HTT) of  
12 Microalgae: Detailed Molecular Characterization of HTT Oil in View of HTT Mechanism Elucidation. *Energ Fuel*  
13 **2012**, *26* (1), 658-671. DOI 10.1021/ef201417e
- 14 28. Torri, C.; Soragni, E.; Prati, S.; Fabbri, D., Py-SPME-GC-MS with on-fiber derivatization as a new  
15 solvent-less technique for the study of polar macromolecules: Application to natural gums. *Microchem J*  
16 **2013**, *110*, 719-725. DOI 10.1016/j.microc.2013.08.006
- 17 29. Torri, C.; Barreiro, D. L.; Conti, R.; Fabbri, D.; Brillman, W., Fast Procedure for the Analysis of  
18 Hydrothermal Liquefaction Biocrude with Stepwise Py-GC-MS and Data Interpretation Assisted by Means of  
19 Non-negative Matrix Factorization. *Energ Fuel* **2016**, *30* (2), 1135-1144. DOI  
20 10.1021/acs.energyfuels.5b02688
- 21 30. Ralph, J.; Hatfield, R. D., Pyrolysis-Gc-Ms Characterization of Forage Materials. *J Agr Food Chem* **1991**,  
22 *39* (8), 1426-1437. DOI 10.1021/jf00008a014
- 23 31. Thring, R. W., Alkaline-Degradation of Alcell(R) Lignin. *Biomass Bioenerg* **1994**, *7* (1-6), 125-130. DOI  
24 Doi 10.1016/0961-9534(94)00051-T
- 25 32. Mahmood, N.; Yuan, Z. S.; Schmidt, J.; Xu, C. B., Production of polyols via direct hydrolysis of kraft  
26 lignin: Effect of process parameters. *Bioresource Technol* **2013**, *139*, 13-20. DOI  
27 10.1016/j.biortech.2013.03.199
- 28 33. Roberts, V. M.; Stein, V.; Reiner, T.; Lemonidou, A.; Li, X. B.; Lercher, J. A., Towards Quantitative  
29 Catalytic Lignin Depolymerization. *Chem-Eur J* **2011**, *17* (21), 5939-5948. DOI 10.1002/chem.201002438
- 30 34. Beauchet, R.; Monteil-Rivera, F.; Lavoie, J. M., Conversion of lignin to aromatic-based chemicals (L-  
31 chems) and biofuels (L-fuels). *Bioresource Technol* **2012**, *121* (Supplement C), 328-334. DOI  
32 <https://doi.org/10.1016/j.biortech.2012.06.061>
- 33 35. Teri, G.; Luo, L.; Savage, P. E., Hydrothermal Treatment of Protein, Polysaccharide, and Lipids Alone  
34 and in Mixtures. *Energ Fuel* **2014**, *28* (12), 7501-7509. DOI 10.1021/ef501760d
- 35 36. Yong, T. L. K.; Matsumura, Y., Kinetic Analysis of Lignin Hydrothermal Conversion in Sub- and  
36 Supercritical Water. *Ind Eng Chem Res* **2013**, *52* (16), 5626-5639. DOI 10.1021/ie400600x
- 37 37. Karagoz, S.; Bhaskar, T.; Muto, A.; Sakata, Y., Comparative studies of oil compositions produced from  
38 sawdust, rice husk, lignin and cellulose by hydrothermal treatment. *Fuel* **2005**, *84* (7-8), 875-884. DOI  
39 10.1016/j.fuel.2005.01.004
- 40 38. Hidajat, M. J.; Riaz, A.; Park, J.; Insyani, R.; Verma, D.; Kim, J., Depolymerization of concentrated  
41 sulfuric acid hydrolysis lignin to high-yield aromatic monomers in basic sub- and supercritical fluids. *Chem*  
42 *Eng J* **2017**, *317*, 9-19. DOI 10.1016/j.cej.2017.02.045
- 43 39. Fiege, H.; Voges, H.-W.; Hamamoto, T.; Umemura, S.; Iwata, T.; Miki, H.; Fujita, Y.; Buysch, H.-J.;  
44 Garbe, D.; Paulus, W., Phenol Derivatives. In *Ullmann's Encyclopedia of Industrial Chemistry*, Wiley-VCH  
45 Verlag GmbH & Co. KGaA: Weinheim, 2000. DOI 10.1002/14356007.a19\_313
- 46 40. Erofeev, Y. V.; Afanas'eva, V. L.; Glushkov, R. G., Synthetic routes to 3,4,5-trimethoxybenzaldehyde  
47 (review). *Pharmaceutical Chemistry Journal* **1990**, *24* (7), 501-510. DOI 10.1007/bf00765001

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**


- 1 41. Forchheim, D.; Hornung, U.; Kruse, A.; Sutter, T., Kinetic Modelling of Hydrothermal Lignin  
2 Depolymerisation. *Waste Biomass Valori* **2014**, *5* (6), 985-994. DOI 10.1007/s12649-014-9307-6
- 3 42. Barbier, J.; Charon, N.; Dupassieux, N.; Loppinet-Serani, A.; Mahe, L.; Ponthus, J.; Courtiade, M.;  
4 Ducrozet, A.; Quoineaud, A. A.; Cansell, F., Hydrothermal conversion of lignin compounds. A detailed study  
5 of fragmentation and condensation reaction pathways. *Biomass Bioenerg* **2012**, *46*, 479-491. DOI  
6 10.1016/j.biombioe.2012.07.011
- 7 43. Lankau, T.; Yu, C. H., Intermediate oxiranes in the base-catalyzed depolymerisation of lignin. *Green*  
8 *Chem* **2016**, *18* (6), 1590-1596. DOI 10.1039/c5gc02192h
- 9 44. Schwenk, E.; Papa, D.; Whitman, B.; Ginsberg, H., Reductions with nickel-aluminum alloy and aqueous  
10 alkali Part II The displacement of groups by hydrogen. *J Org Chem* **1944**, *9* (1), 1-8. DOI 10.1021/jo01183a001
- 11 45. Fabos, V.; Yuen, A. K. L.; Masters, A. F.; Maschmeyer, T., The Role of the Reactor Wall in Hydrothermal  
12 Biomass Conversions. *Chem-Asian J* **2012**, *7* (11), 2638-2643. DOI 10.1002/asia.201200556
- 13 46. Madsen, R. B.; Zhang, H.; Biller, P.; Goldstein, A. H.; Glasius, M., Characterizing Semivolatile Organic  
14 Compounds of Biocrude from Hydrothermal Liquefaction of Biomass. *Energ Fuel* **2017**, *31* (4), 4122-4134.  
15 DOI 10.1021/acs.energyfuels.7b00160
- 16 47. Carrier, M.; Loppinet-Serani, A.; Denux, D.; Lasnier, J. M.; Ham-Pichavant, F.; Cansell, F.; Aymonier,  
17 C., Thermogravimetric analysis as a new method to determine the lignocellulosic composition of biomass.  
18 *Biomass Bioenerg* **2011**, *35* (1), 298-307. DOI 10.1016/j.biombioe.2010.08.067
- 19 48. Bouvier, J. M.; Gelus, M.; Maugendre, S., Wood liquefaction—An overview. *Applied Energy* **1988**, *30*  
20 (2), 85-98. DOI 10.1016/0306-2619(88)90006-2
- 21 49. Petersen, M. Ø.; Larsen, J.; Thomsen, M. H., Optimization of hydrothermal pretreatment of wheat  
22 straw for production of bioethanol at low water consumption without addition of chemicals. *Biomass and*  
23 *Bioenergy* **2009**, *33* (5), 834-840. DOI 10.1016/j.biombioe.2009.01.004
- 24 50. Mattsson, C.; Andersson, S.-I.; Belkheiri, T.; Åmand, L.-E.; Olausson, L.; Vamling, L.; Theliander, H.,  
25 Using 2D NMR to characterize the structure of the low and high molecular weight fractions of bio-oil obtained  
26 from LignoBoost™ kraft lignin depolymerized in subcritical water. *Biomass and Bioenergy* **2016**, *95*, 364-377.  
27 DOI 10.1016/j.biombioe.2016.09.004
- 28 51. Madsen, R. B.; Jensen, M. M.; Glasius, M., Qualitative characterization of solid residue from  
29 hydrothermal liquefaction of biomass using thermochemolysis and stepwise pyrolysis-gas chromatography-  
30 mass spectrometry. *Sustainable Energy & Fuels* **2017**. DOI 10.1039/C7SE00357A
- 31  
32

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**

1 **Synopsis:** Hydrothermal pretreatment severity in second-generation bioethanol production affects  
2 subsequent depolymerization of lignin and yield of products.

3

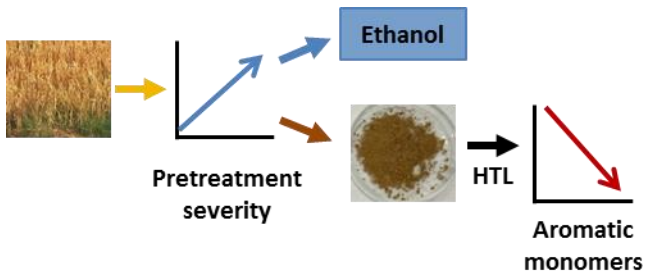

4

5 "For Table of Contents Use Only"

6

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

**When citing, please refer to the published version.**