

Alma Mater Studiorum Università di Bologna
Archivio istituzionale della ricerca

Effect of Particle Functionalization on Structural and Dielectric Properties of Flexible TPU/BaTiO₃/MWCNTs Composite Films

This is the final peer-reviewed author's accepted manuscript (postprint) of the following publication:

Published Version:

Stojchevska E., Popeski-Dimovski R., Kokolanski Z., Gualandi C., Buzarovska A. (2023). Effect of Particle Functionalization on Structural and Dielectric Properties of Flexible TPU/BaTiO₃/MWCNTs Composite Films. *MACROMOLECULAR CHEMISTRY AND PHYSICS*, 224(5), 1-9 [10.1002/macp.202200401].

Availability:

This version is available at: <https://hdl.handle.net/11585/926776> since: 2023-05-25

Published:

DOI: <http://doi.org/10.1002/macp.202200401>

Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>).
When citing, please refer to the published version.

(Article begins on next page)

This is the final peer-reviewed accepted manuscript of:

Stojchevska, E., Popeski-Dimovski, R., Kokolanski, Ž., Gualandi, C., & Bužarovska, A.

(2023). Effect of Particle Functionalization on Structural and Dielectric

Properties of Flexible TPU/BaTiO₃/MWCNTs Composite Films.

Macromolecular Chemistry and Physics, 224(5), 2200401.

The final published version is available online at:

<https://doi.org/10.1002/macp.202200401>

Terms of use:

Some rights reserved. The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

This item was downloaded from IRIS Università di Bologna (<https://cris.unibo.it/>)

When citing, please refer to the published version.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Effect of Particle Functionalization on Structural and Dielectric Properties of Flexible TPU/BaTiO₃/MWCNTs Composite Films

E. Stojchevska, R. Popeski-Dimovski, Ž. Kokolanski, C. Gualandi, A. Bužarovska**

E. Stojchevska, A. Bužarovska

Ss Cyril and Methodius University, Faculty of Technology and Metallurgy, Rudjer Boskovic
16, 1000 Skopje, N. Macedonia

E-mail: abuzar@tmf.ukim.edu.mk

R. Popeski-Dimovski

Ss Cyril and Methodius University, Faculty for Natural sciences and Mathematics, Institute of
Physics, Arhimedova 3, 1000 Skopje, N. Macedonia

Ž. Kokolanski

Ss Cyril and Methodius University, Faculty of Electrical Engineering and information
technologies, Rudjer Boskovic 16, 1000 Skopje, N. Macedonia

C. Gualandi

Department of Chemistry “Giacomo Ciamician” and INSTM UdR of Bologna, University of
Bologna, Via Selmi, 2, 40126 Bologna, Italy

E-mail: c.gualandi@unibo.it

Keywords: thermoplastic polyurethane, barium titanate, MWCNTs, surface functionalization,
dielectric materials

Abstract

Flexible, low-cost thermoplastic polyurethane (TPU) composite films with functionalized BaTiO₃ (BT) and multiwall carbon nanotubes (MWCNTs) are prepared by solution casting method and tested as dielectric materials. Different volume content loadings of BT filler (between 10 and 80 vol%) and 0.12 vol% of MWCNTs are applied. The effects of particle functionalization and BT content on the structural, mechanical and energy storage properties are studied by Fourier infrared spectroscopy (FTIR), differential scanning calorimetry (DSC), as well as puncture and dielectric measurements. It is found that the particle functionalization

and BT content significantly affect the hydrogen bonding within the polymer matrix, and have a huge impact on the mechanical and dielectric properties. The optimal concentration (30 vol% functionalized BT and 0.12 vol% of functionalized MWCNTs) giving the highest dielectric constant of 30.28 and dielectric breakdown strength of 42 kV/mm is determined.

1. Introduction

The rapid development of various technologies for the production of electricity from renewable energy sources has imposed the need for new energy storage devices. Dielectrics, able to store electrical energy as a consequence of polarization under an external electric field, are the core materials of some kinds of energy storage devices, such as capacitors. To achieve high energy storage density, several key parameters, such as high dielectric constants, high breakdown strength, and low dielectric losses, are needed. Following the constant demand, current scientific research is devoted to developing cheap, easily processable and high dielectric constant materials.

In this context, ferroelectric ceramics have already been proven as excellent dielectric materials due to their high dielectric constants and capability of storing a large amount of electricity. However, a wider use of ceramic materials is limited due to their brittleness, relatively low breakdown strength and high dielectric losses. On the other hand, polymers as easy processable materials are characterized by low dielectric losses, high breakdown strength and flexibility, but they possess very low dielectric constants. Consequently, the introduction of ceramic particles into a polymer matrix is a good strategy to integrate the advantages of both materials in order to develop highly flexible composites with desired dielectric properties.^[1] Numerous composites based on various polymer ferroelectric matrices, such as poly(vinylidene fluoride) (PVDF), its copolymers and ceramic fillers with high dielectric constants, have been already developed and published.^[2-4] In spite of the relatively good characteristics of the ferroelectric polymers, their poor temperature stability and high price were the main reasons to develop composite materials based on non-ferroelectric polymer matrices and high dielectric constant ceramics in high loadings. In this context, various electrically inactive matrices such as poly(dimethylsiloxane), thermoplastic poly(urethanes), etc. have already been employed.^[5,6]

Thermoplastic poly(urethanes) (TPUs) are unique, linear block copolymers with high flexibility and excellent mechanical properties such as tensile strength, toughness and elongation at break.^[7] The different behaviour in TPUs arises from their dual-phase microstructure based on alternating hard and soft segments, depending on the type of

1 polyisocyanates, chain extenders and polyols or long polyesters. Therefore, the properties of
2 TPU can be controlled by adjusting the chemical structure and morphology of the segments.
3 This class of material is extensively used to prepare components for flexible devices and has
4 promising dielectric properties according to previous results^[8] and density functional theory.^[9]
5 Barium titanate (BaTiO₃, BT) is a widely used ceramic filler in different composites owing to
6 its high dielectric permittivity and high density. In comparison to all other ceramic fillers
7 based on lead, BaTiO₃ is an environmentally friendlier material. The dielectric properties of
8 BaTiO₃ were found to be highly affected by its particle size. Huan et al. have revealed that
9 BaTiO₃ with an average grain size of around 1 μm has increased dielectric constant,
10 piezoelectric coefficient and planar electromechanical coupling factor up to 6079, 519 pC/N
11 and 39.5%, respectively.^[10] Opposite to this, a lot of research papers have confirmed
12 increased dielectric properties with decreasing grain size.^[3] Besides the particle size, the
13 loading content is an additional important parameter when evaluating the dielectric properties.
14 Dielectric permittivity usually increases with BaTiO₃ loadings in corresponding composites,
15 but at the same time, the flexibility and breakdown strength of the polymer matrix
16 significantly decrease. Additionally, the weak interaction between the ceramic filler and the
17 polymer matrix might hamper the proper particle distribution within the polymer matrix and,
18 consequently, the improvement of the dielectric properties of the composite. Thus, numerous
19 efforts have been made to improve the interface between the ceramic filler and the polymer
20 matrix. The introduction of hydroxyl groups on the surface of BaTiO₃ particles with proper
21 functionalization treatment promoted the formation of chemical interactions with PVDF
22 matrix, leading to improved dielectric properties of the PVDF/BaTiO₃ composites.^[11]
23 The dielectric properties can be further improved by incorporating electrically conductive
24 nanofillers, such as carbon nanotubes (CNTs), graphene and different metal nanoparticles.^[12]
25 The main advantage of using conductive CNTs is that a conductive network for charge
26 transfer can be obtained by using a small amount of nanofiller, due to the large surface area
27 and aspect ratio.^[13] On the other hand, bare CNTs are easily disposed to aggregation, forming
28 bundles and making them difficult to use. To overcome this problem, proper functionalization
29 of CNTs with different acids introducing surface COOH groups was reported.^[14]
30 The aim of this research was to produce flexible, low-cost, thermoplastic
31 polyurethane/BaTiO₃/MWCNTs composite films with improved dielectric properties. The
32 BaTiO₃ ceramic filler and multiwall carbon nanotubes (MWCNTs) were properly
33 functionalized in order to promote better dispersion within the TPU polymer matrix and
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

investigate the possible formation of polymer-particles “network” and its influence on morphological, structural, mechanical and dielectric properties of the final composites.

2. Results and Discussion

2.1. Surface functionalization of BaTiO₃ and MWCNTs

The surface functionalization of BaTiO₃ and MWCNTs was performed in order to create a network of hydrogen bonds between -OH groups in BT, -COOH groups in MWCNT and urethane groups in TPU, to stabilize the regions at the interface between the different phases, improve the dispersibility of the fillers and enhance the dielectric properties of TPU composite films.

The proper functionalization of MWCNTs was investigated with UV/Vis spectroscopy.

Figure 1a reports the UV/Vis spectra of MWCNTs before and after nitric acid treatment. The strong absorption peak that appeared at 255 nm was characteristic of MWCNTs chemically modified with HNO₃,^[15] thus confirming the presence of attached -COOH groups. The FTIR spectra of unmodified and functionalized BaTiO₃ particles are presented in Figure 1b. Two new bands in the spectrum of functionalized BaTiO₃ were detected, positioned at 3220 cm⁻¹ and 1625 cm⁻¹ corresponding to the OH stretching and OH bending vibrations, thus confirming a successful attachment of -OH groups onto the surface of BaTiO₃ particles.

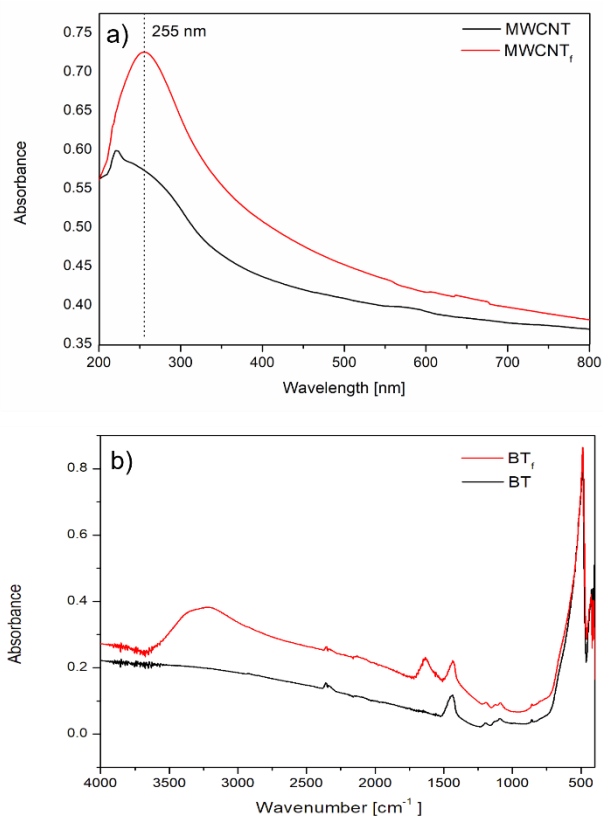


Figure 1. (a) UV/Vis spectra of functionalized MWCNTs and (b) FTIR spectra of functionalized BaTiO₃ particles.

2.2. Characterization of composite films

Composite samples with different content of fillers were prepared by solvent casting technique. Two series of composites were prepared: TPU/BaTiO₃, and TPU filled with functionalized BaTiO₃ and MWCNTs particles (**Table 1**).

Table 1. Samples abbreviation and composition of TPU and its composite films.

Sample code	BaTiO ₃ [vol%]	MWCNTs [vol%]
TPU	/	/
TPU/BT10	10	/
TPU/BT20	20	/
TPU/BT30	30	/
TPU/BT80	80	/
TPU/BT _f 10/MWCNT _f	10	0.12
TPU/BT _f 20/MWCNT _f	20	0.12
TPU/BT _f 30/MWCNT _f	30	0.12
TPU/BT _f 80/MWCNT _f	80	0.12

SEM analysis of film cross-sections was carried out to assess the distribution and morphology of the fillers in the polymer matrix. **Figure 2** reports representative sem images of TPU and TPU/BT series (two different magnifications) and of TPU/BT_f/MWCNT_f series (a single high magnification). BT particles can be clearly distinguished from the TPU matrix and their concentration increases according to the feed formulations. BT appear homogeneously distributed across the section as single particles, with diameters in the range 300-500 nm, although few agglomerates with diameters up to 1 μm are present, especially in the composites containing the highest BT amount, in line with the nominal BT dimension provided by the supplier. No remarkable differences can be found between the morphology and the distribution of functionalized and unfunctionalized BT particles, whereas the MWCNTs detection was difficult due to their low concentration.

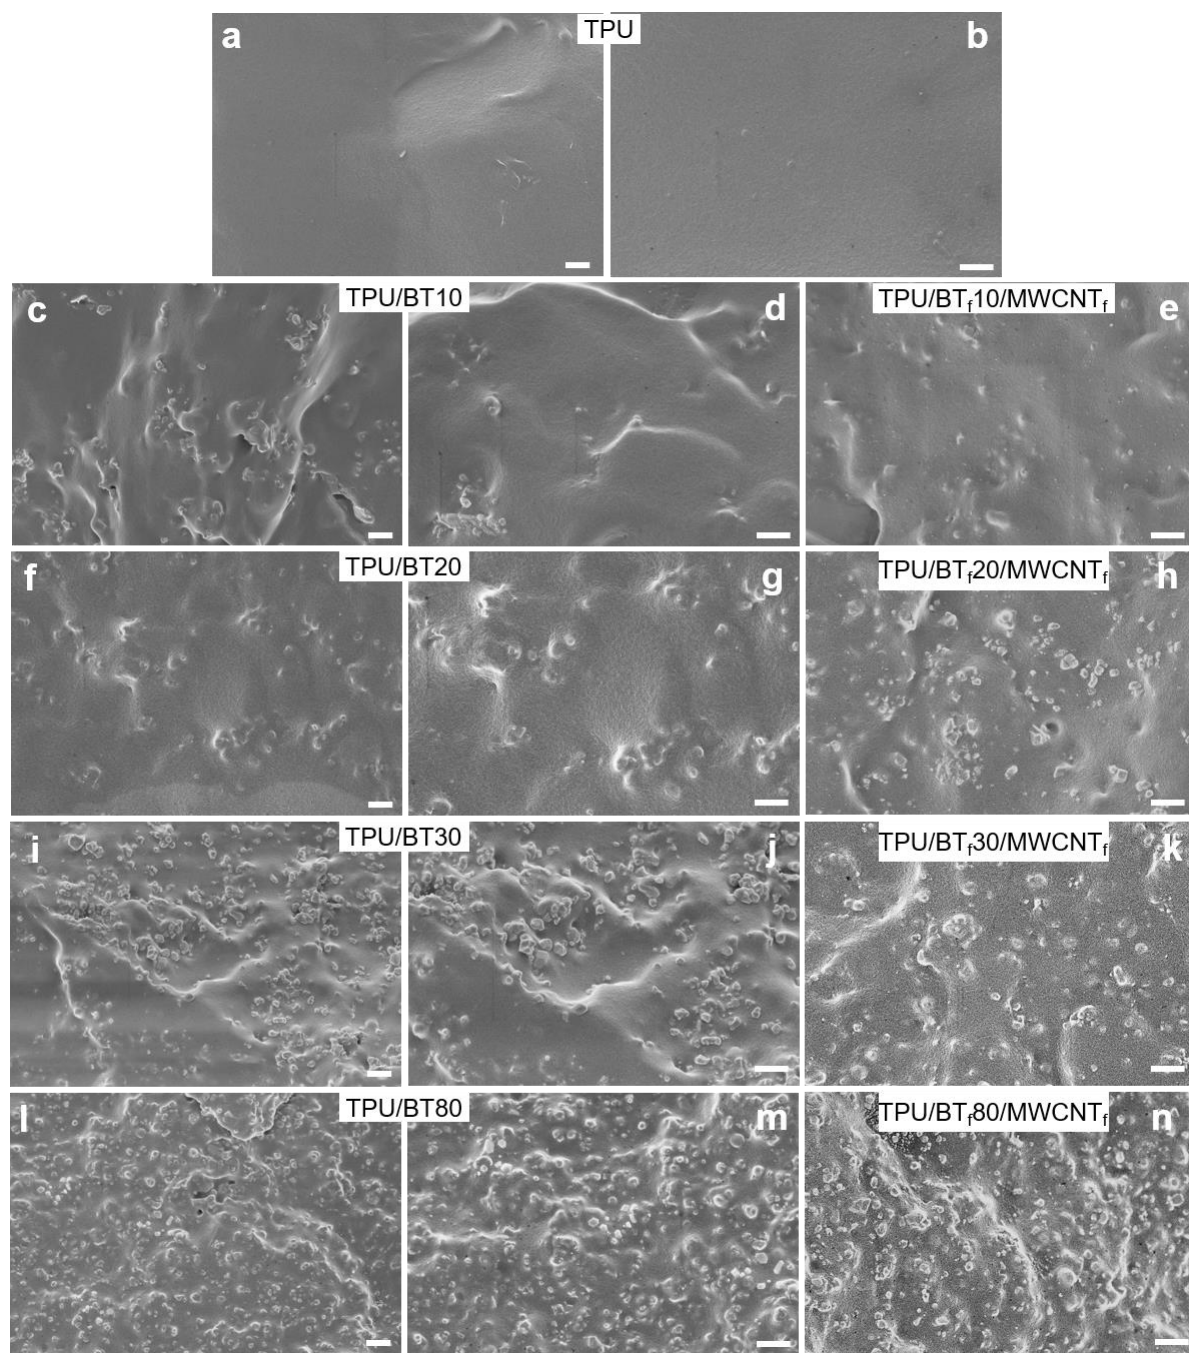


Figure 2. Representative SEM images of sample sections: (a-b) TPU; (c-d) TPU/BT10; (e) TPU/BT_f10/MWCNT_f; (f-g) TPU/BT20; (h) TPU/BT_f20/MWCNT_f; (i-j) TPU/BT30; (k) TPU/BT_f30/MWCNT_f; (l-m) TPU/BT80; (n) TPU/BT_f80/MWCNT_f. Scale bar = 2 μ m.

FTIR analysis of TPU composite films was conducted, aiming to settle possible interactions between the polymer matrix and the functionalized fillers through the evaluation of the hydrogen bonding index (HBI). It is well known that hydrogen bonding in polyurethanes is mainly attributed to the interactions of NH with the carbonyl groups in urethane groups of the hard segments (HS) or interactions with ether groups characteristic of the soft segments (SS).

[16] The recorded spectra of pure TPU and the corresponding composites are shown in **Figure 3**. The spectrum of pure TPU showed an absorption band at 3325 cm^{-1} that was attributed to the hydrogen-bonded N-H stretching vibration in the urethane group.^[16] The strong absorption peaks positioned at 2916 cm^{-1} and 2846 cm^{-1} were correlated to the asymmetrical and symmetrical vibrational modes in CH_2 groups, respectively. The absorption band at 1696 cm^{-1} was associated with the hydrogen-bonded carbonyl group, while the peak at 1727 cm^{-1} was related to the free urethane carbonyl ($\text{C}=\text{O}$) groups. It could be noted that the incorporation of non-functionalized BT and functionalized $\text{BT}_f/\text{MWCNT}_f$ particles in the TPU matrix had no pronounced influence on its absorption bands shifting. Nevertheless, the addition of non-functionalized filler and fillers with proper functional groups might alter the hydrogen bonding within the macromolecular chains affecting the final properties. The hydrogen bonding index (HBI) was calculated using Equation 1:^[17]

$$\text{HBI} = \frac{A_{\text{bonded C=O}}}{A_{\text{free C=O}}} \quad [1]$$

where $A_{\text{bonded C=O}}$ and $A_{\text{free C=O}}$ are the integrated areas of absorption peaks located at 1697 cm^{-1} and 1727 cm^{-1} , respectively.^[17] As these two peaks were not well separated, curve fitting with Gaussian function was performed using Origin 8.1 software (Inset in Figure 3a). Greater values of HBI indicate increased participation of the carbonyl group to the hydrogen bonding. The calculated HBI indices for pure TPU and its composites are collected in **Table 2**. It is evident that the estimated HBI indices for both series of composite films were higher than the HBI index of TPU and increased with increasing the amount of the fillers. This result suggests that the presence of fillers promotes the formation of hydrogen bonding, no matter whether they are functionalized or not. It is worth noting that in the $\text{TPU}/\text{BT}_f/\text{MWCNT}_f$ composite films (Figure 3b) the HBI indices were generally lower when compared to those of TPU/BT system at the same BaTiO_3 concentration. A trivial explanation of this result cannot be found, given that the presence of MWCNT_f may affect also the HBI indices. In the case of TPU with unfunctionalized BT, it can be assumed that hydrogen bondings concentrate only on the polymer matrix and that an increasing amount of BT may induce densification of polymer chains to better promote polymer-polymer interaction and free-volume decrease, thus resulting in an HBI increase. Differently, by using functionalized fillers, hydrogen bonds can be established at the polymer-particle interface, thus reducing the tendency of the chain to segregate from the particles.^[18]

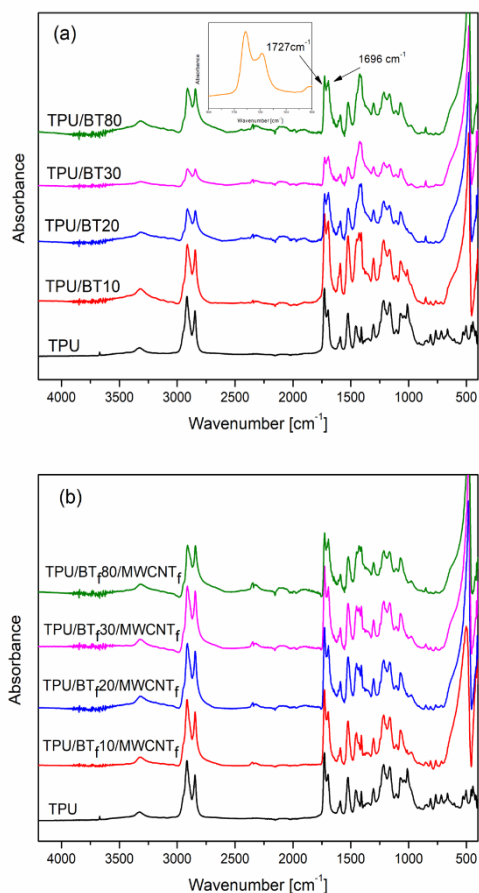


Figure 3. FTIR spectra of (a) TPU/BT and (b) TPU/BT_f/MWCNT_f composite films. Inset in (a) curve-fitted peaks located at 1727 cm⁻¹ and 1696 cm⁻¹.

Table 2. Integrated areas of curve fitted peaks at 1696 cm⁻¹ and 1727 cm⁻¹ and hydrogen bonding indices (HBI) for TPU, TPU/BT and TPU/BT_f/MWCNT_f composite films.

Sample	Peak 1696 cm ⁻¹	Peak 1727 cm ⁻¹	HBI ^(a)
TPU	3.49	4.31	0.81
TPU/BT10	5.77	7.0	0.82
TPU/BT20	4.95	3.17	1.56
TPU/BT30	3.40	1.99	1.70
TPU/BT80	7.63	3.66	2.08
TPU/BT _f 10/MWCNT _f	5.63	5.92	0.95
TPU/BT _f 20/MWCNT _f	7.08	5.93	1.19
TPU/BT _f 30/MWCNT _f	7.20	5.91	1.21
TPU/BT _f 80/MWCNT _f	7.17	4.09	1.75

a) calculated by applying Equation 1.

DSC heating curves recorded for the pure TPU and its composite films are shown in **Figure 4**. The existence of two glass transition temperatures can be observed: the lower glass transition T_{g1} is related to the SS, and the higher glass transition T_{g2} is ascribable to the HS of TPU.^[19] Since TPU is a completely amorphous polymer, no visible melting endotherms were detected. The summarized DSC data of the performed measurements are listed in **Table 3**. In TPU/BT films the T_{g1} increased with the increased content of BT, while the T_{g2} values were constant. The increased T_{g1} values indicated a reduction of chain mobility in soft segments. In these composite films, the ceramic filler does not possess any functional groups and therefore the restricted chain mobility in SS cannot be ascribed to polymer-particle interactions. A possible explanation is that the addition of unfunctionalized BT promotes polymer-polymer interaction and free volume reduction, thus initiating more intimate contact between the TPU macromolecules and resulting in restricted chain mobility.^[16] In TPU/BT_f/MWCNT_f composite films, the T_{g1} values were almost constant with the increased content of functionalized BT, but significantly lower when compared to the T_{g1} values relevant for TPU/BT systems. Additionally, a slight decrease in the second T_{g2} values could be noted with the increase in BT loadings. The reason for such a behaviour might be due to the participation of both fillers in the formation of hydrogen bonding, causing possible perturbing the strong interactions in urethane groups.^[17] These results perfectly corroborate with those obtained from the FTIR analysis.

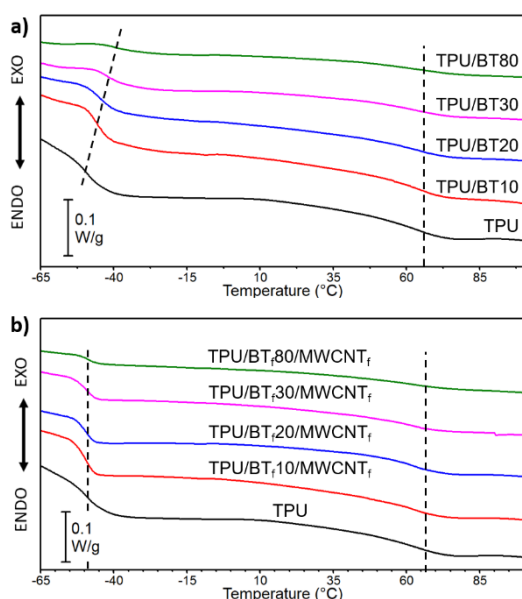


Figure 4. DSC thermograms of (a) TPU/BT and (b) TPU/BT_f/MWCNT_f composite films.

Table 3. Calorimetric data and results of puncture test of TPU, TPU/BT and TPU/BT_f/MWCNT_f composite films.

Sample	T _{g1} [°C]	ΔC _{p1} [Jg ⁻¹ C ⁻¹]	T _{g2} [°C]	ΔC _{p2} [Jg ⁻¹ C ⁻¹]	ε	σ [kPa]
TPU	-49	0.21	63	0.114	29.90 ± 0.03	361.6 ± 40.3
TPU/BT10	-46	0.19	64	0.108	36.100 ± 0.004	675.7 ± 11.1
TPU/BT20	-45	0.15	64	0.077	27.200 ± 0.003	783.9 ± 15.1
TPU/BT30	-40	0.11	64	0.067	15.60 ± 0.04	970.3 ± 13.7
TPU/BT80	-38	0.048	64	0.040	1.400 ± 0.003	1381.2 ± 47.0
TPU/BT _f 10/MWCNT _f	-50	0.19	65	0.103	15.90 ± 0.03	486.0 ± 23.0
TPU/BT _f 20/MWCNT _f	-50	0.14	63	0.092	11.500 ± 0.007	651.5 ± 21.1
TPU/BT _f 30/MWCNT _f	-50	0.13	60	0.077	8.300 ± 0.002	736.9 ± 41.3
TPU/BT _f 80/MWCNT _f	-50	0.05	61	0.065	1.400 ± 0.005	990.8 ± 32.2

The results obtained from the puncture measurements of the polymer composite films are summarized in Table 3. It is evident that the puncture elongation decreased with the increased content of the fillers. This was not surprising, taking into account the high volume content of inorganic phase, contributing to increased brittleness of the polymer films.^[20] It is interesting to note that lower elongation values were determined for TPU/BT_f/MWCNT_f composite films when compared to TPU/BT composites, probably because of the formed “network” between the polymer matrix and the fillers, reducing the elasticity of the systems. In both series of TPU composite films, the puncture strength increased with the increase of BT content. However, the puncture strength values for TPU/BT_f/MWCNT_f composites are lower compared to those of TPU/BT composite films at the same BT concentration. Such a behaviour nicely corroborates with the higher HBI indices in TPU/BT systems determined by FTIR spectroscopy.

2.2. Dielectric measurements

Figure 5 and **6** show the frequency dependence of the dielectric constant (ϵ_r) and dielectric loss ($\tan \delta$) of the neat TPU and its composite films. It can be seen that the ϵ_r of both series of composites displayed almost no correlation to frequency. The recorded dielectric constants of all investigated samples at 1 MHz are summarized in **Table 4**. The dielectric constant for the neat TPU was 7.26 which was approximate to the reference literature values.^[21] Furthermore,

1 ϵ_r of TPU/BT composite films increased with the addition of BT, but these obtained results
2 were lower than expected, taking into account the high volume of ceramic loadings. These
3 observed results could be due to the grain size of BT particles, which directly affects the
4 dielectric properties of the composite.^[5,22] On the other hand, the composite films with
5 modified fillers showed an increasing trend of ϵ_r , as soon as the BT_f content was within 30
6 vol%, thus confirming the indications that the dielectric properties are largely dependent on
7 the polymer matrix/filler interactions.^[23] Surprisingly, the ϵ_r of the composite film filled with
8 80 vol% BT_f (TPU/BT_f80/MWCNT_f) was comparable to that of pure TPU. To confirm if
9 there is a decreasing trend of ϵ_r for filler loadings higher than 30 vol%, two TPU films with 40
10 and 60 vol % of functionalized BT_f and 0.12 vol% of MWCNT_f as fillers were additionally
11 produced. The dielectric constant of TPU/BT_f30/MWCNT_f was equal to 30.28 at 1 MHz, but
12 as can be seen in Figure 5b, for TPU/BT_f40/MWCNT_f and TPU/BT_f60/MWCNT_f the
13 dielectric permittivity drops to 19.68 and 12.08, respectively. Consequently, it can be
14 concluded that the optimal concentration of fillers for this type of composite film is 30 vol%
15 of BT_f and 0.12 vol% of MWCNT_f. It is obvious that the dielectric response increased in
16 TPU/BT_f/MWCNTs composite films, but not as expected. Although MWCNTs exhibit high
17 value of the dielectric constant and increased electrical conductivity, their functionalization
18 and interactions with functionalized BT particles and TPU urethane groups diminish these
19 effect.

20 The dissipation factor is an important property for materials intended for capacitors, and
21 ideally, materials for this type of application require the lowest possible dielectric losses.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

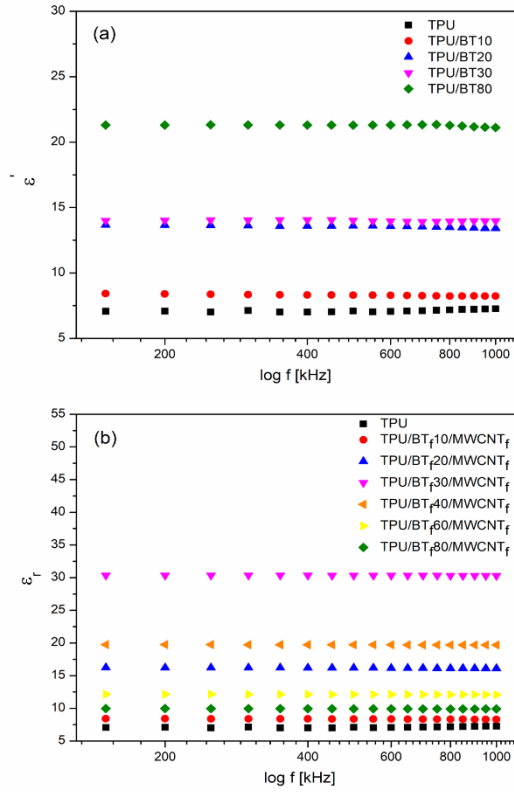


Figure 5. Frequency dependence of the dielectric constant ϵ_r in (a) TPU/BT and (b) TPU/BT_f/MWCNT_f composite films.

Table 4. Dielectric constant (ϵ_r), dielectric loss ($\tan \delta$), average breakdown voltage (U_b), average thickness (d) and dielectric breakdown strength (E_b) of TPU, TPU/BT and TPU/BT_f/MWCNT_f composite films.

Sample	ϵ_r	$\tan \delta$	U_b [kV]	d [mm]	E_b [kV/mm]
TPU	7.26	0.325	5.43 ± 0.6	0.097	56.0 ± 6.2
TPU/BT10	8.22	0.223	6.75 ± 0.3	0.099	68.18 ± 3.5
TPU/BT20	13.41	0.198	7.00 ± 0.1	0.101	70.29 ± 1.4
TPU/BT30	13.97	0.174	6.80 ± 0.2	0.096	70.83 ± 2.8
TPU/BT80	21.11	0.082	5.30 ± 0.1	0.188	28.19 ± 2.3
TPU/BT _f 10/MWCNT _f	8.29	0.038	3.73 ± 0.1	0.093	40.14 ± 1.2
TPU/BT _f 20/MWCNT _f	16.10	0.033	3.78 ± 0.1	0.097	39.0 ± 1.0
TPU/BT _f 30/MWCNT _f	30.28	0.031	4.12 ± 0.3	0.098	42.09 ± 3.9
TPU/BT _f 80/MWCNT _f	9.89	0.018	5.10 ± 0.4	0.152	33.55 ± 3

In contrast to the dielectric constant, the dielectric loss of all TPU films showed frequency dependence, especially for TPU/BT films, as shown in **Figure 6**.^[21] As it can be seen from Table 4, both series of TPU films exhibited reduced dielectric losses with the addition of BT, however, lower values were found for TPU films with modified fillers, which indicated that the incorporation of a specific quantity of MWCNT_f can increase the dielectric constant and decrease the loss tangent.^[5,24]

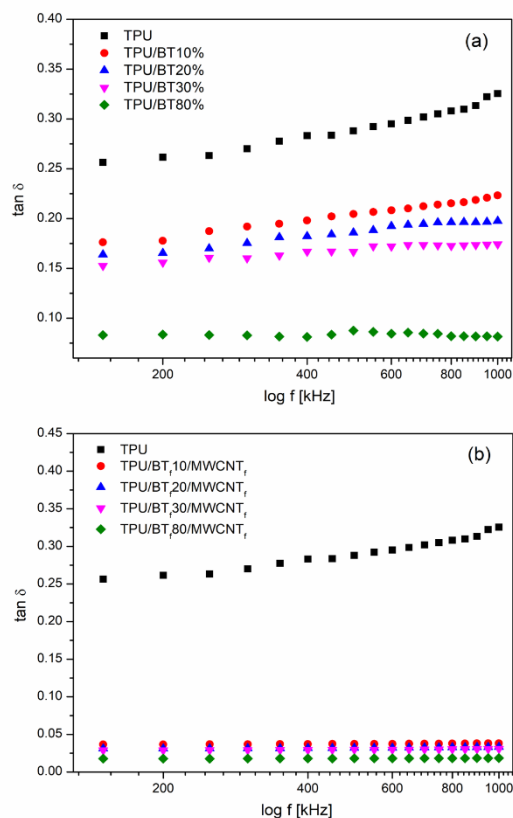


Figure 6. Frequency dependence of the dielectric losses ($\tan \delta$) on (a) TPU/BT and (b) TPU/BT_f/MWCNT_f composite films.

One of the basic requirements for the application of dielectric materials in capacitors is to possess resistivity to higher electric fields. To examine this behavior, the dielectric breakdown strength (E_b) of the TPU composite films was analyzed by measuring the breakdown voltage. The obtained results for dielectric breakdown strength, summarized in Table 4, showed relatively high values.^[25,26] The variations of E_b with the BaTiO_3 content, for both types of composites, are shown in **Figure 7**. It could be seen that the breakdown strength of the TPU/BT composite films (Figure 7a) showed an expected increasing trend with the addition of BaTiO_3 filler, while a sharp drop in its value was determined for TPU/BT80 composite. This drastic reduction of E_b at a high volume fraction of BaTiO_3 might be due to the fact that

high ceramic filler loadings lead to more defects and voids, increasing the risk of failure.^[27,28]

However, the E_b values of the composite films filled with modified fillers exhibited an irregular and decreasing trend (Figure 7b), mainly as a result of the addition of MWCNTs, making the polymer matrix conductive.^[29] Nevertheless, the obtained dielectric breakdown strength values remained relatively high, since the functionalized $BaTiO_3$ particles retained the insulating properties of the composite films.

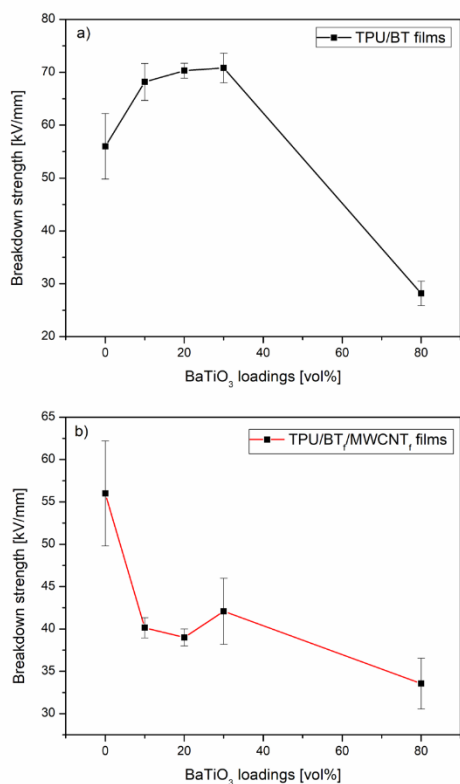


Figure 7. Breakdown strength of (a) TPU/BT and (b) TPU/BT_f/MWCNT_f composite films as a function of $BaTiO_3$ concentration.

3. Conclusion

Thermoplastic polyurethane composite films with functionalized $BaTiO_3$ and MWCNTs fillers were prepared by solution casting method and characterized for potential energy storage applications. Functionalization of BT particles with -OH groups and of MWCNTs with -COOH groups was confirmed by FTIR and UV/VIS spectroscopy, respectively. Albeit the functionalization of BT and MWCNTs did not significantly affect the morphology and the distribution of the particles, it had a high influence on the hydrogen bonding index (HBI) and on composite thermal transitions, in particular on the mobility of the chain soft segments.

Significantly increased puncture strengths (up to 990 kPa) and lower elasticity were achieved

with the increase of BT filler content. The highest dielectric permittivity of 30.28 and satisfactory dielectric breakdown strength of 42 kV/mm were achieved in the composite containing 30 vol% of functionalized BaTiO₃. The overall results of TPU/BT and TPU/BTf/MWCNTf composite films are promising for designing new energy storage dielectrics with high flexibility.

4. Experimental section

Materials: bio-based thermoplastic polyurethane ($M_n = 160$ kDa, PDI = 6), synthesized and characterized in a previous work, was used as a polymer matrix.^[30] BaTiO₃ (BT) powder (purity $\geq 99\%$), with a nominal particle size in the range of 0.85 - 1 μm , was purchased from Acros Organics. NC7000 MWCNTs (90%) were supplied by NANOCYL S.A. (Belgium), with average length and diameter of 1.5 μm and 9.5 nm, respectively. Chloroform (purity $\geq 99\%$), used as a solvent, was supplied by Sigma Aldrich. Hydrogen peroxide (30%), nitric acid (%) and ethanol (purity $\geq 96\%$) were products of Alkaloid, Skopje. All chemicals were used as received without previous purification.

Functionalization of BaTiO₃ and MWCNTs: a proper amount of BT powder was mixed with hydrogen peroxide solution (30%) and refluxed at 110 °C for 5 h. Subsequently, the sample was rinsed with distilled water, filtered and dried at 80 °C for 24 h. The functionalization of MWCNTs was performed using 3 M nitric acid under reflux, for 24 h at 80 °C, followed by rinsing, centrifugation and drying in oven at 80 °C.

Composite films preparation: for preparing TPU/BT series of composite, TPU was dissolved in chloroform (5 wt%) at room temperature (RT) for 24 h. Then, appropriate amount of BT powder was added to the solution, sonicated with a Bandelin Sonopuls ultrasonic homogenizer and then the prepared solutions were cast onto Petri dishes (d = 5 cm) and dried at RT. For preparing TPU/BTf/MWCNTf the functionalized particles at proper contents were mutually ultrasonically treated in ethanol for 30 min and then dried at 60 °C. The obtained mixtures were then ground and dispersed in TPU solutions, as it was described for TPU/BT composites.

Characterization: Infrared spectroscopy was carried out with a Fourier Infrared (FTIR) Shimadzu IRAffinity-1S spectrometer by recording 32 scans in the range of 4000 - 400 cm^{-1} , with a resolution of 4 cm^{-1} . The UV/VIS absorption spectroscopy was carried out with Hewlett Packard 8452A diode Array Spectrometer (USA). Scanning electron microscopy (SEM) was performed on a Zeiss LEO 1530 FE-SEM, operated at 5 kV. Samples were sputter-coated with gold before SEM observations. And observed with an In-lens SE detector.

Differential Scanning Calorimetry (DSC) was carried out using a Q2000 DSC apparatus (TA instruments) equipped with a Refrigerated Cooling System (RCS90). Samples were subjected to a first heating scan in the temperature range -90-110 °C at a rate of 20 °C min⁻¹, followed by a controlled cooling at 20 °C min⁻¹ to -90 °C and a second heating scan at 20 °C min⁻¹ to 110 °C. The glass transition temperatures (T_g) were taken at half-height of the glass transition heat capacity steps. Puncture properties were measured using a TA.XT. Plus-Stable Micro System (UK). The analyzed samples with dimensions 15 mm x 15 mm were fixed on a perforated platform with duct tape. A 2 mm diameter probe was used to punch the squared samples in the centre with a speed of 1 mm s⁻¹. The average puncture strength (σ) and elongation (ϵ) were taken as averaged values of five measurements per sample. The dielectric properties of the samples were measured by Impedance analyzer, Keysight E4990A and Keysight 16451B Dielectric Test Fixture with electrode B (d = 5 mm), in a frequency range of 20 Hz to 20 MHz with basic accuracy of 0.045% (typ.). The 16451B is a Dielectric Test Fixture used with impedance analyzers for accurate measurement of insulating and dielectric materials. The 16451B employed the parallel plate method, which sandwiches the material between two electrodes to form a capacitor. An impedance analyzer is then used to measure the capacitance. The dielectric constant of the samples was calculated as follows:

$$\epsilon_r = \frac{C_p}{\epsilon_0} \frac{t_a}{A} \quad [2]$$

where ϵ_0 is the permittivity in vacuum (8.85×10^{-12} F m⁻¹), t_a is the average thickness of the test material [m], A is the area of Guarded electrode [m²] and C_p is the equivalent parallel capacitance [F]. Additionally, the dielectric dissipation factor ($\tan \delta$) was measured and the obtained results were the actual values of dielectric loss for TPU composites. Dielectric breakdown strengths were measured using a homemade breakdown voltage generator, operating with a direct electric signal, with a voltage up to 6 kV and a maximum electric current of 10 mA. Test spikes from the instrument were placed on a randomly selected surface on both sides of the test specimens. The measurement of the breakdown voltage of each sample was performed three times, and the declared measured value was calculated as the average value. The measurements were performed at RT and relative humidity of 54%. The measuring instrument allows a continuous increase of the test voltage with a step of approximately 10 V until the breakthrough voltage was reached, when it was automatically switched off and the result was displayed on the indicator. The declared accuracy of the instrument in the measurement area of 6 kV is:

$$\Delta = \pm |1,5 \% U_b + 2 \text{dig}| \quad [3]$$

1 where U_b is the value displayed on the indicator of the instrument, while "dig" represents the
2 resolution of the instrument (which is 10 V). The obtained results for dielectric strength were
3 then calculated by dividing the breakdown voltage by the thickness of the sample. The data is
4 expressed in kV mm^{-1} . The measurements were performed with a variation of the effective
5 voltage value of the electrical distribution network of less than 2%.
6
7
8
9
10
11

12 Acknowledgements

13 This work was financially supported by NATO grant - Project number NATO SPS G5772.
14
15
16

17 Received: ((will be filled in by the editorial staff))

18 Revised: ((will be filled in by the editorial staff))


19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
66
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
841
842
843
844
845
846
847
848
849
850
851
852
853
854
855
856
857
858
859
860
861
862
863
864
865
866
867
868
869
870
871
872
873
874
875
876
877
878
879
880
881
882
883
884
885
886
887
888
889
890
891
892
893
894
895
896
897
898
899
900
901
902
903
904
905
906
907
908
909
910
911
912
913
914
915
916
917
918
919
920
921
922
923
924
925
926
927
928
929
930
931
932
933
934
935
936
937
938
939
940
941
942
943
944
945
946
947
948
949
950
951
952
953
954
955
956
957
958
959
960
961
962
963
964
965
966
967
968
969
970
971
972
973
974
975
976
977
978
979
980
981
982
983
984
985
986
987
988
989
990
991
992
993
994
995
996
997
998
999
1000

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
- [11] T. Zhou, J. W. Zha, R.Y. Cui, B.H. Fan, J.K. Yuan, Z.M. Dang, *ACS Appl. Mater. Interfaces* **2011**, *3*, 2184.
- [12] H. Y. Wang, Y. bin You, J. W. Zha, Z. M. Dang, *Compos. Sci. Technol.* **2020**, *200*, 108405.
- [13] K. Dash, N. K. Hota, B. P. Sahoo, *J. Mater. Sci.* **2020**, *55*, 12568.
- [14] L. Shao, G. Tobias, C.G. Salzmann, B. Ballesteros, S.Y. Hong, A. Crossley, B.G. Davis, M.L.H. Green, *Chem. Commun.* **2007**, *1*, 5090.
- [15] W. Zhimin, L. Qingchun, Z. Hui, L. Hanfan, C. Yongming, Y. Mingshu, *Carbon* **2007**, *45*, 285.
- [16] F. Şen, E. Baştürk, B. Karadoğan, S. Madakbaş, M. V. Kahraman, *Polym. - Plast. Technol. Eng.* **2016**, *55*, 1325.
- [17] B. Molki, W. M. Aframehr, R. Bagheri, J. Salimi, *J. Memb. Sci.* **2018**, *549*, 588.
- [18] Y. Sun, J. Teng, Y. Kuang, S. Yang, J. Yang, H. Mao, Z. Gu, *Front. Bioeng. Biotechnol.* **2022**, *10*, 1.
- [19] C. Bueno-Ferrer, E. Hablot, F. Perrin-Sarazin, M. C. Garrigós, A. Jiménez, L. Averous, *Macromol. Mater. Eng.* **2012**, *297*, 777.
- [20] A. Bužarovska, G. Bogoeva-Gaceva, R. Fajgar, *J. Polym. Eng.* **2016**, *36*, 181.
- [21] M. N. Khan, N. Jelani, C. Li, J. Khaliq, *Ceram. Int.* **2017**, *43*, 3923.
- [22] M. C. Cheung, H. L. W. Chan, C. L. Choy, *J. Mater. Sci.* **2001**, *36*, 381.
- [23] M. T. Sebastian, H. Jantunen, *Int. J. Appl. Ceram. Technol.* **2010**, *7*, 415.
- [24] A. S. M. Iftekhar Uddin, D. Lee, C. Cho, B. Kim, *Coatings* **2022**, *12*, 77.
- [25] Z. Luo, L. Zhang, Y. Liang, S. Wen, L. Liu, *Polym. Test.* **2022**, *111*, 107592.
- [26] [24] I. Nurul, J. Mariatti, *Polym. Eng. Sci.* **2018**, *58* E36.
- [27] X. He, J. Zhou, L. Jin, X. Long, H. Wu, L. Xu, Y. Gong, W. Zhou, *Materials* **2020**, *13*, 1.
- [28] Z. Pan, L. Yao, J. Zhai, B. Shen, H. Wang, *Compos. Sci. Technol.* **2017**, *147*, 30.
- [29] R. Han, Y. Liu, J. Shi, G. X. Chen, Q. Li, *E-Polymers* **2021**, *21*, 272.
- [30] A. Bužarovska, S. Dinescu A.D. Lazar, M. Serban, G.G Pircalabioru, M. Costache, C. Gualandi, L. Avérous, *Mater. Sci. Eng. C*, **2019**, *104*, 109893.

In this study two series of TPU/BT and TPU/BT_f/MWCNT_f composite films are prepared. The flexibility of TPU and the proper functionalization of BaTiO₃ and MWCNTs contributed to increased permittivity and acceptable dielectric breakdown strengths. Despite the high BT loadings, TPU/BT and TPU/BT_f/MWCNT_f composite films are considered as elastic materials with high strength, suitable for energy storage devices.

E. Stojchevska, R. Popeski-Dimovski, Ž. Kokolanski, C. Gualandi*, A. Bužarovska*

Title Effect of Particle Functionalization on Structural and Dielectric Properties of Flexible TPU/BaTiO₃/MWCNTs Composite Films

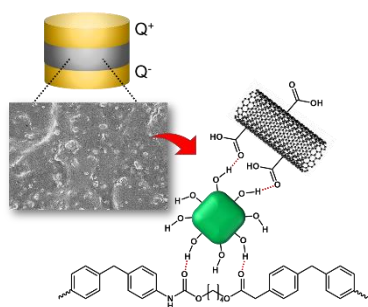



Click here to access/download
Production Data
Production data.docx

In this study two series of TPU/BT and TPU/BT_f/MWCNT_f composite films are prepared. The flexibility of TPU and the proper functionalization of BaTiO₃ and MWCNTs contributed to increased permittivity and acceptable dielectric breakdown strengths. Despite the high BT loadings, TPU/BT and TPU/BT_f/MWCNT_f composite films are considered as elastic materials with high strength, suitable for energy storage devices.

